

Magnetic point groups and space groups

Ron Lifshitz

School of Physics and Astronomy
Raymond and Beverly Sackler Faculty of Exact Sciences
Tel Aviv University, Tel Aviv 69978, Israel
E-mail: ronlif@tau.ac.il

10 May 2004

1 Introduction

Magnetic groups—also known as antisymmetry groups, Shubnikov groups, Heesch groups, Opechowski-Guccione groups, as well as dichromatic, 2-color, or simply black-and-white groups—are the simplest extension to standard point group and space group theory. They allow directly to describe, classify, and study the consequences of the symmetry of crystals, characterized by having a certain property, associated with each crystal site, that can take one of two possible values. This is done by introducing a single external operation of order two that interchanges the two possible values everywhere throughout the crystal. This operation can be applied to the crystal along with any of the standard point group or space group operations, and is denoted by adding a prime to the original operation. Thus, any rotation g followed by this external operation is denoted by g' .

We begin here with a few typical examples of this two-valued property, some of which are illustrated in Figure 1. In section 2 we discuss the notion of a magnetic point group, followed by a discussion on magnetic space groups in section 3. In section 4 we describe one of the most direct consequences of having magnetic symmetry in crystals which is the extinction of magnetic Bragg peaks in neutron diffraction patterns. We finish in section 5 by

mentioning the generalization of magnetic point groups to cases where the property associated with each crystal site is not limited to having only one of two possible values.

Let us begin by considering the structure of crystals of the cesium chloride type. In these crystals the atoms are located on the sites of a body-centered cubic (bcc) lattice. Atoms of one type are located on the simple cubic lattice formed by the corners of the cubic cells, and atoms of the other type are located on the simple cubic lattice formed by the body centers of the cubic cells. The parent bcc lattice is partitioned in this way into two identical sublattices, related by a body-diagonal translation. One may describe the symmetry of the cesium chloride structure as having a simple cubic lattice of ordinary translations, with a basis containing one cesium and one chlorine atom. Alternatively, one may describe the symmetry of the crystal as having twice as many translations, forming a bcc lattice, half of which are primed to indicate that they are followed by the external operation that exchanges the chemical identities of the two types of atoms. A similar situation occurs in crystals whose structure is of the sodium chloride type in which a simple cubic lattice is partitioned into two identical face-centered cubic sublattices.

Another typical example is the orientational ordering of magnetic moments (spins), electric dipole moments, or any other tensorial property associated with each site in a crystal. Adopting the language of spins, if these can take only one of two possible orientations—“up” and “down”—as in simple antiferromagnets, we have the same situation as above, with the two spin orientations replacing the two chemical species of atoms. In the case of spins the external prime operation is a so-called antisymmetry operation that reverses the signs of the spins. Physically, one may think of using the operation of time inversion to reverse the directions of all the spins without affecting anything else in the crystal.

Finally, consider a periodic or quasiperiodic scalar function of space $f(\mathbf{r})$, as in Figure 1(e), whose average value is zero. It might be possible to extend the point group or the space group describing the symmetry of the function $f(\mathbf{r})$ by introducing an external prime operation that changes the sign of $f(\mathbf{r})$.

For the sake of clarity we shall adopt the picture of up-and-down spins, and the use of time inversion to exchange them, for the remaining of our discussion. It should be emphasized, though, that most of what we say here (except for the discussion of extinctions in section 4) applies equally to all the

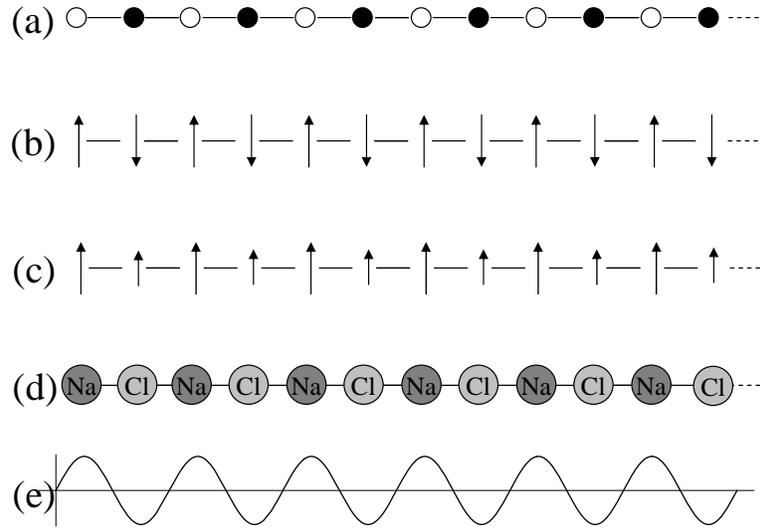


Figure 1: Several realizations of the simple one-dimensional magnetic space group $p_p\bar{1}$. Note that the number of symmetry translations is doubled if one introduces an operation e' that interchanges the two possible values of the property, associated with each crystal site. Also note that spatial inversion $\bar{1}$ can be performed without a prime on each crystal site, and with a prime ($\bar{1}'$) between every two sites. (a) An abstract representation of the two possible values as the two colors—black and white. The operation e' is the nontrivial permutation of the two colors. (b) A simple antiferromagnetic arrangement of spins. The operation e' is time inversion which reverses the signs of the spins. (c) A ferromagnetic arrangement of two types of spins, where e' exchanges them as in the case of two colors. (d) A 1-dimensional version of salt. e' exchanges the chemical identities of the two atomic species. (e) A function $f(x)$ whose overall sign changes by application of the operation e' .

other two-valued properties. We describe the magnetic crystal using a scalar spin density field $S(\mathbf{r})$ whose magnitude gives the magnitude of an atomic magnetic moment, or some coarse-grained value of the magnetic moment, at position \mathbf{r} . The sign of $S(\mathbf{r})$ gives the direction of the spin—a positive sign for up spins and a negative sign for down spins. Thus, the function $S(\mathbf{r})$ can be a discrete set of delta functions defined on the crystal sites as in Figure 1(b), or a continuous spin density field as in Figure 1(e).

2 Magnetic point groups

A d -dimensional magnetic point group G_M is a subgroup of $O(d) \times 1'$, where $O(d)$ is the group of d -dimensional rotations, and $1'$ is the time inversion group containing the identity e and the time inversion operation e' . Note that we use the term “rotation” to refer to proper as well as improper rotations such as mirrors.

Three cases exist: (1) All rotations in G_M appear with and without time inversion; (2) Half of the rotations in G_M are followed by time inversion and the other half are not; and (3) No rotation in G_M is followed by time inversion. More formally, if G is any subgroup of $O(d)$, it can be used to form at most three types of magnetic point groups, as follows:

1. $G_M = G \times 1'$. Thus, each rotation in G appears in G_M once by itself and once followed by time inversion. Note that in this case $e' \in G_M$.
2. $G_M = H + g'H$, where $G = H + gH$, and $g \notin H$. Thus, exactly half of the rotation in G , which belong to its subgroup H , appear in G_M by themselves, and the other half, belonging to the coset gH , are followed by time inversion. Note that in this case $e' \notin G_M$.
3. $G_M = G$. Thus, G_M contains rotations none of which are followed by time inversion.

Enumeration of magnetic point groups is thus straightforward. Any ordinary point group G [*i.e.* any subgroup, usually finite, of $O(d)$] is trivially a magnetic point group of type 3, and along with the time inversion group gives another magnetic point group of type 1, denoted as $G1'$. One then lists all distinct subgroups H of index 2 in G , if there are any, to construct additional magnetic point groups of type 2. These are denoted either by the group-subgroup pair $G(H)$, or by using the International (Hermann-Mauguin) symbol for G and adding a prime to those elements in the symbol that do not belong to the subgroup H (and are therefore followed by time inversion). The set of magnetic groups—here magnetic point groups G_M —formed in this way from a single ordinary group G —here an ordinary point group—is sometimes called the *magnetic superfamily* of the group G . For example, the orthorhombic point group $G = mm2 = \{e, m_x, m_y, 2_z\}$ has three subgroups of index 2, $H_1 = \{e, m_x\}$, $H_2 = \{e, m_y\}$, and $H_3 = \{e, 2_z\}$, of

which the first two are equivalent through a relabeling of the x and y axes. This yields a total of four magnetic point groups: $mm2$, $mm21'$, $m'm2'$ (equivalently expressed as $mm'2'$), and $m'm'2$.

Magnetic point groups of type 3 are equivalent to ordinary non-magnetic point groups and are listed here only for the sake of completeness. Strictly speaking, they can be said to describe the symmetry of ferromagnetic structures with no spin-orbit coupling. We shall not consider groups of this type any further. Magnetic point groups of type 2 can be used to describe the point symmetry of finite objects, as described in 2.1, as well as that of infinite crystals, as described in 2.2. Magnetic point groups of type 1 can be used to describe the point symmetry of infinite crystals, but because they include e' as a symmetry element they cannot be used to describe the symmetry of finite objects, as we now define.

2.1 Magnetic point groups of finite objects

The magnetic symmetry of a finite object, such as a molecule or a cluster containing an equal number of two types of spins, can be described by a magnetic point group. We say that a primed or unprimed rotation from $O(d) \times 1'$ is in the magnetic point group G_M of a *finite object* in d dimensions, if it leaves the object *invariant*. Clearly, only magnetic point groups of type 2, listed above, can describe the symmetry of finite magnetically-ordered structures. This is because time inversion e' changes the orientations of all the spins and therefore cannot leave the object invariant unless it is accompanied by a nontrivial rotation. It should be mentioned that in this context, point groups of type 1 are sometimes called “gray” groups, as they describe the symmetry of “gray” objects which stay invariant under the exchange of black and white.

2.2 Magnetic point groups of crystals

The magnetic point group of a d -dimensional magnetically-ordered *periodic crystal*, containing an equal number of up and down spins, is defined as the set of primed or unprimed rotations from $O(d) \times 1'$ that leave the crystal *invariant to within a translation*. The magnetic point group of a crystal can be either of the first or of the second type listed above. It is of type 1 if time

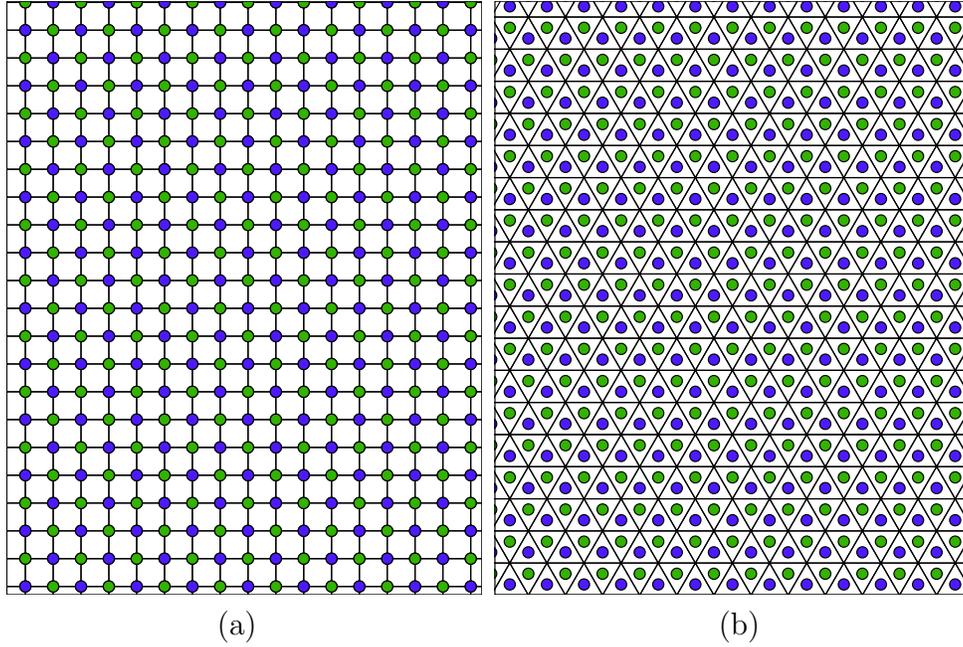


Figure 2: Periodic antiferromagnets. (a) A square crystal with magnetic point group $G_M = 4mm1'$ and magnetic space group p_p4mm (also denoted p_c4mm). (b) A hexagonal crystal with magnetic point group $G_M = 6'mm'$ and magnetic space group $p6'mm'$.

inversion by itself leaves the crystal invariant to within a translation. Recall that in this case any rotation in the magnetic point group can be performed either with or without time inversion. If time inversion cannot be combined with a translation to leave the crystal invariant, the magnetic point group is of type 2, in which case half the rotations are performed without time inversion and the other half with time inversion.

Figure 2(a) shows an example of a magnetically-ordered crystal whose magnetic point group is of type 1. This is a square crystal with magnetic point group $G_M = 4mm1'$ where time inversion can be followed by a translation to leave the crystal invariant. Figure 2(b) shows an example of a crystal whose magnetic point group is of type 2. This is a hexagonal crystal with point group $G_M = 6'mm'$. Note that all right-side-up triangles contain a dark circle (spin up) and all up-side-down triangles contain a light circle (spin down). Time inversion, exchanging the two types of spins, cannot be combined with a translation to recover the original crystal. Time inversion must be combined

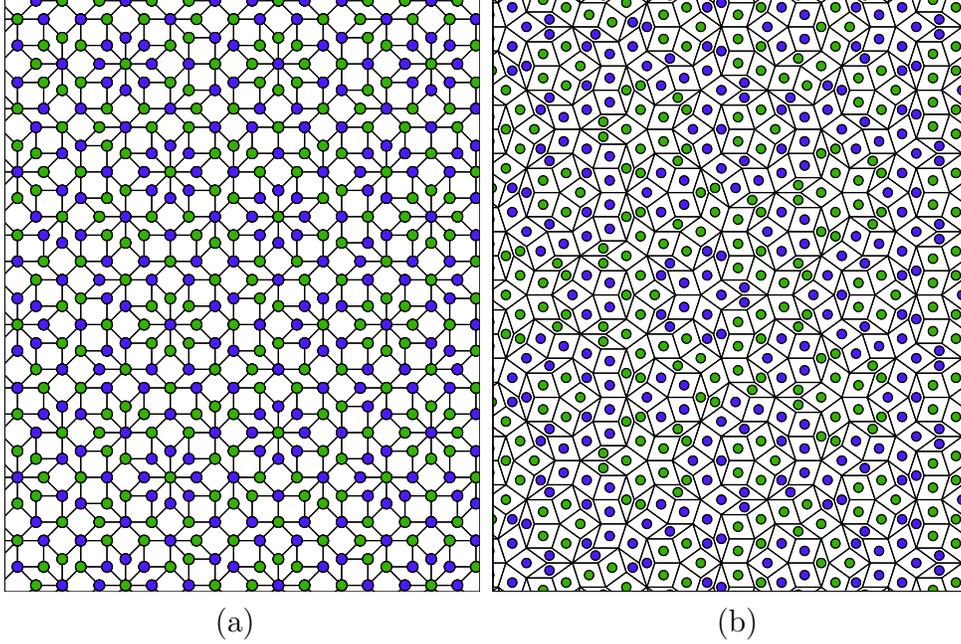


Figure 3: Quasiperiodic antiferromagnets. (a) An octagonal quasicrystal with magnetic point group $G_M = 8mm1'$ and magnetic space group p_p8mm , first appeared in an article by Niizeki [*J. Phys. A: Math. Gen.* **23** (1990) 5011]. (b) A decagonal quasicrystal with magnetic point group $G_M = 10'm'm$ and magnetic space group $p10'm'm$, based on the tiling of Li, Dubois, and Kuo [*Philos. Mag. Lett.* **69** (1994) 93].

with an operation, such as the 6-fold rotation or the horizontal mirror, that interchanges the two types of triangles to recover the original crystal. Note that the vertical mirror (the first m in the International symbol) leaves the crystal invariant without requiring time inversion and is therefore unprimed in the symbol.

More generally, the magnetic point group of a d -dimensional magnetically-ordered *quasiperiodic crystal* (quasicrystal), is defined as the set of primed or unprimed rotations from $O(d) \times 1'$ that leave the crystal *indistinguishable*. This means that the rotated and unrotated crystals contain the same spatial distributions of finite clusters of spins of arbitrary size. The two are statistically the same though not necessarily identical. For the special case of periodic crystals, the requirement of indistinguishability reduces to the requirement of invariance to within a translation. Figure 3 shows two quasiperi-

odic examples, analogous to the two periodic examples of Figure 2. Figure 3(a) shows an octagonal crystal with magnetic point group $G_M = 8mm1'$. One can see that time inversion rearranges the spin clusters in the crystal but they all still appear in the crystal with the same spatial distribution. This is because any finite spin cluster and its time-reversed image appear in the crystal with the same spatial distribution. Figure 3(b) shows a decagonal crystal with magnetic point group $G_M = 10'm'm$. In this case, time inversion does not leave the crystal indistinguishable. It must be combined either with odd powers of the 10-fold rotation, or with mirrors of the vertical type.

3 Magnetic space groups

The full symmetry of a magnetically-ordered crystal, described by a scalar spin density field $S(\mathbf{r})$, is given by its magnetic space group \mathcal{G}_M . We said that the magnetic point group G_M is the set of primed or unprimed rotations that leave a periodic crystal invariant to within a translation, or more generally, leave a quasicrystalline crystal indistinguishable. We still need to specify the distinct sets of translations \mathbf{t}_g or $\mathbf{t}_{g'}$ that can accompany the rotations g or g' in a periodic crystal to leave it invariant, or provide the more general characterization of the nature of the indistinguishability in the case of quasicrystals.

3.1 Periodic crystals

As in the case of point groups, one can take any space group \mathcal{G} of a periodic crystal and form its magnetic superfamily, consisting of one trivial group, $\mathcal{G}_M = \mathcal{G}$, one gray group $\mathcal{G}_M = \mathcal{G}1'$, and possibly nontrivial magnetic groups of the form $\mathcal{G}_M = \mathcal{H} + (g'|\mathbf{t}_{g'})\mathcal{H}$, where \mathcal{H} is a subgroup of index 2 of \mathcal{G} . Only the latter, nontrivial, groups are relevant as magnetic space groups consisting of operations that leave the magnetically-ordered crystal *invariant*. These nontrivial magnetic space groups are divided into two types depending on their magnetic point groups G_M :

1. *Class-equivalent magnetic space groups*: The magnetic point group G_M is of type 1 and therefore all rotations in G appear with and without time inversion. In this case the point groups of \mathcal{G} and \mathcal{H} are the same,

but the Bravais lattice of \mathcal{H} contains exactly half of the translations that are in the Bravais lattice of \mathcal{G} .

2. *Translation-equivalent magnetic space groups:* The magnetic point group G_M is of type 2. Here the Bravais lattices of \mathcal{G} and \mathcal{H} are the same, but the point group H of \mathcal{H} is a subgroup of index 2 of the point group G of \mathcal{G} .

Enumeration of translation-equivalent magnetic space group types is very simple. Given a space group \mathcal{G} , all that one needs to do is to consider all subgroups H of index 2 of the point group G of \mathcal{G} , as explained in section 2. The only additional consideration is that with an underlying Bravais lattice there may be more than one way to orient the subgroup H relative to the lattice. Take, for example, the magnetic point group $m'm2'$ which we earlier said was equivalent to $mm'2'$. If the lattice is an A -centered orthorhombic lattice, then the x - and y -axes are no longer equivalent and one needs to consider both options as distinct groups. We say that $Am'm2'$ and $Amm'2'$ belong to the same *magnetic geometric crystal class* (*i.e.* have the same magnetic point group), but to two distinct *magnetic arithmetic crystal classes*. Translation-equivalent magnetic space groups are denoted by taking the International symbol for \mathcal{G} and adding a prime to those elements in the symbol that do not belong to \mathcal{H} and are therefore followed by time inversion.

Enumeration of class-equivalent magnetic space group types can proceed in two alternative ways. Given a space group \mathcal{G} , one may consider all distinct sublattices of index 2 of the Bravais lattice of \mathcal{G} . Alternatively, given a space group \mathcal{H} , one may consider all distinct superlattices of index 2 of the Bravais lattice of \mathcal{H} . Also note that if one prefers to look at the reciprocal lattices in Fourier space, instead of the lattices of real-space translations, the roles of superlattice and sublattice are exchanged. Although the lattice of \mathcal{G} contains twice as many points as the lattice of \mathcal{H} , the reciprocal lattice of \mathcal{G} contains exactly half of the points of the reciprocal lattice of \mathcal{H} .

Because of the different enumeration methods there are conflicting notations in the literature for class-equivalent magnetic space groups. The Opechowski-Guccione (OG) notation follows the first approach (sublattices of \mathcal{G}), taking the International symbol for the space group \mathcal{G} with a subscript on the Bravais class symbol denoting the Bravais lattice of \mathcal{H} . The Belov notation follows the second approach (superlattices of \mathcal{H}), taking the International symbol for

the space group \mathcal{H} with a subscript on the Bravais class symbol denoting one of the primed translations $\mathbf{t}_{e'}$ in the coset $(e'|\mathbf{t}_{e'})\mathcal{H}$. The Lifshitz notation, which follows a third approach (sublattices of \mathcal{H} in Fourier space), resembles that of Belov but generalizes more easily to quasiperiodic crystals.

There is an additional discrepancy in the different notations which has been the cause of some confusion over the years. It is due to the fact that when $e' \in G_M$ ordinary mirrors or rotations when unprimed may become glide planes or screw axes when primed, and *vice versa*. The only consistent way to avoid this confusion is to use only unprimed elements for the symbols of class-equivalent magnetic space group types. This is the approach adopted by both the Belov and the Lifshitz notations, but unfortunately not by the OG notation, having introduced errors into their list of magnetic space group types. In any case, there is no need to leave the 1' at the end of the symbol, as it is clear from the existence of a subscript on the lattice symbol that the magnetic point group G_M contains e' .

Let us list all the class-equivalent magnetic space group types with point group 432. In the cubic system there are two lattice-sublattice pairs: (1) The simple cubic lattice P has a face-centered sublattice F of index 2; and (2) The body-centered cubic lattice I has a simple cubic sublattice P of index 2. Also recall that the reciprocal of F is a bcc lattice in Fourier space, denoted by I^* , and the reciprocal of I is an fcc lattice, denoted F^* . In the Belov notation we have F_s432 , F_s4_j32 , P_I432 , and P_I4_j32 with $j = 1, 2, 3$. The subscript s is for “simple”. In the Lifshitz notation, using Fourier space lattices, these groups become I_P^*432 , $I_P^*4_j32$, $P_{F^*}432$, and $P_{F^*}4_j32$. In the OG notation these groups should become P_F432 , P_F4_j32 , I_P432 , and I_P4_j32 . Instead, they list P_F432 , P_F4_232 , I_P432 , I_P4_132 , $I_P4'_132'$, and $I_P4'_132'$, using primes inconsistently and clearly missing two groups. We therefore recommend to refrain from using primes when denoting class-equivalent magnetic space groups.

We refer the reader to references in the “Further reading” section for complete lists of magnetic space group types. Let us only summarize some statistics. Starting from the 17 space group types in 2 dimensions, also known as the 17 plane groups, one can form a total of 80 magnetic space group types as follows: 17 trivial groups, 17 gray groups, and 46 nontrivial groups of which 18 are class-equivalent and 28 are translation-equivalent. Starting from the 230 space group types in 3 dimensions one can form a total of 1651 magnetic space group types as follows: 230 trivial groups, 230 gray groups, and 1191

nontrivial groups of which 517 are class-equivalent and 674 are translation-equivalent. These numbers have no particular significance other than the fact that they are surprisingly large.

3.2 Quasiperiodic crystals

3.2.1 Lattices and Bravais classes

Magnetically-ordered quasiperiodic crystals, in general, possess no lattices of real space translations that leave them invariant, but they do have reciprocal lattices (or Fourier modules) L that can be inferred directly from their neutron diffraction diagrams. To be a bit more specific, consider spin density fields with well defined Fourier transforms

$$S(\mathbf{r}) = \sum_{\mathbf{k} \in L} S(\mathbf{k}) e^{i\mathbf{k} \cdot \mathbf{r}}, \quad (1)$$

in which the set L contains at most a countable infinity of plane waves. In fact, the *reciprocal lattice* L of a magnetic crystal can be defined as the set of all integral linear combinations of wave vectors \mathbf{k} determined from its neutron diffraction diagram, as we expect to see a magnetic Bragg peak at every \mathbf{k} in the Fourier transform of $S(\mathbf{r})$, unless it is forbidden by symmetry, as explained in section 4 below. The *rank* D of L is the smallest number of vectors needed to generate L by integral linear combinations. If D is finite the crystal is quasiperiodic. If, in particular, D is equal to the number d of spatial dimensions, and L extends in all d directions, the crystal is periodic. In this special case the magnetic lattice L is reciprocal to a lattice of translations in real space that leave the magnetic crystal invariant. The reciprocal lattices L of magnetic crystals are classified into Bravais classes, just like those of ordinary non-magnetic crystals.

3.2.2 Phase functions and space group types

The precise mathematical statement of indistinguishability, used earlier to define the magnetic point group, is the requirement that any symmetry operation of the magnetic crystal leave invariant all spatially-averaged n^{th} -order

autocorrelation functions of its spin-density field,

$$C^{(n)}(\mathbf{r}_1, \dots, \mathbf{r}_n) = \lim_{V \rightarrow \infty} \frac{1}{V} \int_V d\mathbf{r} S(\mathbf{r}_1 - \mathbf{r}) \cdots S(\mathbf{r}_n - \mathbf{r}). \quad (2)$$

One can prove that two quasiperiodic spin density fields $S(\mathbf{r})$ and $\hat{S}(\mathbf{r})$ are indistinguishable in this way, if their Fourier coefficients, defined in Eq. (1), are related by

$$\hat{S}(\mathbf{k}) = e^{2\pi i \chi(\mathbf{k})} S(\mathbf{k}), \quad (3)$$

where χ is a real-valued linear function (modulo integers) on L , called a *gauge function*. By this we mean that for every pair of wave vectors \mathbf{k}_1 and \mathbf{k}_2 in the magnetic lattice L ,

$$\chi(\mathbf{k}_1 + \mathbf{k}_2) \equiv \chi(\mathbf{k}_1) + \chi(\mathbf{k}_2), \quad (4)$$

where “ \equiv ” means equal to within adding an integer. Thus, for each element g or g' in the magnetic point group G_M of the crystal, that by definition leaves the crystal indistinguishable, there exists such a gauge function $\Phi_g(\mathbf{k})$ or $\Phi_{g'}(\mathbf{k})$, called a *phase function*, satisfying

$$S(g\mathbf{k}) = \begin{cases} e^{2\pi i \Phi_g(\mathbf{k})} S(\mathbf{k}), & g \in G_M, \\ -e^{2\pi i \Phi_{g'}(\mathbf{k})} S(\mathbf{k}), & g' \in G_M. \end{cases} \quad (5)$$

Since for any $g, h \in G$, $S([gh]\mathbf{k}) = S(g[h\mathbf{k}])$, the corresponding phase functions for elements in G_M , whether primed or not, must satisfy the *group compatibility condition*,

$$\Phi_{g^*h^\dagger}(\mathbf{k}) \equiv \Phi_{g^*}(h\mathbf{k}) + \Phi_{h^\dagger}(\mathbf{k}), \quad (6)$$

where the asterisk and the dagger denote optional primes. A *spin space group*, describing the symmetry of a magnetic crystal, whether periodic or aperiodic, is thus given by a lattice L , a magnetic point group G_M , and a set of phase functions $\Phi_g(\mathbf{k})$ and $\Phi_{g'}(\mathbf{k})$, satisfying the group compatibility condition (6).

Magnetic space groups are classified in this formalism into *magnetic space group types* by organizing sets of phase functions satisfying the group compatibility condition (6) into equivalence classes. Two such sets Φ and $\hat{\Phi}$ are

equivalent if: (I) they describe indistinguishable spin density fields related as in (3) by a gauge function χ ; or (II) they correspond to alternative descriptions of the same crystal that differ by their choices of absolute length scales and spatial orientations. In case (I) Φ and $\hat{\Phi}$ are related by a *gauge transformation*,

$$\hat{\Phi}_{g^*}(\mathbf{k}) \equiv \Phi_{g^*}(\mathbf{k}) + \chi(g\mathbf{k} - \mathbf{k}), \quad (7)$$

where, again, the asterisk denotes an optional prime.

In the special case that the crystal is periodic ($D = d$) it is possible to replace each gauge function by a corresponding d -dimensional translation \mathbf{t} , satisfying $2\pi\chi(\mathbf{k}) = \mathbf{k} \cdot \mathbf{t}$, thereby reducing the requirement of indistinguishability to that of invariance to within a translation. Only then does the point group condition (5) become

$$S(g\mathbf{r}) = \begin{cases} S(\mathbf{r} - \mathbf{t}_g), & g \in G_M, \\ -S(\mathbf{r} - \mathbf{t}_g), & g' \in G_M, \end{cases} \quad (8)$$

the gauge transformation (7) becomes a mere shift of the origin, and the whole description reduces to that given in the section 3.1 for periodic crystals.

We refer the reader to references in the ‘‘Further reading’’ section for details regarding the enumeration of magnetic space groups of quasiperiodic crystals and for complete lists of such groups.

4 Extinctions in neutron diffraction of anti-ferromagnetic crystals

We said earlier that every wave vector \mathbf{k} in the lattice L of a magnetic crystal is a candidate for a diffraction peak unless symmetry forbids it. We are now in a position to understand exactly how this happens. Given a wave vector $\mathbf{k} \in L$ we examine all magnetic point-group operations g or g' for which $g\mathbf{k} = \mathbf{k}$. For such elements, the point-group condition (5) can be rewritten as

$$S(\mathbf{k}) = \begin{cases} e^{2\pi i\Phi_g(\mathbf{k})} S(\mathbf{k}), & g \in G_M, \\ -e^{2\pi i\Phi_{g'}(\mathbf{k})} S(\mathbf{k}), & g' \in G_M, \end{cases} \quad (9)$$

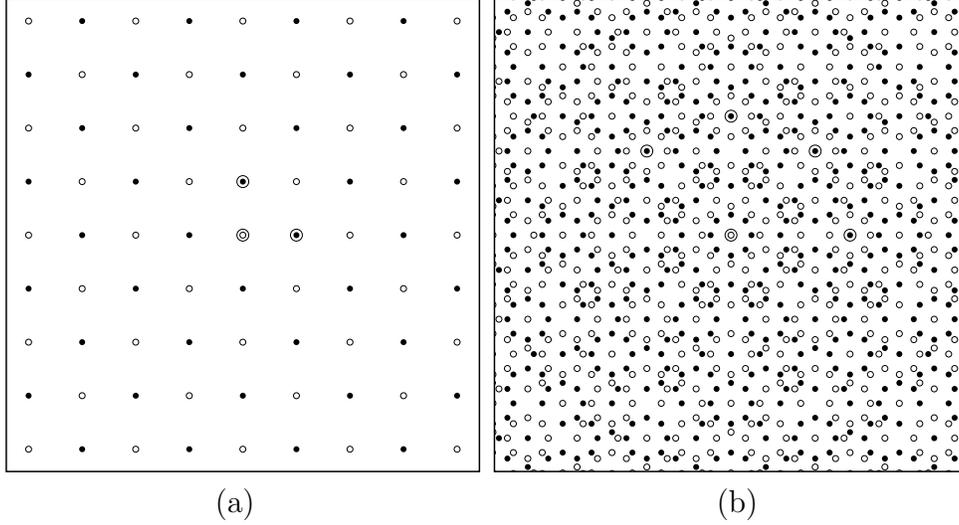


Figure 4: Extinctions of magnetic Bragg peaks in crystals with magnetic point groups of type 1, containing time inversion e' . Both figures show the positions of expected magnetic Bragg peaks indexed by integers ranging from -4 to 4. Filled circles indicate observed peaks and open circles indicate positions of extinct peaks. The origin and the D vectors used to generate the patterns are indicated by an additional large circle. (a) corresponds to the square crystal in Figure 2(a) with magnetic space group p_p4mm and (b) corresponds to the octagonal crystal in Figure 3(a) with magnetic space group p_p8mm .

requiring $S(\mathbf{k})$ to vanish unless $\Phi_g(\mathbf{k}) \equiv 0$, or $\Phi_{g'}(\mathbf{k}) \equiv 1/2$, or unless both conditions are satisfied when both g and g' are in G_M . It should be noted that the phase values in Eq. (9), determining the extinction of $S(\mathbf{k})$, are independent of the choice of gauge (7), and are therefore uniquely determined by the magnetic space-group type of the crystal.

Particularly striking are the extinctions when the magnetic point group is of type 1, containing time inversion e' . The relation $(e')^2 = e$ implies—through the group compatibility condition (6) and the fact that $\Phi_e(\mathbf{k}) \equiv 0$ —that $\Phi_{e'}(\mathbf{k}) \equiv 0$ or $1/2$. It then follows from the linearity of the phase function that on exactly half of the wave vectors in L $\Phi_{e'}(\mathbf{k}) \equiv 1/2$ and on the remaining half, which from a sublattice L_0 of index 2 in L , $\Phi_{e'}(\mathbf{k}) \equiv 0$. Thus, in magnetic crystals with magnetic point groups of type 1 at least half of the diffraction peaks are missing. Figure 4 shows the positions of the expected magnetic Bragg peaks corresponding to the square and octagonal magnetic

structures shown in Figures 2(a) and 3(a), illustrating this phenomenon.

5 Generalizations of magnetic groups

There are two natural generalizations of magnetic groups. One is to color groups with more than two colors, and the other is to spin groups where the spins are viewed as classical axial vectors free to rotate continuously in any direction.

An n -color point group G_C is a subgroup of $O(d) \times S_n$, where S_n is the permutation group of n colors. Elements of the color point group are pairs (g, γ) where g is a d -dimensional (proper or improper) rotation and γ is a permutation of the n colors. As before, for (g, γ) to be in the color point group of a finite object it must leave it invariant, and for (g, γ) to be in the color point group of a crystal it must leave it indistinguishable, which in the special case of a periodic crystal reduces to invariance to within a translation. To each element $(g, \gamma) \in G_C$ corresponds a phase function $\Phi_g^\gamma(\mathbf{k})$, satisfying a generalized version of the group compatibility condition (6). The color point group contains an important subgroup of elements of the form (e, γ) containing all the color permutations that leave the crystal indistinguishable without requiring any rotation g .

A spin point group G_S is a subgroup of $O(d) \times SO(d_s) \times 1'$, where $SO(d_s)$ is the group of d_s -dimensional proper rotations operating on the spins, and $1'$ is the time inversion group as before. Note that the dimension of the spins need not be equal to the dimension of space (*e.g.* one may consider a planar arrangement of 3-dimensional spins). Also note that because the spins are axial vectors there is no loss of generality by restricting their rotations to being proper. Elements of the spin point group are pairs (g, γ) where g is a d -dimensional (proper or improper) rotation and γ is a spin-space rotation possibly followed by time inversion. Here as well, elements of the form (e, γ) play a central role in the theory, especially in determining the symmetry constraints imposed by the corresponding phase functions $\Phi_e^\gamma(\mathbf{k})$ on the patterns of magnetic Bragg peaks, observed in elastic neutron diffraction experiments.

Acknowledgments

I would like to thank David Mermin for teaching me the symmetry of crystals, and Shahar Even-Dar Mandel for joining me in my investigation of the magnetic symmetry of quasicrystals. My research in these matters is funded by the Israel Science Foundation through grant No. 278/00.

See also:

Crystals
Quasicrystals
Point groups
Space groups
Long-range order
Neutron diffraction
Magnetism

Further reading:

On magnetic groups, color groups, and spin groups of periodic crystals:

1. W. Opechowski (1986), *Crystallographic and metacrystallographic groups* (North-Holland, Amsterdam).
2. A. V. Shubnikov, N. V. Belov and others (1964), *Colored symmetry* (Pergamon Press, New York).
3. W. Opechowski and R. Guccione (1965), in *Magnetism*, eds. G. T. Rado and H. Suhl, Vol. 2A, Chap. 3 (Academic Press, New York).
4. R. L. E. Schwarzenberger (1984), “Colour symmetry,” *Bull. London Math. Soc.* **16**, 209–240.
5. M. Senechal (1990), “Crystalline symmetries: An informal mathematical introduction,” (Adam Hilger, Bristol).

6. D. B. Litvin and W. Opechowski (1974), “Spin groups,” *Physica* **76** 538–554; D. B. Litvin (1973), “Spin translation groups and neutron diffraction analysis,” *Acta Cryst.* **A29**, 651–660; and D. B. Litvin (1977), “Spin point groups,” *Acta Cryst.* **A33**, 279–287.

On the symmetry of quasiperiodic crystals:

7. For a review see N. D. Mermin (1992), “The space groups of icosahedral quasicrystals and cubic, orthorhombic, monoclinic, and triclinic crystals,” *Rev. Mod. Phys.* **64**, 3–49.
8. For an elementary introduction see R. Lifshitz (1996), “The symmetry of quasiperiodic crystals,” *Physica A* **232**, 633–647.

On magnetic groups, color groups, and spin groups of quasiperiodic crystals:

9. R. Lifshitz (1997), “Theory of color symmetry for periodic and quasiperiodic crystals,” *Rev. Mod. Phys.* **69**, 1181.
10. R. Lifshitz and S. Even-Dar Mandel (2004), “Magnetically-ordered quasicrystals: Enumeration of spin groups and calculation of magnetic selection rules.” *Acta Cryst.* **A60** 167–178.