Flux ow resistivity in the system with multiple superconducting gaps

Jun Goryo and Hiroshi Matsukawa Department of Physics and Mathematics, Aoyama Gakuin University, 5-10-1 Fuchinobe, Sagamihara, Kanagawa, 229-8558, Japan

A bstract

We calculate the ux ow resistivity in a superconductor with multiple s-wave superconducting gaps. Our result agrees well with anom alous eld dependence of the resistivity recently observed in the two-gap superconductor M gB₂.

Keywords: ux ow, multi-gap structure, MgB₂

The vortex lines under an applied current catch the Lorentz force and m ove perpendicular to the current and m agnetic eld when the Lorentz force becomes larger than the pinning force. This is the ux ow state and the nite resistivity arises[1]. The essence of the ux ow resistivity is the presence of the bound states inside the vortex core with small energy gap, so that the conductivity in the core is practically norm al in the usual temperature range. Such states were found by C aroli, de G ennes and M atricon by using the m icroscopic m ethods[1]. Bardeen and Stephen found that the ux ow resistivity is basically proportional to the m agnetic eld H in both of the dirty and m oderately clean s-wave superconductors[1, 2]. This relation holds well alm ost all of the eld range in the vortex state.

The superconductivity of M gB₂ has the highest transition temperature (T_c ' 39K) in the m etallic m aterials at present[3] and the great amount of investigations has been done[4]. As one of the characteristic features in this superconductor, we can point out the fact that two di erent superconducting gaps with s-wave pairing symmetry exist on the two separated Ferm isurfaces having roughly equal density of states (DOS) [4]. Recently, the measurement

Submitted to SCES'04

of the ux ow resistivity in $M gB_2$ was reported by M atsuda's group [5]. Large deviations from the H -linear dependence for the ux ow resistivity has been found, in spite of the fact that the pairing symmetry of $M gB_2$ is s-wave[4]. Such anom alous behavior will be related to the multi-gap structure, but a clear explanation has not been shown so far. In this paper, we investigate the ux ow state in the multi-gap m odel and propose new m echanism for the anom alous ux ow resistivity.

First, let us rem ind the ux ow in the system with single superconducting band with a s-wave gap [1]. We suppose that the magnetic eld H = H 2and that the pinning force is negligible [5]. The velocity of ux lines v is related to the applied current J by the balance equation

$$J \quad \hat{z} \frac{0}{C} = V; \qquad (1)$$

where $_0 = hc=2e$ is the unit ux and the lhs. and the rhs of Eq. (1) denote the Lorentz force and viscous force, respectively. The origin of viscosity

is the dissipation caused by the C alori-de G ennes-M atricon bound states inside the core with sm all energy gap [1]. The dissipation induces the electric eld and its m acroscopic value is E = H v=c. By using this equation and Eq. (1), we can derive J = E = f, where $f = _0H = c^2$ denotes the ux ow resistivity. As we mentioned, Bardeen and Stephen found that f is proportional to the magnetic eld, namely, $f = _nH = H_{c2}$, where $_n$ is the norm all state resistivity [1]. Then, we obtain , which is independent of H , and v is determined by Eq. (1).

Next, we discuss the multi-gap system. We suppose that there are two superconducting bands with di erent-sized s-wave gaps in the system. The vortex states appear for each bands when the magnetic eld greater than the lower critical value is applied to the system. The applied current J is divided and the ux ow states arise for each two bands. Let J_1 and J_2 be the divided current in 1st-band and that in 2nd-band, respectively. We suppose that vortices in the 1st-band and that in the 2nd-band have the same velocity, since two kind of the cores would be overlapped because of the nature of the superconductivity.

W e extend the balance equation Eq. (1) to the two-gap system, that is

$$J_{i} \quad 2 \frac{0}{C} = i V; \qquad (2)$$

where i (i = 1;2) is the viscosity for the i-th band vortices. By using the equation E = H v=c, we can derive $J_i = E = {i \choose f}$, where ${i \choose f} = {}_0H = {}_ic^2$

denotes the ux ow resistivity in i-th band. Then,

$$J = \sum_{i=1}^{X^2} J_i = \sum_{i=1}^{X^2} \frac{1}{(i)} E;$$
(3)

and this equation indicates that the total ux ow resistivity in this system is

$$\frac{1}{t_{\rm W} \circ}_{\rm f} = \frac{X^2}{{}_{\rm i=1}} \frac{1}{{}_{\rm f}}; \qquad (4)$$

which rem inds us the parallel connection between two di erent resisters.

The resistivity $f_{f}^{(i)}$ may obey the Bardeen-Stephen relation, i.e.,

$${}_{f}^{(i)} = \frac{H}{H_{c2}^{(i)}} {}_{n}^{(i)};$$
(5)

where $H_{c2}^{(i)}$ and $n^{(i)}$ are the upper critical eld for the vortex state and norm al-state resistivity in the i-th band, respectively.

Let us compare f^{two} in Eq. (4) and the experimental results. First we would like to check the eld dependence of f^{two} . Suppose that $H_{c2}^{(1)} > H_{c2}^{(2)}$. By using Eq. (5),

$$t_{f}^{\text{two}} = \begin{pmatrix} 8 & \frac{H}{\frac{H}{c_{c}^{2}}} & \text{(low er critical eld < H} & H_{c2}^{(2)} \text{);} \\ \frac{H}{c_{c}^{2}} & \frac{H}{\frac{C_{c}^{2}}{c_{c}^{2}}} & \frac{H}{c_{c}^{2}} & \text{(low er critical eld < H} & H_{c2}^{(2)} \text{);} \\ \frac{H}{c_{c}^{2}} & \frac{H}{c_{c}^{2}} & \frac{H}{c_{c}^{2}} & H_{c2}^{(1)} \text{);} \\ \frac{H}{c_{c}^{2}} & \frac{H}{c_{c}^{2}} & H_{c2}^{(1)} \text{);} \\ \frac{H}{c_{c}^{2}} & \frac{H}{c_{c}^{2}} & \frac{H}{c_{c}^{2}} \text{);} \\ \frac{H}{c_{c}^{2}} & \frac{H}{c_{c}^{2}} & \frac{H}{c_{c}^{2}} \text{);} \\ \frac{H}{c_{c}^{2}} & \frac{H}{c_{c}^{2}} & \frac{H}{c_{c}^{2}} \text{);} \\ \frac{$$

Then, f_{f}^{two} is H-linear in the low eld regime, convexly in the high eld regime and continuously connected to the normal-state resistivity in the two-band system $(1 = n^{(1)} + 1 = n^{(2)})^{-1}$.

The ow resistivity measurement in MgB₂ was demonstrated for the magnetic eld parallel to the c-axes of the crystal and also for the eld in ab-plane and both of which show anomalous behavior[5]. We use the parameters $H_{c2}^{(2)} = H_{c2}^{(1)} = 0.04$ and $n_{n}^{(2)} = n_{n}^{(1)} = 0.26$ for H k ab case, and $H_{c2}^{(2)} = H_{c2}^{(1)} = 0.06$ and $n_{n}^{(2)} = n_{n}^{(1)} = 0.5$ for H k c case. The order of these values appear to be consistent with the facts that the DOS for each two bands are roughly equal, the energy size of larger gap is 7 m ev and that

of sm aller gap is 2m ev [4], and the carrier scattering rates for each two bands are almost equal[5]. As is given in Fig. 1, our result agrees well with experimental data, especially for H k c case.

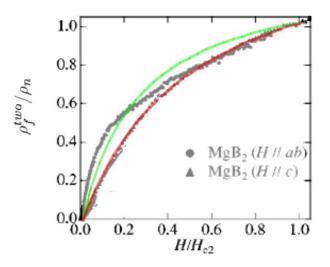


Figure 1: W e compare the experimental data of ux ow resistivity in M gB₂ given by Ref. [5] and our result Eq. (6). B lack dots and triangles show the experimental results for H k ab case and H k c case, respectively. G reen line shows Eq. (6) with parameters $H_{c2}^{(2)} = H_{c2}^{(1)} = 0.04$ and $n_{n}^{(2)} = n_{n}^{(1)} = 0.26$, and Red line shows that with $H_{c2}^{(2)} = H_{c2}^{(1)} = 0.06$ and $n_{n}^{(2)} = n_{n}^{(1)} = 0.55$.

In summary, we have considered a system with two superconducting bands. The total ux ow resistivity in the system is written as the parallel connection of the ux ow resistivity for the 1st-band vortices and that for the 2nd-band vortices. The result agrees with anomalous eld dependence of the ow resistivity recently observed in the two-gap superconductor $M gB_2$. Our discussion would be generalized to the system with n (> 2) superconducting bands. The detailed discussion will be published elsewhere.

References

- [1] \Introduction to Superconductivity", M.Tinkham (2nd.ed., McGraw-Hill, Singapore, 1996), and references therein.
- [2] Y.Matsuda, et alPhys.Rev.B 66 (2002) 014527.
- [3] Nagam atsu, N. et al. Nature (London) 410 (2001) 63.
- [4] See, for the recent review, P.C.Can eld and G.W Crabtree, Physics Today 56 (3), (2003) 34.
- [5] A.Shibata et al.Phys.Rev.B 68 (2003) 060501(R).