

# Gap Symmetry of Superconductivity in UPd<sub>2</sub>Al<sub>3</sub>

H. Won,<sup>1</sup> D. Parker,<sup>2</sup> K. Maki,<sup>2</sup> T. Watanabe,<sup>3</sup> K. Izawa,<sup>3</sup> and Y. Matsuda<sup>3</sup>

<sup>1</sup>*Department of Physics, Hallym University, Chuncheon 200-702, South Korea*

<sup>2</sup>*Department of Physics and Astronomy,  
University of Southern California, Los Angeles, CA 90089-0484 USA*

<sup>3</sup>*Institute for Solid State Physics, University of Tokyo,  
Kashiwanoha 5-1-5, Kashiwa, Chiba 277-8581, Japan*

(Dated: March 22, 2022)

## Abstract

The angle dependent thermal conductivity of the heavy-fermion superconductor UPd<sub>2</sub>Al<sub>3</sub> in the vortex state was recently measured by Watanabe et al. Here we analyze this data from two perspectives: universal heat conduction and the angle-dependence. We conclude that the superconducting gap function  $\Delta(\mathbf{k})$  in UPd<sub>2</sub>Al<sub>3</sub> has horizontal nodes and is given by  $\Delta(\mathbf{k}) = \Delta \cos(2\chi)$ , with  $\chi = ck_z$ .

PACS numbers:

## 1. Introduction

Since the discovery of the heavy-fermion superconductor  $\text{CeCu}_2\text{Si}_2$  in 1979[1] the gap symmetries of unconventional superconductors have become a central issue in condensed-matter physics[2]. In the last few years, the angle-dependent magnetothermal conductivity in the vortex state of nodal superconductors has been established as a powerful technique to address the gap symmetry. This is in part due to the theoretical understanding of the quasi-particle spectrum in the vortex state of nodal superconductors, following the path-breaking work by Volovik[3, 4, 5]. Using this approach, Izawa et al have succeeded in identifying the gap symmetries of superconductivity in  $\text{Sr}_2\text{RuO}_4$ ,  $\text{CeCoIn}_5$ ,  $\kappa\text{-(ET)}_2\text{Cu(NCS)}_2$ ,  $\text{YNi}_2\text{B}_2\text{C}$ , and  $\text{PrOs}_4\text{Sb}_{12}$ [6, 7, 8, 9, 10].

Superconductivity in  $\text{UPd}_2\text{Al}_3$  was discovered by Geibel et [11] in 1991. The reduction of the Knight shift in NMR[12] and the Pauli limiting of  $H_{c2}$ [13] indicate spin singlet pairing in this compound. Nodal superconductivity with horizontal nodes has been suggested from the thermal conductivity data [14] and from the c-axis tunneling data of thin film  $\text{UPd}_2\text{Al}_3$  samples[15]. Very recently, McHale et al [16] have proposed  $\Delta(\mathbf{k}) = \Delta \cos(\chi)$  (with  $\chi = ck_z$ ) based on a model where the pairing interaction arises from antiparamagnon exchange with  $\mathbf{Q} = (0, 0, \frac{\pi}{c})$  [17]. Furthermore, the thermal conductivity data of  $\text{UPd}_2\text{Al}_3$  for a variety of magnetic field orientations have been reported[18]. At first glimpse the experimental data appeared to support the model proposed by McHale et al.

The object of the present paper is to show that an alternative model, i.e.  $\Delta(\mathbf{k}) = \Delta \cos(2\chi)$ , describes the thermal conductivity data more consistently. For this purpose we first generalize the universal heat conduction initially proposed in the context of d-wave superconductivity[19, 20] to a variety of nodal superconductors. We limit ourselves to quasi-2D systems with  $\Delta(\mathbf{k}) = \Delta f$  and  $f = \cos(2\phi), \sin(2\phi), \cos \chi, e^{i\phi} \cos \chi, \cos(2\chi) \sin \chi$ , and  $e^{i\phi} \sin \chi$ . It is found that the in-plane thermal conductivity  $\kappa_{xx}$  is independent of  $f$ . On the other hand, the out-of-plane thermal conductivity  $\kappa_{zz}$  can discriminate different  $f$ 's. Second, we extend an early study of the angle-dependent thermal conductivity[21] for  $\kappa_{yy}$  in a magnetic field rotated in the z-x plane. The comparison of these results with experimental data indicates  $\Delta(\mathbf{k}) = \Delta \cos(2\chi)$ .

## 2. Universal Heat Conduction

Here we consider the thermal conductivity  $\kappa$  in the limit  $T \rightarrow 0K$  in the presence of disorder. It is assumed that the impurities are in the unitary scattering limit[20]. We consider

the quasi-2D gap functions  $\Delta(\mathbf{k}) = \Delta f$  with  $f = \cos(2\phi), \sin(2\phi)$  [d-wave superconductor as in the high- $T_c$  cuprates],  $\cos \chi, e^{i\phi} \cos \chi$  (f-wave superconductor as proposed for  $\text{Sr}_2\text{RuO}_4$  [6]),  $\cos(2\chi), \sin \chi$ , and  $e^{i\phi} \sin \chi$ . Following Ref.[20], the thermal conductivity within the conducting plane is given by

$$\kappa_{xx}/\kappa_n = \kappa_{yy}/\kappa_n = \frac{\Gamma_0}{\Delta} \langle (1 + \cos(2\phi)) \frac{C_0^2}{(C_0^2 + |f|^2)^{\frac{3}{2}}} \rangle \quad (1)$$

$$= \frac{2\Gamma_0}{\pi\Delta\sqrt{1+C_0^2}} E\left(\frac{1}{\sqrt{1+C_0^2}}\right) = I_1(\Gamma/\Gamma_0) \quad (2)$$

where  $\kappa_n$  is the thermal conductivity in the normal state when  $\Gamma = \Gamma_0$ , and  $\Gamma$  is the quasi-particle scattering rate in the normal state. Here  $\langle \dots \rangle$  denotes the average over  $\phi$  and  $\chi$ , and Eq.(1) tells us that the planar thermal conductivity is independent of the gap functions given above. Also  $\Gamma_0 = \frac{\pi}{2\gamma} T_c = 0.866 T_c$  and  $T_c$  is the superconducting transition temperature of the pure system. However, the quasi-particle scattering rate at  $E=0$  is given by  $\Delta C_0$ , and  $C_0$  is determined by [20]

$$\frac{C_0^2}{\sqrt{1+C_0^2}} K\left(\frac{1}{\sqrt{1+C_0^2}}\right) = \frac{\pi\Gamma}{2\Delta} \quad (3)$$

and  $\Delta = \Delta(0, \Gamma)$  has to be determined self-consistently as in [20]. Here  $K(k)$  and  $E(k)$  are the complete elliptic integrals. We show  $I_1(\Gamma/\Gamma_0)$  in Fig.1. Now let us look at the out-of-plane thermal conductivity  $\kappa_{zz}$ . This is given by

$$\kappa_{zz}/\kappa_n = \frac{\Gamma_0}{\Delta} \langle (1 - \cos(2\chi)) \frac{C_0^2}{(C_0^2 + |f|^2)^{\frac{3}{2}}} \rangle \quad (4)$$

$$= I_1(\Gamma/\Gamma_0) \quad (5)$$

for  $f = \cos(2\phi), \sin(2\phi)$  and  $\cos(2\chi)$ , but

$$\frac{\kappa_{zz}}{\kappa_n} = \frac{4\Gamma_0}{\pi\Delta\sqrt{1+C_0^2}} \left( E\left(\frac{1}{\sqrt{1+C_0^2}}\right) - C_0^2 \left( K\left(\frac{1}{\sqrt{1+C_0^2}}\right) - E\left(\frac{1}{\sqrt{1+C_0^2}}\right) \right) \right) \quad (6)$$

$$= I_2\left(\frac{\Gamma}{\Gamma_0}\right) \quad (7)$$

for  $f = \cos \chi, e^{\pm i\phi} \cos \chi$ , and

$$\kappa_{zz}/\kappa_n = \frac{2\Gamma_0\Gamma}{\Delta} \left( 1 - \frac{E\left(\frac{1}{\sqrt{1+C_0^2}}\right)}{K\left(\frac{1}{\sqrt{1+C_0^2}}\right)} \right) \equiv I_3\left(\frac{\Gamma}{\Gamma_0}\right) \quad (8)$$

for  $f = \sin \chi, e^{i\phi} \sin \chi$ . These functions are shown in Fig. 1.

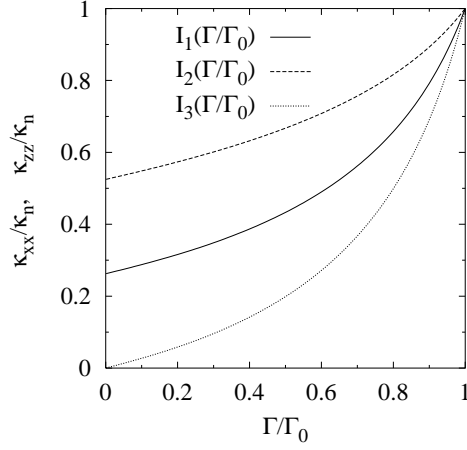


FIG. 1: The functions  $I_1$ ,  $I_2$  and  $I_3$ .

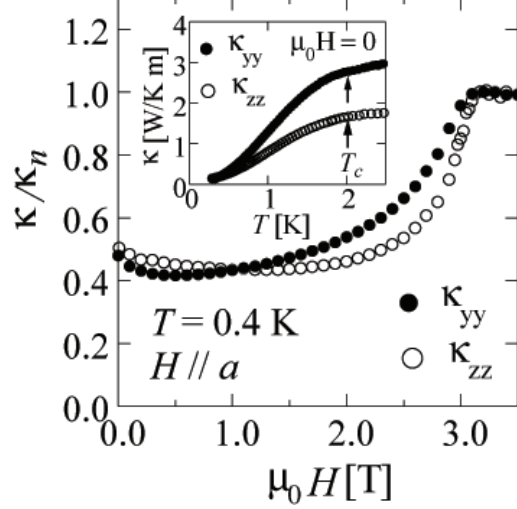


FIG. 2:  $\kappa_{yy}(H)$  and  $\kappa_{zz}(H)$  for  $\text{UPd}_2\text{Al}_3$

In Fig. 2 we show  $\kappa_{yy}(H)$  and  $\kappa_{zz}$  for  $\mathbf{H} \parallel \hat{z}$  taken for  $\text{UPd}_2\text{Al}_3$  [22]. In particular  $(\kappa_{00})_{yy} = (\kappa_{00})_{zz}$  indicates  $\Delta(\mathbf{k}) \sim \cos(2\chi)$ . Of course the effect of the magnetic field is not equivalent to the effect of impurities. But this comparison points to  $\Delta(\mathbf{k}) \sim \cos(2\chi)$  for  $\text{UPd}_2\text{Al}_3$ . We note also that for  $f = \sin \chi$  and  $e^{i\phi} \sin \chi$ , there will be no universal heat

conduction in  $\kappa_{zz}$ .

### 3. Angle-dependent magnetothermal conductivity

First let us recapture the quasiparticle density of states in the vortex state of nodal superconductors. [4] For simplicity we consider f's with horizontal nodes:  $f = e^{i\phi} \cos \chi, \cos \chi, \cos 2\chi, \sin \chi$  and  $e^{i\phi} \sin \chi$  [21]. Then the first two f's have nodes at  $\chi_0 = \pm \frac{\pi}{2}$ , whereas  $f = \cos 2\chi$  at  $\chi_0 = \pm \frac{\pi}{4}$  and  $f = \sin \chi$  and  $e^{i\phi} \sin \chi$  at  $\chi_0 = 0$ .

In an arbitrary field orientation we obtain the quasiparticle density of states

$$\mathcal{G}(\mathbf{H}) \equiv \frac{N(0, \mathbf{H})}{N_0} = \frac{2}{\pi^2} \frac{v_a \sqrt{eH}}{\Delta} I_1(\theta) \quad (9)$$

for the superclean limit and

$$\mathcal{G}(\mathbf{H}) \simeq \left(\frac{2\Gamma}{\pi\Delta}\right)^{1/2} [\log(4\sqrt{\frac{2\Delta}{\pi\Gamma}})]^{1/2} \left(1 + \frac{v_a^2 eH}{8\pi^2 \Gamma \Delta} \log\left(\frac{\Delta}{v_a \sqrt{eH}}\right) I_2(\theta)\right) \quad (10)$$

for the clean limit, where

$$\begin{aligned} I_1(\theta) &= (\cos^2 \theta + \alpha \sin^2 \theta)^{1/4} \frac{1}{\pi} \int_0^\pi d\phi (\cos^2 \theta + \sin^2 \theta (\sin^2 \phi + \alpha \sin^2 \chi_0) + \sqrt{\alpha} \sin(\chi_0) \cos \phi \sin(2\theta))^{1/2} \\ &\simeq (\cos^2 \theta + \alpha \sin^2 \theta)^{1/4} (1 + \sin^2 \theta (-\frac{1}{2} + \alpha \sin^2 \chi_0))^{1/2} \left(1 - \frac{1}{64} \frac{\sin^2 \theta (\sin^2 \theta + 16\alpha \sin^2 \chi_0 \cos^2 \theta)}{(1 + \sin^2 \theta (-\frac{1}{2} + \alpha \sin^2 \chi_0))^2}\right) \end{aligned}$$

and

$$I_2(\theta) = (\cos^2 \theta + \alpha \sin^2 \theta)^{1/2} (1 + \sin^2 \theta (-\frac{1}{2} + \alpha \sin^2 \chi_0)). \quad (11)$$

Here  $\alpha = (v_c/v_a)^2$  and  $\theta$  is the angle  $\mathbf{H}$  makes from the z-axis. Then the specific heat, the spin susceptibility and the planar superfluid density in the vortex state in the limit  $T \rightarrow 0K$  are given by [23]

$$C_s/\gamma_N T = \mathcal{G}(\mathbf{H}), \frac{\chi_S}{\chi_N} = \mathcal{G}(\mathbf{H}), \quad (12)$$

$$\frac{\rho_{S\parallel}(\mathbf{H})}{\rho_{S\parallel}(0)} = 1 - \mathcal{G}(\mathbf{H}) \quad (13)$$

Similarly the thermal conductivity  $\kappa_{yy}$  when the magnetic field is rotated in the z-x plane is given by

$$\frac{\kappa_{yy}}{\kappa_n} = \frac{2}{\pi^3} \frac{v_a^2 eH}{\Delta^2} F_1(\theta) \quad (14)$$

in the superclean limit and

$$\frac{\kappa_{yy}}{\kappa_{00}} = 1 + \frac{v_a^2 (eH)}{6\pi^2 \Gamma \Delta} F_2(\theta) \log(2\sqrt{\frac{2\Delta}{\pi\Gamma}}) \log\left(\frac{2\Delta}{v_a \sqrt{eH}}\right) \quad (15)$$

in the clean limit where

$$F_1(\theta) = \sqrt{\cos^2 \theta + \alpha \sin^2 \theta} (1 + \sin^2 \theta (-\frac{3}{8} + \alpha \sin^2 \chi_0)) \quad (16)$$

$$F_2(\theta) = \sqrt{\cos^2 \theta + \alpha \sin^2 \theta} (1 + \sin^2 \theta (-\frac{1}{4} + \alpha \sin^2 \chi_0)) \quad (17)$$

We show in Fig. 3  $F_1(\theta)$  and  $F_2(\theta)$  for  $\alpha = 0.69$  (the value appropriate for UPd<sub>2</sub>Al<sub>3</sub>) and

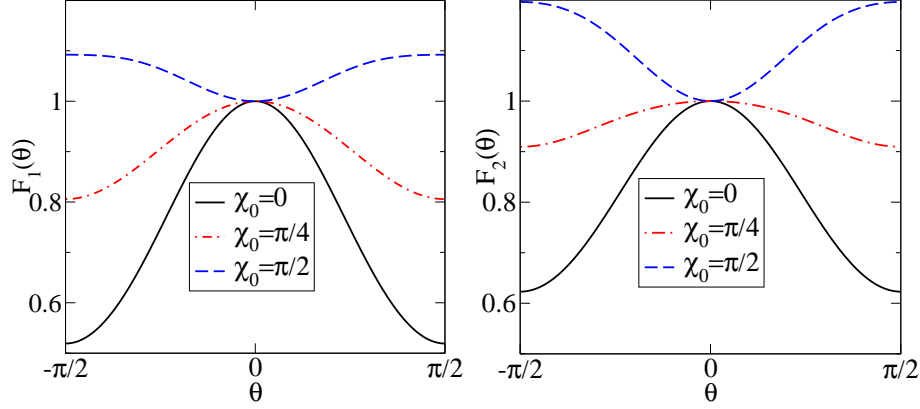


FIG. 3: The angular functions  $F_1(\theta)$  (left) and  $F_2(\theta)$

$\chi_0 = 0, \frac{\pi}{4}$ , and  $\frac{\pi}{2}$ , which is compared with the experimental data [18] taken at  $T = 0.4K$  shown in Fig. 4. Except for the data taken for  $H = 2.5T$ , the data for  $H = 0.5T, 1T$  and  $2T$  are consistent with  $\chi_0 = \frac{\pi}{4}$ , indicating again  $f = \cos 2\chi$ . We note also the sign of the twofold term in  $\kappa_{yy}$  at  $T = 0.4K$  changes sign at  $H = 0.36T$ . This is consistent with the fact that for  $T < v\sqrt{eH}$  the nodal excitations are mostly due to the Doppler shift while for  $T > v\sqrt{eH}$  the thermal excitations dominate[24].

#### 4. Concluding Remarks

We have analyzed recent thermal conductivity data [18] of UPd<sub>2</sub>Al<sub>3</sub> from 2 perspectives: universal heat conduction and the angle-dependence. The present study indicates  $\Delta(\mathbf{k}) = \Delta \cos(2\chi)$ . This is different from the conclusion reached in Ref.[18]. Also we have extended the universal heat conduction for a class of superconducting order parameters  $\Delta(\mathbf{k})$ , which will be useful for identifying the gap symmetry of new superconductors such as URu<sub>2</sub>Si<sub>2</sub> and UNi<sub>2</sub>Al<sub>3</sub>.

Furthermore, we have worked out the expressions for  $\kappa_{yy}$  when the magnetic field is rotated within the z-x plane. The angle dependence of  $\kappa_{yy}$  is extremely useful to locate the nodal lines when all nodal lines are horizontal. Perhaps  $\kappa_{yy}$  in Sr<sub>2</sub>RuO<sub>4</sub> will help to identify the precise position of the horizontal nodal lines in  $\Delta(\mathbf{k})$ , if a further study of

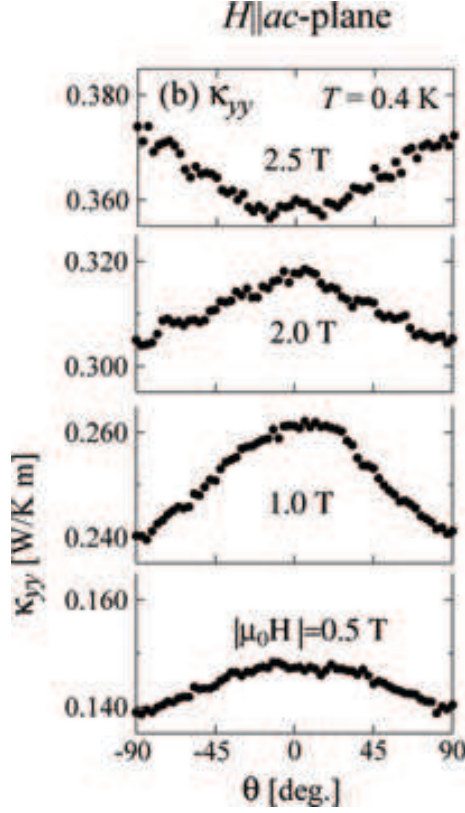


FIG. 4: Angular-dependent magnetothermal conductivity  $\kappa_{yy}$  of  $\text{UPd}_2\text{Al}_3$

nodal lines is necessary. Also after  $\text{UPt}_3$  and  $\text{UPd}_2\text{Al}_3$  we expect many of the U-compound superconducting energy gaps have horizontal lines.

### Acknowledgments

We thank Balazs Dora, Hae-Young Kee, Peter Thalmeier, and Attila Virosztek for helpful collaborations on related subjects.

- 
- [1] F. Steglich, J. Aarts, C.D. Bredl, W. Lieke, D. Meschede, W. Franz and H. Schäfer, Phys. Rev. Lett. **43**, 1892 (1979).
  - [2] M. Sigrist and K. Ueda, Rev. Mod. Phys. **63**, 239 (1991).
  - [3] G.E. Volovik, JETP Lett. **58**, 469 (1993).
  - [4] H. Won and K. Maki, cond-mat/0004105.
  - [5] T. Dahm, H. Won and K. Maki, cond-mat/0006301.
  - [6] K. Izawa et al, Phys. Rev. Lett. **86**, 2653 (2001).

- [7] K. Izawa et al, Phys. Rev. Lett. **87**, 57002 (2001).
- [8] K. Izawa et al, Phys. Rev. Lett. **88**, 27002 (2002).
- [9] K. Izawa et al, Phys. Rev. Lett. **89**, 137006 (2002).
- [10] K. Izawa et al, Phys. Rev. Lett. **90**, 11701 (2003).
- [11] C. Geibel et al, Z. Phys. B **84**, 1 (1991).
- [12] H. Tou et al, J. Phys. Soc. Jpn. **64**, 725 (1995).
- [13] J. Hessert et al, Physica B **230-232**, 373 (1997).
- [14] May Chiao, B. Lussier, E. Elleman and L. Taillefer, Physica B **230**, 370 (1997).
- [15] M. Jourdan, M. Huth and H. Adrian, Nature **398**, 47 (1999).
- [16] P. MacHale, P. Thalmeier and P. Fulde, cond-mat/0401520.
- [17] N. Bernhoeft, Eur. Phys. J. **B**, 685 (2000).
- [18] T. Watanabe et al, cond-mat/0405211.
- [19] P. A. Lee, Phys. Rev. Lett. **71**, 1887 (1993).
- [20] Y. Sun and K. Maki, Europhys. Lett. **32**, 335 (1995).
- [21] P. Thalmeier and K. Maki, Europhys. Lett. **58**, 119 (2002).
- [22] T. Watanabe et al (unpublished).
- [23] H. Won and K. Maki, Europhys. Lett. **56**, 729 (2001).
- [24] H. Won and K. Maki, Current Appl. Phys. **1**, 291 (2001); also in “Vortices in Unconventional Superconductors and Superfluids”, edited by G. E. Volovik, N. Schopohl and R. P. Huebener (Springer, Berlin 2002).