

Structural aspects of metamagnetism in $\text{Ca}_{2-x}\text{Sr}_x\text{RuO}_4$ ($0.2 < x < 0.5$): field tuning of orbital occupation

M. Kriener,¹ P. Steffens,¹ J. Baier,¹ O. Schumann,¹ T. Zabel,¹ T. Lorenz,¹ O. Friedt,¹ R. Müller,¹ A. Gukasov,² P. Radaelli,^{3,4} P. Reutler,^{5,6} A. Revcolevschi,⁶ S. Nakatsuji,⁷ Y. Maeno,^{7,8} and M. Braden^{1,*}

¹ *II. Physikalisches Institut, Universität zu Köln, Zùlpicher Str. 77, D-50937 Köln, Germany*

² *Laboratoire Léon Brillouin, C.E.A./C.N.R.S., F-91191 Gif-sur-Yvette CEDEX, France*

³ *ISIS Facility, Rutherford Appleton Laboratory,*

Chilton, Didcot, Oxon OX11 0QX, United Kingdom

⁴ *Department of Physics and Astronomy, University College London, London WC1E 6BT, United Kingdom*

⁵ *II. Physikalisches Institut, RWTH Aachen, Huykensäweg, D-52056 Aachen, Germany*

⁶ *Laboratoire de Physico-Chimie de l'Etat Solide, Université Paris Sud, 91405 Orsay Cedex, France*

⁷ *Department of Physics, Kyoto University, Kyoto 606-8502, Japan*

⁸ *International Innovation Center and Departement of Physics, Kyoto 606-8502, Japan*

(Dated: October 6, 2018, **preprint**)

The crystal structure of $\text{Ca}_{2-x}\text{Sr}_x\text{RuO}_4$ with $0.2 < x < 1.0$ has been studied by diffraction techniques and by high resolution capacitance dilatometry as a function of temperature and magnetic field. Upon cooling in zero magnetic field below about 25 K the structure shrinks along the c -direction and elongates in the a, b planes ($0.2 < x < 1.0$), whereas the opposite occurs upon cooling at high-field ($x = 0.2$ and 0.5). These findings indicate an orbital rearrangement driven by temperature and magnetic field, which accompanies the metamagnetic transition in these compounds.

The phase diagram of $\text{Ca}_{2-x}\text{Sr}_x\text{RuO}_4$ possesses quite different end members with the spin-triplet superconductor Sr_2RuO_4 on the one side [1] and the antiferromagnetically ordered Mott insulator Ca_2RuO_4 on the other side [2, 3]. Since Sr and Ca are both divalent, one has to attribute the different physical behavior [4, 5] entirely to the difference in the ionic radii. For small Ca content the octahedra present a c axis rotation and for higher Ca content ($x < 0.5$) a tilt of the octahedra around an in-plane axis occurs [6]. These distortions, through reduction of the hybridization, imply smaller band widths, which together with a constant Hubbard type interaction, enhance the correlation effects [7]. For Sr content lower than 0.2, finally Mott localization occurs in a material [4, 5] which exhibits a strong rotation and a strong tilt deformation [6].

Outstanding physical properties are found in compounds in the metallic regime but close to localization, $0.2 < x < 0.5$. At $T \sim 2$ K samples with $x \sim 0.5$ exhibit a magnetic susceptibility a factor of 200 higher than that of pure Sr_2RuO_4 [8]. In addition, the linear coefficient in the specific heat is exceptionally high, of the order of $C/T \sim 250 \frac{\text{mJ}}{\text{mole K}^2}$ [8, 9], well in the range of typical heavy fermion compounds. Inelastic neutron scattering has revealed strongly enhanced magnetic fluctuations of incommensurate character [10], very different from those in pure Sr_2RuO_4 [11, 12].

For Sr concentrations lower than 0.5, but still in the metallic phase, the tilt distortion occurs and strongly modifies the physical properties. The magnetic susceptibility at 2 K, measured in a low field, decreases with decreasing Sr content and increasing tilt; for $0.2 < x < 0.5$ there is a maximum in the temperature dependence of the susceptibility [5]. In this concentration range the

low-temperature low-field magnetization is, hence, small compared with the extrapolation both from high temperature and from high Sr concentration. A metamagnetic transition occurs in these compounds at low temperature yielding a high-field magnetization for $x = 0.2$ which actually exceeds that for $x = 0.5$ [8]. A similar metamagnetic transition has been reported for $\text{Sr}_3\text{Ru}_2\text{O}_7$ [13], where the related quantum critical end point has been proposed to cause outstanding transport properties.

Single crystals of $\text{Ca}_{2-x}\text{Sr}_x\text{RuO}_4$ were grown by a floating zone technique in image furnaces at Kyoto University ($x = 0.2, 0.62$ and 1.0) and at Université Paris Sud ($x = 0.5$); a powder sample of $\text{Ca}_{1.8}\text{Sr}_{0.2}\text{RuO}_4$ was prepared by the standard solid state reaction at Universität zu Köln. Single crystal neutron diffraction experiments were performed on the lifting counter diffractometer 6T.2 at the Orphée reactor in magnetic fields up to 7 T. Using the GEM time of flight diffractometer at the ISIS facility, powder diffraction patterns were recorded in fields up to 10 T. Thermal expansion and magnetostriction were studied in magnetic fields up to 14 T [14].

The thermal expansion was determined on the single crystals of compositions, $x = 0.2, 0.5, 0.62$, and 1.0 , along the c axis and along an in-plane direction. The results are presented in Fig. 1 together with the relative length changes obtained by integration. In all samples we find qualitatively identical anomalies occurring near $T \sim 25$ K; these are strongest in $\text{Ca}_{1.8}\text{Sr}_{0.2}\text{RuO}_4$. There is a shrinking of the c axis and an elongation of the RuO_2 plane at low temperature. In contrast to these low-temperature anomalies, the thermal expansion at higher temperature is qualitatively different within the series. Samples with $x > 0.5$ show a normal positive thermal expansion along the planes but a negative thermal expansion

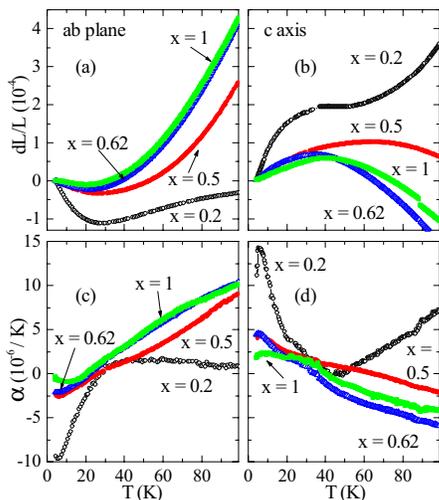


FIG. 1: Temperature dependence of the integrated relative length changes a), b) and the thermal expansion coefficients c), d) for different Sr concentrations: a), c) and b), d) refer to the in-plane and to the c directions, respectively.

sion coefficient along c , whereas the samples with smaller Sr content exhibit nearly the opposite.

Whereas all high-temperature effects may be explained by the structural arguments [15], the thermal expansion anomalies at low temperature must have an electronic origin. The expansion coefficients exhibit extrema below 10 K excluding an explanation by anomalous phonon Grüneisen parameters, since there are no optical or zone-boundary modes in the energy range of 1 meV and below. Instead, the electronic Grüneisen parameter at low temperature appears to be extraordinarily large.

The thermal-expansion anomalies have been confirmed by diffraction techniques, which may analyze both orthorhombic in-plane directions independently, see Fig. 2. The low-temperature expansion upon cooling is observed along both in-plane directions, whereas the a and b directions show a different thermal expansion at higher temperature due to the tilt-induced orthorhombic distortion. The low-temperature anomalies are thus not directly related to the tilt distortion. Nevertheless, the fact that all features are strongest in the sample with strongest tilt distortion suggests a pronounced coupling. The observed expansion of the lattice along the planes and the compression perpendicular to them qualitatively resembles the effect observed at the metal-insulator transition in Ca_2RuO_4 [6]. However, in Ca_2RuO_4 , the changes of the lattice constants are about a factor 30 – 50 larger, and the electric resistivity strongly increases below the structural change, whereas $\text{Ca}_{1.8}\text{Sr}_{0.2}\text{RuO}_4$ stays metallic to the lowest temperatures [5]. Nevertheless, the structural anomalies in $\text{Ca}_{1.8}\text{Sr}_{0.2}\text{RuO}_4$ are associated with the same electronic effect: a down shift of the d_{xy} orbital energy compared to those of the d_{xz} and d_{yz} orbitals and, hence, a transfer of electrons from the one-dimensional

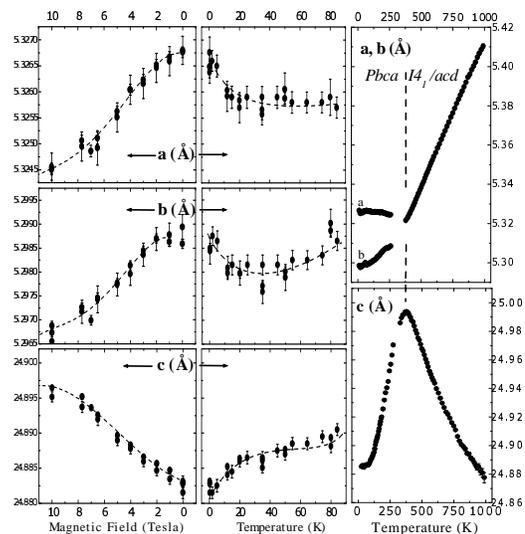


FIG. 2: Lattice parameters as a function of temperature and magnetic field: Right and middle: temperature dependence of the orthorhombic lattice parameters in $\text{Ca}_{1.8}\text{Sr}_{0.2}\text{RuO}_4$ determined with a Laboratory X-ray diffractometer and the GEM diffractometer at ISIS. Left: magnetic field dependence of the lattice parameters obtained by neutron diffraction on GEM at 0.35 K.

bands into the planar γ -band [17] (for notation see [18]).

For $\text{Ca}_{1.8}\text{Sr}_{0.2}\text{RuO}_4$, there is clear evidence that the anomalous structural behavior at low temperature is accompanied by anomalies in the magnetic and electronic properties detected earlier. In Fig. 3a) – c) the change in the lattice constants is compared to the temperature dependencies of the low-field magnetization and of the in-plane electric resistivity. The latter shows a down-turn just around the temperature range where the thermal expansion anomaly is observed. The magnetic susceptibility deviates from Curie-Weiss behaviour in this temperature range, presenting a maximum at about 10 K [4, 5]. We conclude that the structural anomaly in $\text{Ca}_{1.8}\text{Sr}_{0.2}\text{RuO}_4$ is associated with an electronic mechanism. In $\text{Ca}_{1.5}\text{Sr}_{0.5}\text{RuO}_4$ there is a similar though much weaker effect in the in-plane resistivity [4]; a related reduction of the low-temperature magnetic susceptibility might be hidden by its normal low-temperature increase.

The response to the metamagnetic transition in $\text{Ca}_{1.8}\text{Sr}_{0.2}\text{RuO}_4$ was studied by neutron diffraction, see Fig. 2, by the measurement of the magnetostriction with a high-resolution capacitance dilatometer, Fig. 3d) and 3g), and by heat capacity studies, Fig. 3h) [22]. In the magnetostriction experiment, see Fig. 3d) and 3g), the field was oriented along the c direction and the length change was recorded parallel to the field. The metamagnetic transition is clearly seen at 7 T leading to an enhancement of the c axis by $\epsilon_c = \frac{\Delta L(B)}{L} \sim 6 \times 10^{-4}$. In close resemblance with their temperature dependen-

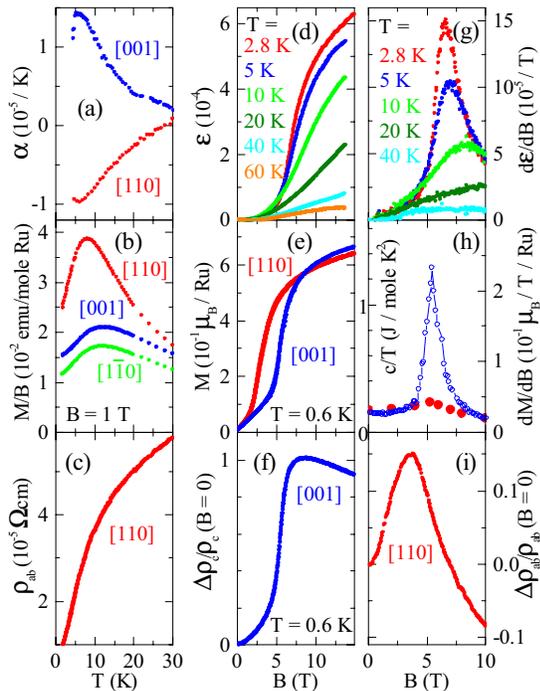


FIG. 3: Comparison of the temperature dependencies of a) thermal expansion, b) magnetization, and c) in-plane resistivity for $\text{Ca}_{1.8}\text{Sr}_{0.2}\text{RuO}_4$. d) – i) Comparison of the magnetic-field dependencies in $\text{Ca}_{1.8}\text{Sr}_{0.2}\text{RuO}_4$: d) the longitudinal magnetostriction $\varepsilon_c = \Delta L/L$ for a field along the c direction, e) the magnetization for fields along [110] and [001] directions (note that the metamagnetic transition depends on the orientation of the field), f) the magneto-resistivity along c direction, g) the field derivative of the magnetostriction, h) the field derivative of the magnetization and the linear coefficient of the specific heat $\frac{C_p}{T}$ [22], and i) the in-plane longitudinal magneto-resistivity. Resistivity, magneto-resistivity and magnetization data were taken from references [4, 5, 8].

cies, the structural change at the metamagnetic transition is accompanied by changes in magnetization and electrical resistivity. As shown in Fig. 3d) – f) magnetization, length change and c axis magneto-resistivity scale with each other. The field derivatives corresponding to the magnetostriction and the field dependent susceptibility show a similar field dependence as the in-plane magneto-resistivity [23]. Also the specific heat over T ratio, $\frac{C_p}{T}$ [22], increases around the critical field but much less. Comparing the susceptibility with $\frac{C_p}{T}$ quantitatively, one finds a normal Wilson ratio at low and high fields, whereas the Wilson ratio at the metamagnetic transition is strongly enhanced, close to 40, due to the much stronger effect of the susceptibility. The maximum of the specific heat coefficient at the metamagnetic field indicates that the system transits between two different instabilities [10]. It appears most likely that the metamagnetic transition in compounds close to $x = 0.5$ is shifted towards zero field; therefore, the large susceptibility and the high Wilson ratio of $\text{Ca}_{1.5}\text{Sr}_{0.5}\text{RuO}_4$ [8] at zero field may still be caused by the same physics.

In the diffraction experiment the metamagnetic transition is smeared out due to the random orientation of the grains with respect to the field [8]. However, the overall magnetostriction remains clearly visible, see Fig. 2. Crossing the transition into the high-field phase we find a shrinking along both in-plane directions and an enhancement along the c direction. The absolute value of the magnetostriction along c agrees well with the dilatometer result. These observations indicate that the structural distortion occurring upon cooling in zero-field may be suppressed and even be inverted by applying a high field at low temperature. From the neutron powder diffraction data obtained on GEM at ISIS we may deduce that the crystal structure remains essentially unchanged with the field. In particular, there is no evidence for superstructure reflections which would appear or disappear with magnetic field. By measuring the tilt superstructure reflection on a single crystal with the lifting counter diffractometer 6T.2 at the Orphée reactor, we can precisely determine the tilt angle reduction to only 3% (under a field of 7 T) in agreement with the powder diffraction study on GEM (ISIS). Since the tilt distortion is coupled with a shrinking of the c axis and with an increase of the averaged in-plane parameters, the observed tilt reduction agrees well with the effect in the lattice constants.

The comparison of the thermal expansion coefficients measured with and without magnetic field is shown in Fig. 4 for $\text{Ca}_{1.8}\text{Sr}_{0.2}\text{RuO}_4$ and $\text{Ca}_{1.5}\text{Sr}_{0.5}\text{RuO}_4$. The pronounced shrinking along the c direction in zero field is successively suppressed by the field and turns into a low-temperature elongation at fields larger than 6 T. In contrast, the effect observed along the RuO_2 planes in $\text{Ca}_{1.5}\text{Sr}_{0.5}\text{RuO}_4$ changes from a low-temperature elongation into a low-temperature compression. All our observations indicate that there is an electronic rearrangement occurring at low temperature which may be tuned by the magnetic field. At zero field, electrons shift from d_{xz} and d_{yz} orbitals into the d_{xy} orbitals upon cooling, whereas they do the opposite at high field. This thermal effect is largely enhanced by the octahedron tilt. The structural anomalies indicate a competition between different electronic ground states similar to typical heavy fermion compounds [19] or LiV_2O_4 [20, 21]. The low-magnetization state is most likely related to the magnetic instability evidenced in the strongly enhanced magnetic fluctuations in $\text{Ca}_{1.5}\text{Sr}_{0.5}\text{RuO}_4$ [10].

The observed anomalies in the temperature dependence of the lattice parameters clearly indicate a change in the orbital occupation which may be tuned by the external field. We propose an interpretation based on the van Hove singularity, vHs, in the γ -band formed by the d_{xy} orbitals [18]. The vHs is unoccupied in pure Sr_2RuO_4 , but the electronic structure is significantly changed by the rotational distortion which reduces the width of the γ -band. LDA calculations and recent ARPES measurements indicate that the vHs in

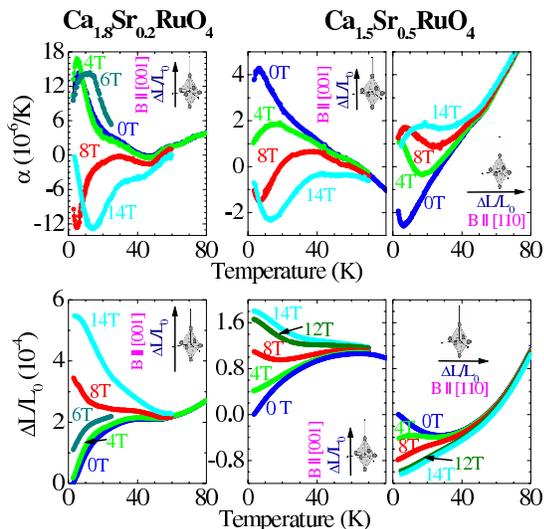


FIG. 4: a) (Top) Thermal expansion and integrated length changes (Bottom) determined at different magnetic fields. The left and right parts present data for $\text{Ca}_{1.8}\text{Sr}_{0.2}\text{RuO}_4$ and $\text{Ca}_{1.5}\text{Sr}_{0.5}\text{RuO}_4$, respectively. In a) – d) data were taken parallel to the field applied along the c direction, in e) the field was applied parallel to the RuO_2 planes.

$\text{Ca}_{1.5}\text{Sr}_{0.5}\text{RuO}_4$ is occupied and that the γ -band is hole-like [7, 24], as it was also deduced from the inelastic magnetic scattering [10]. The zero-field thermal expansion anomalies are associated with a transfer of electrons from the one-dimensional d_{xz} and d_{yz} bands into the γ -band. This corresponds to a shift of the DOS peak related to the vHs away from the Fermi level, as the vHs singularity is below the Fermi-level in $\text{Ca}_{1.5}\text{Sr}_{0.5}\text{RuO}_4$ [24]. Since the high DOS is intrinsically related to ferromagnetism, the shift may explain the reduction of magnetic susceptibility as a function of both temperature and Sr content. In the tilted phase the structural anomalies are strengthened due to some direct coupling between the tilt and orbital occupation. The tilting reduces the band width in the one-dimensional bands [7], thereby increasing the local character of these particles, and induces a further deformation of the RuO_6 octahedra, i. e. an elongation perpendicular to the tilt axis [4, 6]. Upon increase of the magnetic field, the high DOS arrangement is stabilized, thereby the structural distortions are reversed and electrons are shifted from the γ -band to the one-dimensional bands. The almost localized character of the electrons in this concentration range rather close to the metal-insulator transition must be very important, since the relatively small structural changes are able to cause qualitatively different physical behavior. Also, the occurrence of the zero-field thermal expansion anomalies at low temperature may be understood in such a picture only if the Fermi surface and Fermi liquid effects are restricted to low temperature. In an usual metal the

interplay between the crystal structure and the electron system should be determined at much higher temperature due to the high electronic energy scale involved.

In conclusion, we find strong anomalies in the temperature and field dependence of the crystal structure in $\text{Ca}_{2-x}\text{Sr}_x\text{RuO}_4$ ($0.2 < x < 0.5$) which indicate that the t_{2g} orbital occupation is tuned by Sr concentration, temperature and external magnetic field.

Acknowledgments This work was supported by the Deutsche Forschungsgemeinschaft through the Sonderforschungsbereich 608 and by Grants-in-Aid for scientific research from MEXT of Japan. We are grateful to L. Balicas and D. Khomskii for interesting discussions.

- * Electronic address: braden@ph2.uni-koeln.de
- [1] Y. Maeno et al., Y. Maeno, J. of Sol. State Chem. **156**, 26 (2001).
 - [2] S. Nakatsuji et al., J. Phys. Soc. Jpn. **66**, 1868 (1997).
 - [3] M. Braden et al., Phys. Rev. B **58**, 847 (1998).
 - [4] S. Nakatsuji et al., Phys. Rev. B **62**, 6458 (2000).
 - [5] S. Nakatsuji et al., Phys. Rev. Lett. **84**, 2666 (2000).
 - [6] O. Friedt et al., Phys. Rev. B **63**, 174432 (2001).
 - [7] Z. Fang et al. Phys. Rev. B **64**, 020509 (2001).
 - [8] S. Nakatsuji et al., Phys. Rev. Lett. **90**, 137202 (2003).
 - [9] R. Jin et al., cond-mat/0112405.
 - [10] O. Friedt et al., cond-mat/0311652
 - [11] Y. Sidis et al., Phys. Rev. Lett. **83**, 3320 (1999).
 - [12] M. Braden et al., Phys. Rev. B **66**, 064522 (2002).
 - [13] S.A. Grigera et al., Science **294**, 329 (2001); R.S. Perry et al., Phys. Rev. Lett. **86**, 2661 (2001).
 - [14] R. Pott and R. Schefzyk, J. Phys. E **16**, 444 (1983); T. Lorenz et al., Phys. Rev. B **55**, 5914 (1997).
 - [15] The increase of the static tilt deformation causes a shrinking of the c parameter, see reference [16]. Since uniaxial pressure along c stabilizes the tilt, it will cause a frequency softening and a negative Grüneisen parameter in the non-tilted phase.
 - [16] M. Braden et al., Z. Physik B **94**, 29 (1994).
 - [17] T. Mizokawa et al., Phys. Rev. Lett. **87**, 077202 (2001).
 - [18] D. J. Singh, Phys. Rev. B **52**, 1358 (1995); A. Liebsch and A. Lichtenstein, Phys. Rev. Lett. **84**, 1591 (2000); T. Oguchi, Phys. Rev. B **51**, 1385 (1995).
 - [19] S.H. Liu, Handbook on the Physics and Chemistry of Rare Earths, Vol. 17, Elsevier Science Publishers, **87** (1993), G.R. Stewart, Rev. Mod. Phys. **56**, 755 (1984).
 - [20] S. Kondo et al., Phys. Rev. Lett. **78**, 3729 (1997).
 - [21] O. Chmaissem et al., Phys. Rev. Lett. **79**, 4866 (1997).
 - [22] T. Zabel, PhD-thesis, Universität zu Köln (2004).
 - [23] The longitudinal c -axis magneto-resistivity may be understood through the elongation of the c axis, whereas the maximum in-plane magnetoresistivity just at the field of the metamagnetic transition suggests scattering with low-energy fluctuations. Therefore, the c and in-plane magneto-resistivity scale with the magnetization and its field derivative, respectively.
 - [24] S.-C. Wang et al., cond-mat/0407040.