

Single-crystal growth and dependences on the hole concentration and magnetic field of the magnetic ground state in the edge-sharing CuO_2 chain system $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$

K. Kudo, S. Kurogi, and Y. Koike[†]

Department of Applied Physics, Graduate School of Engineering,
Tohoku University, Aoba-yama 6-6-05, Aoba-ku, Sendai 980-8579, Japan

T. Nishizaki and N. Kobayashi

Institute for Materials Research, Tohoku University,
Katahira 2-1-1, Aoba-ku, Sendai 980-8577, Japan

(Dated: April 14, 2024)

We have succeeded in growing large-size single-crystals of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ with $0 \leq x \leq 1.67$ and measured the magnetic susceptibility, specific heat and magnetization curve, in order to study the magnetic ground state in the edge-sharing CuO_2 chain as a function of hole concentration and magnetic field. In $0 \leq x \leq 1.3$, it has been found that an antiferromagnetically ordered phase with the magnetic easy axis along the b -axis is stabilized and that a spin- op transition occurs by the application of magnetic fields parallel to the b -axis. The antiferromagnetic transition temperature decreases with increasing x and disappears around $x = 1.4$. Alternatively, a spin-glass phase appears around $x = 1.5$. At $x = 1.67$ where the hole concentration is $1/3$ per Cu, it appears that a spin-gap state is formed owing to the formation of spin-singlet pairs. No sign of the coexistence of an antiferromagnetically ordered state and a spin-gap one suggested in $\text{Ca}_{1-x}\text{CuO}_2$ has been found in $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$.

PACS numbers: 75.40.-s, 75.40.Cx, 75.10.Jm

I. INTRODUCTION

Recently, it has been no more doubtful that the mechanism of the high temperature superconductivity links to the magnetism in the two-dimensional CuO_2 plane. Enormous volumes of experimental and theoretical works on the magnetism have revealed a variety of Cu^{2+} -spin states as a function of carrier doping [1]. The carrier doping drastically changes the antiferromagnetically ordered phase to a spin-glass phase, a stripe ordered one of spins and/or holes, a spin-gap one or a superconducting one. Therefore, the change of the magnetism through the carrier doping has attracted great interest.

One-dimensional chain systems composed of Cu^{2+} and O^{2-} ions are carrier-dopable as well. They are categorized into corner-sharing chain systems or edge-sharing chain ones. In the former, CuO_4 squares are connected with each other by sharing a oxygen at the corner, while they are connected by sharing two oxygens at the edge in the latter. Doped holes make CuO_4 squares nonmagnetic through the change of the Cu valency from Cu^{2+} to Cu^{3+} or the formation of Zhang-Rice singlet pairs of oxygen holes and Cu^{2+} spins [2], to divide the magnetic intrachain interaction. The layered cuprate $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ [3] possesses pre-doped edge-sharing CuO_2 chains [4] whose spin-state exhibits a spin

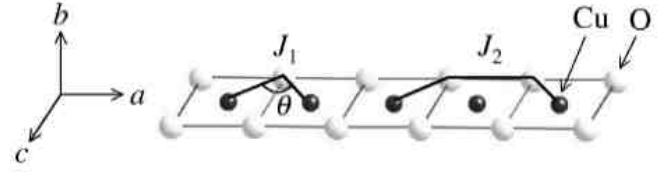


FIG. 1: Structure of the edge-sharing CuO_2 chain. The θ is the Cu-O-Cu bond angle. The J_1 and J_2 are the nearest and second nearest neighbor interactions between Cu^{2+} spins, respectively.

gap [5, 6, 7, 8, 9, 10, 11, 12, 13, 14, 15, 16]. With decreasing hole concentration in the chain through the substitution of La^{3+} , Y^{3+} or Ca^{2+} for Sr^{2+} , the Cu^{2+} -spin state changes from a spin-gap state to an antiferromagnetically ordered one [6, 16, 17, 18, 19]. However, the study of the carrier-doping effect in the chain is not easy in $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ because of the existence of the spin-ladder plane of Cu_2O_3 . A simple structure system composed of carrier-dopable edge-sharing CuO_2 chains is $\text{Ca}_{1-x}\text{CuO}_2$, whose hole-concentration is controlled by changing x . According to the theoretical calculation [20], the magnetic interaction between the nearest neighbor Cu^{2+} spins in the edge-sharing CuO_2 chain is antiferromagnetic for $\theta > 95^\circ$, while it is ferromagnetic for $\theta < 95^\circ$, where θ is the Cu-O-Cu bond angle as shown in Fig. 1. The θ value in Ca_xCuO_2 has been estimated as 95° which is located at the boundary [21, 22], implying that an attractive spin-state may appear. Actually, a novel coexistence of an antiferromagnetically ordered state and a spin-gap one has been suggested in a

[†] Present address: Institute for Materials Research, Tohoku University, Katahira 2-1-1, Aoba-ku, Sendai 980-8577, Japan; Electronic address: kudo@imr.tohoku.ac.jp

[†] Electronic address: koike@teion.apph.tohoku.ac.jp

range of 0.164 \times 0.190 from the magnetic susceptibility and specific heat measurements [24] and also from the structural analysis [23]. In order to explain the coexistence, Hiroiet al. [24] have proposed a two-sublattice model in which a single chain is divided into two independent chains, taking into account the theoretical result that the magnetic interaction between the second nearest neighbor Cu^{2+} spins, J_2 , is antiferromagnetic and that $|J_2|$ is much larger than the absolute value of the nearest neighbor interaction, J_1 [20]. That is, every other Cu^{2+} spin belonging to one sublattice is regarded as forming an antiferromagnetic long-range order, while holes and Cu^{2+} spins belonging to the other sublattice are regarded as being localized and forming spin-singlet pairs with a spin gap, respectively. From the structural analysis, on the other hand, Isobe et al. [23] have proposed another model in which holes are located almost periodically at intervals of two Cu^{2+} spins. In this case, it follows that Cu^{2+} spins on both sides of a hole form a spin-singlet pair with a spin gap, while a small amount of residual Cu^{2+} spins exhibit an antiferromagnetic order. The interpretation on the coexistence of the two states in $\text{Ca}_{1-x}\text{CuO}_2$ has not yet been settled. However, detailed experiments have not been carried out, because it is very hard to grow single crystals of $\text{Ca}_{1-x}\text{CuO}_2$.

A similar edge-sharing CuO_2 chain system is $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$. The value at $x = 0$ has been estimated as 91 [27]. With increasing x , increases and reaches 93.4 at $x = 2$ [27], which is comparable with that of $\text{Ca}_{1-x}\text{CuO}_2$ [22]. Therefore, a similar coexistence of an antiferromagnetically ordered state and a spin-gap one is expected in $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ with large x values as well. As shown in Fig. 2(a), it possesses a layered structure composed of stacked ac -planes where edge-sharing chains run along the a -axis. The magnetic properties have been studied so far mainly using polycrystalline samples. It has been found from the magnetic susceptibility [25, 26, 27], specific heat [26] and neutron scattering measurements [28, 29] that the sample without any hole carriers at $x = 0$ exhibits an antiferromagnetic order at low temperatures below the antiferromagnetic transition temperature $T_N = 30$ K and that Cu^{2+} spins are arranged ferromagnetically along the chain and the inter-chain coupling is antiferromagnetic. With increasing x , namely, with the increase of doped holes, T_N decreases and finally disappears around $x = 1.5$. The single-crystal growth of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ has been reported by Oka et al. [30] for $x = 0$ and 0.5. The magnetic susceptibility measurements of these crystals have revealed that the magnetic easy axis is the b -axis [30, 31]. Moreover, the magnetic dispersion relation has been clarified from the neutron scattering experiment [32]. The single crystal growth for $x > 0.5$ has also been reported [33], but the grown crystals are too small to be available for the detailed measurements, though the novel ground state in $\text{Ca}_{1-x}\text{CuO}_2$ is expected to appear at $x > 0.5$ in $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$.

Therefore, we have tried to grow large-size single-

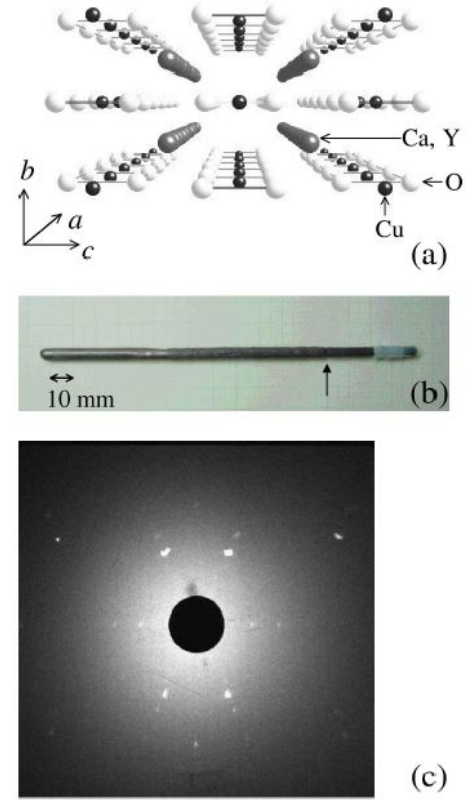


FIG. 2: (a) Schematic crystal structure of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$. (b) Picture of a single crystal of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ with $x = 1.5$ grown by the TSFZ method, which is a left part of the rod from the upward arrow. (c) X-ray back-Laue photograph of a grown crystal of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ with $x = 1.5$ in the x-ray parallel to the c -axis.

crystals of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ with $x > 0.5$ and succeeded in the growth up to $x = 1.67$. In this paper, we report results of the single-crystal growth and the magnetic susceptibility, specific heat and magnetization curve measurements using the single crystals of $x = 0, 0.5, 1.0, 1.2, 1.3, 1.5$ and 1.67 , and discuss the hole-concentration and magnetic-field dependences of the magnetic ground state of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$. The preliminary results have already been reported by Kurogi et al. [34].

II. EXPERIMENTAL

Single crystals of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ were grown by the Traveling-Solvent Floating-Zone (TSFZ) method. In order to prepare the feed rod for the TSFZ growth, first, we prepared the polycrystalline powder of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ by the solid-state reaction method. The prescribed amount of CaCO_3 , Y_2O_3 and CuO powders with 99.9% purity was mixed, ground and pressed at 900 $^\circ\text{C}$ in air for 12 h. After pulverization, the prepared powder was mixed and sintered at 1000 $^\circ\text{C}$ for 1

TABLE I: Growth conditions, chemical compositions and dimensions of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ single crystals.

x	nominal composition	solvent	growth rate (mm/h)	atmosphere	composition (ICP-AES)	dimensions	
	Ca : Y : Cu	Ca : Y : Cu			Ca : Y : Cu	(mm)	(mm)
0	2.0 : 2.0 : 5.0	1.00 : 0.45 : 5.10	0.50	air 1 atm	1.94 : 2.09 : 4.96	6	60
0.5	2.5 : 1.5 : 5.0	1.00 : 0.15 : 4.20	0.50	O_2 1 atm	2.51 : 1.52 : 4.97	6	60
1.0	3.0 : 1.0 : 5.0	1.00 : 0.10 : 3.50	0.40	O_2 6 atm	2.99 : 1.05 : 4.96	6	60
1.2	3.2 : 0.8 : 5.0	1.00 : 0.10 : 4.02	0.35	O_2 10 atm	3.21 : 0.78 : 5.01	6	40
1.3	3.3 : 0.7 : 5.0	1.00 : 0.10 : 4.28	0.35	O_2 10 atm	3.29 : 0.69 : 5.02	6	40
1.5	3.5 : 0.5 : 5.0	1.00 : 0.10 : 4.80	0.35	O_2 10 atm	3.52 : 0.55 : 4.93	6	40
1.67	3.667 : 0.333 : 5.0	1.00 : 0.07 : 4.08	0.35	O_2 10 atm	3.64 : 0.32 : 5.04	6	40

week with several times of intermediate grinding. After 1 h grinding, the powder was isostatically cold-pressed at 400 bar into a rod of 7 mm in diameter and 150 mm in length. Then, the rod was sintered at 1000 °C in air for 1 day. As a result, a tightly and densely sintered feed rod was prepared. As $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ melts incongruently [30, 33], solvent disks with different compositions were prepared sintering at 900 °C in air for 12 h. The composition of the solvent listed in Table I was determined referring to the previous report by Oka et al. [33]. The TSFZ growth was carried out with the obtained feed rod and a disk of the solvent material in an infrared heating furnace equipped with a quartet ellipsoidal mirror (Crystal Systems Inc., Model FZ-T-4000-H). The rotation speed of the upper and lower shafts was 10 rpm in the opposite direction to secure the homogeneity of the liquid in the molten zone. The rotation of the lower shaft was stopped when the ac-plane became visible during the growth [35]. The growth rate and the atmosphere listed in Table I were optimized for each x by trial and error. The grown crystals were then characterized using the x-ray back-Laue photography and were confirmed having a single phase by the powder x-ray diffraction. The chemical compositions were determined by the inductively coupled plasma atomic emission spectroscopy (ICP-AES).

The temperature dependence of the magnetic susceptibility was measured in a magnetic field of 1 T, using a SQUID magnetometer (Quantum Design, Model MPMS). The specific heat measurements were carried out in magnetic fields up to 9 T by the thermal relaxation technique (Quantum Design, Model MPMS). The magnetization curve in magnetic fields up to 14 T was measured using a vibrating sample magnetometer (Oxford Instruments, Model MagLab).

III. RESULTS AND DISCUSSION

A. Single-crystal growth

Figure 2(b) shows a picture of a grown single-crystal of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ with $x = 1.5$. The cross section is ellipsoidal in shape, owing to the layered structure

stacking along the b-axis. Figure 2(c) shows the x-ray back-Laue photography in the x-ray parallel to the c-axis. The diffraction spots exhibit a two-fold symmetry and are very sharp, indicating the good quality of the single crystal. The typical dimensions of a single domain are 6 mm (40{60} mm), as listed in Table I for various x values. The dimensions of single crystals with 1.0 ≤ x ≤ 1.67 are as large as those with x = 0 and 0.5. The powder x-ray diffraction patterns of the single crystals with 0 ≤ x ≤ 1.67 reveal no impurity phases. Figure 3 shows the x dependence of the lattice constants a , b , and c parallel to the a- and b- and c-axes, respectively. With increasing x, b tends to increase, while both a and c tend to decrease slightly. Taking into account that the substitution of Ca^{2+} (ionic radius = 0.99 Å) for Y^{3+} (0.92 Å) expands the distance between ac-planes and that induced holes in the CuO_2 chain shorten the distance between Cu^{2+} and O^{2-} ions in the ac-plane, the substitution is regarded as being successful. The x dependence is in rough agreement with that of polycrystalline samples [25]. As listed in Table I, the chemical composition determined by ICP-AES almost coincides with the nominal composition also. Thus, it is said that the growth of large-size single crystals of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ with 0 ≤ x ≤ 1.67 is successful.

Here, we note the reasons why we have succeeded in growing single crystals of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ with large x values by the TSFZ method. The first is that the high oxygen pressure of 10 atm was applied. Oka et al. [33] have performed the TSFZ growth under the oxygen pressure up to 6 atm and reported that the oxygen pressure tends to suppress the formation of impurity phases. The high oxygen pressure of 10 atm might suppress the formation of impurity phases in our trial as well. The second is that a seed of a single crystal was used. The third is that the rotation of the lower rod was stopped when the ac-plane appeared. Although the effect has not been clarified, it is a matter of fact that the growth was not successful for $x > 1.0$ without this procedure [35]. The fourth is that the growth rate was rather small. In fact, there existed many cracks in the single crystals grown at a rapid rate, which may be due to the small supersaturation on account of the narrow liquidus line.

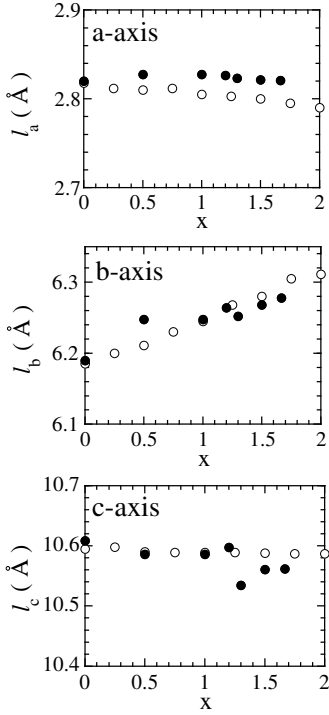


FIG. 3: Hole-concentration dependence of the lattice constants, l_a , l_b and l_c , parallel to the a-, b- and c-axes of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$, respectively. Closed and open circles indicate data of the present work and Hayashi et al. [25], respectively.

B. Hole-concentration dependence of the magnetic ground state

Figure 4 shows the temperature dependence of the magnetic susceptibilities, χ_a , χ_b and χ_c , of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ with $0 \leq x \leq 1.67$ in a magnetic field of 1 T parallel to the a-, b- and c-axes, respectively. In $x = 0, 0.5, 1.0, 1.2$ and 1.3 , it is found that χ_b increases with decreasing temperature and exhibits a sharp peak indicating the antiferromagnetic transition. The T_N is determined at the peak to be 31 K and 29 K for $x = 0$ and 0.5 , respectively, which is similar to the result by Yamaguchi et al. [31]. Furthermore, T_N is estimated as 20 K, 15 K and 12 K for $x = 1.0, 1.2$ and 1.3 , respectively. Both χ_a and χ_c tend to become constant below T_N , so that the b-axis is regarded as the magnetic easy axis in $0 \leq x \leq 1.3$. In $x = 1.5$ and 1.67 , on the other hand, no antiferromagnetic transition is observed, but a small and broad shoulder appears around 20 K not only in χ_b but also in χ_a and χ_c . The isotropic broad shoulder is not characteristic of the antiferromagnetic long-range order but analogous to a broad peak observed in a spin-gap state [8, 9, 10, 11, 12, 23, 24]. Here, note that the value of the magnetic susceptibility in $x = 1.67$ is remarkably small, which is discussed later.

Figure 5 shows the temperature dependence of χ_a , χ_b

and χ_c on both zero-field cooling and field cooling in a magnetic field of 100 Oe. The temperature dependence exhibits a hysteresis in $1.3 \leq x \leq 1.67$, while it is reversible in $x = 1.2$. The hysteresis indicates a spin-glass transition with the transition temperature $T_{\text{spin glass}} \approx 6$ K. $T_{\text{spin glass}}$ is independent of x . Moreover, the hysteresis is much smaller in $x = 1.3$ and 1.67 than in $x = 1.5$. Accordingly, the spin-glass phase observed in $x = 1.3$ and 1.67 may not be a main phase but a minor one due to the inhomogeneity of x in a crystal. As shown in the inset of Fig. 5, in fact, the temperature dependence of the spin-glass order parameter, q , of $x = 1.67$ defined by $q = \chi_0 + (1 - q)C/T$ [36, 37] almost coincides with that of $x = 1.5$, indicating that the spin-glass phase of $x = 1.67$ quite resembles that of $x = 1.5$. Here, χ_0 and C are the constant susceptibility and the Curie constant, respectively. From the fitting analysis using $q = (T_{\text{spin glass}} - T)^{-\beta}$, the critical exponent β is estimated as 0.97 and 0.98 for $x = 1.5$ and 1.67 , respectively. These values are close to the mean-field prediction $\beta = 1$ and to experimental values, such as 0.7 and 0.9 for CuMn [38] and 0.9{0.97 for $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ with $0.03 \leq x \leq 0.05$ [36, 37].

Here, we discuss small values of both χ_a and χ_b and χ_c in $x = 1.67$. For all the measured single-crystals, the temperature dependence of the magnetic susceptibility, χ , at high temperatures between 250 K and 300 K is well fitted using the Curie-Weiss law, $\chi = \chi_0 + N_f N g^2 \frac{S(S+1)}{4k_B(T - \theta)}$, where N_f is the number of free spins per Cu, N the number of Cu atoms, g the g-factor, \hbar the Bohr magneton, S the spin quantum number, k_B the Boltzmann constant and θ the Weiss temperature. The g value is estimated from the fitting of the data of $x = 0$ where $N_f = 1$. It is dependent on the field direction and estimated as $g_a = 2.13$ (H || a-axis), $g_b = 2.39$ (H || b-axis) and $g_c = 2.10$ (H || c-axis). Using these values, values of N_f and θ are estimated, as plotted in Figs. 6(a) and (b). It is found that the obtained value of N_f is comparable with that estimated from the chemical formula for $0 \leq x \leq 1.5$, while N_f is roughly one half or one third of the latter for $x = 1.67$. The value in $x = 1.67$ is $\approx 30 \pm 10$ K, whose absolute value is remarkably large compared with those of the other x values. The marked decrease of N_f in $x = 1.67$ may be explained as follows. According to the theoretical result [20], magnetic interactions between Cu^{2+} spins, expressed as J_1 and J_2 in Fig. 1 and Fig. 6(c), are expected to be ferromagnetic and antiferromagnetic, respectively, as mentioned in Sec. I. Therefore, this spin system is regarded as being highly frustrated. As for $x = 1.67$, the hole concentration is $1/3$ per Cu. Therefore, when holes are located in order at every third site in the chain, it follows that all the Cu^{2+} spins can form such spin-singlet dimers as shown in Fig. 6(c) without residual spins and without the frustration between J_1 and J_2 , leading to the marked decrease of N_f [39]. As mentioned in Sec. I, a similar arrangement of holes and spins has been proposed by Isobe et al. [23] from the structural analysis of $\text{Ca}_{1-x}\text{CuO}_{2+x}$ with $x = 0.176$, whose

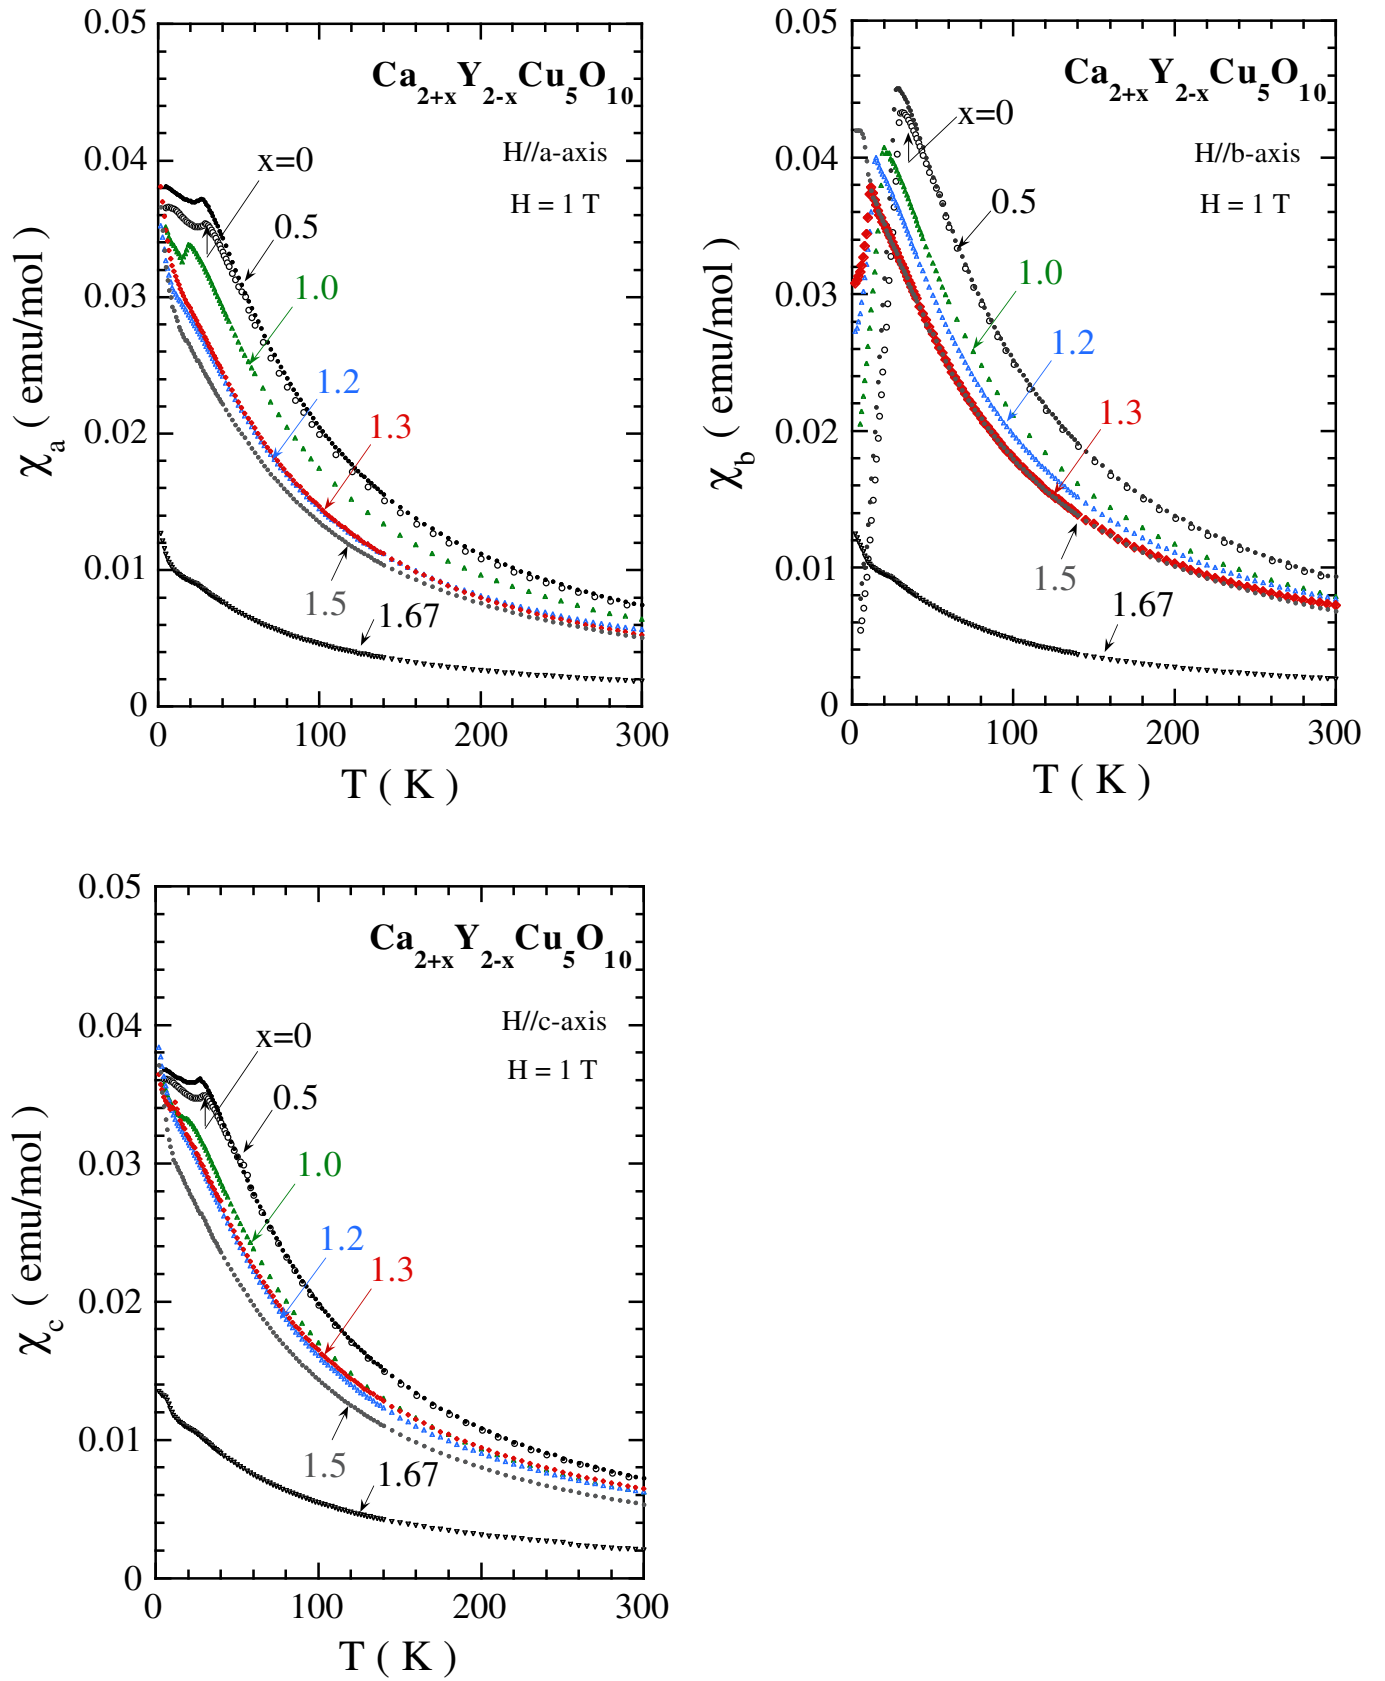


FIG. 4: (Color online) Temperature dependence of the magnetic susceptibilities, χ_a , χ_b and χ_c , of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ with $0 \leq x \leq 1.67$ in a magnetic field of 1 T parallel to the a -, b - and c -axes, respectively.

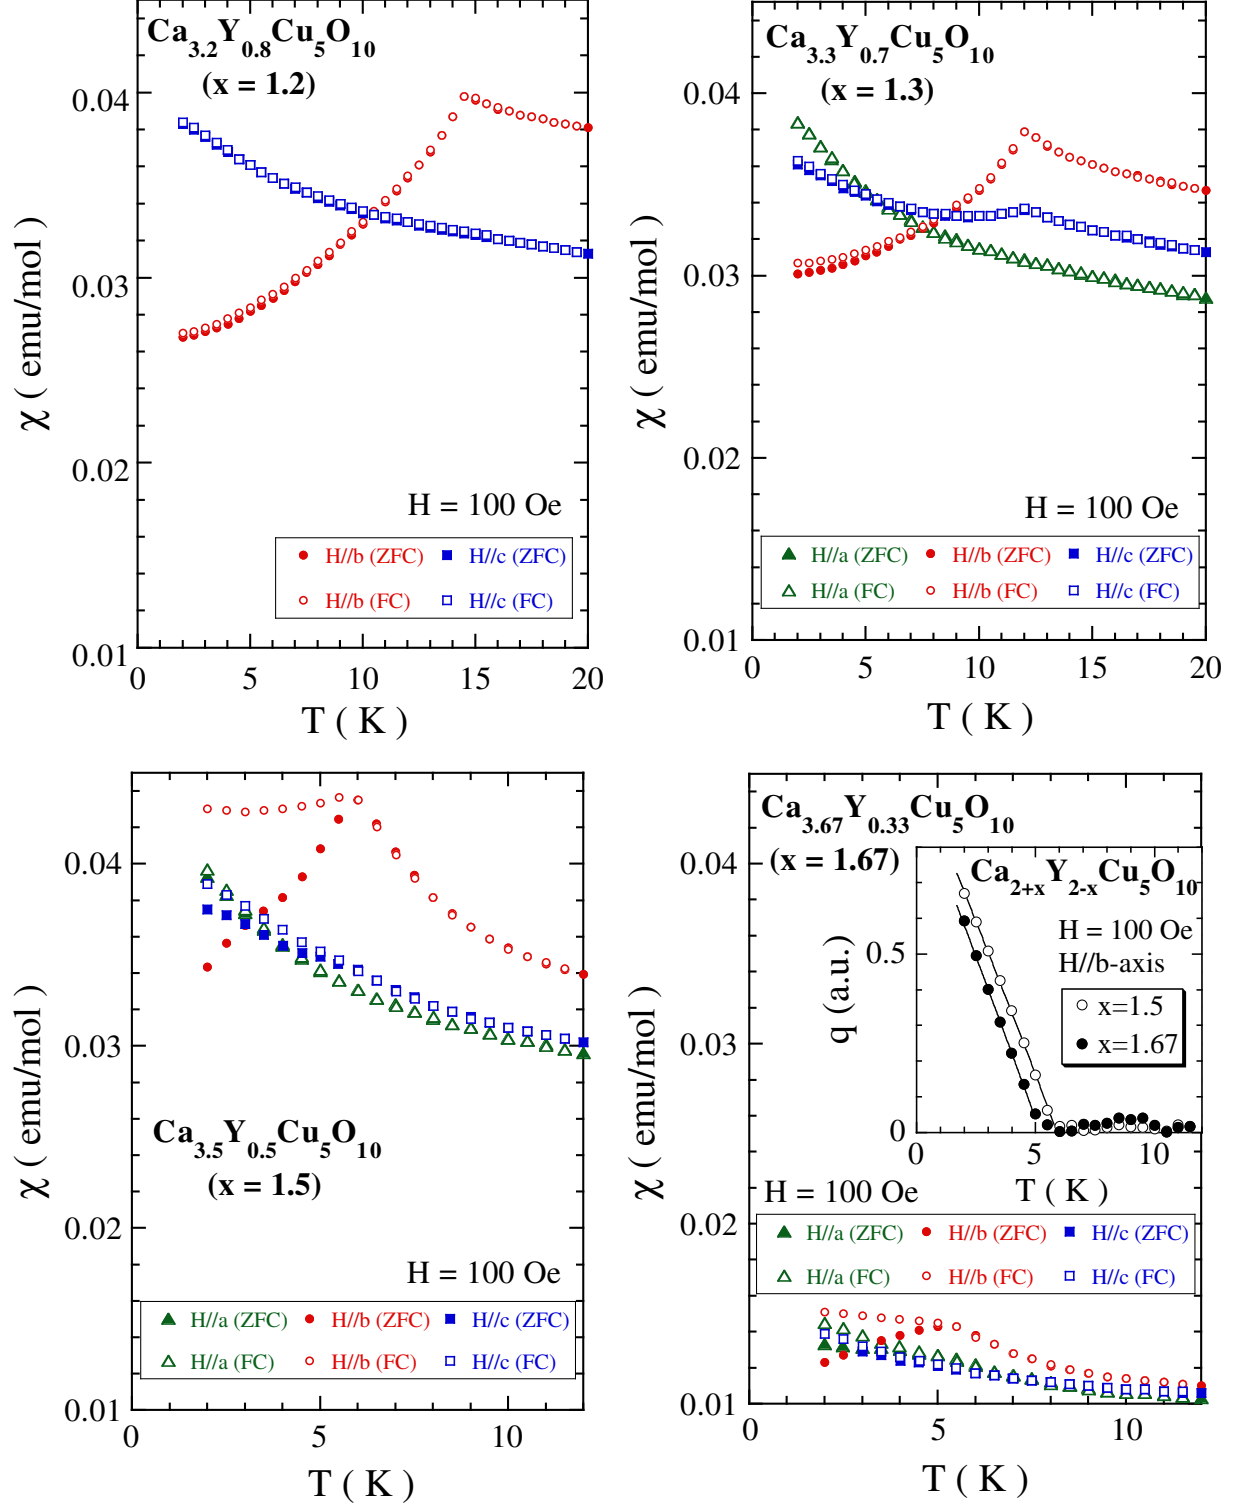


FIG. 5: (Color online) Temperature dependence of the magnetic susceptibilities, χ_a , χ_b and χ_c , of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ with $1.2 \leq x \leq 1.67$ on both zero-field cooling and field cooling in a magnetic field of 100 Oe. Closed and open symbols correspond to the data on zero-field cooling and field-cooling, respectively. The inset shows the temperature dependence of the spin-glass order parameter, q , in $x = 1.5$ and 1.67 . Solid lines denote fitting curves proportional to $(T_{\text{spin glass}} - T)$.

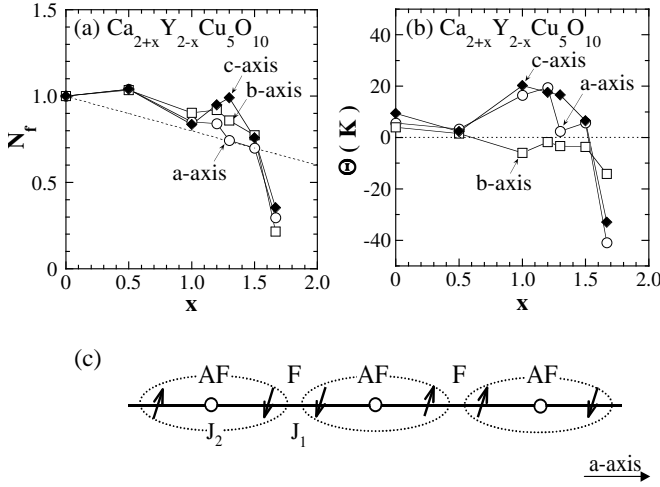


FIG. 6: Dependences on x of (a) the number of free spins per Cu, N_f , and (b) the Weiss temperature, Θ , in $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$. (c) Possible picture of spin-singlet pairs in $x = 1:67$. Arrows and circles indicate Cu^{2+} spins and holes, respectively. The dotted line in (a) indicates N_f estimated from the chemical formula. Dotted ellipses in (c) indicate spin-singlet pairs.

hole-concentration is close to that of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ with $x = 1.67$. Accordingly, the magnetic ground state in $x = 1:67$ may be spin-singlet pairs with a spin gap. To be conclusive, the neutron scattering experiment for $x = 1:67$ is under way [40].

Figure 7 shows the temperature dependence of the specific heat, C , of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ in zero field. A λ -type peak is observed in $x = 0, 0.5, 1.0, 1.2$ and 1.3 , corresponding to the antiferromagnetic transition. The T_N is estimated at the peak to be 29 K, 26 K, 18 K, 15 K and 12 K for $x = 0, 0.5, 1.0, 1.2$ and 1.3 , respectively. These values are consistent with those estimated from the magnetic susceptibility measurements. The λ -type peak is smeared and shifted to lower temperatures with increasing x , and finally disappears at $x = 1.5$. Formerly, Chahot et al. [41] have stated from the specific heat measurements of polycrystalline samples that the temperature dependence of the specific heat in $x = 1.0$ is regarded as a behavior characteristic of the one-dimensional Heisenberg antiferromagnetic chain, taking into account the result that no λ -type peak is observed at $T = 0.5$ K. The difference may be attributed to the quality of the samples, because it is described in Ref. 41 that a large Curie tail has been observed in the temperature of the magnetic susceptibility at $x > 0$, while no Curie tail is observed in our samples. As for $x = 1.5$ and 1.67 , the specific heat exhibits a broad peak around 10 K instead of a λ -type peak. Such a peak may be regarded as being due to a static short-range order like a spin glass or due to a spin gap caused by the formation of spin-singlet pairs. Taking into account the result that the onset temperature of the broad peak of the spe-

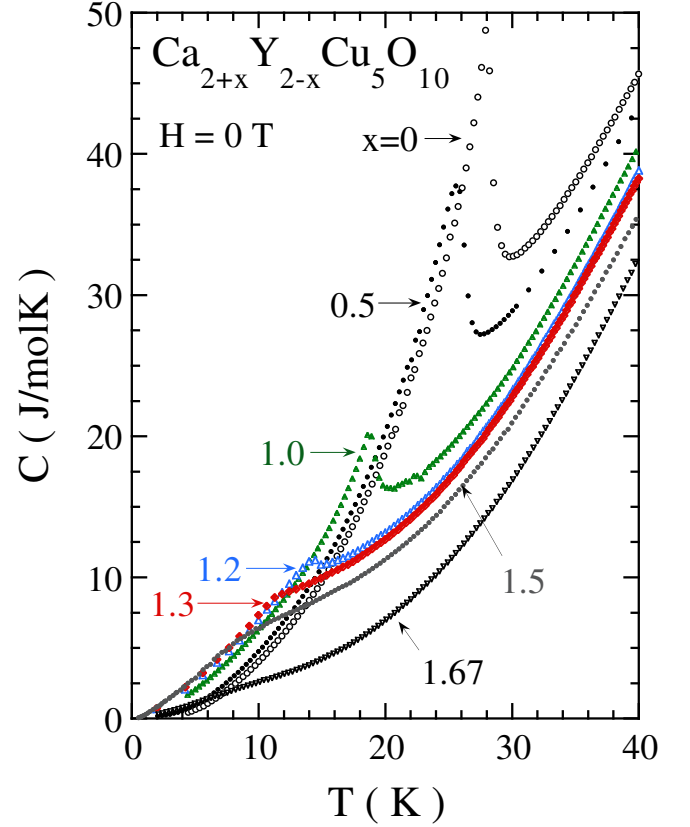


FIG. 7: (Color online) Temperature dependence of the specific heat, C , of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ with $0 \leq x \leq 1.67$ in zero field.

cific heat (> 20 K) coincides with the temperature of the broad shoulder observed in the temperature dependence of the magnetic susceptibility, the origin seems to be the spin-gap formation. However, this is inconsistent with the result that the broad peak in $x = 1:67$ is smaller than that in $x = 1:5$, because the number of spin-singlet pairs in $x = 1:67$ should be larger than that in $x = 1:5$. Taking into account the results that the spin-glass phase in $x = 1:67$ may be a minor phase and that the broad peak in $x = 1:5$ appears to systematically change from the λ -type peak of $x = 1:3$, the origin is probably the formation of a static short-range order like a spin glass.

Here, we would like to calculate the entropy of Cu^{2+} spins, S_{spin} , from the specific heat of spins, C_{spin} , as $S_{\text{spin}} = \int_0^T C_{\text{spin}} dT$. However, the precise evaluation of S_{spin} is hard, because the specific heat of phonons, C_{phonon} , is unknown. Here, suffice it to say that S_{spin} is likely to exhibit the minimum at $x = 1:67$ among the present samples, assuming that C_{phonon} is independent of x . This is qualitatively consistent with the small value of N_f in $x = 1:67$ shown in Fig. 6(a). Therefore, it is concluded that the specific heat data also indicate the formation of spin-singlet pairs with a spin gap at $x = 1:67$.

Figure 8 summarizes the x dependence of the characteristic temperatures in zero field for $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$.

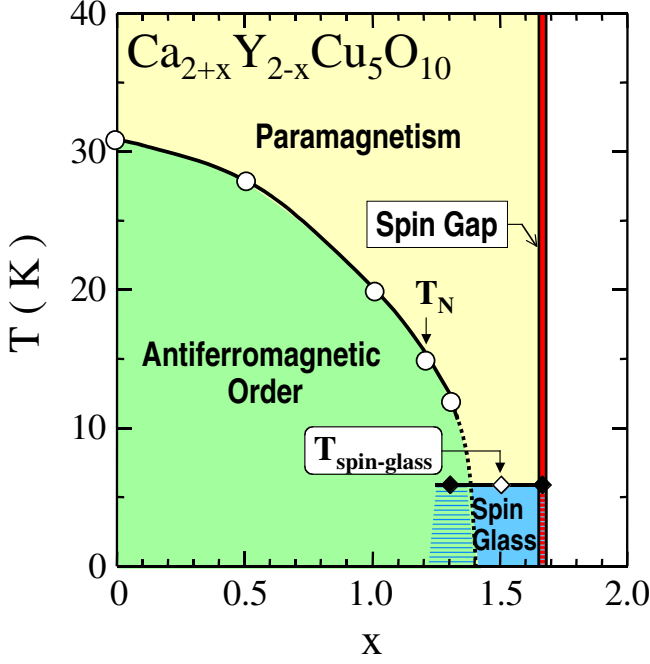


FIG. 8: (Color online) Magnetic phase diagram of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ in zero field. Open and closed symbols indicate temperatures below which the main phase and the minor phase appear, respectively.

An antiferromagnetically ordered phase is found in small x values. The T_N decreases with increasing x and disappears around 1.4. Alternatively, a spin-glass phase appears around $x = 1.5$. The spin-glass phase observed in $x = 1.3$ and 1.67 may be a minor phase. In $x = 1.67$, it appears that more than half of Cu^{2+} spins form spin-singlet pairs with a spin gap in the measured temperature-range.

Referring to Ref. 27, the value of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ with $x = 1.67$ is estimated as 93, which is comparable with that of $\text{Ca}_{1-x}\text{CuO}_2$ [22]. Therefore, not only hole concentrations but also values in these systems are almost similar to each other. However, no sign of the coexistence of an antiferromagnetically ordered state and a spin gap one suggested in $\text{Ca}_{1-x}\text{CuO}_2$ has been found in $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$. This may be because the intense modulation in the ac -plane and/or the randomness of Ca^{2+} and Y^{3+} ions in $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ suppress the mobility of holes so as not to make any suitable arrangement of holes for the formation of the coexistence state. In fact, the modulation periods parallel to the a - and c -axes in $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ with $x = 1.67$ are as small as 90 % and 40 % of those in $\text{Ca}_{1-x}\text{CuO}_2$, respectively [27].

C. Magnetic-field dependence of the magnetic ground state

1. $x = 0, 0.5, 1.0, 1.2$ and 1.3

Figures 9(a)–(e) show the temperature dependence of the specific heat in magnetic fields parallel to the b -axis for $x = 0, 0.5, 1.0, 1.2$ and 1.3 . With increasing magnetic field, the λ -type peak is reduced and shifted to lower temperatures. By the application of magnetic fields parallel to the a - and c -axes, on the other hand, the shift of the peak is very small, as shown in Figs. 9(f)–(h). The anisotropic effect of magnetic field on the peak is consistent with the result that the magnetic easy axis is parallel to the b -axis. That is, in magnetic fields parallel to the b -axis, T_N is markedly lowered due to the competition between the exchange energy and the Zeeman energy. In magnetic fields parallel to the a - and c -axes (i.e. perpendicular to the spin direction), the component parallel to the b -axis of magnetic moments keeps the antiferromagnetic arrangement, though the magnetic moments gradually tend toward the field direction. Accordingly, T_N does not decrease with increasing field so much.

Figures 10(a)–(e) show the magnetization curves in magnetic fields up to 14 T parallel to the b -axis. In $x = 0, 0.5, 1.0$, a jump is clearly observed at low temperatures below T_N [42]. This magnetization jump is regarded as being due to a spin- $\uparrow\downarrow$ transition, because the extrapolated line of the magnetization curve at high magnetic fields above the spin- $\uparrow\downarrow$ transition field, H_{SF} , tends to cross the origin. With increasing x , the spin- $\uparrow\downarrow$ transition becomes smeared. In $x = 1.2$ and 1.3 , the spin- $\uparrow\downarrow$ transition is not detected as a jump but a bend. By the application of magnetic fields parallel to the a - and c -axes, on the other hand, the magnetization increases linearly with increasing field, as shown in Figs. 10(g)–(k). This is due to the gradual tendency of magnetic moments toward the field direction. Here, it is noted that Chabot et al. [41] have previously estimated H_{SF} as 5 T around 25(30 K in $x = 0$ from the magnetization curve of grain-aligned polycrystalline samples. However, such a transition is not detected in our measurements using a single crystal with $x = 0$ of good quality.

Figure 11 summarizes the characteristic fields and temperatures in the antiferromagnetically ordered state. H_{SF} 's shown by closed symbols are defined at the maximum point of the field-derivative of the magnetization curve for $0 \leq x \leq 1.0$ and at the point where linear extrapolations of the segments of the magnetization curve below and above H_{SF} intersect with each other for $x = 1.2$ and 1.3 . Transition temperatures defined at the peak of the temperature dependence of the specific heat are plotted by open symbols. It is found that the initial spin arrangement changes into a spin- $\uparrow\downarrow$ one at H_{SF} with increasing field and that the region of the initial spin arrangement becomes narrow through the hole doping.

Here, we estimate the magnitude of the exchange field and the magnetic anisotropy field parallel to the b -

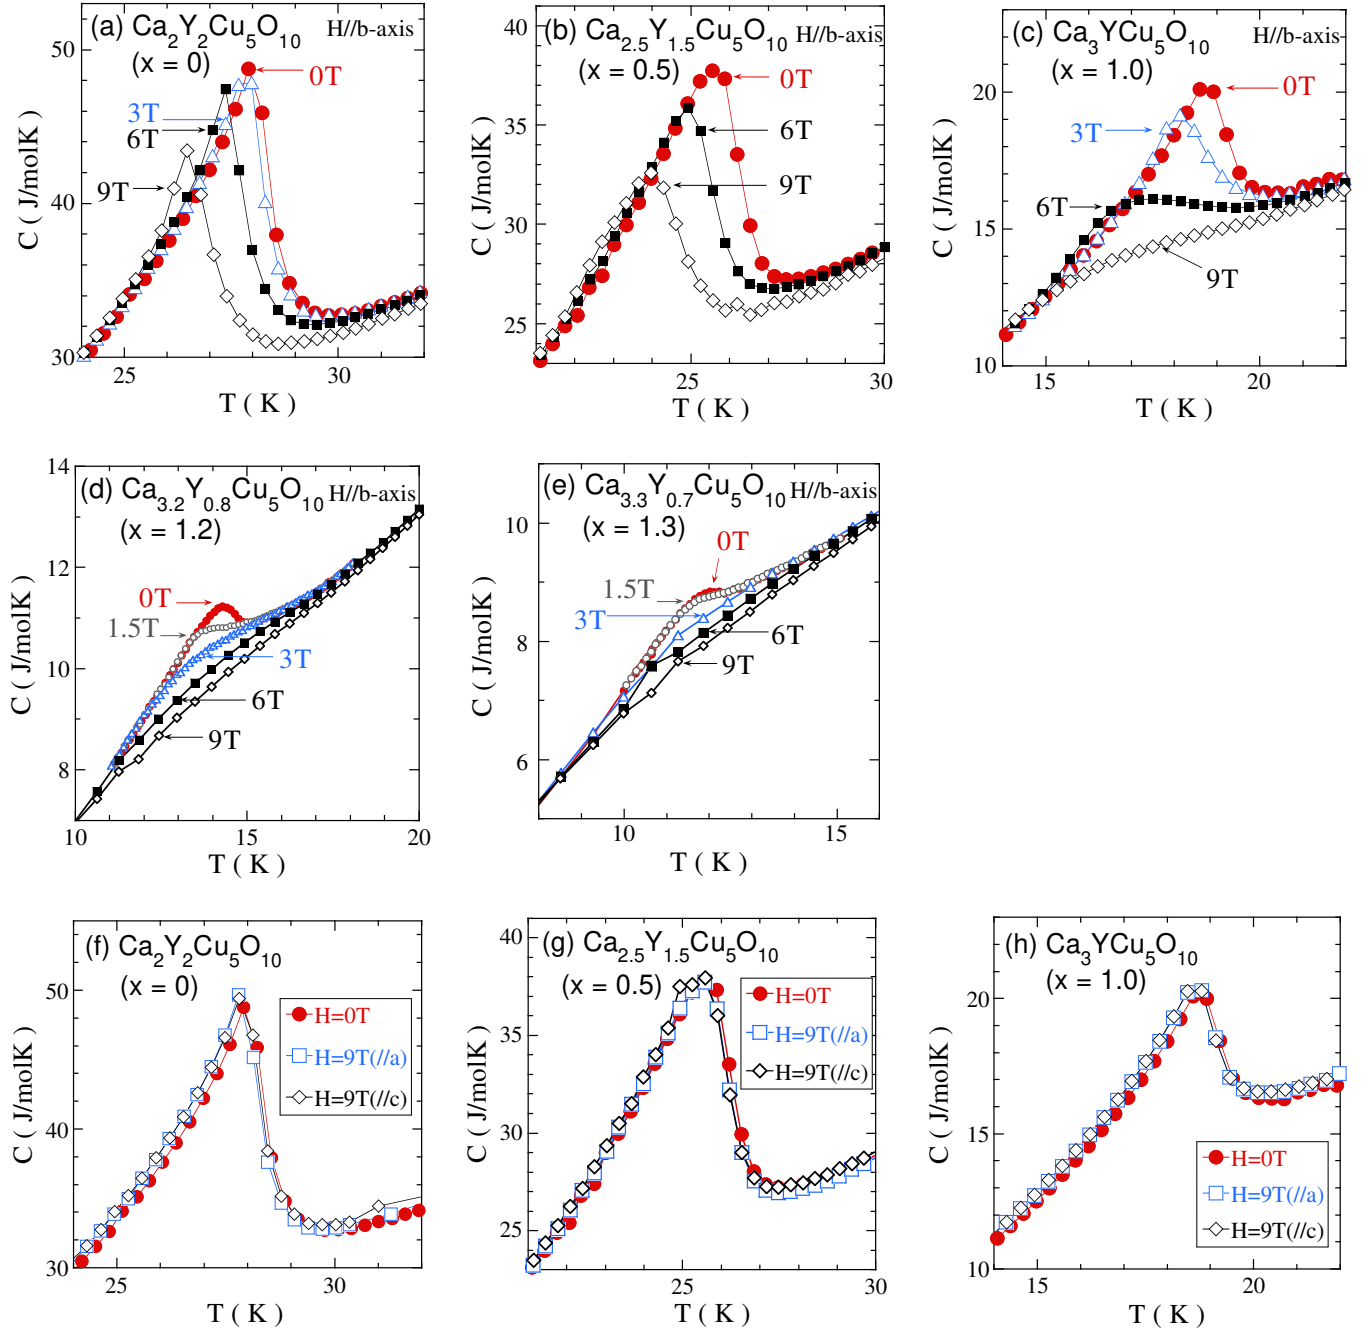


FIG. 9: (Color online) Temperature dependence of the specific heat, C , of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ with $0 \leq x \leq 1.3$ in magnetic fields up to 9 T (a)–(e) parallel to the b -axis and (f)–(h) parallel to the a - and c -axes.

axis. The spin- \uparrow spin- \downarrow transition takes place at H_{SF} where the gain of the Zeeman energy overcomes the loss due to the magnetic anisotropy energy responsible for the preferred spin direction. In terms of a simple uniaxial mean-field model[44], the spin- \uparrow spin- \downarrow transition field at 0 K is given by $H_{SF}(0) = (2H_E H_A - H_A^2)^{1/2}$, where H_A and H_E are the magnetic anisotropy field and the exchange field, respectively. H_E is roughly given by $(1/2)H_0$, where H_0 is a field where the Cu^{2+} moment is saturated. By

extrapolating the magnetization curve to the saturated value estimated from the number of Cu^{2+} spins, H_0 is estimated as 70 T for $x = 0, 0.5, 1.0, 1.2$ and 1.3 , which is almost independent of x . So, H_E is calculated to be 35 T, implying no change of the magnitude of the exchange interaction up to $x = 1.3$. Using the extrapolated value of $H_{SF}(0) = 10.5$ T, 10.0 T, 8.5 T, 4.0 T and 3.0 T, H_A 's are calculated to be 1.6 T, 1.5 T, 1.0 T, 0.2 T and 0.1 T for $x = 0, 0.5, 1.0, 1.2$ and 1.3 , respec-

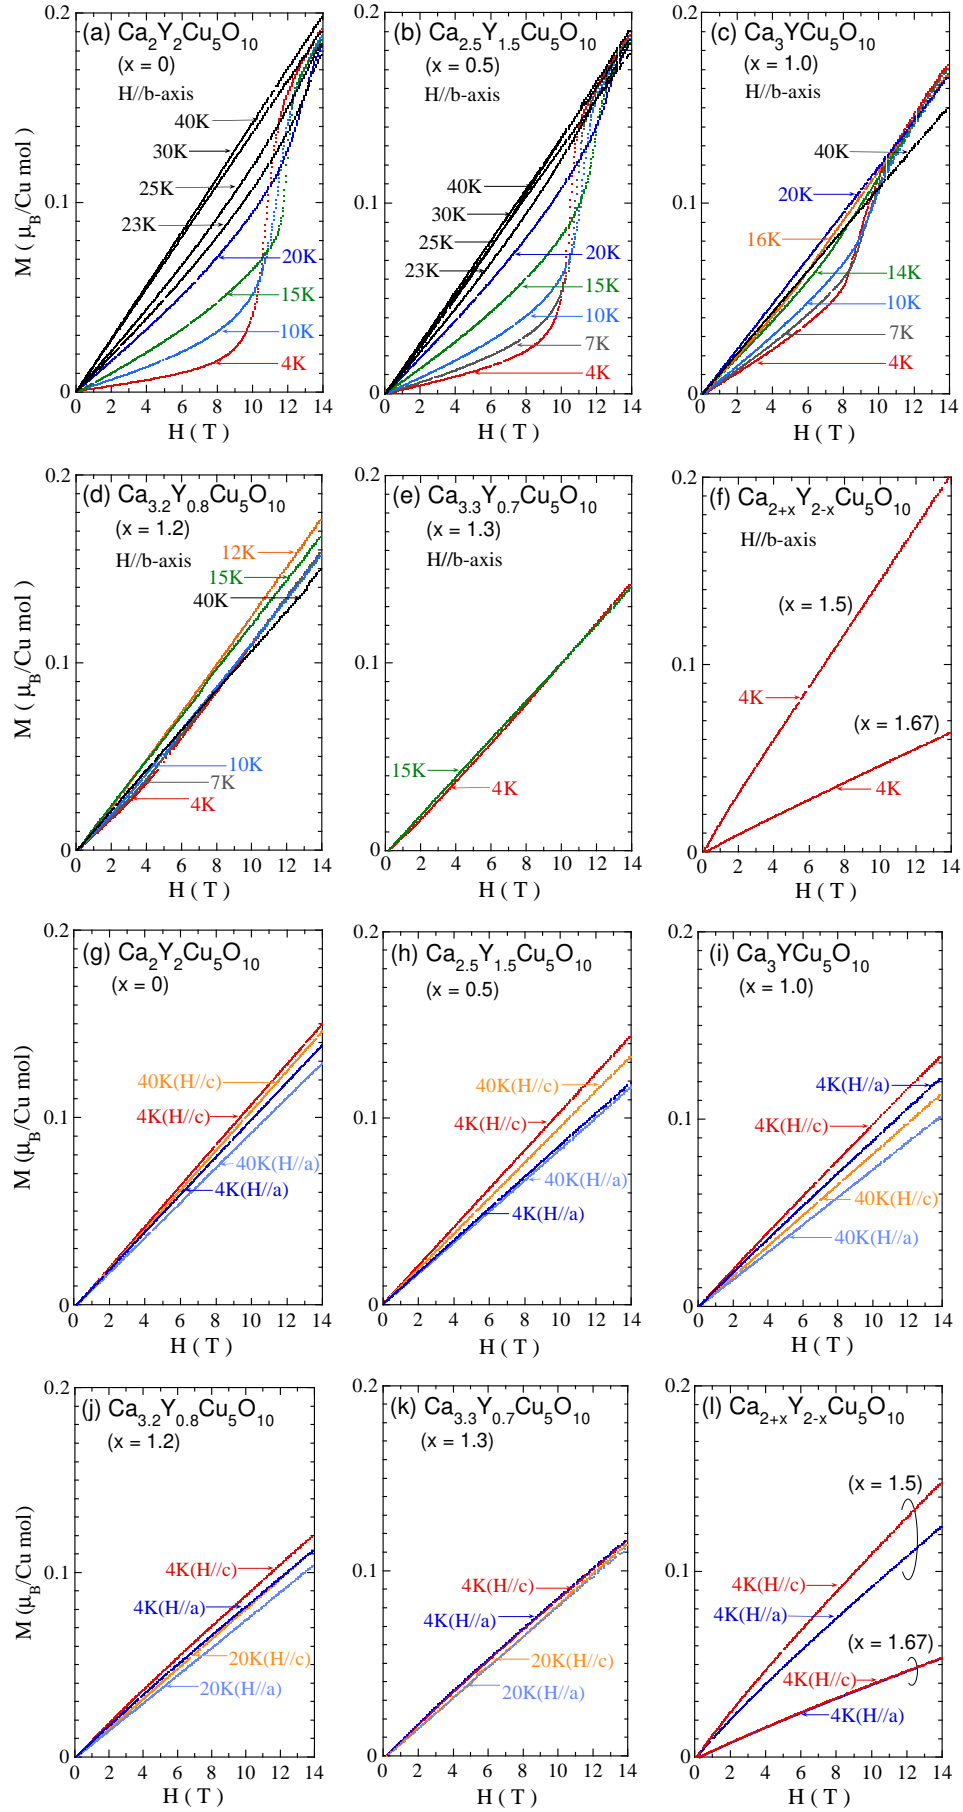


FIG. 10: (Color online) Magnetic field dependence of the magnetization curve of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ with $0 \leq x \leq 1.67$ at various temperatures in magnetic fields up to 14 T (a)–(f) parallel to the b-axis and (g)–(l) parallel to the a- and c-axes.

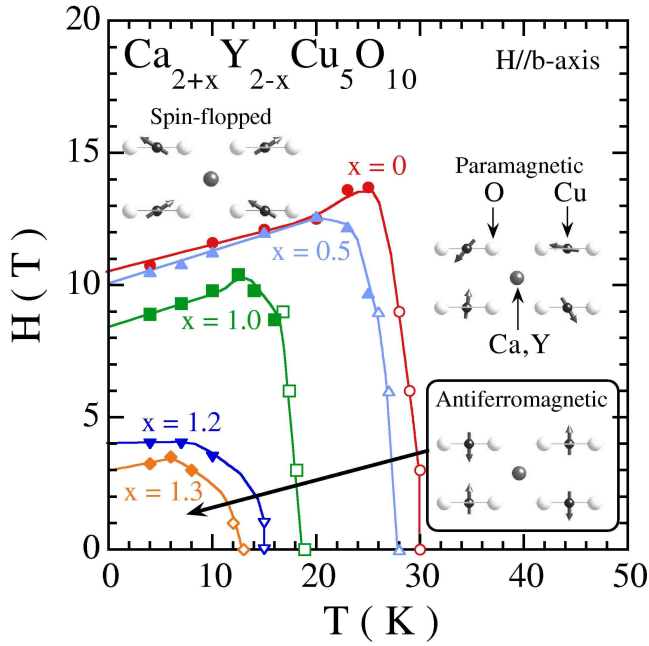


FIG. 11: (Color online) Magnetic phase diagram of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ with $0 \leq x \leq 1.3$ as a function of magnetic field and temperature. Magnetic fields are applied parallel to the b -axis. Closed and open symbols indicate characteristic magnetic fields and temperatures estimated from the magnetization curve and specific heat measurements, respectively. Typical spin arrangements seen along the a -axis (i.e. parallel to the CuO_2 chain) are shown in the paramagnetic, antiferromagnetically ordered and spin-flopped phases.

tively. Therefore, it is suggested that the decrease of T_N through the hole doping is not attributed to the decrease of J_1 corresponding to H_E but the decrease of the magnetic anisotropy parallel to the b -axis corresponding to H_A . This is consistent with the recent inelastic neutron scattering results of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ that J_1 is almost independent of x and that the anisotropic exchange interaction, D , decreases with increasing x [40].

Meanwhile, a metamagnetic transition has been reported in the edge-sharing CuO_2 chain system of $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$ [45]. The difference in the transition in magnetic fields between $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$ and $\text{Ca}_2\text{Y}_2\text{Cu}_5\text{O}_{10}$ is explained as being due to that in J_1 . That is, J_1 estimated from the neutron scattering experiments is as small as D in $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$ [46], while J_1 is about 10-100 times larger than D in $\text{Ca}_2\text{Y}_2\text{Cu}_5\text{O}_{10}$ [40]. Therefore, H_E and H_A are comparable with each other in $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$, so that the metamagnetic transition takes place rather than the spin-flop transition. These results remind us that the magnetic interaction in the edge-sharing CuO_2 chain exhibits a remarkable change as a function of x .

2. $x = 1.5$ and 1.6

Figure 12 shows the temperature dependence of the specific heat of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ with $x = 1.5$ and 1.67 in zero field and in a magnetic field of 9 T parallel to the a -, b - and c -axes. The broad peak observed around 10 K in zero field suggests the formation of a spin-glass state, as discussed in Sec. II B. The peak does not change by the application of a magnetic field of 9 T parallel to the a -, b - and c -axes. This may be reasonable, because the magnetic field of 9 T is much smaller than $\mu_B J_1/k_B$ which brings about short-range magnetic order. For $x = 1.5$ and 1.67, in fact, $\mu_B J_1/k_B$ has been estimated as 80 K [40]. It is found that the spin-gap state in $x = 1.67$ is also not affected by the application of magnetic field. This is also reasonable, because the spin gap, Δ_{SG} , is expected to be much larger than 9 T. In fact, it has been found that Δ_{SG}/k_B in the similar edge-sharing CuO_2 chain of $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ is as large as 100 K [6, 7, 11, 13, 16]. Therefore, a possible peak of the specific heat due to the spin-gap formation in $x = 1.67$ may be located at a much higher temperature than the observed broad peak and hidden by the large contribution of C_{phonon} .

Figures 10 (f) and (l) show the magnetization curve of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ with $x = 1.5$ and 1.67 at 4 K in magnetic fields up to 14 T parallel to the b -, a - and c -axes. The magnetic-field dependence looks like a paramagnetic one. The paramagnetic behavior in $x = 1.5$ may be due to the weak interaction between short-range magnetically ordered regions in the spin-glass state, because the magnetization in $x = 1.5$ is much larger than that in

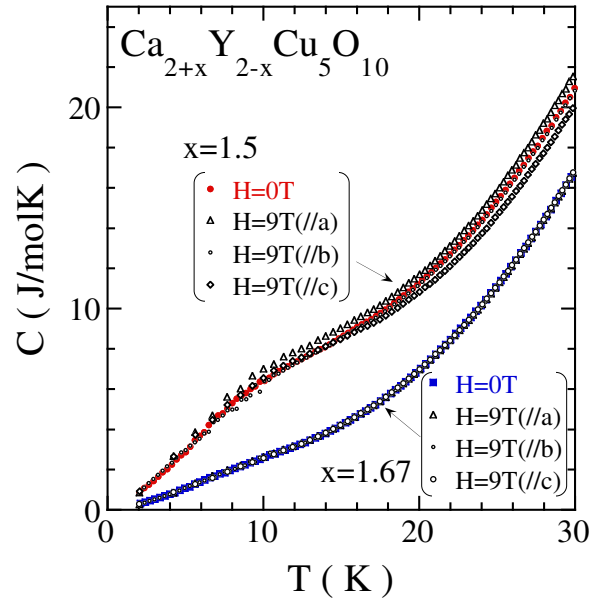


FIG. 12: (Color online) Temperature dependence of the specific heat, C , of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ with $x = 1.5$ and 1.67 in zero field and in a magnetic field of 9 T parallel to the a -, b - and c -axes.

$x = 1.67$ where the spin-glass phase is a minor one. As for $x = 1.67$, on the other hand, the strong suppression of the magnetic susceptibility suggestive of the spin-gap formation is observed as shown in Fig. 4 and discussed above. The suppression is also observed in the magnetization curve. However, the magnetization curve does not exhibit any kink up to 14 T, suggestive of the close of the spin gap, but the paramagnetic behavior due to a minor phase of the spin-glass. This is reasonable, because μ_B is speculated to be much larger than 14 T as discussed from the specific heat measurements.

IV. SUMMARY

We have succeeded in growing large-size single-crystals of $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$ with $0 < x < 1.67$ by the TSFZ method and measured the magnetic susceptibility, specific heat and magnetization curve. In $0 < x < 1.3$, an antiferromagnetic phase transition with the magnetic easy axis along the b-axis has been detected in both magnetic susceptibility and specific heat measurements and a spin- op transition has been observed in the magnetization curve. It has been found that T_N decreases with increasing x and disappears around $x = 1.4$. Alternately,

a spin-glass phase appears around $x = 1.5$. The spin-glass state in $x = 1.3$ and 1.67 may be due to a minor phase. At $x = 1.67$ where the hole concentration is $1/3$ per Cu, the pretty small magnetic susceptibility is indicated that a spin-gap state due to the formation of spin-singlet pairs seems to emerge as a main phase. No sign of the coexistence of an antiferromagnetically ordered state and a spin-gap state suggested in $\text{Ca}_{1-x}\text{CuO}_2$ has been found in $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$. This may be due to the intense modulation in the ac-plane and/or the randomness of Ca^{2+} and Y^{3+} ions in $\text{Ca}_{2+x}\text{Y}_{2-x}\text{Cu}_5\text{O}_{10}$.

Acknowledgments

We are grateful to Professor K. Kumagai, Professor F. Matsubara, Professor H. Kato, Dr. M. Matsuda and Dr. Y. Miyazaki for the useful discussion. We are indebted to Professor T. Nojima and Dr. S. Nakamura for the use of a vibrating sample magnetometer at Center for Low Temperature Science, Tohoku University. This work was supported by a Grant-in-Aid for Scientific Research from the Ministry of Education, Culture, Sports, Science and Technology, Japan, and also by CREST of Japan Science and Technology Corporation.

-
- [1] For a review, M. A. Kastner, R. J. Birgeneau, G. Shirane and Y. Endo, Rev. Mod. Phys. 70, 897 (1998).
 - [2] F. C. Zhang and T. M. Rice, Phys. Rev. B 37, 3759 (1988).
 - [3] For a review, E. Dagotto, Rep. Prog. Phys. 62, 1525 (1999).
 - [4] T. Osaifune, N. Motoyama, H. Eisaki and S. Uchida, Phys. Rev. Lett. 78 1980 (1997).
 - [5] S. Tsuji, K. Kumagai, M. Kato and Y. Koike, J. Phys. Soc. Jpn. 65, 3474 (1996).
 - [6] M. Matsuda, K. Katsumata, H. Eisaki, N. Motoyama, S. Uchida, S. M. Shapiro and G. Shirane, Phys. Rev. B 54, 12199 (1996).
 - [7] R. S. Eccleston, M. Azuma and M. Takano, Phys. Rev. B 53, R14721 (1996).
 - [8] M. Kato, K. Shiotani and Y. Koike, Physica C 258, 284 (1996).
 - [9] M. Kato, T. Adachi and Y. Koike, Physica C 265, 107 (1996).
 - [10] M. Kato, K. Shiotani, T. Adachi and Y. Koike, Czechoslovak J. Phys. 46, Suppl. S5, 2701 (1996).
 - [11] M. Matsuda and K. Katsumata, Phys. Rev. B 53, 12201 (1996).
 - [12] S. A. Carter, B. Batlogg, R. J. Cava, J. J. Krajewski, W. F. Peck, Jr. and T. M. Rice, Phys. Rev. Lett. 77, 1378 (1996).
 - [13] K. I. Kumagai, S. Tsuji, M. Kato and Y. Koike, Phys. Rev. Lett. 78, 1992 (1997).
 - [14] M. Takigawa, N. Motoyama, H. Eisaki and S. Uchida, Phys. Rev. B 57, 1124 (1998).
 - [15] R. S. Eccleston, M. Uehara, J. Akimitsu, H. Eisaki, N. Motoyama and S. I. Uchida, Phys. Rev. Lett. 81, 1702 (1998).
 - [16] S. Tsuji, K. Maki and K. Kumagai, J. Low Temp. Phys. 117, 1683 (1999).
 - [17] M. Hiroi, M. Sera, N. Kobayashi, T. Nagata, H. Fujino and J. Akimitsu, J. Low Temp. Phys. 117, 1677 (1999).
 - [18] M. Isobe, Y. Uchida and E. Takayama-Muromachi, Phys. Rev. B 59, 8703 (1999).
 - [19] T. Nagata, H. Fujino, J. Akimitsu, M. Nishi, K. Kakurai, S. Katano, M. Hiroi, M. Sera and N. Kobayashi, J. Phys. Soc. Jpn. 68, 2206 (1999).
 - [20] Y. Mizuno, T. Tohyama, S. Maekawa, T. Osaifune, N. Motoyama, H. Eisaki and S. Uchida, Phys. Rev. B 57, 5326 (1998).
 - [21] T. G. Babu and C. Greaves, Mater. Res. Bull. 26, 499 (1991).
 - [22] Recently, the more precise value of δ in Ca_xCuO_2 has been evaluated by Isobe et al. [23] as 93.27% from the Rietveld refinement of the x-ray diffraction data using a modulated-structure analysis technique.
 - [23] M. Isobe, K. Kinoto and E. Takayama-Muromachi, J. Phys. Soc. Jpn. 71, 782 (2002).
 - [24] Z. Hiroi, M. Okumura, T. Yamada and M. Takano, J. Phys. Soc. Jpn. 69, 1824 (2000).
 - [25] A. Hayashi, B. Batlogg and R. J. Cava, Phys. Rev. B 58, 2678 (1998).
 - [26] M. Matsuda and K. Katsumata, J. Magn. Magn. Mater. 177-181, 683 (1998).
 - [27] Y. Miyazaki, I. Gamson and P. P. Edwards, J. Solid State Chem. 145, 511 (1999).
 - [28] M. Matsuda, K. Ohoyama and M. Ohashi, J. Phys. Soc. Jpn. 68, 269 (1999).
 - [29] H. F. Fong, B. Keimer, J. W. Lynn, A. Hayashi and R.

- J. Cava, Phys. Rev. B 59, 6873 (1999).
- [30] K. Oka, H. Yamaguchi and T. Ito, Physica B 284-288, 1390 (2000).
- [31] H. Yamaguchi, K. Oka and T. Ito, Physica C 320, 167 (1999).
- [32] M. Matsuda, H. Yamaguchi, T. Ito, C. H. Lee, K. Oka, Y. Mizuno, T. Tohyama, S. Maekawa and K. Kakurai, Phys. Rev. B 63, 180403 (2001).
- [33] K. Oka, H. Yamaguchi and T. Ito, J. Cryst. Growth 229, 419 (2001).
- [34] S. Kurogi, K. Kudo, T. Noji, Y. Koike, T. Nishizaki and N. Kobayashi, J. Low Temp. Phys. 131, 353 (2003).
- [35] In the TSFZ growth of a layered compound, the cross section of the single-crystal rod tends to be ellipsoidal in shape. In this case, the rotation of the ellipsoidal rod is often hard to keep the molten zone stable. Empirically, the rotation had better be stopped in order to grow a large-size single-crystal.
- [36] F. C. Chou, N. R. Belk, M. A. Kastner, R. J. Birgeneau and A. Aharony, Phys. Rev. Lett. 75, 2204 (1995).
- [37] S. Wakimoto, S. Ueki, Y. Endoh and K. Yamada, Phys. Rev. B 62, 3547 (2000).
- [38] R. Omari, J. J. Prejean and J. Souletie, J. Phys. (Paris) 44, 1069 (1983).
- [39] In fact, the inhomogeneity of x induces residual Cu^{2+} - spins, which produce a minor phase of spin glass. At $x = 1.5$, on the other hand, a spin-glass phase emerges as a major phase because of a large number of residual Cu^{2+} - spins.
- [40] M. Matsuda, K. Kakurai, S. Kurogi, K. Kudo, Y. Koike, H. Yamaguchi, T. Ito and K. Oka, to be published.
- [41] M. D. Chabot and J. T. Marnett, Phys. Rev. Lett. 86, 163 (2001).
- [42] In $x = 0$, a jump has also been observed in the thermal conductivity at the same magnetic field as in the magnetization curve [43].
- [43] K. Kudo, Y. Koike, S. Kurogi, T. Noji, T. Nishizaki and N. Kobayashi, J. Magn. Mater. 272-276, 94 (2004).
- [44] K. Yoshida, Theory of Magnetism (Springer-Verlag, Berlin, 1996).
- [45] U. Ammerahl, B. Buchner, C. Kerpen, R. Gross and A. Revcolevschi, Phys. Rev. B 62, R3592 (2000).
- [46] M. Matsuda, K. Kakurai, J. E. Lorenzo, L. P. Regnault, A. Hies and G. Shirane, Phys. Rev. B 68, 060406(R) (2003).