

NMR as a probe of the relaxation of the magnetization in magnetic molecules

P. Santini¹, S. Carretta¹, E. Livio¹, G. Amoretti¹, P. Carretta², M. Filibian², A. Lascialfar² and E. M. Scott²¹INFM and Dipartimento di Fisica, Università di Parma, I-43100 Parma, Italy and²INFM and Dipartimento di Fisica A. Volta, Università di Pavia, I-27100 Pavia, Italy

(Dated: January 12, 2005)

We investigate the time autocorrelation of the molecular magnetization $M(t)$ for three classes of magnetic molecules (antiferromagnetic rings, grids and nanomagnets), in contact with the phonon heat bath. For all three classes, we find that the exponential decay of the fluctuations of $M(t)$, associated with the irreversible exchange of energy with the heat bath, is characterized by a single characteristic time $(T; B)$ for not too high temperature T and field B . This is reflected in a nearly single-Lorentzian shape of the spectral density of the fluctuations.

We show that such fluctuations are effectively probed by NMR, and that our theory explains the recent phenomenological observation by Bak et al. (PRB 70, 134434) that the Larmor-frequency dependence of $1/T_1$ data in a large number of AFM rings fits to a single-Lorentzian form.

PACS numbers: 76.60.Es, 76.60.-k, 75.60.Jk

A central aspect of the physics of magnetic molecules is the way molecular observables, and particularly the magnetization M , are affected by interactions of the spins with other degrees of freedom. When the latter behave as a heat bath, they cause decoherence of the time evolution of molecular observables, usually leading to relaxation dynamics and exponential time-decay of equilibrium fluctuations. The understanding and characterization of relaxation mechanisms in crystals containing magnetic molecules is not only important for evident fundamental reasons, but also because relaxation and, more generally, decoherence, constitute a major obstacle in the envisaged technological applications of these molecules. In particular, relaxation of M through phonons sets an upper bound [1] to the temperature range in which nanomagnets could be used as classical bits in a memory. In the possible application of some molecules as elementary units (qubits) in quantum information processing (QIP) [2], energy dissipation from the qubits to the nuclear-spins heat bath is the main concern regarding the efficiency of quantum logical gates and the performance of the computation.

In this work, we show that for three important classes of magnetic molecules (antiferromagnetic (AFM) rings, grids and nanomagnets), the exponential decay of the fluctuations of $M(t)$ due to spin-phonon interactions is dominated by a single characteristic time $(T; B)$ over a wide range of temperatures and applied fields. While this was already known for the long-time decay of M in nanomagnets, our results show that this applies to completely different classes of molecules, and holds on much shorter time-scales as well. Indeed, in the considered $(T; B)$ regimes this single characteristic frequency $\omega_0 = 1/\tau_0$ dominates the fluctuations spectrum to such a large extent that even experimental probes whose intrinsic frequency is very different from ω_0 will nevertheless detect mostly this single spectral contribution. In particular, we show that NMR measurements of the longitudinal nuclear relaxation rate $1/T_1$ can be used as a direct probe of the fluctuations of M , and that experimental

$1/T_1$ data are fully consistent with our picture. For instance, we explain the recent experimental observation [3] that the Larmor-frequency dependence of $1/T_1$ data in a large number of AFM rings fits to a Lorentzian form, and we elucidate the meaning and behavior of the characteristic time $(T; B)$ of this Lorentzian. In addition, we collected new data on the Mn₃×3 grid which give further support to our picture. At last, we reanalyzed NMR data on the prototype nanomagnet Fe₈.

Each magnetic molecule can be described by the spin Hamiltonian

$$H = \sum_{i,j=1;N}^X J_{ij} S_i \cdot S_j + \sum_{i=1;N}^X \sum_{k;q}^X b_k^q(i) O_k^q(S_i) + \sum_{i=1;N}^X S_i \cdot D_j S_j + \sum_{i=1;N}^X g_B B S_z; \quad (1)$$

where S_i are spin operators of the i^{th} magnetic ion in the molecule. The first term is the isotropic Heisenberg exchange interaction. The second term describes local crystal-fields (CFs), with $O_k^q(S_i)$ Stevens operator equivalents for the i -th ion [4] and $b_k^q(i)$ CF parameters. The third term represents dipolar anisotropic intra-cluster spin-spin interactions. The last term is the Zeeman coupling with an external field B with $S_z = \sum_i S_{i,z}$. The Heisenberg contribution is usually largely dominant, and therefore the energy spectrum of H consists of a series of level multiplets with an almost definite value of the total spin S .

Much of the physics of nanomagnets such as Fe₈ can be described to a good degree of approximation by retaining the lowest S -multiplet (e.g., $S = 10$ in Fe₈) [5]. In AFM rings such as Fe₆ and Cr₈ and in grids, several distinct S -multiplets must be included for a good description. The ground and first-excited multiplets have $S = 0$ and $S = 1$ in AFM rings [6], while they have $S = 5/2$ and $S = 7/2$ in the Mn₃×3 grid [7]. In rings and grids the anisotropic terms in Eq. (1) have no qualitative effects for most observables, (including those on which we focus here) and in most situations (i.e. away from intermultiplet (anti)-

crossings caused by B). In view of this, and since numerical calculations based on the full Hamiltonian Eq. (1) are cumbersome, in these two classes of systems we will use Eq. (1) neglecting the anisotropic terms. In addition, large-scale numerical techniques must be used for M $n \times 3$, resulting in a limitation in the range of T which can be studied.

Our first goal is the calculation of the damping of equilibrium fluctuations of the molecular magnetization $M(t)$ gS_z due to interactions of the electron spins with a heat bath. We adopt the well-established framework presented in [8] for the irreversible evolution of the density matrix $\rho_{st}(t)$ (in the representation of the exact eigenstates of (1)) in presence of a heat bath. Here we focus on time scales much longer than the typical periods of free evolution of the system ($2\pi\hbar/(E_s - E_t)$), with E_s and E_t eigenvalues of (1)). In this case, the so-called "secular approximation" enables the time evolution of the off-diagonal matrix elements $\rho_{st}(t)$ to be decoupled from that of the diagonal elements $\rho_{ss}(t) = p_s(t)$. In a frequency-domain picture (e.g., the outcome of a scattering experiment), this corresponds to a clear separation of inelastic (IE) and quasielastic (QE) spectral contributions. Then the (single-Lorentzian) broadening of IE transitions merely reflects the lifetimes of the involved pair of levels (basically determined by Fermi's golden rule applied to the spin-bath interaction). These IE off-diagonal contributions to the evolution equations for $M(t)$ will be neglected since we are here interested in the subtler QE components of the dynamics. Only the latter are detected by low-frequency probes such as AC-susceptibility or NMR.

In the secular approximation the populations of the molecular eigenstates, $p_s(t)$, evolve through the well-known rate (master) equations

$$\dot{p}_s(t) = \sum_t W_{st} p_t(t); \quad (2)$$

where W_{st} is the st element of the rate matrix W , i.e. the probability per unit time that a transition between levels j_i and j_s is induced by the interaction with the heat bath ($W_{ss} = -\sum_t W_{ts}$).

We are here focusing on temperatures for which relaxation is determined by interactions of the spin degrees of freedom of each molecule with the crystal phonon heat bath. Since we are interested in general qualitative features of the relaxation dynamics and not in compound-specific details, we will eventually assume a unique simple form for the spin-phonon coupling for all compounds. The main contribution to this coupling comes from the modulation of the local rank-2 crystal fields $b_2^q(l)O_2^q(s_l)$ by phonons:

$$V = \sum_{i=1;N} \sum_{l=1} \sum_{q=1} V_{il} Q_{l;1} C_{l;1}; \quad (3)$$

where $Q_{l;1}$ are symmetrized displacements of neighboring atoms of the l th magnetic ion, labelled by irreducible

representations Γ_l of the local point group of ion l , Γ_l being the component. $C_{l;1}$ are linear combinations of $O_2^q(s_l)$ transforming as Γ_l . For instance, in octahedral local environment, if $C_{3;1} = O_2^0(s_l) = \sqrt{3}$ and $C_{2;2} = O_2^2(s_l)$. The symmetrized displacements $Q_{l;1}$ of the neighboring atoms can be expanded in terms of normal coordinates q_k of the full crystal lattice,

$$Q_{l;1} = \sum_k a_k(l) q_k; \quad (4)$$

where $a_k(l)$ are known as Van Vleck coefficients. This leads to the following general form for the spin-phonon coupling potential

$$V = \sum_{i=1;N} \sum_{Q=0;2} \sum_{k=1} C_Q(l;k) O_2^Q(s_l) (q_k + c_k^y); \quad (5)$$

where $C_Q(l;k)$ is the coupling constant between the Q -type electric quadrupole on ion l ($O_2^Q(s_l)$), and phonon modes of wavevector k and branch index $[9]$. Clearly, a detailed microscopic calculation of $C_Q(l;k)$ is unfeasible: it would require to model the (complicated) phonon spectrum, and to fix the value of a great number of parameters V_{il} . Yet, experimental information is completely insufficient to accomplish this. Therefore, we have chosen as usual [10] to adopt a Debye model for phonons, and for the sake of simplicity we assume $Q = 0;1;2$ with $C_Q(l;k)$ independent of l and Q , although compound-specific $C_Q(l;k)$ would be needed for precise quantitative calculations, which are beyond the aim of this work. We have checked that the results do not change qualitatively if different choices are made [11].

The rate matrix W appearing in Eq. (2) can be calculated by first-order perturbation theory applied to V , leading to

$$W_{st} = \sum_{i=1;N} \sum_{Q=0;1;2} \sum_{j=1} O_2^Q(s_i) \langle j | V_{st}^2 | i \rangle n(x); \quad (6)$$

with $n(x) = (e^{-x} - 1)^{-1}$; $\dot{p}_{st} = (E_s - E_t)\dot{p}_{st}$. In our simplified spin-phonon model is the unique free parameter and describes the spin-phonon coupling strength. It will be determined by comparison with experimental data. The next step is the calculation of the Fourier-transform $S_{A;B}(\omega)$ of the cross-correlation function $\langle A(t) B(0) \rangle$ implied by Eq. (2) for equilibrium fluctuations of two generic observables A, B . We exploit the fluctuation-dissipation theorem, which implies

$$S_{A;B}(\omega) = \frac{2k_B T \text{Im} \chi_{A;B}^0(\omega)}{\omega} = 2k_B T \text{Re} \chi_{A;B}^0(\omega); \quad (7)$$

with $\chi_{A;B}^0(\omega)$ the imaginary part of the susceptibility, and $\text{Re} \chi_{A;B}^0(z)$ the real part of the Laplace transform of the relaxation function $R_{A;B}(t)$. The latter is defined as $\lim_{\epsilon \rightarrow 0} \int_0^\infty dt e^{-\epsilon t} \langle A(t) B(0) \rangle$, with a perturbation B abruptly switched-on at $t = 0$. We have calculated

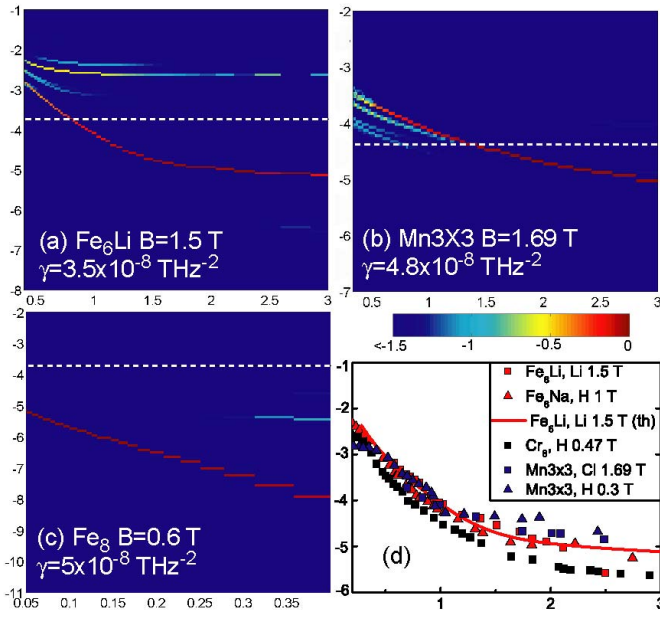


FIG. 1: Calculated frequency weights $A(i; T; B)$ of the magnetization autocorrelation vs T (a,b), with the exchange gap, or vs $1/T$ (c) (x-axis). The y-axis is $\log_{10}(A(i; T; B))$ (in THz). The color maps $\log_{10}(A(i; T; B))$ (see Eq. (9)). The hamiltonian parameters are given in [5, 6, 7]. For each value of T , the spectra have been normalized by T , which is proportional to the size of equilibrium fluctuations. The white dashed lines are the ^7Li (a), ^{35}Cl (b), and ^1H (c) Larmor angular frequencies. The results for Cr_3 (not shown) are similar to those of Fe_6Li , with $\gamma = 5 \cdot 10^{-7} \text{ THz}^{-2}$. Panel (d) shows the characteristic frequency ω_0 vs T for Cr_3 , Fe_6Li , Fe_6Na and Mn_3x_3 extracted from the experimental $1/T_1$ data (see text). The data are taken from ref. [3], apart from those for Mn_3x_3 which are new. The red line represents the dominant frequency ω_0 of Fe_6Li deduced from panel (a).

$R_{A,B}(t)$ by solving the system of equations (2), obtaining the following expression:

$$S_{A,B}(\omega) = \sum_{q,t} (B_{tt} - \hbar B \omega^{(eq)}) \text{Re} \left(\frac{1}{i\omega - W} \right)_{qt}; \quad (8)$$

where $p_t^{(eq)}$ is the equilibrium population of the t -th level, and $B_{tt} = \hbar B \omega^{(eq)}$. This leads to correlations decaying as a sum of exponentials with n characteristic times $\tau_{QE}^{(i)}$ given by the inverse eigenvalues of W , n being the dimension of the molecule spin Hilbert space. Therefore, the QE frequency-spectrum is in general a sum of Lorentzians centered at zero frequency having width $\Gamma = \tau_{QE}^{(i)}$. It should be stressed that the n $\tau_{QE}^{(i)}$ cannot be directly determined from the n level lifetimes $\tau_{life}^{(s)}$. Although both $\tau_{QE}^{(i)}$ and $\tau_{life}^{(s)}$ contain integrated information on the spin-bath dissipation channels, this information is different for the

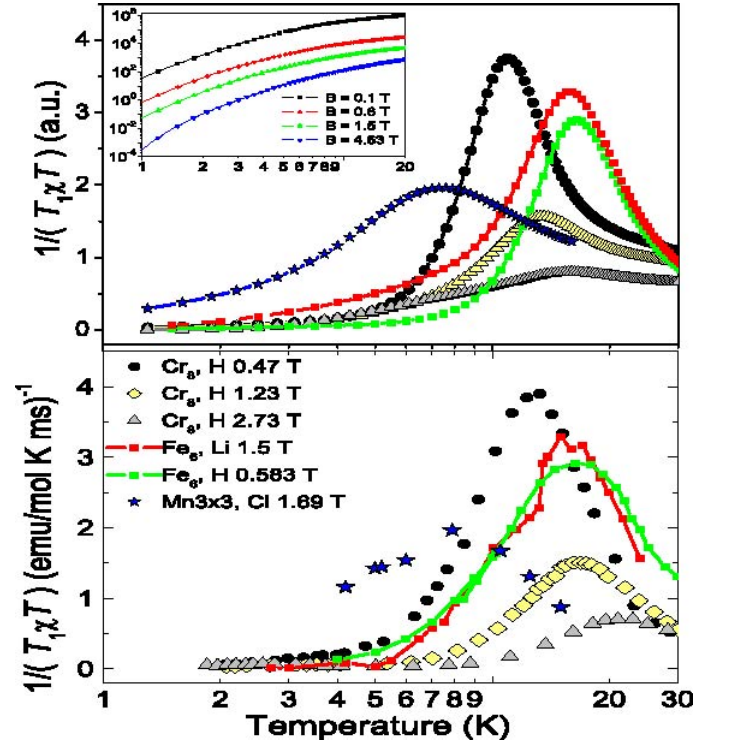


FIG. 2: Up: calculated $1/T_1(T)$ as a function of the temperature T for Cr_3 , Fe_6Li and Mn_3x_3 for different fields and nuclei. Inset: Calculated $1/T_1(T)$ (in a.u.) for Fe_6Li for different values of B applied along the easy axis. Down: Measured $1/T_1(T)$ vs T for Cr_3 , Fe_6Li and Mn_3x_3 . In order to fit the figure, data for Fe_6Li were divided by 3, and those for Mn_3x_3 by 5.

two sets. Thus, low-frequency measurements probing the QE dynamics provide different and complementary information with respect to direct lifetime measurements by high-frequency techniques (e.g., inelastic neutron scattering).

We focus now on the important case $A = B = S_z$, i.e. we study the spectrum of fluctuations of the cluster magnetization. In general, many different $1 = \tau_{QE}^{(i)}$ may be expected to contribute to this spectrum, i.e.

$$S_{S_z, S_z}(\omega; T; B) = \sum_{i=1, n} A(i; T; B) \frac{\tau_{QE}^{(i)}(T; B)}{\tau_{QE}^{(i)}(T; B)^2 + \omega^2}; \quad (9)$$

where $\tau_{QE}^{(i)}(T; B) = 1/\tau_{QE}^{(i)}$. Figure 1 shows intensity plots of the frequency weights $A(i; T; B)$ of the magnetization autocorrelation, calculated from Eq. (8), as function of temperature T for three representative systems. The single free parameter has been estimated by the observed peak in the T -dependence of the NMR $1/T_1$ (see below), apart from Fe_6Li for which relaxation data allow to fix directly. The precise value of γ does not change the spectra appreciably, but merely sets the frequency scale.

The calculations reported in Fig. 1 show that for a fairly wide range of values of T and B , a single frequency $\omega_0(T; B)$ (and therefore a single Lorentzian) dominates

the spectrum in the three classes of molecules we considered (AFM rings, AFM grids and nanomagnets). The dominating frequency ω_0 is different from the lifetime broadening of any level. In the special case of nanomagnets (Fe_8 , Mn_{12}), the calculated ω_0 coincides with the smallest ω_i . Hence, in this case ω_0^{-1} is also the time determining the asymptotic return to equilibrium of the magnetization when the nanomagnet is prepared in a highly nonequilibrium state by a strong applied field. Instead, our calculations show that in rings and grids ω_0 is orders of magnitude larger than the smallest ω_i (the latter is not visible in Fig. 1 since the associated weight is tiny). AFM rings are characterized by a single dominating characteristic frequency ω_0 for $B < B_c$ with B_c the field at which an $S = 1$ level crosses $S = 0$, and for $T \ll 12J = N$. This corresponds to the regime in which the magnetization and its fluctuations are mainly determined by levels belonging to the $S = 1$ manifold. In this single-frequency regime, the decay of fluctuations takes place mostly through indirect Orbach-like processes involving higher-lying S -manifolds, resulting in an approximately exponential dependence in $1/T$ of ω_0 (see Fig. 1). A different T -dependence occurs at low T , where direct transitions within the field-split $S = 1$ manifold constitute the main relaxation mechanism. Fe_8 is also characterized by a single dominating characteristic frequency ω_0 , depending exponentially on $1/T$, if the Zeeman energy is small with respect to the anisotropy barrier. Finally, the Mn_{12} grid is again characterized by a dominating frequency for $B < B_c$ with B_c the field at which an $S = 7/2$ level crosses $S = 5/2$, and for $T \ll k_B$, with $k_B \approx 0.9$ meV the exchange gap. Therefore, for all these systems the calculated dynamical structure factor of Eq. (9) is dominated by a single contribution:

$$S_{S_z;S_z}(\omega;T;B) \sim A(\omega;T;B) \frac{\omega_0(T;B)}{\omega_0(T;B)^2 + \Gamma^2} \quad (10)$$

From linear-response theory $A(\omega;T;B) \propto (\chi(B;T)T)$, with $\chi(B;T)$ the static Curie susceptibility. Therefore, a measurement of $S_{S_z;S_z}$ allows the T - and B -dependence of $\omega_0(T;B)$ to be extracted straightforwardly. In the following we will show that NMR confirms this picture and allows $\omega_0(T;B)$ to be determined.

The nuclear spin-lattice relaxation rate $1/T_1$ can be calculated by a perturbative treatment of the hyperfine interactions between nuclear and electronic spins [12]. Within this framework, $1/T_1$ is given by a linear combination of the Fourier transforms of electronic spin correlation functions $S_{S_i;S_j}$, evaluated at the Larmor frequency $\omega_L(B)$. By considering only the Heisenberg and Zeeman terms in H (Eq. (1)), the spin lattice relaxation rate of a magnetic nucleus of Larmor frequency ω_L interacting with a cluster composed of N spins may be written as

$$1/T_1 = \sum_{i,j=1}^N \langle S_{S_i}^z; S_{S_j}^z(\omega_L) \rangle$$

$$+ S_{S_i}^z; S_{S_j}^z(\omega_L) \rangle + \langle S_{S_i}^+; S_{S_j}^-(\omega_L) \rangle + S_{S_i}^+; S_{S_j}^-(\omega_L) \rangle + S_{S_i}^+; S_{S_j}^-(\omega_L) \rangle + S_{S_i}^+; S_{S_j}^-(\omega_L) \rangle; \quad (11)$$

where $\langle S_{S_i}^+; S_{S_j}^-(\omega_L) \rangle$ and $\langle S_{S_i}^-; S_{S_j}^+(\omega_L) \rangle$ are geometrical coefficients of the dipolar interaction between nuclear and electronic spins. Since generally $\omega_L \ll \omega_{st}$, only the QE part of the $S_{A;B}(\omega)$ in the above formula contributes to $1/T_1$. If anisotropy is neglected, Eq. (8) shows that only the $\omega = \omega_L$ terms are nonzero because $\langle S_{S_i}^x; S_{S_j}^x \rangle = \langle S_{S_i}^y; S_{S_j}^y \rangle = 0$. In addition, for a magnetic ring $\langle S_{S_i}^z; S_{S_j}^z \rangle = \langle S_{S_j}^z; S_{S_i}^z \rangle = 1/N \langle S_{S_z}^z; S_{S_z}^z \rangle$, where S_z is the z component of the total spin operator S . Then,

$$1/T_1 = G S_{S_z;S_z}(\omega_L); \quad (12)$$

where G is a scale factor depending only on the positions and spins of the probed nuclei. The same result holds also for grids as long as the ground multiplet gives the main contribution (i.e. at sufficiently low T). In fact, in this regime all $S_{S_{i;z};S_{j;z}}(\omega) / S_{S_z;S_z}(\omega)$. We have numerically checked that this holds approximately in the single-Lorentzian regime (see Fig. 1). If magnetic anisotropy cannot be neglected, as in the case of Fe_8 , the simple result of Eq. (12) can be recovered if B is along the easy axis, by exploiting the fact that within the ground S -multiplet $S_{S_{i;z};S_{j;z}}(\omega) / S_{S_z;S_z}(\omega)$. Therefore, in all these systems NMR measurements of $1/T_1$ can be used as a probe of $S_{S_z;S_z}(\omega)$.

Eqs. (10) and (12) imply that, as a function of T , $1/T_1(T)$ should display a single peak when $(T;B) = (\omega_L(B))$. Moreover, since $(T;B)$ depends little on B for not too large B , $1/T_1(T)$ measured on different nuclei and by setting the value of B in order to keep $\omega_L(B)$

fixed, should display a peak at approximately the same T . This is clearly visible, for instance, in our calculations of $1/T_1(T)$ for Fe_8 , Li and H nuclei, shown in Fig. 2, which contains our calculated T -dependence of $1/T_1$. By increasing B by a factor p and keeping the nucleus fixed, the peak value of $1/T_1(T)$ should decrease by about p . This can be seen in Fig. 2 in the calculated curves for Cr_8 . This is what had been experimentally observed in [3], where a phenomenological single-Lorentzian expression for the Larmor-frequency dependence of $1/T_1$ had been shown to fit NMR data in several AFM rings very well. Part of the data are included in the lower panel of Fig. 2 together with new data we collected on the Mn_{12} grid. The agreement with our calculations is very good. In addition, panel (d) in Fig. 1 contains the T -dependence of the characteristic frequency ω_0 extracted from the Lorentzian fit of the data [3]. The results are in good agreement with the behavior of the calculated ω_0 in panels (a,b). Similar agreement is obtained for the Cr_8 ring. We remark that in the T -range where the peak in $1/T_1$ occurs the calculated T -dependence of ω_0 is exponential in $1/T$ (relaxation through intermultiplet Orbach processes), and in good agreement with experimental data. Hence, the phenomenological power-law T -dependence assumed in [3], although fitting the

data over a limited temperature range, is not confirmed by our microscopic calculation.

In the case of Fe_3 , the free parameter has been fixed in order to reproduce the T -dependence of the relaxation time of the magnetization in the thermally-activated regime measured in [13]. There is therefore no free parameter in the calculation. As can be seen in Fig. 1, the calculated $\chi_0(T)$ is much smaller than the ^1H Larmor frequency. Indeed, measured $1/T_1$ data do not show a peak [14], and are in good agreement with our parameter-free calculations reported in the inset of Fig. 2.

In conclusion, a general expression for the quasielastic part of the dynamic structure factor in presence of a heat bath has been derived, starting from the master equation applied to the full microscopic Hamiltonian. By specializing this expression to the case of the total molecule magnetization, we have calculated (Fig. 1) the frequency spectral weights of the decay of fluctuations of this ob-

servable. We have shown that in AFM rings, grids and nanomagnets the decay of equilibrium fluctuations due to interactions with phonons is characterized by a single characteristic frequency $\chi_0(T;B)$ over a wide range of temperatures and fields. We have also shown that the NMR spin-lattice relaxation rate $1/T_1$ can be used to measure $\chi_0(T;B)$. This microscopic result differs from the previous phenomenological models of $1/T_1$ in rings [3] and nanomagnets [14], where $1/T_1$ was assumed to probe level lifetimes in presence of phonons, and not a relaxation time. Our calculations are in good agreement with existing experimental NMR data, and with our new measurements on the Mn_3X_3 grid.

Useful discussions with F. Borsa are gratefully acknowledged. We thank L.K. Thompson for the synthesis of Mn_3X_3 , for which preliminary NMR results are published here.

-
- [1] D. Gatteschi and R. Sessoli, *Angew. Chem. Int. Ed.* 42, 268 (2003).
 - [2] M. N. Leuenberg, D. Loss, *Nature* 410, 789 (2001).
 - [3] S.-H. Baek, M. Luban, A. Lascialfari, E. Micotti, Y. Furukawa, F. Borsa, J. van Slageren, and A. Comia, *Phys. Rev. B* 70, 134434 (2004).
 - [4] A. Abragam and B. Bleaney, *Electron paramagnetic resonance of transition ions*, Clarendon Press, Oxford (1970).
 - [5] R. Caciuo, G. Amoretti, A. Murani, R. Sessoli, A. Caneschi and D. Gatteschi, *Phys. Rev. Lett.* 81, 4744 (1998); S. Carretta, E. Livioti, N. Magnani, P. Santini and G. Amoretti, *Phys. Rev. Lett.* 92, 207205 (2004).
 - [6] A. Lascialfari et al., *Phys. Rev. B* 55, 14341 (1997); S. Carretta et al., *Phys. Rev. B* 67, 094405 (2003).
 - [7] T. Guidi et al., *Phys. Rev. B* 69, 104432 (2004).
 - [8] K. Blum, *Density Matrix Theory and Applications*, Plenum Press, NY (1996); A. Wurger, *J. Phys.: Condens. Matter* 10, 10075 (1998).
 - [9] G. A. Gehring and K. A. Gehring, *Rep. Prog. Phys.* 38, 1 (1975).
 - [10] P. Politi, A. Rettori, F. Hartmann-Bouttronn and J. Villain, *Phys. Rev. Lett.* 75, 537 (1995).
 - [11] In principle, modulation of the intracuster dipolar inter-

- action provides an additional contribution to the spin-phonon coupling. Since generally the anisotropy is mainly determined by the CF, we expect the same to hold also for the magnetoelastic interaction. In any case, the effect of the inclusion of a dipolar contribution is substantially equal to a different choice for the $C_0(i;k;\lambda)$.
- Within the model used here for rings and grids, the simplified site-independent form chosen for V does not allow relaxation to equilibrium of the most general non-equilibrium density matrix. We have made calculations using more complicated site-dependent forms for V (which may originate for example from low-symmetry local dynamic distortions). In addition, we have tried different combinations of the local quadrupole operators. No qualitative changes in our results on the dynamics of the magnetization are seen. Experimental information much more selective than the available data would be needed to probe effects due to specific choices of V .
- [12] T. Moriya, *Progr. Theor. Phys.* 16, 23 (1956).
- [13] C. Sangregorio et al., *Phys. Rev. Letters* 78, 4645 (1997).
- [14] Y. Furukawa et al., *Phys. Rev. B* 64, 094439 (2001).