Synthesis, structure and magnetization studies on (Fe_{1-x}Cr_x)₂TeO₆ tellurate system

K. D. Singh Mudher^{1*}, K. Krishnan¹ and I. K. Gopalakrishnan²

¹Fuel Chemistry Division, ²Novel Materials and Structural Chemistry Division Bhabha Atomic Research Centre, Mumbai 400085, India

Darshan C. Kundaliya

Center for Superconductivity Research, Department of Physics, University of Maryland, College Park, MD-20742, U.S.A

and

S.K. Malik*

Tata Institute of Fundamental Research, Colaba, Mumbai 400005, India

Abstract

The effect of substitution of Fe by Cr on the structural and magnetic properties of Fe₂TeO₆ in the system (Fe_{1-x}Cr_x)₂TeO₆, ($0.0 \le x \le 1.0$) has been investigated on polycrystalline samples synthesized by solid state reaction. The lattice parameters are found to obey Vegard's law in the entire composition range. The Néel temperature decreases linearly with increasing Cr content from ~230 K for x=0 to 90 K for x=1 and is attributed to the weakening of antiferromagnetic exchange interaction as Cr³⁺ replaces Fe³⁺ in Fe₂TeO₆.

Keywords: A. antiferromagnet; E. magnetization; C. rietveld refinement;

*Corresponding authors: S.K. Malik Email: skm@tifr.res.in Fax: +91-22-2280 4610; Tel: +91-22-2280 4545 K.D. Singh Email: kdsingh@apsara.barc.ernet.in

Introduction

The compounds Fe₂TeO₆ and Cr₂TeO₆ are members of isomorphous series of compounds possessing an ordered inverse-trirutile structure with tetragonal symmetry (space group P4₂/mnm, No. 136) [1-3]. The structure can be regarded as a superlattice of rutile with a regular distribution of Cr³⁺ or Fe³⁺ and Te⁶⁺ in octahedral coordination. Neutron diffraction studies by Kunnmann et al [4] have shown that these compounds are antiferromagnetically ordered at 4.2 K. The ordered state in Fe₂TeO₆ and Cr₂TeO₆ shows that the magnetic ions have collinear spin arrangements in a magnetic cell identical with the chemical cell with 3*d* ion moments of 4.19µ_B and 2.45µ_B, respectively [4]. In Fe₂TeO₆, the spins are directed along the *c*-axis while in Cr₂TeO₆ these are directed along the basal plane. From magnetization and specific heat measurement, Yamaguchi and. Ishikawa [5] have shown that Fe₂TeO₆ and Cr₂TeO₆ have Néel temperatures (T_N) of 80 K and 230 K, respectively. In this paper we report the effect of substituting Fe by Cr in (Fe₁. _xCr_x)₂TeO₆ on the structural and magnetic properties in the entire composition range ($0.0 \le x \le 1.0$)

Experimental

The compounds in the series $(Fe_{1-x}Cr_x)_2TeO_6$ were prepared by solid state reaction techniques from high purity Fe₂O₃ (99.9%), Cr₂O₃(99.9%) and TeO₂(99.99%). The components were weighed to obtain desired concentration (x = 0.0, 0.2, 0.4, 0.6, 0.8 and 1.0), mixed intimately and heated in alumina boats at 700 °C for 20 h. After this initial firing, the standard procedure of repeated grinding and firing at 700 °C was employed until X-ray diffraction analysis showed them to be single phase compounds The identification of the phases and determination of the lattice parameters was done by X-ray powder diffraction analysis using graphite monochromatatised CuK α radiation (λ =0.15406 nm) on a STOE diffractometer. Silicon powder was used as an external standard. Structural analysis was carried by Rietveld method for the X-ray intensity data collected for the range $10^{\circ} \angle 2\theta \angle 100^{\circ}$, counting for 5s at each step of 0.02°.

Magnetization measurements on $(Fe_{1-x}Cr_x)_2TeO_6$ compounds were carried out at various temperatures and fields using a SQUID magnetometer (MPMS, Quantum Design). The temperature dependence of the magnetization was measured in zero-field-cooled (ZFC) mode in the temperature range between 4.5 and 300 K. The field dependence of the magnetization was measured at different temperatures in magnetic fields upto 55 kOe.

Results and Discussions

a. Structural studies:

The compounds Fe₂TeO₆ and Cr₂TeO₆ crystallize in the tetragonal trirutile structure [4-6]. Powder X-ray diffraction (XRD) analysis of $(Fe_{1-x}Cr_x)_2TeO_6$, (0 $0 \leq x \leq 1.0$) samples show that the compounds with in-between compositions have the same crystal structure as the end members, thus forming a solid solution in the entire range of composition. This is evident from the data presented in Figures 1 which show the lattice parameters and molar volume (Inset figure) decrease linearly as a function of Cr content obeying Vegard's law. The decrease can be attributed to the fact that ionic radius of Cr³⁺ (0.62 Å) is smaller than that of Fe³⁺ (0.65 Å) for 6-coordination. Figure 2 shows the detailed structural analysis performed on the XRD data of $(Fe_{1-x}Cr_x)_2TeO_6$, by Rietveld pofile refinement method with the computer code DBWS 11 [7], using atomic coordinates of Cr_2TeO_6 . The occupancy factors for the Fe and Cr were refined along with other variables like scale factor, background parameters, halfwidth parameters defining pseudo-Voigt peak shape, the unit cell dimensions, etc. The structural parameters including atomic coordinates and isotropic thermal parameters of atoms and selected inter-atomic distances for $(Fe_{1-x}Cr_x)_2TeO_6$ are given in Table 1. In the trirutile structure, each Cr or Fe atom is surrounded by six oxygen atoms in an octahedral coordination. The cation oxygen octahedra form edge-sharing chains which are alternately occupied by Cr (or Fe)O₆ and TeO₆ octahedra in the ratio of 1:2.

b. Magnetization studies

Figure 3 (a) shows the plot of magnetization (ZFC) vs. temperature for the polycrystalline samples in the $(Fe_{1-x}Cr_x)_2TeO_6$ system with x = 0, 0.1 .15, .25, 5, .75, .9 and 1.0. The isothermal magnetization data of the end compounds, Fe₂TeO₆ and Cr₂TeO₆, as a function of field at different temperatures are presented in Figures 3(b) & (c), respectively. It can be seen from Figure 4 that the magnetization of the samples passes through a broad maxima as the temperature is lowered. The end compounds Fe₂TeO₆ and Cr₂TeO₆ being antiferromagnets [4-6], it is reasonable to attribute the magnetization maxima observed in the samples in (Fe_{1-x}Cr_x)₂TeO₆ system to the Néel temperature (T_N). This is also evident from the isothermal magnetization is linear and without any hysteresis. The variation of T_N in (Fe_{1-x}Cr_x)₂TeO₆ with concentration x is plotted in Fig. 4. It can be seen that T_N decreases as the Cr concentration increases. The decrease of T_N is linear upto x = 0.75, after which T_N remains nearly constant at 90 K. The Néel temperatures of the end compounds are in good agreement with those reported in the literature [5].

Figure 5 depicts the trirule structure of Fe₂TeO₆. Small filled circles with arrows indicate Fe atoms while small open circles indicate Te atoms. Oxygen is represented by large open circles. The arrows indicate the directions of the Fe³⁺ ion magnetic moment. Antiferromagnetism in Fe_2TeO_6 has been attributed to the exchange interaction between Fe^{3+} ions through Fe-O-Fe pathway [4, 6]. The exchange interaction between Fe^{3+} -ions in Fe_2TeO_6 takes place through an intervening O^{2-} ion and is referred as supercxchange interaction [8]. In Fe₂TeO₆, there are two different Fe-O-Fe pathways for antiferromagnetic superexchange interaction as depicted in Fig. 5. The first one is the antiferromagnetic ordering of Fe layers into double layers without correlation of these double layers with each other. The ordering of two neighbouring Fe layers would be accomplished by antiferromagnetic superexchange between next-nearest- neigbour (nnn) Fe^{3+} ions through an oxygen ion with an Fe-O-Fe angle of 125° (marked by doted line in Figure 5). In this way, the magnetic ordering is restricted to the bilayer without correlation along the c-axis due to the intervening Te layer. The second pathway (marked by a dashed line) is the antiferromagnetic superexchange between nearest Fe^{3+} ions at an angle of 100°. The two possible pathways available for superexhange antiferromagnetic interactions in Fe_2TeO_6 are not equivalent. This may explain the rather rounded maxima observed around T_N in Fe₂TeO₆. Cr₂TeO₆ is structurally equivalent to Fe₂TeO₆ except that the spins are directed along the basal plane [4]. The observed decrease in the Néel temperature (T_N) with increasing Cr content in $(Fe_{1-x}Cr_x)_2TeO_6$ may be attributed to a weakening of antiferromagnetic exchange interaction as $Cr^{3+}(d^3)$ replaces $Fe^{3+}(d^5)$.

In conclusion, we have synthesized trirutiles in the $(Fe_{1-x}Cr_x)_2TeO_6$ system. X-ray diffraction analyses of the samples show that they form solid solution in the entire composition range ($0.0 \le x \le 1.0$). DC magnetization studies as a function field and temperature show that all these compounds are antiferromagnetic. The Néel temperature, T_{N_y} decreases from 230 K to 90 K as x increases from 0.0 to1.0.

References:

- 1. G.J. Bayer, J. Amer.Ceram. Soc. 43(1960) 495.
- 2. G.G. Gopodinov, K.M. Gjurova, Thermochim. Acta 210 (1992) 321
- K. Krishnan, K.D. Singh Mudher, G.A. Rama Rao, V. Venugopal, J. Alloys comp. 316 (2001) 264.
- 4. W. Kunnmann, S. La Placa, L.M. Corliss, J.M. Hastings, E. Banks, J. Phys. Chem. Solids 29 (1968) 1359.
- 5. M Yamaguchi, M. Ishikawa, J. Phys. Soc. Japan 63 (1994) 1666.
- 6. J.T. Dehn, R.E. Newnham, L.N. Mulay, J. Chem. Phys 49 (1968) 3201.
- R.A.Young, A.Sakthivel, T.S.Moss, C.O.Paivaa- Santos, Program DBWS-9411, Georgia institute of Tech., Atlanta, GA, 1994.
- 8. J.B. Goodenough, Magnetism and chemical bond, Interscience, New York, 1963.

Figure Captions

- Figure 1. The variation of lattice parameter *a* and *c* of $(Fe_{1-x}Cr_x)_2TeO_6$ as a function of Cr content (x). Inset shows the variation of molar volume of $(Fe_{1-x}Cr_x)_2TeO_6$ as a function of Cr content (x)
- Figure 2. The observed (dots) and profile fitted (curves) room temperature X-ray diffractogram of a typical $(Fe_{1-x}Cr_x)_2TeO_6$. The bottom trace is the difference pattern. The vertical bars indicate peak positions.
- Figure 3. (a) Temperature dependence of magnetization (ZFC) of $(Fe_{1-x}Cr_x)_2TeO_6$ at an applied field of 100Oe, (b) Isothermal magnetization of Fe_2TeO_6 at different temperatures, (c) Isothermal magnetization of Cr_2TeO_6 at different temperatures.
- Figure 4. The variation of Néel temperature (T_N) as a function of Cr content in $(Fe_{1-x}Cr_x)_2TeO_6$.
- Figure 5. Trirutile magnetic structure of Fe_2TeO_6 .

Wavelength (Å)			1.5406		
a (Å)			4.5760(2)		
b (Å)			4.5760(2)		
c (Å)			9.0464(4)		
Space group			P4 ₂ /mnm		
R_{p} (%)			11.2		
R _{wp} (%)			12.7		
R_{exp} (%)			8.8		
Goodness of fit			1.19		
Positional	paramete	rs			
Atom	site	X	у	Z	B(Å ²)
	4e	0	0	0.3341(4)	1.5
Cr or Fe		0	0	0	1.2
	2a	0			2.5
Cr or Fe Te O1	2a 4f	0.3063(18)	0.3063(18)	0	2.5

Table 1. Structural parameters for (Fe,Cr)TeO₆ as determined by Rietveld analysis of X-ray data

Distances (Å) in octahedral coordination

Te-O1×2	1.982(8)
Te-O1×4	1.937(7)
Cr/Fe-O1×2	1.955(6)
Cr/Fe-O1×2	1.977(8)
Cr/Fe-O1×2	1.992(5)

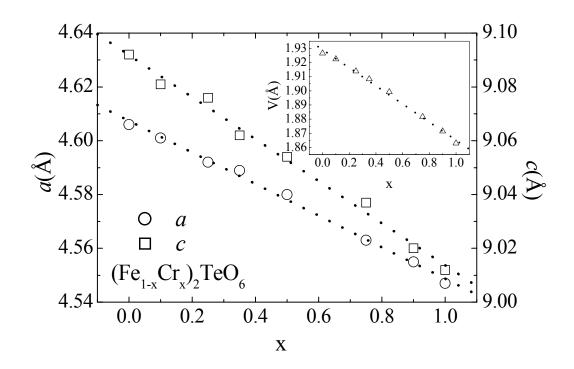


Figure 1 Singh et al.

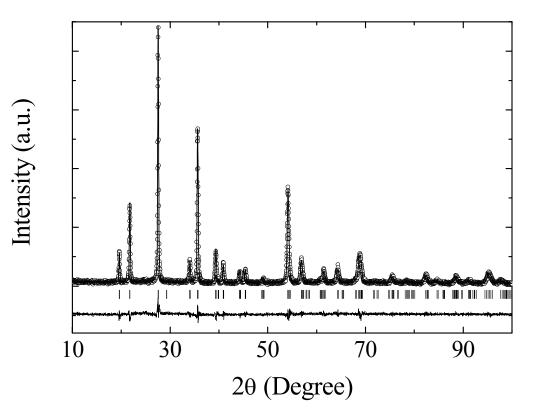


Figure 2 Singh et al.

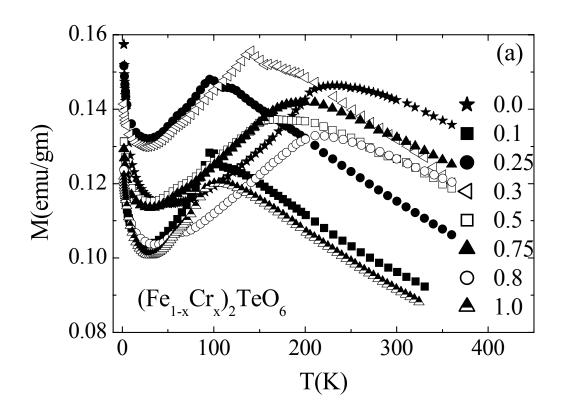


Figure 3 (a) Singh et al.

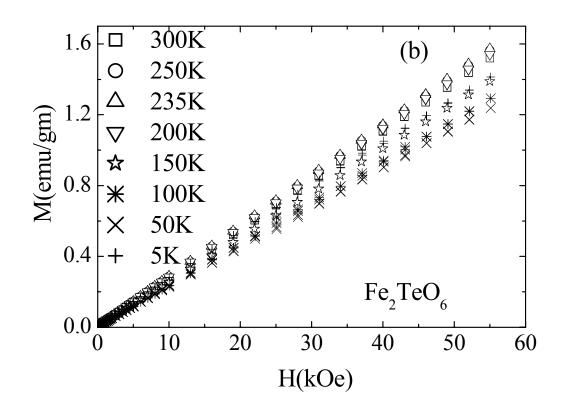


Figure 3 (b) Singh et al.

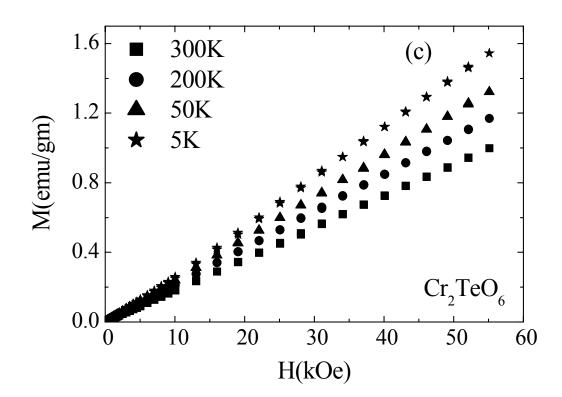


Figure 3(c) Singh et al.

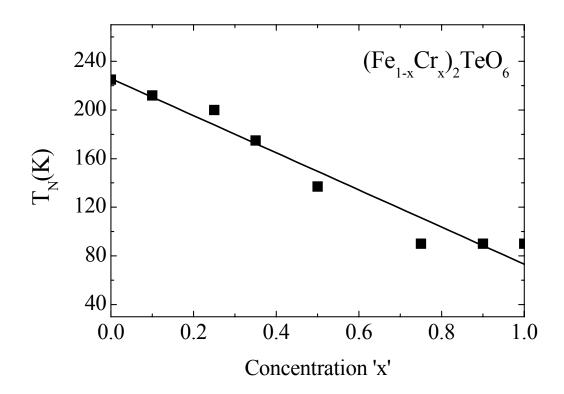


Figure 4 Singh et al.

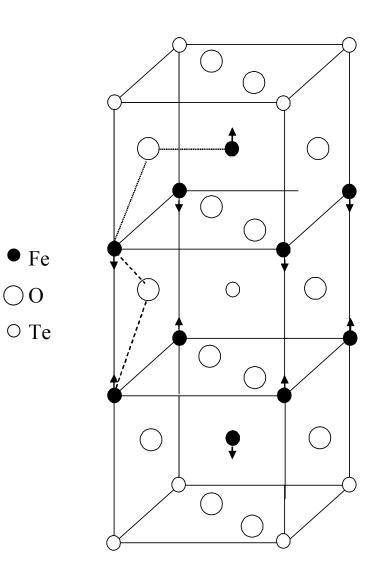


Figure 5 Singh et al.