

Lattice-coupled Antiferromagnet on Frustrated Lattices

Chenglong Jia¹ and Jung Hoon Han^{1,2,*}

¹*Department of Physics, BK21 Physics Research Division,
Sung Kyun Kwan University, Suwon 440-746, Korea*

²*CSCMR, Seoul National University, Seoul 151-747, Korea*

(Dated: March 23, 2022)

Lattice-coupled antiferromagnetic spin model is analyzed for a number of frustrated lattices: triangular, Kagomé, and pyrochlore. In triangular and Kagomé lattices where ground state spins are locally ordered, the spin-lattice interaction does not lead to a static deformation of the lattice. In the pyrochlore structure, spin-lattice coupling supports a picture of the hexagon spin cluster proposed in the recent experiment[S. H. Lee *et al.*, Nature, **418**, 856 (2002)]. Through spin-lattice interaction a uniform contraction of the individual hexagons in the pyrochlore lattice can take place and reduce the exchange energy. Residual hexagon-hexagon interaction takes the form of a 3-states Potts model where the preferred directions of the spin-loop directors for nearby hexagons are mutually orthogonal.

PACS numbers: 75.10.Hk, 75.10.Jm

The continued interest in insulating antiferromagnet appears to have a twofold objective. One is the search for a novel type of quantum ground state, other than the conventional Néel-ordered state, particularly in two dimensions¹. A resonating-valence-bond ground state, if it should exist, is believed to lead naturally to a superconducting phase when doped with holes². In a separate development, understanding the nature of antiferromagnetic ground state defined on the frustrated lattice, even at the classical level, has been the focus of much theoretical³ as well as experimental activity⁴.

In both these cases the fundamental Hamiltonian describing the spin interaction is

$$H = \sum_{\langle ij \rangle} J_{ij} S_i \cdot S_j \quad (J_{ij} > 0) \quad (1)$$

defined for an appropriate set of bonds $\langle ij \rangle$. The antiferromagnetic interaction for an insulating magnet is mediated by the superexchange process in which overlap of Wannier orbitals localized at different positions provides the necessary (virtual) hopping mechanism. As such, it is not surprising that the exchange energy J_{ij} should depend on the separation of orbitals. Existing experimental data suggests that J_{ij} falls off as 6-14th power of the separation⁵.

Writing the equilibrium position of the ions by i and j , and the displacement vector of each ion by u_i and u_j , the exchange integral has the expansion in the small displacements

$$J_{ij} = J(|i + u_i - j - u_j|) \approx J_0 - J_1 \hat{e}_{ji} \cdot (u_j - u_i) \quad (2)$$

where $\hat{e}_{ji} = (j - i)/|j - i|$ is the unit vector, and J_0 and J_1 are positive constants. For an Einstein, or optical, phonon mode and ignoring the kinetic energy of the displacement, we arrive at the lattice-coupled spin model⁶

$$H = \sum_{\langle ij \rangle} (J_0 - J_1 \hat{e}_{ji} \cdot (u_j - u_i)) S_i \cdot S_j + \frac{K}{2} \sum_i u_i^2. \quad (3)$$

The purpose of this paper is to analyze the ground state of the model Hamiltonian, Eq. (3), for a number of frustrated lattices: triangular, Kagomé, and pyrochlore⁷.

By rescaling the displacements, $u_i \rightarrow u_i/\sqrt{K}$, J_1 is rescaled to $J_1/\sqrt{K} \equiv \alpha$, while the overall energy scale is fixed by J_0 , which is set to one. The reduced Hamiltonian has the form

$$H = \sum_{\langle ij \rangle} S_i \cdot S_j - \alpha \sum_i u_i \cdot f_i + \frac{1}{2} \sum_i u_i^2 \quad (4)$$

with $f_i = \sum_{j \in i} \hat{e}_{ij} S_i \cdot S_j$. We introduce the notation $j \in i$ to indicate all bonds j that are exchange-coupled to site i . Minimizing the energy gives the condition relating the lattice positions with the spins:

$$u_i/\alpha = \langle f_i \rangle = \sum_{j \in i} \hat{e}_{ij} \langle S_i \cdot S_j \rangle. \quad (5)$$

Classical antiferromagnet on a triangular lattice has a ground state characterized by a 120° angle between a pair of adjacent spins. Long-range order is established at the mean-field level. When Eq. (5) is applied to the ground state spin arrangements of the triangular antiferromagnet, one finds $u_i = 0$. Unrestricted numerical solution of Eq.(5) together with the classical mean-field equations for the spin average $\langle S_i \rangle$ also yields $u_i = 0$, consistent with a preliminary Monte Carlo simulation of the model Eq.(3)⁸. Thus, at the classical level, the ground state of the classical antiferromagnet on a triangular lattice is unaffected by the coupling to lattice. Employing the acoustic phonon model, $(K/2) \sum_{\langle ij \rangle} (u_i - u_j)^2$, alters the mean-field equation to $\sum_{j \in i} (u_i - u_j)/\alpha = \langle f_i \rangle$, which also gives zero for u_i ⁹.

The effective Hamiltonian after “integrating out” the displacement u_i ,

$$H_{eff} = \sum_{\langle ij \rangle} S_i \cdot S_j - \frac{1}{2} \alpha^2 \sum_i f_i^2, \quad (6)$$

can be expanded around its classical minimum by use of the Holstein-Primakoff (HP) theory. Up to quadratic order in the HP bosons¹⁰,

$$H_{eff} = E_0 + \frac{zS}{2} \sum_k \left[\omega_k \left(b_k^\dagger b_k + \frac{1}{2} \right) - \frac{A_k}{2} \right] \quad (7)$$

with

$$A_k = 1 + \frac{\gamma_k}{2}, \quad B_k = \frac{3\gamma_k}{4}, \\ E_0 = -\frac{1}{4} N z S^2, \quad \omega_k = \sqrt{A_k^2 - (2B_k)^2},$$

where $\gamma_k = \frac{1}{z} \sum_{\langle ij \rangle} e^{ik \cdot (r_j - r_i)}$, $z = 6$ is the coordination number for triangular lattice, and N is the number of sites. There are no terms in the effective Hamiltonian proportional to α^2 up to quadratic order in the HP bosons, and the “vacuum” of the Hamiltonian remains unaltered after the introduction of spin-lattice coupling.

Average of f_i can be worked out within the quadratic theory, yielding

$$\langle f_i \rangle = \left[\frac{S^2}{2} - \frac{S}{N} \sum_k \left[\omega_k \left(n_B(k) + \frac{1}{2} \right) - \frac{A_k}{2} \right] \right] \sum_{j \in i} \hat{e}_{ji} = 0 \quad (8)$$

for the triangular lattice, and $n_B(k)$ is the boson occupation number of energy ω_k . Therefore, small quantum or thermal fluctuation fails to produce a lattice distortion, or “spin-Peierls effects” as it is often known in the literature. The higher-order terms in the HP bosons may have interesting consequences, including a spontaneous distortion of the lattice, and shall be considered in the future.

Classical ground state of the antiferromagnet on the Kagomé lattice is defined by the condition $\sum_{i \in \tau} S_i = 0$ where $i = 1, 2, 3$ are the three corners of a triangle τ , for all τ . This leads to the well-known ground-state degeneracy of order 2^N , where N is the number of triangles in the lattice. Nevertheless, ground-state spin-spin correlation $S_i \cdot S_j$ equals $-1/2$ for all nearest-neighbor pairs $\langle ij \rangle$. Although there is no long-range order, the spins are

locally ordered, with a coherence length of one lattice spacing. The spin ordering patterns for triangular and Kagomé lattices are summarized in Fig.1.

The r.h.s. of Eq.(5) gives zero for the Kagomé lattice, as in the triangular lattice, because the local spin structures are the same in both lattices, $S_i \cdot S_j = -1/2$. HP boson analysis of the Kagomé lattice also reveals the absence of static lattice distortion, whether with optical or acoustic phonons. Our findings may be summarized as follows: In the triangular lattice where spins are long-range ordered, and the Kagomé lattice which has a local spin ordering without the long-range order, spin-lattice coupling fails to produce the static lattice distortion, or the spin-Peierls effect.

Pyrochlore lattice is distinct from the previous two cases in the sense that spins do not order even locally. Ground state manifold of classical spins on the pyrochlore lattice is defined by the condition $\sum_{i \in \tau} S_i = 0$ where the basic building block τ is a tetrahedron, for all the tetrahedra forming the lattice. The requirement is not sufficient to determine $S_i \cdot S_j$ uniquely for nearest-neighbor sites, hence the claim that local spin ordering is missing in the pyrochlore lattice.

Interaction energy $-(\alpha^2/2) \sum_i f_i^2$ is minimized for f_i^2 maximum at each site. This selects the collinear spins (all spins parallel or antiparallel to each other) as the preferred ground state. The collinear spin patterns and the associated lattice distortion were analyzed in details in Ref. 11, following the pioneering work on the spin-Peierls effect in the pyrochlore structure in Ref. 12.

Recently, neutron scattering data on the pyrochlore compound ZnCr_2O_4 revealed a very interesting picture of the spin dynamics¹³. According to Ref. 13, each non-overlapping hexagon embedded inside the pyrochlore lattice has six spins form a collinear, antiferromagnetic cluster, which are energetically decoupled from those of other hexagonal clusters. The resulting block spins are christened “spin-loop directors”, or directors for short, in Ref. 13. While this picture is intuitively appealing, no quantitative justification for the formation, and the stability of, such a hexagonal spin cluster appears to exist to date.

In the rest of the paper we show that spin-lattice coupling can aid in the formation of a hexagonal cluster suggested in Ref. 13. We argue that each hexagon can shrink - uniform contraction without breaking C_6 symmetry - to maximize the gain in exchange energy within the cluster. Spins within each hexagon is antiferromagnetically ordered, at the classical level. The contraction imposes a constraint, via Eq.(5), that the directors of nearby hexagons be mutually orthogonal, thus lifting the huge degeneracy of the original ground state manifold.

We first analyze the case of a single hexagonal antiferromagnetic chain coupled to the lattice as in Eq.(3). The classical ground state of the effective Hamiltonian is given by the staggered spin, $S_i^0 = \pm S \hat{z}$. The staggered spins give u_i all pointing inward to the center of the hexagon, as given by

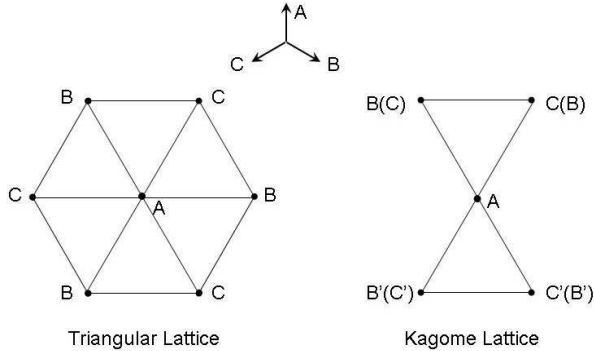


FIG. 1: Ground-state spin configuration of the triangular and Kagomé lattice. A, B, C refer to three orientations of the spin.

$$\langle f_i \rangle = \left[S(S+1) - \frac{S}{6} \sum_k \omega_k \left(n_B(k) + \frac{1}{2} \right) \right] \sum_{j \in i} \hat{e}_{ji}$$

in the HP analysis. Here ω_k is the dispersion of a single hexagonal unit: $\omega_k = 2|\sin k|$, $k = 2\pi(\text{integer})/6$. The orientation of the antiferromagnetic spins defines the spin-loop director of Ref. 13.

Taking individual hexagon as a structural unit, the pyrochlore lattice is built up of four different types of non-overlapping hexagons (defined A, B, C, and D), depending on the orientation of the face of a hexagon. The four directions correspond also to the normal of the four faces of a tetrahedron. Planes perpendicular to each orientation defines a Kagomé lattice embedded in a pyrochlore structure. Taking one such Kagomé plane as the basal plane, spanned by \hat{e}_1 and \hat{e}_2 , and the vector \hat{e}_3 connecting two nearby basal planes, the A-type hexagons are given the coordinates $(3m, 2n, p)$, or $3m\hat{e}_1 + 2n\hat{e}_2 + p\hat{e}_3$, for integers m, n , and p (Fig. 2). The other three types are sandwiched between two nearby Kagomé planes that are shown in Fig. 2. Coordinates of a B-type hexagon, for example, is defined by those of the A-type lying nearest to it. The remaining hexagons are then each located at $(B; 3m, 2n+1, p)$, $(C; 3m-1, n, 2p+1)$, and $(D; 3m-1, n, 2p)$. An A-type hexagon at $(3m, 2n, p)$ is neighbored by four B-type hexagons located at $(3m, 2n+1, p-1)$, $(3m, 2n-1, p-1)$, $(3m, 2n+1, p)$ and $(3m, 2n-1, p)$. Two other hexagons, of type C and D, surround the A-type hexagon, too. Such “connectivity” of a given hexagon type to other hexagons can be worked out, for all hexagon types.

A unit cell has a $2 \times 2 \times 3$ structure with eight hexagons, two of each orientation¹³. Each hexagon is surrounded by six nearest-neighboring hexagons as shown in Fig. 3. According to the previous discussion, a single hexagon undergoes a uniform contraction and has six collinear, antiferromagnetic spins. Requiring such hexagon contraction throughout the whole pyrochlore lattice, the r.h.s. of Eq.(5) imposes the condition that the directors of the

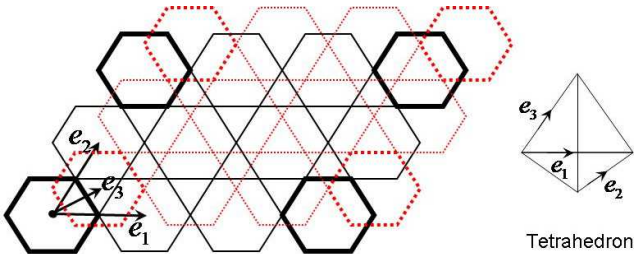


FIG. 2: Three vectors that span the pyrochlore: \hat{e}_1 , \hat{e}_2 , and \hat{e}_3 . \hat{e}_1 and \hat{e}_2 lie within a Kagomé plane, while \hat{e}_3 connects the nearest-neighbor Kagomé planes. Each plane is drawn by full and dashed lines. The angle between the three vectors are shown in a single tetrahedron. Thick black (first layer), and thick red (second layer) hexagons shrink due to spin-lattice coupling.

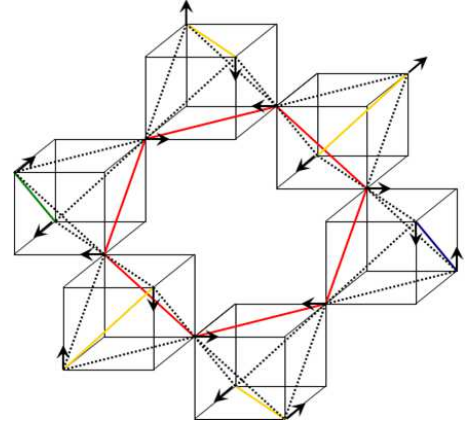


FIG. 3: Local spin configurations of the distorted pyrochlore lattice. Short (long) bonds are denoted by color (dashed) lines after the lattice distortion. Each short bond belongs to one and only one hexagon cluster.

nearest-neighbor hexagons be orthogonal (Fig.3)¹⁴. A self-consistency requirement on the hexagons is therefore that the network of hexagons be “colored” in one of three colors, say R, G, and B, with no two neighboring hexagons having the same color. In other words, the relative orientations of the directors satisfy an antiferromagnetic 3-state Potts model

$$H_{3SP} = J_{eff} \sum_{\langle IJ \rangle} \delta(d_I, d_J) \quad (9)$$

for the nearest-neighbour hexagons, $\langle IJ \rangle$, and their respective directors, (d_I, d_J) , where d_I, d_J takes on R, G, or B. We find, through explicit construction, that such coloring of the hexagon units can indeed be realized for a pyrochlore lattice. The strength of coupling between the directors J_{eff} depends on the spin-lattice interaction α , and also on the level of quantum fluctuation within a hexagonal cluster. A severe quantum fluctuation leads to the reduction of $\langle S_i \cdot S_j \rangle$ for i, j belonging to different hexagons, and an effectively weaker α in Eq.(5). In the extreme limit $J_{eff} \rightarrow 0$ the hexagons are completely decoupled from each other, but more generally a residual hexagon-hexagon interaction of order J_{eff} lifts the degeneracy and leads to a band of excitation spectra.

So far the distortion mode is discussed in terms of the hexagon as a unit. Now, let us consider the distortion of an isolated tetrahedron. For a single tetrahedron, there are six vibrational modes: singlet A_1 , a doublet E , and a triplet T_2 ¹¹. When the pyrochlore lattice assumes the hexagonal distortion we discuss, the resulting distortion for an isolated tetrahedron is not tetragonal (E) as discussed in Ref. 11, but is a linear combination of a doublet E and a triplet T_2 (Fig.4).

In conclusion, lattice-coupled antiferromagnetic Heisenberg spin model on a variety of frustrated lattices is analyzed. For a triangular and Kagomé lattice where the ground state spin structures are locally rigid,

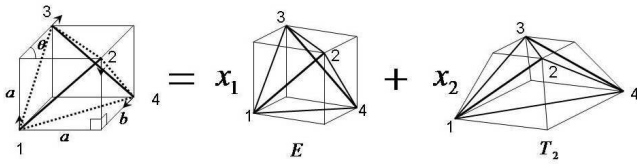


FIG. 4: Distortion of an isolated tetrahedron consistent with a hexagon shrinkage. The spins configuration is coplanar.

no spin-Peierls effect arises. Pyrochlore spins have a continuous manifold of ground states and a lack of local rigidity of spins, and spin-lattice coupling easily induces a lattice distortion leading to a reduction of the ground state degeneracy. A particular pattern of such lattice distortion, namely a hexagon contraction, is proposed and analyzed, following the suggestion of Ref.13. Each hexagonal cluster takes advantage of the lattice defor-

mation to reduce its size and maximize the exchange energy within the cluster. The hexagonal ‘protectorate’ of Ref.13 is thus obtained. Interaction between nearby hexagons is mediated by the spin-lattice condition, Eq.(5), and leads to mutually orthogonal directors of nearby hexagons. In broader perspective, the spin-lattice interaction provides a channel for the self-organization of spins, which helps relieve the frustration inherent in the underlying microscopic Hamiltonian.

Acknowledgments

We thank S.-W. Cheong and Je-Geun Park for insightful discussions. HJH is supported by grant No. R01-2002-000-00326-0 from the Basic Research Program of the Korea Science & Engineering Foundation.

* Electronic address: hanjh@skku.edu

¹ A recent development in this direction can be found in T. Senthil *et al.* Science **303**, 1490 (2004).

² P. W. Anderson, Science **235**, 1196 (1987).

³ D. H. Lee, R. G. Caflisch, and J. D. Joannopoulos, Phys. Rev. B **29**, 2680 (1984); Th. Jolicoeur, E. Dagotto, E. Gagliano, and S. Bacci, Phys. Rev. B **42**, 4800 (1990); A. B. Harris, C. Kallin, and J. Berlinsky, Phys. Rev. B **45**, 2899 (1992); R. Moessner and J. T. Chalker, Phys. Rev. B, **58**, 12049 (1998); R. Chitra *et al.* Phys. Rev. B **52**, 1061 (1995).

⁴ H. Mamiya *et al.* J. Appl. Phys. **81**, 5289; S. H. Lee *et al.* Phys. Rev. Lett. **84**, 3718 (2000); S. H. Lee *et al.* Phys. Rev. Lett. **93**, 156407 (2004); Seongsu Lee *et al.* Submitted to Phys. Rev. Lett. (2004).

⁵ W. A. Harrison, *Electronic Structure and the Properties of Solids* (Dover, New York, 1980).

⁶ Spin-lattice interaction through modulation of the exchange integral J_{ij} was discussed in E. Pytte, Phys. Rev. B **10**, 4637 (1974). See also references therein.

⁷ A number of papers analyzed a similar model, but primarily on a square lattice with next-nearest-neighbour bonds.

See F. Becca and F. Mila, Phys. Rev. Lett. **89**, 037204 (2002).

⁸ June Seo Kim, Jung Ho Nam, and Jung Hoon Han, Work in progress.

⁹ We are not concerned with a uniform expansion/contraction of the lattice.

¹⁰ S. J. Miyake, J. Phys. Soc. Japan **61**, 983 (1992); R. R. P. Singh and D. Huse, Phys. Rev. Lett. **68**, 1766 (1992).

¹¹ Oleg Tchernyshyov, R. Moessner, and S. L. Sondhi, Phys. Rev. Lett. **88**, 067203 (2002) and Phys. Rev. B **66**, 064403 (2002).

¹² Yasufumi Yamashita and Kazuo Ueda, Phys. Rev. Lett. **85**, 4960 (2000).

¹³ S.-H. Lee, C. Broholm, W. Ratcliff, G. Gasparovic, Q. Huang, T. H. Kim, and S.-W. Cheong, Nature, **418**, 856 (2002).

¹⁴ It can be shown that $\sum_{j \in i} (u_i - u_j)$ is proportional to u_i for a uniform contraction of hexagons in the pyrochlore. The orthogonality condition of nearby directors therefore applies either for optical, or acoustic phonons.