

Revival of Superconductivity by Y^{3+}/Ca^{2+} substitution in $YBa_2Cu_{2.7}Co_{0.3}O_7$ without reported phase transformation

M.A. Ansari, Rashmi Nigam, V.P.S. Awana^{*,§}, Anurag Gupta, R.B. Saxena and H. Kishan
National Physical Laboratory K.S. Krishnan Marg, New Delhi 110012, India

N.P. Lalla, V. Ganesan and A.V. Narlikar
Inter-University Consortium for DAE Facilities, University Campus, Khandwa Road, Indore-452017, MP, India

C A. Cardoso[§]
Center for Superconductivity Research, University of Maryland, College Park, MD 20742-4111, USA

Results of phase formation, resistivity (ρ), and thermo-electric power (S), are reported on $Y_{1-x}Ca_xBa_2Cu_{2.7}Co_{0.3}O_7$ compounds with $x = 0.1$ and 0.2 . Pristine compound i.e. without Co or Ca substitution crystallizes in orthorhombic structure with space group P/mmm . Cu-site Co substituted compound i.e. $YBa_2Cu_{2.7}Co_{0.3}O_7$ is tetragonal. With simultaneous doping of Ca at Y site in Co substituted compound i.e. $Y_{1-x}Ca_xBa_2Cu_{2.7}Co_{0.3}O_7$ the tetragonal nature still remains. $\rho(T)$ measurements showed superconducting transition temperature (T_c) to decrease from 90K ($YBa_2Cu_3O_7$) to 33 K for $YBa_2Cu_{2.7}Co_{0.3}O_7$ which with further Ca substitution increases from 33K to 53K ($Y_{0.9}Ca_{0.1}Ba_2Cu_{2.7}Co_{0.3}O_7$) and 67 K for $Y_{0.8}Ca_{0.2}Ba_2Cu_{2.7}Co_{0.3}O_7$. T_c decreases first with Cu-site Co substitution by hole-filling and later recovers by simultaneous hole creation by Y site Ca substitution. Room temperature thermoelectric power $S(300\text{ K})$, which is an indirect measure of mobile carriers shows the decrease of carriers with Co doping and creation by Ca substitution. Our results demonstrate the hole filling by Co substitution is compensated by simultaneous Ca substitution.

Key Words: $Y_{1-x}Ca_xBa_2Cu_{2.7}Co_{0.3}O_7$ compounds, Thermoelectric power, Hole filling and hole creation.

* Corresponding Authors: e-mail; awana@mail.nplindia.ernet.in

\$ Presenting Author

INTRODUCTION

Various on-site substitutional studies in high T_c superconducting (HTSc) compounds had attracted a lot of attention, for example [1] and references there in. Basically all HTSc compounds in their ground state are antiferromagnetic insulators with Cu spins ordering above room temperature [1]. By doping of carriers through charge neutrality with various on-site alliovalent substitutions or oxygen content, one frustrates the Cu magnetic ordering and brings in the metallic behavior accompanied with superconductivity at low temperatures [1]. Phase diagrams are drawn in terms of doped carriers on the basis of mentioned substitutional studies for different HTSc families [1,2].

In a p-type (most HTSc compounds except few) conductor higher valent on-site substitutions fill the mobile holes and decreases both conductivity and superconductivity of the parent system. The examples are Ba^{2+} site La^{3+} , Sm^{3+} , Pr^{3+} and Cu^{2+} site Co^{3+} , Fe^{3+} , La^{3+} , Ru^{5+} substitutions in $YBa_2Cu_3O_7$ compound [1-3]. On the other hand in a p-type conductor the lower valent on-site substitutions, viz. Y^{3+} site Ca^{2+} increases the carriers and improves the superconductivity of under-doped system [4,5]. This is however the most simplistic picture being given above. In reality with various alliovalent substitutions, the induction or reduction of carriers is accompanied with various structural changes and also the charge neutrality is not straight forward as the overall oxygen content of the system changes [6,7]. For example, in $Y_{1-x}Ca_xBa_2Cu_3O_7$ system, some of the carriers being introduced by Y^{3+}/Ca^{2+} substitution are compensated by decrease in over all oxygen content of the system [6,7], which is not the case when parent system is under-doped viz. $Y_{1-x}Ca_xBa_2Cu_3O_{6.6}$ [4,5]. Hole filling by higher or hole creation by lower valent substitutions independently has been studied extensively over the years [4-7]. At the same time substitutional studies pertaining to simultaneous hole filling and hole creation in a composite HTSc system are still not explored fully [8,9]. Moreover in such a composite system viz. $Y_{1-x}Ca_xBa_2Cu_{3-y}Co_yO_7$, the structural changes with both hole creating (Y^{3+}/Ca^{2+}) and hole filling (Cu^{2+}/Co^{3+}) taking place simultaneously might be complicated. In this short article we report the phenomenon of hole filling and hole creation in a composite system $Y_{1-x}Ca_xBa_2Cu_{2.7}Co_{0.3}O_7$ compounds with $x = 0.1$ and 0.2 . More interestingly we report the revival of Superconductivity by Y^{3+}/Ca^{2+} substitution in $YBa_2Cu_{2.7}Co_{0.3}O_7$ without reported [9] phase transformation. The results

of phase formation (XRD), resistivity (ρ), and thermo-electric power (S), are reported on $Y_{1-x}Ca_xBa_2Cu_{2.7}Co_{0.3}O_7$ compounds with $x = 0.1$ and 0.2 .

EXPERIMENTAL

Samples of $Y_{1-x}Ca_xBa_2Cu_{2.7}Co_{0.3}O_7$ system with $x = 0.1$ and 0.2 synthesized by solid-state reaction route from ingredients of Y_2O_3 , $CaCO_3$, $BaCO_3$, CuO and Co_3O_4 . Calcinations were carried out on the mixed powder at 900 , 910 , 915 and $925^\circ C$ each for 24 hours with intermediate grindings. The pressed circular pellets were annealed in a flow of oxygen at $920^\circ C$ for 40 hours and subsequently cooled slowly to room temperature with an intervening annealing for 24 hours at $600^\circ C$. X-ray diffraction (XRD) patterns were obtained at room temperature (MAC Science: MXP18VAHF²²; CuK_α radiation). Resistivity Measurements were carried out by conventional four-probe method. Thermoelectric power (TEP) measurements were carried out by dc differential technique over a temperature range of $5 - 300$ K, using home made set up. Temperature gradient of ~ 1 K is maintained throughout the measurement.

RESULTS AND DISCUSSION

Room temperature X-ray diffraction (XRD) patterns of $YBa_2Cu_3O_7$, $YBa_2Cu_{2.7}Co_{0.3}O_7$, and $Y_{0.8}Ca_{0.2}Ba_2Cu_{2.7}Co_{0.3}O_7$ are shown in Fig. 1. Pristine $YBa_2Cu_3O_7$ (Y:123) system is orthorhombic with $a = 3.826(5)$ Å, $b = 3.892(4)$ Å and $c = 11.6734(7)$ Å.

In Y: 123 type compounds, a sheet of Cu and O atoms with variable composition CuO_x interconnects the $BaO/CuO_2/Y/CuO_2/BaO$ slabs. The oxygen sites in $Cu-O_2$ planes are identified as O (2) and O (3). The O (2) resides between two Cu atoms along a-axis, while the one towards b-axis is named O (3) site. The copper atoms in $Cu-O_2$ planes are termed as Cu (2), while in CuO_x chains are named as Cu (1). The oxygen site in Ba-O plane is named as O (4), while the RE-plane is found to be devoid of any oxygen. The oxygen sites in CuO_x strings, often called as Cu-O chains, are named as O (5) (along a-axis) and O (1) (along b-axis) sites. In orthorhombic Y:123, O(1) are fully occupied, while O(5) are unoccupied, giving rise to $b > a$. With 10% Co doping at Cu-site i.e. $YBa_2Cu_{2.7}Co_{0.3}O_7$ both a , b lattice parameters become equal and system turns to be tetragonal with $a = b = 3.856(4)$ Å and $c = 11.6637(8)$ Å. With Co substitution at Cu site in Y:123 the c-lattice parameter is decreased, due to lower ion $Co^{2+/3+}$ ion substitution at Cu^{2+} site. This result is in agreement with previous reports on Cu/Co substitution [1-3,9]. The explanation for

tetragonal structure is the occupation of otherwise un-filled O(5) sites in CuO_x chains. The orthorhombic or the tetragonal structure of Y:123 system can be identified by looking at some characteristic peaks intensity and nature of splitting. For orthorhombic system, at $2(\theta)$ of around 47.6° and 48.9° the split peaks appear with high intensity low angle and low intensity high angle sequence having indices [020], [200] and [123], [213] respectively, which is the case for $\text{YBa}_2\text{Cu}_3\text{O}_7$ sample, see, bottom XRD in Fig.1. As the orthorhombic distortion of the system decreases the split peaks start merging with each other. Interestingly when system becomes tetragonal the split peaks sequence of angle and intensity reverses. For tetragonal Y:123 though the sequence at $2(\theta)$ of around 47.6° and 48.9° becomes low intensity low angle and high intensity high angle with indexing of [006], [200] and [116], [213], respectively, please see middle XRD in Fig.1 for $\text{YBa}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$. When the splitting of these peaks is not clear, one has to deconvolute them and carry out the Reitveld analysis to confirm the structure. In present case as the splitting of these characteristic peaks is clear thus the need for deconvolution or the Reitveld analysis is not necessary. The XRD of $\text{Y}_{0.8}\text{Ca}_{0.2}\text{Ba}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$ compound is shown in top part of Fig.1. As seen from the splitting nature characteristic peaks in the XRD, pattern the compound is tetragonal. According to some previous reports [9], $\text{Y}^{3+}/\text{Ca}^{2+}$ substitution in tetragonal $\text{YBa}_2\text{Cu}_{3-y}\text{Co}_y\text{O}_7$ system had brought about the tetragonal to orthorhombic phase transformation. On the contrary our XRD results clearly show that $\text{Y}_{0.8}\text{Ca}_{0.2}\text{Ba}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$ compound is tetragonal.

With Co substitution at Cu site in Y:123 the c -lattice parameter is decreased, due to lower ion $\text{Co}^{2+/3+}$ ion substitution at Cu^{2+} site [1]. The lattice parameters for $x = 0.10$ and 0.20 samples of series $\text{Y}_{1-x}\text{Ca}_x\text{Ba}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$ are respectively, $a = b = 3.843(5)\text{\AA}$, $c = 11.6691(9)\text{\AA}$, and $a = b = 3.838(4)\text{\AA}$, $c = 11.6703(8)\text{\AA}$ respectively. With Ca substitution in $\text{YBa}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$ a lattice parameter has a slight decreasing trend. This is due to the fact that though the a lattice parameter is supposed to increase slightly due to relatively bigger ion Ca substitution, the increasing number of carriers due to $\text{Y}^{3+}/\text{Ca}^{2+}$ substitution decrease the in plane $\text{Cu}(2)\text{--O}(2)$ distance and hence the former effect is nullified. It is known that increasing p-type carriers in HTSC compounds increase the hybridization of the in-plane $\text{Cu}(3d)$ and $\text{O}(2p)$ orbitals resulting in a decrease both in $\text{Cu}(2)\text{--O}(2)$ distance and the a -lattice parameter [10]. The c -lattice parameter of Co doped samples increase monotonically with increasing x , indicating successful substitution of Y^{3+} by bigger ion Ca^{2+} . The ionic size of Ca^{2+} in eight-fold coordination number is 1.12 \AA , while that of Y^{3+} in the same co-ordination is 1.02 \AA . The system remains tetragonal over the whole range of doping (20%

of Ca^{2+} at Y^{3+}). Monotonic increase of c -lattice parameter with x in $\text{Y}_{1-x}\text{Ca}_x\text{Ba}_2\text{Cu}_3\text{O}_{7-\delta}$ system guarantees the substitution of Ca^{2+} at Y^{3+} site in the same co-ordination number of eight [6,7].

Fig. 2 depicts the resistivity versus temperature (ρ vs. T) behavior of the $\text{Y}_{1-x}\text{Ca}_x\text{Ba}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$ compounds with $x = 0.1$ and 0.2 . ρ (T) measurements showed superconducting transition temperature (T_c) to decrease from 90 K ($\text{YBa}_2\text{Cu}_3\text{O}_7$) to 33 K for $\text{YBa}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$ which with further Ca substitution increases from 33 K to 53 K ($\text{Y}_{0.9}\text{Ca}_{0.1}\text{Ba}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$) and 67 K for $\text{Y}_{0.8}\text{Ca}_{0.2}\text{Ba}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$. T_c decreases first with Cu-site Co substitution by hole-filling and later recovers by simultaneous hole creation by Y^{3+} site Ca^{2+} substitution. $\rho_{300\text{K}}$ is least for pristine $\text{YBa}_2\text{Cu}_3\text{O}_7$ sample and highest for $\text{YBa}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$ sample. This shows that with $\text{Co}^{2+/3+}$ ion substitution at Cu^{2+} the hole filling had taken place and hence the normal state resistivity is increased. With Y^{3+} site Ca^{2+} substitution in $\text{YBa}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$ the $\rho_{300\text{K}}$ is decreased, suggesting the creation of mobile holes in the system. Normal state resistivity ($\rho_{300\text{K}}$) of the various samples is also listed in Table 1. Besides, the T_c and $\rho_{300\text{K}}$ values, the normal state conduction is semiconductor-like for $\text{YBa}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$ and it changes to metallic with further Y^{3+} site Ca^{2+} substitution. Interestingly though the Y^{3+} site Ca^{2+} substitution in underdoped (due to hole filling) $\text{YBa}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$ compound revives superconductivity by increasing T_c , decreasing $\rho_{300\text{K}}$ and improving normal state conduction, but the same is not reached to the level of $\text{YBa}_2\text{Cu}_3\text{O}_7$. This shows that the hole filling ($\text{Co}^{2+/3+}$ ion substitution at Cu^{2+}) and hole creation (Y^{3+} site Ca^{2+} substitution) either do not compensate completely with each other, or there are other negative effects taking place simultaneously.

The results of thermoelectric power (S) measurements on $\text{Y}_{1-x}\text{Ca}_x\text{Ba}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$ with $x = 0.0, 0.10$, and 0.20 are shown in inset of Fig.(2). The value of S at room temperature (290 K) is found to be positive for all the samples, indicating them to be predominantly hole (p) type conductors. $S_{290\text{K}}$ is least for $\text{YBa}_2\text{Cu}_3\text{O}_7$ ($\sim 6\mu\text{V/K}$, plot not shown) and maximum ($\sim 30\mu\text{V/K}$) for $\text{YBa}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$. Further, the value of $S_{290\text{K}}$ decreases with x for $\text{Y}_{1-x}\text{Ca}_x\text{Ba}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$. Implying that the number of mobile p-type carriers increase with increase in x for $\text{Y}_{1-x}\text{Ca}_x\text{Ba}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$ system. For strongly correlated systems the absolute value of S is reported to be inversely proportional to the number of mobile carriers [11]. However this may not be the fact in all the situations, and should be considered with reservations [12]. For example though in $x = 0.20$ sample of presently studied $\text{Y}_{1-x}\text{Ca}_x\text{Ba}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$ series, the overall number of carriers is more, but its $S_{290\text{K}}$ value ($\sim 12\mu\text{V/K}$) is also more than as for $x = 0.10$ ($\sim 10\mu\text{V/K}$). Yet the general

convention holds that decreasing value of S implicates for increase in mobile carriers. Further with decreasing temperature S passes through a maximum (S_{\max}) and later starts decreasing with further decrease in temperature. The temperature corresponding to S_{\max} i.e. $T(S_{\max})$ decreases monotonically with increasing x . Thermoelectric power measurements below $T(S_{\max})$, exhibit transitions to $T_c^{S=0}$ at around 90 K, 29 K, 51 K, and 65 K respectively for $\text{YBa}_2\text{Cu}_3\text{O}_7$, $\text{YBa}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$, $\text{Y}_{0.9}\text{Ca}_{0.1}\text{Ba}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$ and $\text{Y}_{0.8}\text{Ca}_{0.2}\text{Ba}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$ samples. In brief one can conclude that thermoelectric power measurements corroborate the resistance versus temperature results shown in Fig.2.

CONCLUSION

Results of phase formation, resistivity (ρ), and thermo-electric power (S), for $\text{Y}_{1-x}\text{Ca}_x\text{Ba}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$ compounds with $x = 0.1$ and 0.2 , showed the Revival of Superconductivity by $\text{Y}^{3+}/\text{Ca}^{2+}$ substitution in $\text{YBa}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$ without previously reported phase transformation.

FIGURE CAPTIONS

Fig.1 XRD patterns for $\text{Y}_{1-x}\text{Ca}_x\text{Ba}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$ system.

Fig.2 $\rho(T)$ for $\text{Y}_{1-x}\text{Ca}_x\text{Ba}_2\text{Cu}_{2.7}\text{Co}_{0.3}\text{O}_7$ system, inset shows $S(T)$ for the same.

REFERENCES

1. “Crystal chemistry of High Tc superconducting Copper Oxides” by B. Raveau et al (Springer Verlag, 1991).
2. “Studies of high temperature superconductors” Volume 1-10 (1997), NOVA Science Publishers USA, edited by A.V. Narlikar.
3. A. Kebede, C-S. Jee, J. Schwegler, J.E. Crow, T. Mihalisin, G.H. Myer, R.E. Salomon, P. Schlottmann, M.V. Kuric, S.H. Bloom, and R.P. Guertin, Phys. Rev. B 40, 4453(1989).
4. E.M. McCarron III, M.K. Crawford and J.B. Parise J. Solid State Chem. 78 (1989) 192.
5. P. Starowicz, J. Sokolowski, M. Balanda and A. Szytula. Physica C 363 (2001) 80.
6. A. Manthiram, S.-J. Lee and J.B. Goodenough. J. Solid State Chem. 73 (1988) 278.
7. V.P.S. Awana, and A.V. Narlikar, Phys. Rev. B 49, 6353 (1994).
8. E. Suard, A. Maignan, V. Caignaert, and B. Raveau, Physica C 200, 43 (1992).
9. K.M. Pansuria, U.S. Joshi, D.G. Kuberkar, G.J. Baldha, and R.G. Kulkarni, Solid State Communications 98, 1095 (1996).
10. M.H. Whangbo and C.C. Torardi, Science 249, 1143 (1990).
11. J.R. Cooper, B. Alavi, L.W. Zhou, W.P. Beyermann, and G. Gruner, Phys. Rev. B 35, 8794 (1987).
12. J.L. Tallon, C. Bernhard, H. Shaked, R.L. Hitterman, and J.D. Jorgensen, Phys. Rev. B 51, 12911 (1995).

Fig. 1 Ansari et al. (HU-10),

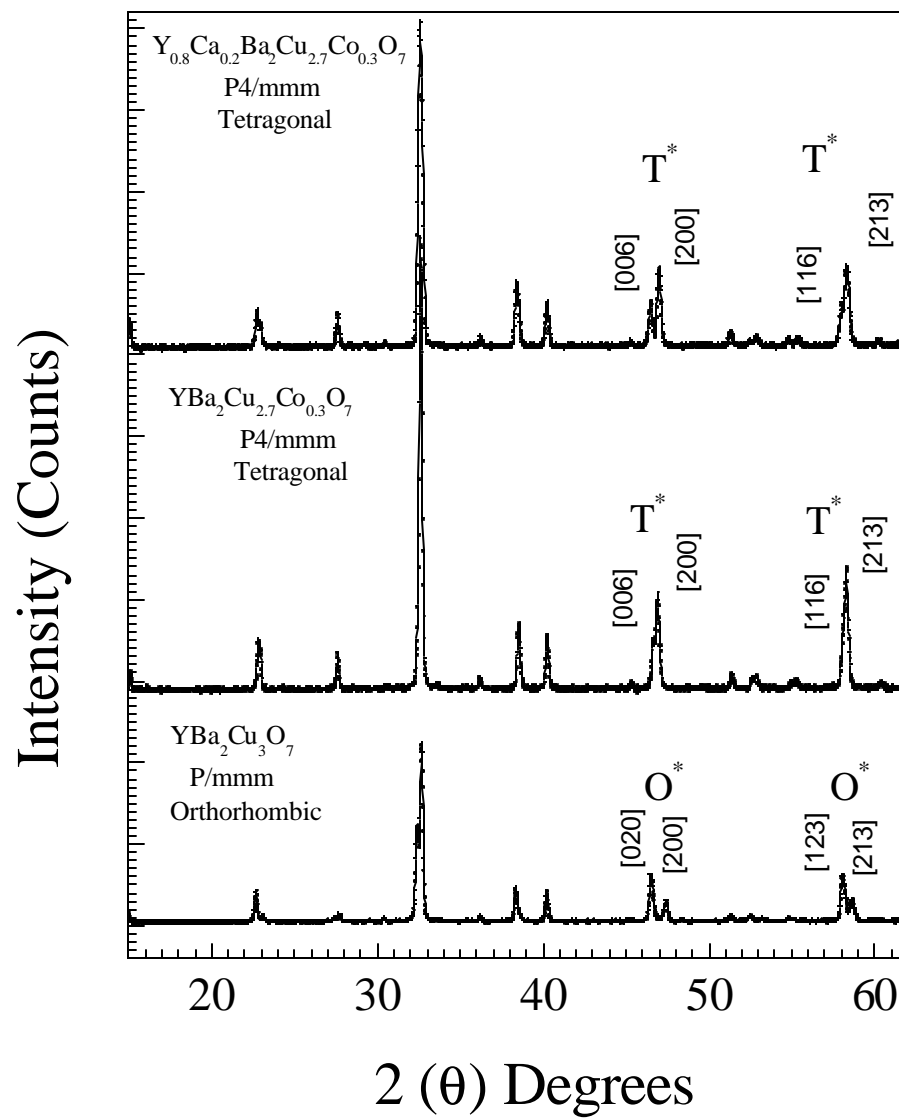


Fig. 2 Ansari et al. (HU-10)

