

Achieving fast oxygen diffusion in perovskites by cation ordering

A. A. Taskin, A. N. Lavrov,^y and Yoichi Ando

Central Research Institute of Electric Power Industry, Komae, Tokyo 201-8511, Japan

The oxygen-exchange behavior has been studied in half-doped manganese and cobalt perovskite oxides. We have found that the oxygen diffusivity in $Gd_{0.5}Ba_{0.5}MnO_3$ can be enhanced by orders of magnitude by inducing crystallographic ordering among lanthanide and alkali-earth ions in the A-site sublattice. Transformation of a simple cubic perovskite, with randomly occupied A-sites, into a layered crystal $GdBaMn_2O_{5+x}$ (or isostructural $GdBaCo_2O_{5+x}$ for cobalt oxide) with alternating lanthanide and alkali-earth planes reduces the oxygen bonding strength and provides disorder-free channels for ion motion, pointing to an efficient way to design new ionic conductors.

PACS numbers: 66.30.Hs, 82.47.Ed

Oxygen ion conductors – solids exhibiting very fast oxygen diffusion – constitute the basis for such emerging technologies as the membrane oxygen separation or the solid-oxide fuel cell (SOFC) power generation.^{1,2} These technologies offer enormous economical and ecological benefits provided high performance materials can be developed: The scientific challenge is to design materials demonstrating high oxygen diffusivity at low enough temperature.

In general, a crystal must meet two fundamental requirements to be a good oxygen-ion conductor: (i) it must contain a lot of vacancies in the oxygen sublattice, and (ii) the energy barrier for oxygen migration from one site to another must be fairly small, typically less than 1 eV. Only a few types of oxides, and perovskites ABO_3 (A is a rare-earth or an alkali-earth element and B is typically a transition metal) among them, have been found to possess these features.^{1,2,3,4,5,6,7,8} Doped perovskites, which possess a high electronic conductivity in addition to the ionic one, are considered for using as electrodes in SOFC and as oxygen-selective membranes; for example, strontium-doped lanthanum manganese oxide, $La_{1-y}Sr_yMnO_3$, is a standard cathode material for SOFC applications operating at temperatures around 1000 °C.⁶ Recently, serious efforts are made to reduce the operation temperature of SOFC, and for the operation at 700–800 °C, strontium-doped lanthanum cobalt oxide, $La_{1-y}Sr_yCoO_3$, is considered to be the most promising cathode material.^{7,8} The performance of perovskite oxides has been already optimized as much as possible mostly by means of various ion substitutions in both A and B sublattices,^{6,7,8,9} but they still fail to operate at low enough temperatures – 500 °C required for successful commercialization of the fuel cell technology.

In this Letter, we show that the oxygen-ion diffusion in a doped perovskite can be enhanced by orders of magnitude if a simple cubic crystal [schematically shown in Fig. 1 (a)] transforms into a layered compound with ordered lanthanide and alkali-earth ions [Fig. 1 (b)], which reduces the oxygen bonding strength and provides disorder-free channels for ion motion.

Recently, the A-site-ordered manganese and cobalt perovskite oxides have been synthesized by several

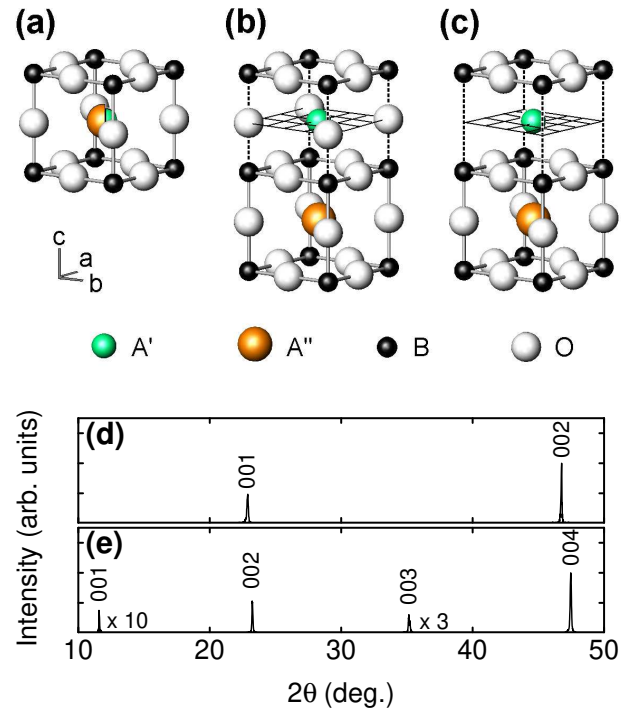


FIG. 1: Ordering of lanthanide A'^{3+} and alkali-earth A''^{2+} ions in the A-site sublattice of half-doped perovskites. (a) A simple cubic perovskite $A'_{0.5}A''_{0.5}BO_3$ with random occupation of A-sites is transformed into (b) a layered crystal $A'A''B_2O_6$ by doubling the unit cell, provided the difference in ionic radii of A' and A'' ions is sufficiently large. (c) Oxygen atoms can be partially or completely removed from lanthanide planes in $A'A''B_2O_{5+x}$, providing a variability of the oxygen content, $0 < x < 1$. (d, e) X-ray Bragg's (00L) peaks obtained for cubic $Gd_{0.5}Ba_{0.5}MnO_3$ (d) and layered $GdBaMn_2O_{5+x}$ (e), which demonstrate the doubling of the unit cell along the c axis with the cation ordering (for convenience, the peak intensity is multiplied by a factor indicated near each peak).

groups.^{10,11} We have succeeded in growing high-quality single crystals of these compounds by the coating-zone (FZ) technique.¹² What makes these layered oxides promising for searching a high oxygen mobility is their remarkable variability of oxygen content: Oxygen atoms can be partially or even completely removed from the

lanthanide planes [as shown in Fig. 1 (c)], creating a lot of vacant sites in the crystal lattice. While polycrystalline air-sintered samples of $\text{GdBaMn}_{2.5+x}\text{O}_{5+x}$ adopt the cubic perovskite crystal structure (and thus should be expressed as $\text{Gd}_{0.5}\text{Ba}_{0.5}\text{MnO}_3$), the ordered phase can be grown under strongly reducing atmosphere of pure argon. The fortunate opportunity to obtain both layered $\text{GdBaMn}_{2.5+x}\text{O}_{5+x}$ and cubic $\text{Gd}_{0.5}\text{Ba}_{0.5}\text{MnO}_3$ phases allows direct comparison of the oxygen behaviour in materials with and without the A-site sublattice ordering. For the cobalt oxide, on the other hand, only the ordered $\text{GdBaCoO}_{2.5+x}$ phase can be obtained even at high oxygen pressure.

The homogeneity and cation stoichiometry of our crystals are confirmed by the electron-probe microanalysis (EPMA) and the inductively-coupled plasma (ICP) spectroscopy. Ordering of the Gd and Ba ions into consecutive (001) layers is confirmed by the X-ray diffraction measurements [Fig. 1(d) and (e)], which clearly demonstrate the doubling of the unit cell along the c axis for $\text{GdBaMn}_{2.5+x}\text{O}_{5+x}$ single crystals. The behaviour of dc resistivity shows that both $\text{GdBaMn}_{2.5+x}\text{O}_{5+x}$ and $\text{GdBaCoO}_{2.5+x}\text{O}_{5+x}$ undergo an insulator-to-metal transition upon increasing temperature; at high temperatures, they possess a metallic conductivity of the order of 10^2 and 10^3 S/cm, respectively. These values are much larger than any ionic conductivity available in solids, indicating that these compounds should be mixed ionic and electronic conductors (MIECs).

It is well known that in MIECs, the ionic conductivity σ_i , which is typically much smaller than the electronic conductivity σ_e , may be determined from diffusion measurements.^{13,14} In oxides with variable oxygen stoichiometry, like $\text{GdBaMn}_{2.5+x}\text{O}_{5+x}$ and $\text{GdBaCoO}_{2.5+x}\text{O}_{5+x}$, a sharp change in conditions (oxygen pressure or temperature) results in a gradual transition into a new equilibrium state that differs in oxygen content; this means that the oxygen concentration in crystal samples changes with time, which can be measured as a weight change. The observed relaxation time depends on two processes: the oxygen exchange at the interface between the gas and the solid, and the oxygen bulk diffusion.^{13,14} In the present study, both the surface exchange coefficient K and the chemical diffusion coefficient D are obtained by examining the weight change of crystals as a function of time.

The oxygen-exchange behaviour in cubic manganese oxide and its layered counterpart, studied in polycrystalline samples with comparable morphology, is shown in Fig. 2. There are two clear consequences of the A-site ordering: First, as shown in Fig. 2 (a), the change in the equilibrium oxygen content x_{eq} upon decreasing oxygen pressure from 1 to 10^{-5} bar at 700 C is much more pronounced in the layered oxide. Thus, it is much easier to remove oxygen from the layered $\text{GdBaMn}_{2.5+x}\text{O}_{5+x}$ than from cubic $\text{Gd}_{0.5}\text{Ba}_{0.5}\text{MnO}_3$. Second, and more important, is a huge difference in the rate of the oxygen uptake. Figure 2 (b) shows a normalized change in the oxygen content $\Delta x_{\text{norm}} = (x - x_0)/(x_{\text{eq}} - x_0)$ (x_0 is the initial oxygen

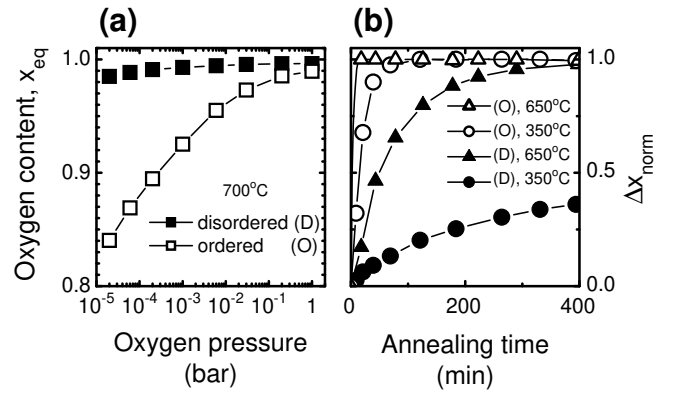


FIG. 2: Comparison of oxygen behaviour in cubic $\text{Gd}_{0.5}\text{Ba}_{0.5}\text{MnO}_3$ with disordered A-site sublattice (i.e. randomly distributed Gd^{3+} and Ba^{2+} ions) and layered $\text{GdBaMn}_{2.5+x}\text{O}_{5+x}$. (a) Equilibrium oxygen content x_{eq} (for $\text{Gd}_{0.5}\text{Ba}_{0.5}\text{MnO}_3$, $x = 1-2$) measured at 700 C as a function of the oxygen partial pressure. (b) Normalized change in the oxygen content with time during annealing in the oxygen gas flow at 350 C and 650 C.

content and x_{eq} is the equilibrium one), measured during the annealing in the oxygen gas flow at 350 C and 650 C, for samples with ordered (open symbols) and disordered (filled symbols) A-site sublattice. The relaxation time is about two orders of magnitude smaller in the layered oxide. Surprisingly, the oxygen accumulation in the layered $\text{GdBaMn}_{2.5+x}\text{O}_{5+x}$ even at 350 C turns out to be faster than that in the cubic $\text{Gd}_{0.5}\text{Ba}_{0.5}\text{MnO}_3$ at 650 C.

Having established that the ordering of the A-site sublattice into a layered structure significantly enhances the oxygen relaxation rate, we now turn to a more quantitative analysis of the oxygen diffusion. For that purpose, however, large single-crystal samples of $\text{GdBaMn}_{2.5+x}\text{O}_{5+x}$ appear to be unsuitable; depending on x , the orthorhombicity (b/a) in $\text{GdBaMn}_{2.5+x}\text{O}_{5+x}$ varies from 0 up to 7%, and the enormous strains emerging upon the oxygen intercalation into large single crystals result in the formation of a regular array of cracks on the crystal surface. We therefore focus our quantitative analysis on another layered material $\text{GdBaCoO}_{2.5+x}\text{O}_{5+x}$, which does not have such a problem. To separate the surface-exchange and bulk-diffusion contributions to the overall oxygen exchange rate, we study the oxygen kinetics in $\text{GdBaCoO}_{2.5+x}\text{O}_{5+x}$ single crystals of different size: the oxygen kinetics is mostly limited by the surface exchange for small-size crystals, while for large-size crystals it is mostly limited by the bulk diffusion. The change in weight with time in a rectangular-shape sample of a given size has an analytical solution,¹⁴ which is a function of both the chemical diffusion coefficient D and the surface exchange coefficient K . Figure 3 shows the experimental data (symbols) and analytical fits (solid lines) of the change in the oxygen content with time for $\text{GdBaCoO}_{2.5+x}\text{O}_{5+x}$ single-crystal samples of different sizes upon annealing in the oxygen flow at 350 C. From this set of data, the parameters D and

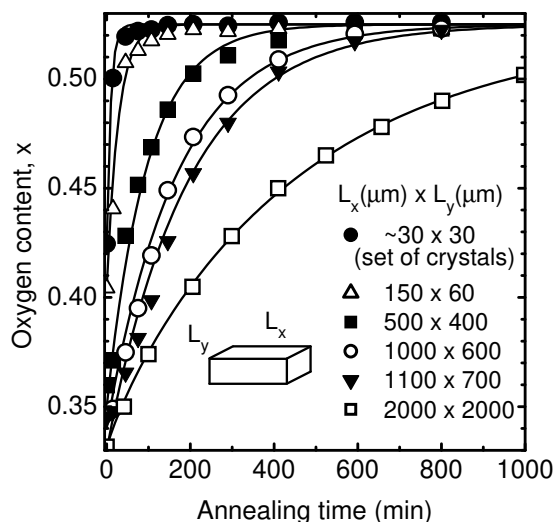


FIG. 3: Time dependence of the oxygen content in rectangular-shaped $\text{GdBaCo}_2\text{O}_{5+x}$ single crystals of different sizes while annealing in the oxygen flow at 350 °C (symbols). Solid lines represent theoretical curves with a unique pair of parameters $D = 3 \cdot 10^{-7} \text{ cm}^2/\text{s}$ and $K = 2 \cdot 10^{-6} \text{ cm/s}$ for the whole set of experimental data.

K can be uniquely determined to be $D = 3 \cdot 10^{-7} \text{ cm}^2/\text{s}$ and $K = 2 \cdot 10^{-6} \text{ cm/s}$. We note that the oxygen kinetics does not show any detectable difference upon varying the sample size along the c axis in the range of 30–500 μm , implying an essentially two-dimensional character of the oxygen diffusion in this layered material.

Using the technique described above, we have determined the parameters D and K for the temperature range of 250–600 °C at 1 bar oxygen pressure [Fig. 4(a)]. These data are well fitted by the activation laws $D (\text{cm}^2/\text{s}) = 0.15 \exp(-0.7 \text{ eV}/kT)$ and $K (\text{cm/s}) = 15 \exp(-0.85 \text{ eV}/kT)$, revealing quite low activation energies for both processes. As a result, the oxygen diffusion in $\text{GdBaCo}_2\text{O}_{5+x}$ becomes very fast already at rather low temperatures, exceeding $10^{-5} \text{ cm}^2/\text{s}$ at 600 °C. To appreciate the true merit of this high oxygen diffusivity in $\text{GdBaCo}_2\text{O}_{5+x}$, it is worth estimating the ionic conductivity, which is uniquely determined by the self-diffusion (or trace-diffusion) coefficient D .¹⁵ One should keep in mind that the chemical diffusion coefficient D , obtained in our experiments, is related to D through a so-called thermodynamic factor [$(\partial \ln P / \partial \ln x) = 2$], $D = D$, reflecting the fact that the true driving force for diffusion is a gradient in the chemical potential but not a gradient in the oxygen concentration.¹⁵ In $\text{GdBaCo}_2\text{O}_{5+x}$, it turns out to be quite low and does

not exceed 10 in the whole temperature and oxygen-pressure range studied [Fig. 4(b)]. Thus, the ionic conductivity of 0.01 S/cm, which is considered as a criterion for SOFCs to be valuable¹, can be achieved in $\text{GdBaCo}_2\text{O}_{5+x}$ already at 500 °C. Clearly, there should still be a possibility for further improvement of properties in ordered perovskite oxides, and the most obvious way is a substitution of different rare earths for Gd.

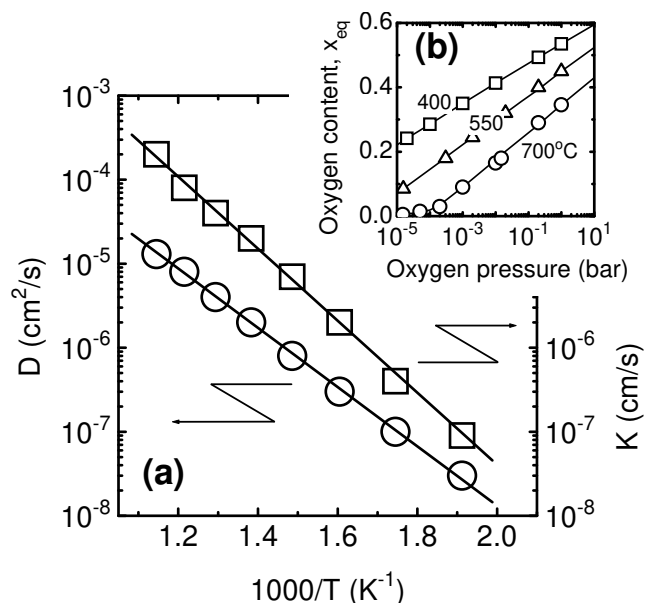


FIG. 4: Oxygen bulk diffusion and surface oxygen exchange in $\text{GdBaCo}_2\text{O}_{5+x}$. (a) Temperature dependences of the diffusion coefficient $D(T)$ and the surface exchange coefficient $K(T)$, obtained from the oxygen kinetics experiments similar to those shown in Fig. 3. The inset (b) shows the dependence of the equilibrium oxygen content x_{eq} on the oxygen pressure P for several temperatures.

In conclusion, we have found a remarkable enhancement of the oxygen diffusivity in ordered perovskite oxides as exemplified in $\text{GdBaMn}_2\text{O}_{5+x}$ and $\text{GdBaCo}_2\text{O}_{5+x}$, which opens a possibility to develop a new class of materials suitable for applications that require a fast oxygen transport in the intermediate temperature range. The improvement of the oxygen transport properties induced by the cation ordering in half-doped perovskites provides a good example of how the formation of a layered crystal structure, with disorder-free channels for ions migration and with a weakened bonding strength of oxygen, can significantly facilitate the oxygen motion in the crystal lattice.

kotaskin@criepidenken.or.jp

^y Present address: Institute of Inorganic Chemistry, Novosibirsk 630090, Russia

¹ B. C. H. Steele and A. Heinzl, Nature 414, 345 (2001).

² N. Q. Minh and T. Takahashi, Science and Technology of Ceramic Fuel Cells (Elsevier, Amsterdam, 1995).

³ P. Lacorre, F. Goutenoire, O. Bohnke, R. Retoux, and Y. Laligant, Nature 404, 856 (2000).

- ⁴ J.B. Goodenough, *Annu. Rev. Mater. Res.* 33, 91 (2003).
- ⁵ Z. Shao and S.M. Haile, *Nature* 431, 170 (2004).
- ⁶ S.J. Skinner, *Int. J. Inorg. Mater.* 3, 113 (2001).
- ⁷ R.A. DeSouza and J.A. Kliner, *Solid State Ionics* 106, 175 (1998).
- ⁸ J.A. Kliner, *Solid State Ionics* 129, 13 (2000).
- ⁹ Y.L. Yang, A.J. Jacobson, C.L. Chen, G.P. Luo, K.D. Ross, and C.W. Chu, *Appl. Phys. Lett.*, 79, 776 (2001).
- ¹⁰ F. Millange, V. Caignaert, B. Domenges, B. Raveau, and E. Suard, *Chem. Mater.* 10, 1974 (1998).
- ¹¹ A. Maignan, C. Martin, D. Pelloquin, N. Nguyen, and B. Raveau, *J. Solid State Chem.* 142, 247 (1999).
- ¹² A.A. Taskin, A.N. Lavrov, and Y. Ando, *Phys. Rev. Lett.* 90, 227201 (2003).
- ¹³ I. Yasuda and M. Hishinuma, *J. Solid State Chem.* 123, 382 (1996).
- ¹⁴ J.A. Lane and J.A. Kliner, *Solid State Ionics* 136–137, 997 (2000).
- ¹⁵ A. Van der Ven, G. Ceder, M. Asta, and P.D. Tepesch, *Phys. Rev. B* 64, 184307 (2001).