

Magnetism in Exact Exchange Density Functional Theory

S. Sharma, J. K. Dewhurst, S. A. Sagmeister, and C. Ambrosch-Draxl
 Institut für Physik, Karl-Franzens-Universität Graz,
 Universitätsplatz 5, A-8010 Graz, Austria.

C. Persson
 Department of Materials Science and Engineering,
 Royal Institute of Technology, SE-100 44 Stockholm, Sweden

S. Shallcross
 Department of Physics and Measurement Technology,
 University of Linköping, SE-581 83 Linköping, Sweden.

L. Nordström
 Department of Physics, Uppsala University,
 Box 530, 751 21 Uppsala, Sweden.
 (Dated: February 20, 2002)

The magnetic properties of the intermetallic compound FeAl are investigated using exact exchange density functional theory. This is implemented within a state of the art all-electron full potential method. We find that FeAl is magnetic with a moment of $0.70 \mu_B$, close to the LSDA result of $0.69 \mu_B$. A comparison with the non-magnetic density of states with experimental negative binding energy result shows a much better agreement than any previous calculations. We attribute this to the fine details of the exchange field, in particular its asymmetry, which is captured very well with the orbital dependent exchange potential.

PACS numbers: 75.10.-b, 71.10.-w

INTRODUCTION

The intermetallic compound FeAl presents an interesting system where one has both a complex interplay between structure and magnetism, and a possible failure of the Local Spin Density Approximation (LSDA) to adequately account for the electronic structure [1, 2, 3]. Disentangling these two strands poses a severe challenge for theory. The controversy surrounding this material turns on the issue of whether completely ordered FeAl is a magnetic or non-magnetic intermetallic, and whether this question is at all relevant to the experimental picture.

Experimentally, FeAl obeys an extended Curie-Weiss law $(\chi - \chi_0)^{-1} = C(T - T_C)$ down to low temperatures, the signature of a paramagnet with finite (local) moments. Mössbauer studies [3] show that it is only the antisite Fe atoms (Fe atoms on the Al sublattice) which contribute to this behaviour, the Fe sublattice being non-magnetic. The rather weak ordering in FeAl means both that a range of defects are thermodynamically stable, and that any crystal of FeAl will have some concentration of these defects. Thus it appears that the question of whether completely ordered FeAl is magnetic or not cannot be answered by experiment.

Nevertheless, the question of the magnetic state of completely ordered FeAl has attracted a lot of attention [1, 2, 3, 4, 5, 6]. This is based on the speculation that it should be non-magnetic [4], and the fact that

LSDA calculations find it to be magnetic with a moment of around $0.69 \mu_B$. The foundation of this speculation appears to be simply that since the magnetism is carried by defects, taking these defects out will leave behind the non-magnetic FeAl sublattice, hence non-magnetic FeAl. However, this excludes that an Fe antisite-Fe sublattice interaction may be responsible for making the Fe sublattice non-magnetic.

The first attempt to go beyond the LSDA was undertaken by Mohn et. al who employed the LDA+U method. The usefulness of this approach was suggested by the fact that both the e_g and t_{2g} bands are rather flat, and hence an improved scheme for the correlation is needed. Although these authors found a non-magnetic solution, a more recent LDA+U calculation [1] disagrees with this result and finds, again, FeAl to be magnetic. The latter work instead suggested that the magnetism may be suppressed by critical spin fluctuations, as is seen for example in the intermetallic compound Ni_2Ga [7]. The dynamical version of LDA+U, the dynamical mean field theory (DMFT) [1], does include some spin-fluctuations and using this it was found that FeAl is non-magnetic.

In complete contrast to these approaches Smimov et. al [2] instead attempted a more realistic modeling of the experimental defect structure within the LSDA. To achieve this they employed the Coherent Potential Approximation (CPA), which allows for the treatment of both structural and magnetic disorder. With an Fe anti-

site concentration similar to that deduced experimentally they found that a spin disordered local moment (DLM) solution is then energetically favoured. Crucially, in this state the Fe sublattice is non-magnetic, with the magnetism carried only by the antisite atoms, exactly as seen in experiment.

Although it is clear that the complex defect structure must be taken into account in order to model correctly the experimental reality, one can note that it is not clear that the magnetism of FeAl is correctly described by the DLM state. Evidence for this comes from the fact that Fe clusters in FeAl order with a non-collinear structure. Thus the Fe antisite-Fe sublattice interaction is not ferromagnetic, and hence the DLM state should be lower in energy. This does not, however, rule out the possibility that some complex non-collinear structure is even lower in energy, and that in this state the Fe lattice is again magnetic.

In this situation, one might wish for a more experimentally rigorous comparison than simply whether FeAl is non-magnetic or not. Unfortunately, and perhaps surprisingly, there is a lack of experimental spectroscopic data for this system. To the best of our knowledge, only one experimental article on this aspect of FeAl is to be found in the literature [5].

In this work we deploy the EXact eXchange (EXX) method, implemented within an all-electron full-potential code EXITING [8], to study both the magnetism and spectroscopic properties of FeAl.

METHOD OF CALCULATION

Recently we have developed EXX equations suitable for non-collinear magnets [9]. Within this formalism the exchange term is treated exactly within Kohn-Sham density functional theory (KS-DFT). The resulting exchange potential is self-interaction free and depends explicitly on the KS orbitals, which are two component Pauli spinors. This formalism leads to coupled integral equations for the exchange potential and magnetic field. In order to avoid an expensive set of fixed spin moment calculations this method is needed even for the study of collinear systems [9]. In the present work we use an all-electron full-potential linearized augmented plane-wave (FP-LAPW) method for the self-consistent EXX calculations. In this scheme, the unit cell is divided into non-overlapping muffin-tin spheres around the atomic nuclei and a remaining interstitial region. The corresponding wave functions are expressed as linear combinations of atomic like functions inside the spheres and plane waves in the interstitial region. The calculations used a $RK_{\text{max}} = 7$ cutoff criterion for the number of plane waves in the basis. The wave function is expanded up to $l = 10$ and the potentials up to $l = 6$. All calculations are done for the experimental lattice parameter of 5.496 au. We have

TABLE I: Magnetic moment of FeAl in Bohr magneton. The FP-EXX and FP-LSDA are our results. The LDA+U results from Refs. 4 and 1 are for $U = 5\text{eV}$. The DMFT results are from Ref. 1 and use $U = 2\text{eV}$.

Expt.	FP-EXX	FP-LSDA	LDA+U [4]	LDA+U [1]	DMFT
?	0.70	0.69	0	0.70	0

used a mesh of 64 k-points in the irreducible part of the Brillouin zone.

RESULTS

The EXX calculations find a magnetic ground state with a moment of $0.70 \mu_B$, very close to the LSDA value $0.69 \mu_B$. It would be interesting at this point to compare the density of states (DOS) for FeAl with the experiments. A comparison between the magnetic DOS and the experimental negative binding energy results of Shabanova et. al will not be meaningful, since, as has been discussed above, the Fe sublattice is non-magnetic in experiment. However, since only 2%–3% of the Fe atoms in the FeAl sample will actually be high moment antisite defect atoms, their contribution to the binding energy signal will be quite small. Hence a rather good approximation to model the experimental results will be to simply make the comparison with non-magnetic FeAl. In principle, of course, one would wish to include the complex defect structure within the EXX approach, however, since this requires either very large supercells or the use of the CPA, this is not feasible at present.

In the lower panel of Fig. 1 we show the results of an EXX calculation of the DOS. A most remarkable feature can immediately be seen which is the shift downwards of the non-bonding t_{2g} states by almost 1.5 eV. This is quite different from the results obtained using the LDA+U [4] and the DMFT [1] methods. Like the LDA+U method we see a broadening of the d-band, in contrast to the DMFT density of states, where the d-band is narrowed by the mass renormalization effects. This spread of results by different methods makes a comparison with experiments most interesting. In the upper panel of Fig. 1 we show the LDA and EXX DOS, as well as that reported in Refs. 4 and 1. Note that for ease of comparison we have convolved our DOS with a Gaussian of width 0.5 eV. Clearly, the peak of the experimental DOS and that given by EXX are in much better agreement than any other method. A further interesting feature of the EXX DOS is a pronounced antibonding e_g peak at around 4 eV, a feature that should be detectable in inverse photoemission experiments.

This enhanced splitting of the t_{2g} and e_g manifolds over LSDA values is the result of the asymmetry in the EXX potential. This is demonstrated in Fig. 2 where the EXX

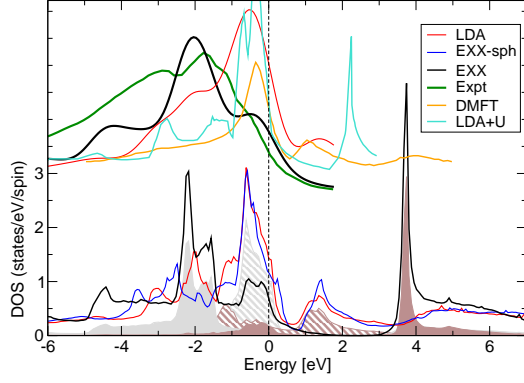



FIG. 1: Total density of states for FeAl. The LDA results are shown in red, EXX results with only $l=0$ part of potential in blue, and full potential EXX in black. The t_{2g} (gray) and e_g (brown) manifolds are shown with solid shading for EXX and hatched shading for LDA. At the top the green curve is the experimental negative binding energy from Ref. [5] alongside the theoretical Gaussian convolved DOS. The cyan curve is the data extracted from Ref. 4 and orange from Ref. 1.

exchange potential (black) along with the LDA exchange potential (red) are displayed. A qualitative difference between the two can be seen in that the EXX potential is strongly asymmetric around the Fe atoms. Looking at the potential along an Al-Fe-Fe path, indicated by the arrows in Fig. 2, one notes structures reflecting the existence of atomic shells. These features are a consequence of the natural orbital dependence of the EXX potential, but are completely absent in the LDA potential which is constructed from only local knowledge of the density. Dips in the EXX potential will mean an effective attractive force which will act to cause localization, the pronounced dip in the Fe-Fe direction, for example, is most likely responsible for the sharp e_g peak in the EXX DOS.

The importance of this asymmetry in the EXX potential may be gauged by retaining only the spherical part in the muffin-tin spheres during a self-consistent calculation. The resulting EXX potential (blue line, Fig. 2) then lacks the asymmetry of the full EXX potential, and the resulting DOS is much closer to that of the LDA, and in disagreement with experiment.

This agreement of the EXX DOS with experiment can be considered somewhat surprising in that previous EXX calculations have not found this to be so for the transition metals Fe, Co, and Ni. Here a quite striking disagreement with experiment, as well as the LSDA, was noted [10]. Although these calculations used the atomic sphere approximation, as well as an inaccurate formulation of EXX for magnetism, our results are qualitatively

FIG. 2: Upper image shows contour plots of the EXX (black) and LDA (red) exchange potential in the [110] plane over two unit cells with contour spacing 3.6 eV. In the lower graph, the same potentials are plotted along the line indicated in the upper graph, with the blue curve corresponding to the $l=0$ EXX. A non-spherical part is added to the EXX potentials to bring them into coincidence with the LDA potential.

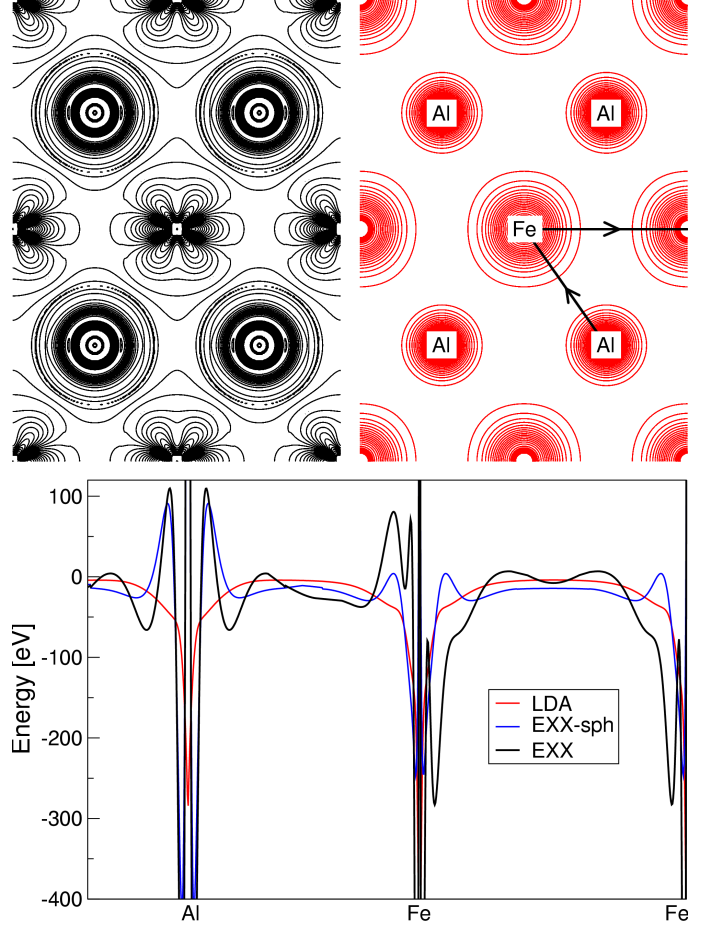

similar [9, 11]. One finds the splitting of the t_{2g} and e_g states for the partially occupied spin down channel is far too large, with the occupied spin up channel being pulled up to 3 eV below the Fermi level. One can speculate upon the reason for the good agreement between EXX and experimental DOS found in this work. Since one of the main effects of the missing correlation will be simply to screen the exchange field, one can note that the presence of Al atoms in this material leads to an effective screening by the delocalized sp Al states. The validity of this proposal will be investigated in a future work on screened EXX.

In conclusion, we find that FeAl prefers to be ferromagnetic in both EXX and LSDA calculations. However, the non-magnetic EXX DOS is in very good agreement with experiment, while the non-magnetic LSDA DOS is not.

Thus our calculations are in agreement with the suggestion of Smimov et al. that the non-magnetic state of the Fe sublattice results from the complex defect structure. However, it is also clear that the LSDA exchange and correlation is not sufficient to reproduce (or understand) all the properties of this interesting system.

Electronic address: sangeeta.sharma@uni-graz.at

- [1] A.G.Petukhov, I.I.Mazin, L.Chioncel, and A.I.Lichtenstein, Phys.Rev.B 67, 153106 (2003).
- [2] A.V.Smimov, W.A.Shelton, and D.D.Johnson, Phys.Rev.B 71, 064408 (2005).
- [3] J.Bogner, W.Steiner, M.Reissner, P.Mohn, P.Blaha, K.Schwarz, R.Krachler, H.Ipser, and B.Sepiol, Phys.Rev.B 58, 14922 (1998).
- [4] P.Mohn, C.Persson, P.Blaha, K.Schwarz, P.Novak, and H.Eschrig, Phys.Rev.Lett. 87, 196401 (2001).
- [5] I.N.Shabanova, V.I.Komilets, and N.S.Terebova, J.Electron Spectroscopy and Related Phenomena 114, 609 (2001).
- [6] D.A.Papaconstantopoulos and K.B.Hathaway, J.Appl.Phys. 87, 5872 (2000).
- [7] A.Aguayo, I.I.Mazin, and D.J.Singh, Phys.Rev.Lett. 92, 147201 (2004).
- [8] J.K.Dewhurst, S.Sharma, and C.Ambrosch-Draxl, EXCITING code developed under the Research and Training Network EXCITING funded by the EU, contract No. HPRN-CT-2002-00317 (2004), URL <http://www.exciting.physics.at>.
- [9] S.Sharma et al, cond-mat/0510800 (2005).
- [10] T.Kotani and H.Akai, Physica B 237, 332 (1997).
- [11] S.Sharma et al, preprint (2005).