

# Pressure effects on the superconducting properties of $\text{YBa}_2\text{Cu}_4\text{O}_8$

R. Khasanov,<sup>1,2,3</sup> T. Schneider,<sup>3</sup> and H. Keller<sup>3</sup>

<sup>1</sup> *Laboratory for Neutron Scattering, ETH Zürich and Paul Scherrer Institut, CH-5232 Villigen PSI, Switzerland*

<sup>2</sup> *DPMC, Université de Genève, 24 Quai Ernest-Ansermet, 1211 Genève 4, Switzerland*

<sup>3</sup> *Physik-Institut der Universität Zürich, Winterthurerstrasse 190, CH-8057, Zürich, Switzerland*

Measurements of the magnetization under high hydrostatic pressure (up to 10.2 kbar) in  $\text{YBa}_2\text{Cu}_4\text{O}_8$  were carried out. From the scaling analysis of the magnetization data the pressure induced shifts of the transition temperature  $T_c$ , the volume  $V$  and the anisotropy  $\gamma$  have been obtained. It was shown that the pressure induced relative shift of  $T_c$  mirrors essentially that of the anisotropy. This observation uncovers a novel generic property of anisotropic type II superconductors, that inexistent in the isotropic case.

PACS numbers: 74.72.Bk, 74.62.Fj, 74.25.Ha, 83.80.Fg

In the cuprate high-temperature superconductors (HTS), the canonical change in  $T_c$  with pressure is that it first increases, passes through a maximum value at some critical pressure, and then decreases.<sup>1,2</sup> It has been argued that there are at least two effects determining the total pressure dependence of  $T_c$ , an intrinsic effect and the one that arises from the pressure-induced changes in the charge carrier concentration.<sup>1,2</sup> However, there are effects which make the discrimination between these contributions difficult. In most HTS the application of pressure doesn't simply compress the lattice, but also prompts mobile oxygen defects to assume a greater degree of local order.<sup>3</sup> This leads to relaxation effects which are both temperature and pressure dependent. An exception is the double-chain compound  $\text{YBa}_2\text{Cu}_4\text{O}_8$  with a fixed oxygen stoichiometry. Bucher *et al.* [4] found that in this compound  $T_c$  increases under hydrostatic pressure with the rate  $dT_c/dp \simeq 5.5$  K/GPa. Subsequent studies revealed that with increasing pressure  $T_c$  passes through a maximum around 9 GPa and then decreases.<sup>1,2,3</sup> Furthermore, measurements of the in-plane penetration depth  $\lambda_{ab}$  of  $\text{YBa}_2\text{Cu}_4\text{O}_8$  revealed pressure induced changes which cannot be simply attributed to the pressure changes of  $T_c$ .<sup>5,6</sup> Since in cuprate high-temperature superconductors, including  $\text{YBa}_2\text{Cu}_4\text{O}_8$ , the critical regime where thermal critical fluctuations dominate is experimentally accessible, various critical properties are not independent but related by universal relations.<sup>7,8,9,10,11,12,13,14</sup> Accordingly, the isotope or pressure effects on these quantities are related as well.<sup>11,14</sup> Here we explore the universal relationship between the pressure effects on transition temperature  $T_c$ , volume  $V$  and anisotropy  $\gamma$  emerging from the pressure induced changes of the magnetization near  $T_c$ . It is shown that in the underdoped  $\text{YBa}_2\text{Cu}_4\text{O}_8$  the pressure effect on  $T_c$  mirrors essentially that on the anisotropy. This uncovers a novel generic property of anisotropic type II superconductors, inexistent in the isotropic case.

The polycrystalline  $\text{YBa}_2\text{Cu}_4\text{O}_8$  samples were synthesized by solid-state reactions using high-purity  $\text{Y}_2\text{O}_3$ ,  $\text{BaCO}_3$  and  $\text{CuO}$ .<sup>5</sup> The hydrostatic pressure was gen-

erated in a copper-beryllium piston cylinder clamp that was especially designed for magnetization measurements under pressure.<sup>15</sup> The sample was thoroughly mixed with Fluorint FC77 (pressure transmitting medium) with a sample to liquid volume ratio of approximately 1/6. The pressure was measured in situ by monitoring the  $T_c$  shift of the small piece of In [ $T_c(p=0) \simeq 3.4$  K] included in the pressure cell. The field-cooled magnetization measurements were performed with a Quantum Design SQUID magnetometer at temperatures ranging from 2 to 100 K. In Fig. 1(a) we displayed the field-cooled (0.5 mT) magnetization  $M$  of a  $\text{YBa}_2\text{Cu}_4\text{O}_8$  powder sample *vs.*  $T$  near  $T_c$  for various applied hydrostatic pressures (0.0 kbar, 2.67 kbar, 4.29 kbar, 7.52 kbar, and 10.2 kbar). To identify the temperature regime where critical fluctuations play an essential role it is instructive to consider the behavior of  $dM/dT$  *vs.*  $T$  displayed in Fig. 1(b). With decreasing temperature  $dM/dT$  is seen to raise below the transition temperature and after passing a maximum value it decreases. This behavior contradicts the mean-field behavior where  $dM/dT$  below  $T_c$  adopts a constant value.<sup>16</sup> It implies that the fluctuation dominated regime is accessible and attained. This calls for an analysis beyond the mean-field approximation as outlined below.

The detailed description of the scaling analysis adopted for magnetization changes caused by isotope substitution or applying pressure can be found in Refs. 17 and 18. Briefly, the basic principles of the analysis can be summarized as follows. When three-dimensional (3D) Gaussian or 3D-XY thermal fluctuations dominate, the combination  $m(T, \delta, H) / (\gamma \epsilon^{3/2}(\delta) T \sqrt{H})$  adopts at  $T_c$  a fixed value<sup>8,9,10,12</sup>

$$\frac{m(T_c)}{T_c [\gamma \epsilon^{3/2}(\gamma, \delta)]_{T_c} \sqrt{H}} = -\frac{k_B C}{\Phi_0^{3/2}}, \quad (1)$$

where  $m = M/V$  is the magnetization per unit volume,  $C$  a constant adopting for Gaussian and 3D-XY fluctuations distinct universal values. Furthermore,  $\epsilon(\delta) = (\cos^2(\delta) + \sin^2(\delta)/\gamma^2)^{1/2}$ , where  $\delta$  is the angle between the applied magnetic field  $H$  and the  $c$ -axis,  $\Phi_0$  the flux

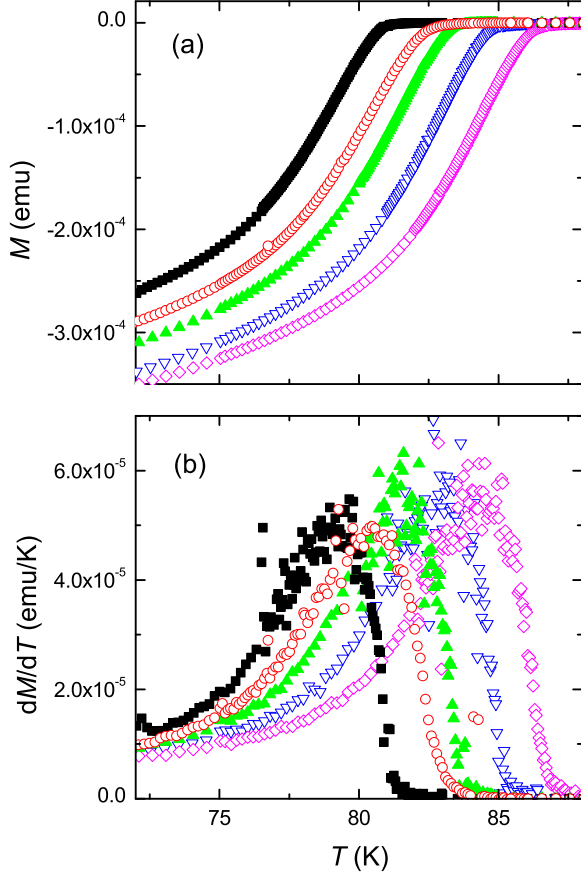


FIG. 1: (a) Field-cooled (0.5mT) magnetization of a  $\text{YBa}_2\text{Cu}_4\text{O}_8$  powder sample *vs.*  $T$  near  $T_c$  for various applied hydrostatic pressures (from the left to the right) 0.0 kbar, 2.67 kbar, 4.29 kbar, 7.52 kbar, and 10.2 kbar. (b)  $dM/dT$  *vs.*  $T$  for the data shown in Fig. 1(a)

quantum, and  $k_B$  Boltzmann's constant. In powder samples this relation reduces to

$$\frac{m(T_c)}{T_c \sqrt{H} f(\gamma(T_c))} = -\frac{k_B C}{\Phi_0^{3/2}}, \quad f(\gamma(T_c)) = \left[ \gamma \left\langle \epsilon^{3/2}(\gamma, \delta) \right\rangle \right]_{T_c}. \quad (2)$$

As the pressure effect on the magnetization at fixed magnetic field is concerned it implies that the relative shifts of the magnetization  $M$ , volume  $V$ , magnetization per unit volume  $m$ , anisotropy  $\gamma$  and  $T_c$  are not independent but close to  $T_c$  related by

$$\frac{\Delta M}{M} = \frac{\Delta V}{V} + \frac{\Delta T_c}{T_c} + \frac{\Delta f}{f}. \quad (3)$$

For  $\text{YBa}_2\text{Cu}_4\text{O}_8$ , where  $\gamma \gg 1$  (see *e.g.* Ref. 19) it

reduces to

$$\frac{\Delta M}{M} = \frac{\Delta V}{V} + \frac{\Delta T_c}{T_c} + \frac{\Delta \gamma}{\gamma} \quad (4)$$

On that condition it is impossible to extract these changes from the temperature dependence of the magnetization. However, supposing that close to criticality the magnetization data scale within experimental error as

$${}^{p=0}M(T) = {}^pM(aT), \quad (5)$$

the universal relation (4) reduces to

$$\frac{\Delta T_c}{T_c} = -\frac{\Delta V}{V} - \frac{\Delta \gamma}{\gamma} = \frac{T_c(p)}{T_c(0)} - 1 = \frac{1}{a} - 1. \quad (6)$$

In Fig. 2 we displayed the magnetization data rescaled according to Eq.(5). Near  $T_c$  the pressure induced changes in  $M(aT)$  is negligibly small so that Eqs. (5) and (6) can be applied within experimental error.

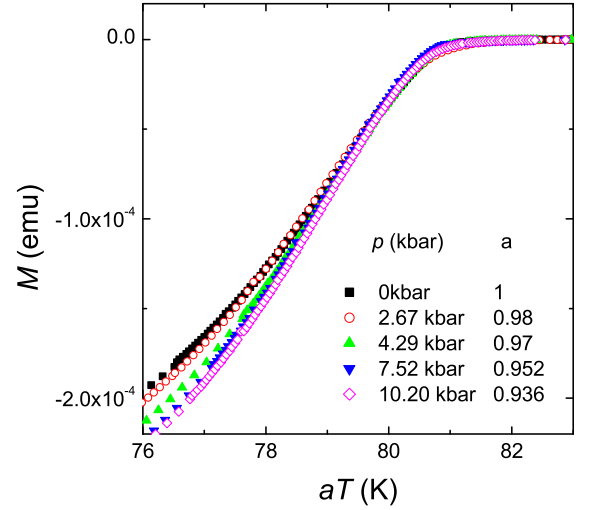


FIG. 2: Magnetization data rescaled according to  ${}^{p=0}M(T) = {}^pM(aT)$  [Eq.(5)].

Since  $a$  is less than one and decreases with increasing pressure the transition temperature increases in the pressure range considered here. Given then the bulk modulus  $B = 1174$  kbar (Ref. 4) for the pressure dependence of the relative volume change we obtain the expression

$$\frac{\Delta V}{V} = -\frac{p(\text{kbar})}{1174}, \quad (7)$$

and with Eq.(6) the estimates for the pressure induced changes of the anisotropy listed in Table I. It is readily

TABLE I: Estimates for the pressure induced relative change of volume  $V$ , transition temperature  $T_c$  and anisotropy  $\gamma$  derived from the data shown in Fig. 2 with the aid of Eqs.(5), (6) and (7).  $T_c$  and  $\lambda_{ab0}^{-2}$  at  $p = 0, 4.29, 7.52$ , and  $10.2$  kbar taken from Khasanov *et al.* Ref. 5.  $T_c$  and  $\lambda_{ab0}^{-2}$  at  $p = 1.2$  and  $2.67$  kbar were obtained from the linear interpolation of  $T_c(p)$  and  $\lambda_{ab0}^{-2}(p)$  data from Ref. 5.  $\Delta\xi_{c0}/\xi_{c0}$  follows from Eq.(9) and  $\Delta\xi_{ab0}/\xi_{ab0}$  from relation (10). Hereafter the relative pressure shift of the physical quantity  $X$  is determined as  $\Delta X(p)/X(0) = [X(p) - X(0)]/X(0)$ .

| $p$ (kbar) | $\Delta V/V$ | $a$   | $\Delta T_c/T_c$ | $\Delta\gamma/\gamma$ | $T_c(K)$ | $\lambda_{ab0}^{-2}(\mu m^{-2})$ | $\Delta\xi_{c0}/\xi_{c0}$ | $\Delta\xi_{ab0}/\xi_{ab0}$ | $2\Delta\lambda_{ab0}/\lambda_{ab0}$ |
|------------|--------------|-------|------------------|-----------------------|----------|----------------------------------|---------------------------|-----------------------------|--------------------------------------|
| 0          | -            | 1     | -                | -                     | 79.07    | 34.3                             | -                         | -                           | -                                    |
| 1.2        | -0.0010      | 0.991 | 0.008            | -0.007                | 79.67    | 35.9                             | -0.04                     | -0.05                       | -0.05                                |
| 2.67       | -0.0023      | 0.98  | 0.017            | -0.015                | 80.41    | 37.5                             | -0.07                     | -0.09                       | -0.09                                |
| 4.29       | -0.0037      | 0.97  | 0.031            | -0.027                | 81.4     | 39.2                             | -0.10                     | -0.13                       | -0.14                                |
| 7.52       | -0.0064      | 0.952 | 0.050            | -0.044                | 82.73    | 44.1                             | -0.19                     | -0.23                       | -0.28                                |
| 10.2       | -0.0087      | 0.936 | 0.068            | -0.059                | 84.22    | 45.0                             | -0.19                     | -0.25                       | -0.32                                |

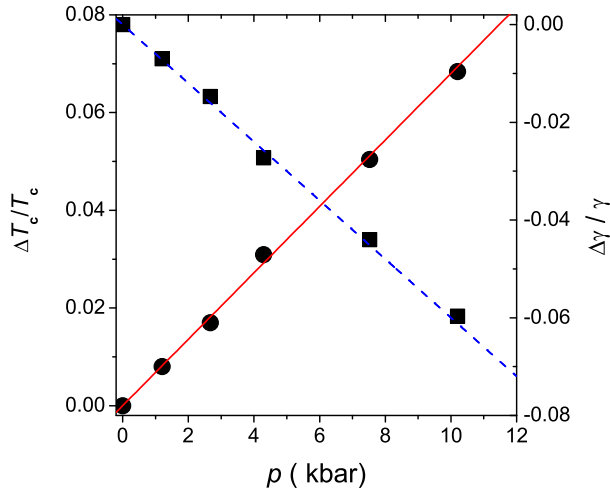


FIG. 3:  $\Delta T_c/T_c$  (●) and  $\Delta\gamma/\gamma$  (■) vs.  $p$  for the estimates listed in Table I. The solid line is  $\Delta T_c/T_c = 0.0068p$  and the dashed one is  $\Delta\gamma/\gamma = -0.006p$  with  $p$  in kbar.

seen that the rise of  $T_c$  mirrors essentially the decrease of the anisotropy. Indeed the relative volume change is an order of magnitude smaller. Furthermore, from Fig. 3, showing  $\Delta T_c/T_c$  and  $\Delta\gamma/\gamma$  versus  $p$  for the estimates listed in Table I, it is seen that in the pressure range considered here, both  $\Delta T_c/T_c$  and  $\Delta\gamma/\gamma$  depend nearly linearly on pressure. Thus, under pressure not only  $T_c$  and the volume changes but the anisotropy is modified as well. A quick glance to Table I reveal that the pressure effect on  $T_c$  mirrors essentially that on the anisotropy.

In addition, recent in-plane penetration depth  $\lambda_{ab}$  measurements revealed that there is a pressure effect on this important property also.<sup>5</sup> It was shown that the in-plane penetration depth data of  $YBa_2Cu_2O_8$  is consistent with 3D-XY critical behavior,<sup>5</sup> where the penetration depth

and correlation length in direction  $i$  diverge near  $T_c$  as  $\lambda_i^2(T) = \lambda_{i0}^2 t^{-\nu}$  and  $\xi_i(T) = \xi_{i0} t^{-\nu}$  with  $t = 1 - T/T_c$  and  $\nu \simeq 2/3$ . Moreover, as listed in Table I, the critical amplitude  $\lambda_{ab0}^{-2}$  was found to be pressure dependent. The consistency with 3D-XY critical behavior implies that the transition temperature  $T_c$  and the critical amplitudes of the in-plane penetration depths  $\lambda_{ab0}$  and the  $c$ -axis correlation lengths  $\xi_{c0}$  are not independent but related by<sup>7,8,9,10,14,20</sup>

$$k_B T_c = \frac{\Phi_0^2}{16\pi^3} \frac{f \xi_{c0}}{\lambda_{ab0}^2}, \quad f \simeq 0.453. \quad (8)$$

Universality implies that this relation holds irrespective of the applied pressure. Thus, in addition to Eq.(6) the pressure induced relative changes are then related by

$$\frac{\Delta T_c}{T_c} = -2 \frac{\Delta \lambda_{ab0}}{\lambda_{ab0}} + \frac{\Delta \xi_{c0}}{\xi_{c0}} \quad (9)$$

and, because of  $\gamma = \xi_{ab0}/\xi_{c0}$ ,

$$\frac{\Delta \gamma}{\gamma} = \frac{\Delta \xi_{ab0}}{\xi_{ab0}} - \frac{\Delta \xi_{c0}}{\xi_{c0}}. \quad (10)$$

Using then the estimates for  $\Delta T_c/T_c$  and  $-2\Delta\lambda_{ab0}/\lambda_{ab0}$  the relative change  $\Delta\xi_{c0}/\xi_{c0}$  is readily calculated with aid of Eq. (9), while the values for  $\Delta\xi_{ab0}/\xi_{ab0}$  follow from relation (10). The values of  $\Delta\xi_{c0}/\xi_{c0}$  and  $\Delta\xi_{ab0}/\xi_{ab0}$  are listed in Table I.

From the scaling analysis of the pressure effect on magnetization and in-plane penetration depth it then emerges that the rise of the transition temperature of underdoped  $YBa_2Cu_4O_8$  with increasing pressure is associated with a decreasing anisotropy and volume  $V$ . The relative change of the transition temperature  $\Delta T_c/T_c$  is seen to mirror essentially that of the anisotropy  $\Delta\gamma/\gamma$ . This is consistent with the generic behavior for high-temperature superconductors, where for a given HTS family  $T_c$  increases with reduced anisotropy.<sup>10,13,14</sup> Although these changes

are small compared to those in the critical amplitudes of the in-plane penetration depth  $\Delta\lambda_{ab0}/\lambda_{ab0}$  and the correlation lengths  $\Delta\xi_{ab0}/\xi_{ab0}$ ,  $\Delta\xi_{c0}/\xi_{c0}$  (see Table I) it becomes clear that the pressure induced change of the anisotropy is the essential ingredient which remains to be understood microscopically. Empirically the anisotropy decreases rather steeply by approaching optimum doping and levels off in the overdoped regime.<sup>10,13,14</sup> Together

with Eq.(6) this explains why the pressure effect on  $T_c$  becomes very small in optimally and overdoped cuprate superconductors.<sup>1,2,3</sup>

This work was partially supported by the Swiss National Science Foundation, the NCCR program *Materials with Novel Electronic Properties* (MaNEP) sponsored by the Swiss National Science Foundation.

- 
- <sup>1</sup> H. Takahashi and N. Mori, in *Studies of High Temperature Superconductors*, ed. by A.V. Narlikar (Nova Science, New York, 1995) Vol.16, p. 1.
- <sup>2</sup> R.J. Wijngaarden, D.T. Jover, and R. Griessen, *Physica B* **265**, 128 (1999).
- <sup>3</sup> A.-K. Klehe, C. Looney, J.S. Schilling, H. Takahashi, N. Mori, Y. Shimakawa, Y. Kubo, T. Manako, S. Doyle, and A.M. Hermann, *Physica C* **257**, 105 (1996).
- <sup>4</sup> B. Bucher *et al.* *Physica C* **157**, 478 (1989).
- <sup>5</sup> R. Khasanov, T. Schneider, R. Brütsch, D. Gavillet, J. Karpinski, and H. Keller, *Phys. Rev. B* **70**, 144515 (2004).
- <sup>6</sup> R. Khasanov, J. Karpinski, and H. Keller, cond-mat/0405643.
- <sup>7</sup> T. Schneider and H. Keller, *Int. J. Mod. Phys. B* **8**, 487 (1993).
- <sup>8</sup> T. Schneider, J. Hofer, M. Willemin, J.M. Singer, and H. Keller, *Eur. Phys. J. B* **3**, 413 (1998).
- <sup>9</sup> T. Schneider and J. M. Singer, *Phase Transition Approach To High Temperature Superconductivity*, (Imperial College Press, London, 2000).
- <sup>10</sup> T. Schneider, in: *The Physics of Superconductors*, edited by K. Bennemann and J.B. Ketterson (Springer, Berlin, (2004), p. 111.
- <sup>11</sup> T. Schneider, *Phys. Rev. B* **67**, 134514 (2003).
- <sup>12</sup> T. Schneider, *Journal of Superconductivity*, **17**, 41 (2004).
- <sup>13</sup> T. Schneider and H. Keller, *New Journal of Physics* **6**, 144 (2004).
- <sup>14</sup> T. Schneider, *Phys. Stat. Sol. B* **242**, 58 (2005).
- <sup>15</sup> T. Strässle, Ph.D. thesis, ETH Zürich, 2002.
- <sup>16</sup> A. Abrikosov, *Zh. Eksp. Teor. Fiz.* **32**, 1442 (1957); *Sov. Phys. JETP* **5**, 1174 (1957).
- <sup>17</sup> T. Schneider, cond-mat/0410547.
- <sup>18</sup> T. Schneider and D.Di Castro, cond-mat/0502202.
- <sup>19</sup> N. Kagawa, T. Ishida, K. Okuda, S. Adachi, and S. Tajima, *Physica C* **357-360**, 302 (2001).
- <sup>20</sup> A. Peliassetto and E. Vicari, *Physics Reports* **368**, 549 (2002).