

Antivortices due to competing orbital and paramagnetic pair-breaking effects

U. Klein

Johannes Kepler Universität Linz, Institut für Theoretische Physik, A-4040 Linz, Austria

Abstract

Thermodynamically stable vortex-antivortex structures in a quasi-two-dimensional superconductor in a tilted magnetic field are predicted. For this geometry, both orbital and spin pair-breaking effects exist, with their relative strength depending on the tilt angle θ . The spectrum of possible states contains as limits the ordinary vortex state (for large θ) and the Fulde-Ferrell-Larkin-Ovchinnikov state (for $\theta = 0$). The quasiclassical equations are solved near H_{c2} for arbitrary θ and it is shown that stable states with coexisting vortices and antivortices exist in a small interval close to $\theta = 0$. The results are compared with recent predictions of antivortices in mesoscopic samples.

PACS numbers: 74.20.-z, 74.78.-w, 74.90.+n

Keywords: superconductivity; antivortices; paramagnetic pair breaking; orbital pair breaking

I. INTRODUCTION

In this paper we shall establish a link between two current topics in superconductivity which seem unrelated at first sight. These two topics are antivortices in mesoscopic samples and paramagnetic pair breaking effects in layered superconductors respectively.

Antivortices are topological singularities of the order parameter with vorticity opposite to ordinary vortices. Generally, the phase of the superconducting order parameter $\psi = |\psi| \exp(i\phi)$ must change by $2\pi n$, when surrounding an isolated zero of ψ which is a topologically singular point. The arbitrary integer n is referred to as topological charge or vorticity. An ordinary vortex in a type II superconductor has positive vorticity, $n = 1$, corresponding to a phase change by 2π , a total flux of a single flux-quantum Φ_0 , and a diamagnetic behavior of the (screening) currents around the vortex center. An antivortex, on the other hand, has negative vorticity (in the simplest case $n = -1$) and carries a negative flux (e.g. $-\Phi_0$). The currents surrounding the antivortex center have opposite direction as compared to the ordinary vortex, i. e. they are paramagnetic in nature. The diamagnetic nature of the screening currents in the ordinary, orbitally-limited, superconducting state is a consequence of the dominating orbital pair-breaking mechanism.

Notwithstanding this fundamentally unfavorable conditions for the occurrence of antivortices, several specific configurations designed to create stable vortex-antivortex structures in orbitally-limited superconductors, either in thermodynamic equilibrium^{1,2,3,4} or as metastable states⁵, have been proposed in recent years. Of particular interest are theoretical predictions in mesoscopic superconducting samples^{1,4}. Free energy calculations in the framework of GL-theory, following the original prediction¹ of stable vortex-antivortex structures, revealed^{6,7} that such structures are in fact unstable in type II superconductors; this result was obtained using a GL-parameter considerably larger than the critical value $\kappa = 1/\sqrt{2}$ separating type II from type I superconductivity. This instability is a consequence of the attraction between vortices and antivortices which consequently annihilate each other in the state of lowest free energy. It may be qualitatively understood by considering the interaction between well separated vortices in bulk samples⁸. In this case, the total interaction between vortices in GL theory is the sum of two contributions, a repulsive electrodynamic part and an attractive condensation energy part. The electrodynamic part exceeds the attractive part for $\kappa > 1/\sqrt{2}$. But for a vortex-antivortex pair the electrodynamic interaction changes

sign and becomes attractive while the condensation energy interaction does not change sign and remains attractive. Thus, the total force between vortices and antivortices becomes attractive.

Nevertheless, the search for stable vortex-antivortex structures in mesoscopic samples was finally successful⁴. A state with total flux of $2\phi_0$, carried by a antivortex and three ordinary vortices in a mesoscopic sample of triangular shape, was found to be stable in a small region below T_c and below $\kappa = 1 = \frac{p}{2}$ (In this part of the $\kappa; T$ plane, GL-theory still applies⁹). This effect, which has not yet been verified experimentally, is essentially a surface effect and cannot be understood in terms of forces between isolated vortices. Contrary to the interpretation of the authors⁴, the decrease of κ below the critical value $1 = \frac{p}{2}$ does not lead to a change in sign of the vortex-antivortex interaction. The latter remains attractive for arbitrary κ since only the electrodynamic part of the interaction changes sign. Nevertheless, the decrease of κ plays an essential role because it weakens the relative importance of the vortex interactions in comparison to that of the confining boundary conditions. The geometric shape (triangular) of the sample is important since no stable vortex-antivortex structure has been found¹⁰ in thin films of quadratic shape.

II. PARAMAGNETIC PAIR-BREAKING AS A STABILIZING FACTOR FOR ANTIVORTICES

Considering the physical mechanism governing the interaction between vortices it seems impossible to create periodic structures with antivortices for values of κ much larger than $1 = \frac{p}{2}$, deep in the type II region. This is in fact true for the purely orbitally-limited superconducting state. However, as will be shown in this paper, an exotic type of superconductivity exists, characterized by the presence of two different competing pair-breaking effects, where vortex-antivortex structures appear quite naturally for a large range of GL parameters κ , not as a surface effect but in an extended, two-dimensional (2D) periodic "vortex"-lattice.

Cooper pairs may either be broken by the orbital effect or by means of the interaction between the external field and the magnetic moment due to the spins of the electrons^{11,12}. This spin pair-breaking effect leads to a paramagnetic response of the superconducting condensate. It is usually much smaller than the orbital effect but becomes important if the orbital effect can be suppressed. Clearly, decreasing the magnitude of the orbital effect

favors the stability of antivortices.

Until recently, in most works only the limit of complete suppression of the orbitale effect was considered. In this paramagnetic limit, a spatially inhomogeneous superconducting state, referred to as FFLO state, has been predicted theoretically by Fulde and Ferrell¹³, and by Larkin and Ovchinnikov¹⁴. With regard to the present problem, the FFLO state itself is not a good candidate for observing antivortices since the diamagnetic response is completely suppressed, and no (anti)vortices at all can exist in the purely paramagnetic limit.

Obviously, coexistence of both pair-breaking mechanisms, with only partial suppression of the diamagnetic effect, provides optimal conditions for the stability of vortex-antivortex structures. Such a situation may be realized by slightly tilting the applied magnetic field, by an angle θ , from the plane-parallel direction. If the conducting layers are completely decoupled and infinitely thin (it has been shown recently that single-atomic layers are required for negligible orbital pair-breaking¹⁵) one has, in fact, a mixture of both pair-breaking mechanisms, with the orbitale effect entirely due to the perpendicular component $H_\perp = H \sin \theta$ and the spin effect mainly due to the parallel component $H_\parallel$. The relative weight of the two pair-breaking effects may be controlled with the help of the angle θ .

The second order phase boundary H_{c2} for this situation has been calculated by Bulaevskii¹⁶ for $T = 0$ and by Shimahara and Rainer¹⁷ for arbitrary T . They found a non-monotonic upper critical field curve with different pieces of the curve belonging to different Landau quantum numbers n ($n = 0; 1; \dots$). For large θ one recovers the usual orbital result $n = 0$. With decreasing θ unusual pairing states with nonzero $n = 1; 2; \dots$ appear for θ smaller than a critical angle of the order of one degree. For $\theta \rightarrow 0$, one obtains $n \rightarrow 1$ and the upper critical field of the FFLO state is recovered.

III. OUTLINE OF CALCULATION

The states below the non-monotonic upper critical field curve which belong to the lowest nonzero quantum numbers, say $n = 1 \dots 4$, are most interesting from the present point of view of antivortices.

We shall make only two very general (and reasonable) assumptions with regard to the structure of these states. The first is, that the order parameter modulus j_j and the local

magnetic induction B are periodic with respect to an arbitrary two-dimensional lattice. The second assumption is that a unit cell of this quasi-periodic lattice carries a single flux quantum Φ_0 . To find the equilibrium structure of these states, all possible lattices must be considered and the global minimum of the free energy must be identified.

Considering the vicinity of the upper critical field, where a second order transition occurs, a free energy expansion, up to terms of fourth order, may be performed. Then, the general scheme of such a calculation is the same as Abrikosov's classical work on type II superconductivity¹⁸. However, microscopic equations should be used here, because a G-L-formulation, with a finite number of gradient terms, is not valid in the present (low-temperature) situation. The quasiclassical theory of superconductivity, generalized with regard to Zeeman coupling terms, provides an appropriate theoretical framework¹⁹ for the present problem.

The nonlinear transport equations for a clean superconductor, including Zeeman coupling, are given by

$$\begin{aligned} \hbar \frac{\partial}{\partial t} \psi_1 + \hbar \mathbf{v}_F(\mathbf{k}) \cdot \nabla_{\mathbf{r}} f(\mathbf{r}; \mathbf{k}; \omega_1) &= 2 \langle \mathbf{r} \rangle g(\mathbf{r}; \mathbf{k}; \omega_1), \\ \hbar \frac{\partial}{\partial t} \psi_1 - \hbar \mathbf{v}_F(\mathbf{k}) \cdot \nabla_{\mathbf{r}} f^+(\mathbf{r}; \mathbf{k}; \omega_1) &= 2 \langle \mathbf{r} \rangle g(\mathbf{r}; \mathbf{k}; \omega_1), \end{aligned} \quad (1)$$

where f ; f^+ ; g are the quasiclassical Green's functions ($g^2 = 1 - ff^+$), ω_1 is the order parameter, and $\nabla_{\mathbf{r}}$ is the gauge-invariant derivative, defined by $\nabla_{\mathbf{r}} = \tilde{\nabla}_{\mathbf{r}} - \{2e\hbar c \mathbf{A}$. The latter term, containing the vector potential $\mathbf{A}$, describes the familiar orbital coupling between Cooper pairs and magnetic field. In addition the coupling between the spins of the electron and the magnetic field is taken into account in Eq. (1). The corresponding Zeeman term B is contained in the complex variable $\psi_1 = \omega_1 + iB$ which replaces the real Matsubara frequency ω_1 . The quantity $\mathbf{v}_F(\mathbf{k})$ denotes the Fermi velocity which depends on the quasiparticle wave-number $\mathbf{k}$.

The order parameter ω_1 is defined in terms of the Green's functions f ; f^+ by the relation

$$2 k_B T \sum_{\mathbf{k}} \frac{1}{\omega_1} + \ln(T/T_c) \langle \mathbf{r} \rangle = k_B T \sum_{\mathbf{k}} \frac{\hbar}{d^2 k^0} f(\mathbf{r}; \mathbf{k}^0; \omega_1) + f(\mathbf{r}; \mathbf{k}^0; \omega_1), \quad (2)$$

where N_D is the cutoff index for the Matsubara sums. To calculate the vector potential $\mathbf{A}$ for given Green's function g , Maxwell's equation

$$\tilde{\nabla}_{\mathbf{r}}^2 B(\mathbf{r}) + 4 M^*(\mathbf{r}) = \frac{16 e^2 k_B T N_F}{c} \sum_{\mathbf{k}} \frac{\hbar}{d^2 k^0} \mathbf{v}_F(\mathbf{k}^0) g(\mathbf{r}; \mathbf{k}^0; \omega_1), \quad (3)$$

has to be solved. Here, N_F is the normal-state density of states at the Fermi level. The r.h.s. of Eq. (3) is the familiar (orbital) London screening current while the magnetization $\mathbf{M}$ is a consequence of the magnetic moments of the electrons and is given by

$$\mathbf{M}(\mathbf{r}) = 2^2 N_F \mathbf{B}(\mathbf{r}) - 4 k_B T N_F \sum_{\mathbf{k}=0}^{\mathbf{k}^D \cdot \mathbf{I}} \frac{d^2 k^0}{4} = g \frac{\mathbf{B}}{B}, \quad (4)$$

The first term on the r.h.s. of Eq. (4) is the normal state spin polarization. The second term is a spin polarization due to quasiparticles in the superconducting state.

Solving these equations one obtains extrema of a free energy functional G (not written down here, see¹⁹), whose global minima represent the stable states. The quasiclassical equations (1)–(4) are rather general; they describe both orbital and paramagnetic pair-breaking effects, and cover the ordinary vortex state as well as the FFLO state in the appropriate limits. In addition, Eqs. (1)–(4) take into account the magnetic response of the superconductor (arbitrary values of the GL-parameter may be considered), which is neglected in most treatments of paramagnetic pair breaking. Note that the familiar London screening current is completely absent in the purely paramagnetic (FFLO) limit.

The calculation generalizes techniques used previously to calculate the upper critical field^{6,17} and the equilibrium structure in the high- T limit²⁰. For the vector potential the same gauge as in previous numerical calculations^{9,21} on the vortex lattice (without Zeeman coupling) may be used. A first important step is the solution of the transport equation (1) for small $\mathbf{j}$, taking derivatives of $\mathbf{j}$ of arbitrary order into account. This is achieved by means of an eigenfunction expansion and the so-called "Helfand-Werthamer Trick", leading to an integral representation for the first-order Green's functions. In the course of the following free energy expansion, up to terms of fourth order in $\mathbf{j}$, a large number of momentum- and configuration space integrations have to be performed. The evaluation of these integrals may be greatly simplified by introducing the gap correlation function. A more detailed description of the lengthy calculation (and a discussion of other results, not related to antivortices) may be found elsewhere¹⁹.

IV. STABLE VORTEX-ANTIVORTEX STRUCTURES FOR $N = 2$

In this section results are reported which show that stable vortex-antivortex structures do in fact exist in bulk superconductors for nonzero n . The most important of these states,

which is most stable and most easily accessible experimentally, belongs to Landau quantum number $n = 2$. Discussion will be restricted here to this single state (Stable structures for other n and a discussion of the general properties of the new paramagnetic vortex states have been reported elsewhere¹⁹). The results depend on 4 input parameters, the dimensionless

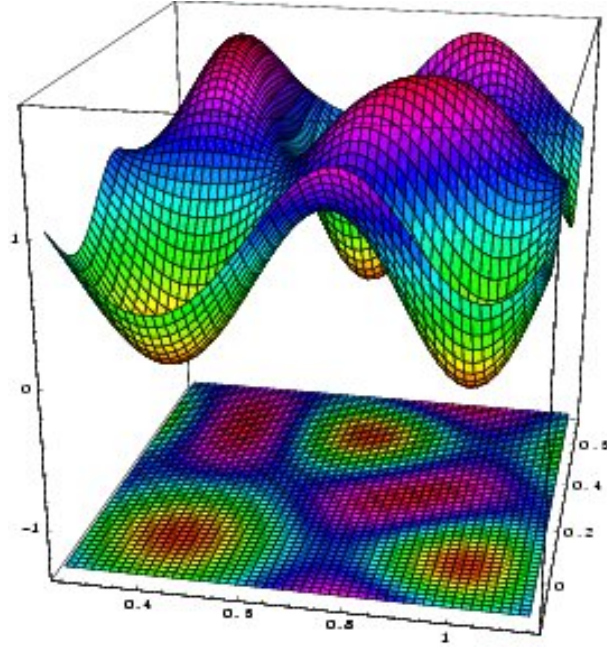


FIG. 1: Square of modulus of order parameter $|j_2|^2$ for Landau level $n = 2$ as a function of $x/a; y/a$ in the range $0.25 < x/a < 1.25$; $0.15 < y/a < 0.7$. This is the stable structure (unit cell parameters $a=b=1$; $\phi = 60^\circ$) for $\tilde{\mu} = 0.1$; $\tilde{\nu} = 10$; $\tilde{\alpha} = 0.7$; $t = 0.2$.

magnetic moment $= k_B T_c = m v_F^2$, Eilenberger's G L-parameter $\tilde{\mu}$ (which is defined in terms of the G L-parameter of a clean superconductor by the relation $\tilde{\mu} = 0.6837 \mu$), the tilt angle ϕ , and the dimensionless temperature $t = T/T_c$. Given these numbers, the critical field B_{c2} , Landau's quantum number n , the unit-cell structure of the stable lattice (which is characterized by the lengths $a; b$ of the unit-cell vectors and by the angle ϕ between them), and the fields $\tilde{\mu}_n(\mathbf{r}); \tilde{B}(\mathbf{r})$ may be calculated¹⁹. The square of the order parameter modulus for pairing in Landau level n is given by the Fourier series

$$|j_n|^2(\mathbf{r}) = \sum_{l,j} \left(\begin{matrix} 2 \\ n \end{matrix} \right)_{l,j} e^{iQ_{l,j}\mathbf{r}}, \quad (5)$$

with reciprocal lattice vectors $\mathbf{Q}_{lj}$ corresponding to the lattice parameters $a; b; c$, and with Fourier coefficients

$$(c_n^2)_{lj} = (c_1)^{lj} e^{i \frac{1}{a} \cos \mathbf{x}_{lj} \cdot \mathbf{L}_n(\mathbf{x}_{lj})}. \quad (6)$$

The quantity $\mathbf{x}_{lj}$ is defined elsewhere¹⁹. The magnetic response of the superconductor is characterized by means of the deviation $\mathbf{B}_1 = \mathbf{B} - \mathbf{B}$ of the local induction from the macroscopic induction $\mathbf{B}$. The parallel component of $\mathbf{B}_1$, which describes a purely paramagnetic behavior, is denoted by B_{1k} . The perpendicular component $B_{1\perp}$ describes a mixed orbital and paramagnetic response. The Fourier coefficients of these quantities are given by

$$(B_{1k})_{lm} = \frac{h j_n^2 i}{\sim^2} \frac{1}{2} B_k^2 (c_1)^{lm} e^{i \frac{1}{a} \cos \mathbf{x}_{lm} \cdot \mathbf{L}_1(\mathbf{x}_{lm})} S_{lm}^{(1)}, \quad (7)$$

$$(B_{1\perp})_{lm} = \frac{h j_n^2 i}{\sim^2} (c_1)^{lm} e^{i \frac{1}{a} \cos \mathbf{x}_{lm} \cdot \mathbf{L}_1(\mathbf{x}_{lm})} B_{\perp}^2 f_1(\mathbf{x}_{lm}) S_{lm}^{(1)} - g_1(\mathbf{x}_{lm}) S_{lm}^{(2)}, \quad (8)$$

where $h j_n^2 i$ denotes the spatial average of the square of the order parameter and the functions $f_1; g_1$ and the Matsubara sums $S_{lm}^{(i)}$ are reported elsewhere¹⁹. Choosing parameters $\beta = 0.1$, $\sim = 10$, $\gamma = 0.7$, and $t = 0.2$ one obtains a Landau quantum number $n = 2$ ($B_{c2} = 4.27086$ if measured in Eilenberger units¹⁹) and a unit cell with $a=b=1$; $c=60$, i.e. a triangular lattice. The order parameter has three zeros per unit cell as shown in Figure 1. Thus, one expects that this stable structure contains two vortices and a single antivortex, because the total flux per unit-cell is 0.

The nature of these order parameter zeros may be further clarified with the help of the local magnetic field. We plot the fields B_k and $B_{1\perp}$ as given by equations. (7)–(8), omitting a common factor $h j_n^2 i = (\sim^2)^2$ and using the same input parameters and the same part of the $x; y$ -plane as in Figure 1. Let us discuss first the parallel component B_{1k} . As shown in Figure 2, the functional form of B_{1k} is nearly identical with that of ϕ plotted in Figure 1. This behavior, though unexpected at first sight, is a consequence of the purely paramagnetic pair-breaking mechanism for the parallel component. The latter implies an enhancement of the local induction at points of enhanced order parameter, which is opposite to the familiar diamagnetic field expulsion.

The spatial dependence of the perpendicular component $B_{1\perp}$, plotted in Figure 3, shows that the order parameter zero on the left hand side of Figure 1 is an antivortex while the

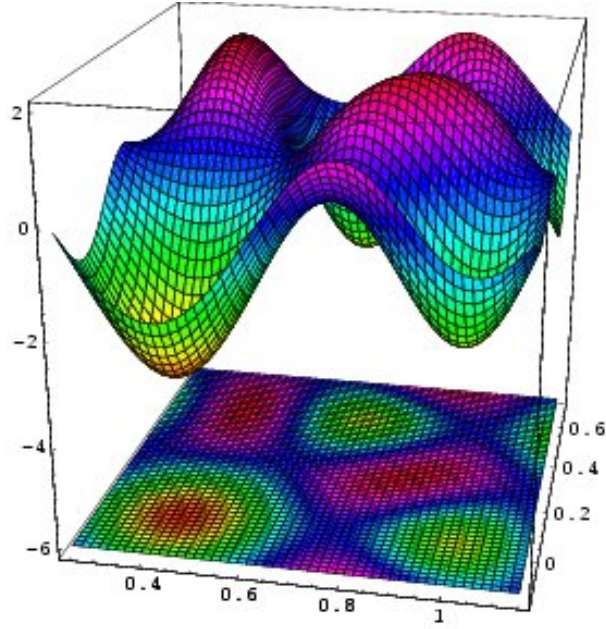


FIG .2: Spatially varying part of the parallel magnetic field $B_{1\parallel}(\mathbf{r})$ using the same input parameters and the same part of the $x; y$ -plane as in Figure 1.

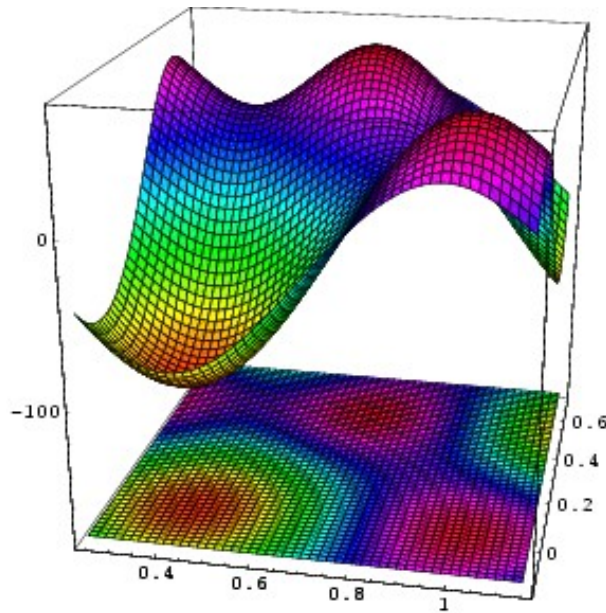


FIG .3: Spatially varying part of the perpendicular component of the magnetic field $B_{1\perp}(\mathbf{r})$ using the same input parameters and the same part of the $x; y$ -plane as in Figure 1.

two remaining zeros belong to ordinary vortices. At the centers of the ordinary vortices the field has a maximum, i.e. shows the familiar behavior of orbitally-limited superconductors. At the center of the antivortex the field has a minimum, i.e. shows the opposite, paramagnetic behavior. Thus, stable vortex-antivortex structures may indeed be produced by means of a 2D-superconductor in a tilted magnetic field. It is the simultaneous presence of both pair-breaking mechanisms which allows the coexistence of vortices and antivortices in a periodic lattice. Calculations¹⁹ for $\alpha = 0.1; 1; 100$ and $t = 0.2; 0.5$ show that the structure displayed in Figures 1-3 is stable for a large range of parameters.

Comparing the present results with previous predictions, one notes that the present unit cell has the same shape as the mesoscopic sample used in the work of Misko et al.⁴; the number and type of order parameter zeros is, however, different. A second common feature is the strong interaction (small distance) between anti/vortices. The basic mechanism responsible for the stability of antivortices is, however, completely different in both cases. Experimental verification of the structure predicted here requires similar conditions as for the FFLO state^{22,23,24,25}, namely a layered superconducting material of high purity with nearly decoupled conducting planes and a very accurate adjustment of the direction of the applied magnetic field. Appropriate materials include the intercalated transition metal dichalcogenide TaS_2 (pyridine), the organic superconductor $(\text{BEDT-TTF})_2\text{Cu}(\text{NCS})_2$, or the magnetic field induced superconductor $(\text{BEDT})_2\text{FeCl}_4$. The predicted phenomena do not sensitively depend on α and t but large values of these parameters are favorable, because of an associated enlargement of the paramagnetic region. A non-monotonic phase boundary in a tilted magnetic field has been observed recently²⁵ in the heavy-fermion superconductor CeCoIn_5 . These data may be related to the present prediction, despite the fact that CeCoIn_5 differs considerably from the simple model considered here.

Acknowledgments

I would like to thank V.V.Moshchalkov for a discussion about his work⁴ on antivortices in mesoscopic samples.

-
- ¹ L.F.Chibotaru, A.Ceulemans, V.Bruyndoncx, and V.V.Moshchalkov, Phys.Rev.Lett 86, 1323 (2001).
- ² S.Erdin, A.F.Kayali, I.F.Lyuksyutov, and V.L.Pokrovsky, Phys.Rev.B 66, 014414 (2002).
- ³ M.V.Milosevic and F.M.Peeters, Phys.Rev.B 68, 024509 (2003).
- ⁴ V.R.Misko, V.M.Fomin, J.T.Devreese, and V.V.Moshchalkov, Phys.Rev.Lett 90, 147003 (2003).
- ⁵ M.Ghinovker, I.Shapiro, and B.Y.Shapiro, Phys.Rev.B 59, 9514 (1999).
- ⁶ J.Bonca and V.V.Kabanov, Phys.Rev.B 65, 012509 (2001).
- ⁷ B.J.Baelus and F.M.Peeters, Phys.Rev.B 65, 104515 (2002).
- ⁸ L.Kramer, Phys.Rev.B 3, 3821 (1971).
- ⁹ U.Klein, J.Low Temp.Phys. 69, 1 (1987).
- ¹⁰ T.Mertelj and V.V.Kabanov, Phys.Rev.B 67, 134527 (2003).
- ¹¹ A.M.Clogston, Phys.Rev.Lett. 9, 266 (1962).
- ¹² B.S.Chandrasekhar, Appl.Phys.Lett. 1, 7 (1962).
- ¹³ P.Fulde and R.A.Ferrell, Phys.Rev. 135, A 550 (1964).
- ¹⁴ A.I.Larkin and Y.N.Ovchinnikov, Sov.Phys.JETP. 20, 762 (1965).
- ¹⁵ S.Manab and U.Klein, Phys.Rev.B 65, 144510 (2002).
- ¹⁶ L.N.Bulaevskii, Sov.Phys.JETP 38, 634 (1974).
- ¹⁷ H.Shimahara and D.Rainer, J.Phys.Soc.Jpn. 66, 3591 (1997).
- ¹⁸ A.A.Abrikosov, Sov.Phys.JETP 5, 1174 (1957).
- ¹⁹ U.Klein, Phys.Rev.B 69, 134518 (2004).
- ²⁰ U.Klein, D.Rainer, and H.Shimahara, J.Low Temp.Phys. 118, 91 (2000).
- ²¹ U.Klein, Phys.Rev.B 40, 6601 (1989).
- ²² H.Shimahara, J.Phys.Soc.Jpn. 71, 1644 (2002).
- ²³ S.Manab and U.Klein, J.Phys.:Condens.Matter 12, L471 (2000).

- ²⁴ M . S . Nam , J . A . Sym ington, J . Singleton, S . J . B lundell, A . A rdavan, J . A . A . J . Perenboom ,
M . Kum oo, and P . Day, J . Phys.: Condens. M atter 11, L477 (1999) .
- ²⁵ H . A . Radovan, N . A . Fortune, T . P . M urphy, S . T . Hannahs, E . C . Palm , S . W . Tozer, and
D . H all, Nature 425, 51 (2003) .