

Distribution of the superconducting gap in an $\text{YNi}_2\text{B}_2\text{C}$ film studied by point contact spectroscopy.

D. L. Bashlakov, Yu. G. Naidyuk, I. K. Yanson
B. Verkin Institute for Low Temperature Physics and Engineering,
National Academy of Sciences of Ukraine, 47 Lenin Ave., 61103 Kharkiv, Ukraine

S. C. Wimbush, B. Holzapfel, G. Fuchs, S.-L. Drechsler
IFW Dresden, P. O. Box 270016, 01171 Dresden, Germany
(dated: October 6, 2021)

The differential resistances $R_d = dV/dI(V)$ of point contacts between a normal metal and a c-axis oriented $\text{YNi}_2\text{B}_2\text{C}$ film ($T_c = 15.2\text{ K}$) in the superconducting (SC) state have been investigated. $R_d(V)$ contains clear "gap" features connected with processes of Andreev reflection at the boundary between normal metal and superconductor that allow the determination of the SC gap and its temperature and magnetic field dependence. A distribution of Δ from $\Delta_{\min} = 1.5\text{ meV}$ to $\Delta_{\max} = 2.4\text{ meV}$ is revealed; however the critical temperature T_c in all cases corresponded to that of the film. The value $2\Delta_{\max}/k_B T_c = 3.66$ is close to the BCS value of 3.52, and the temperature dependence $\Delta(T)$ is BCS-like, irrespective of the actual Δ value. It is supposed that the distribution of Δ can be attributed to a gap anisotropy or to a multiband nature of the SC state in $\text{YNi}_2\text{B}_2\text{C}$, rather than to the presence of nodes in the gap.

PACS numbers: 74.70.Dd, 74.45.+c, 74.50.+r

INTRODUCTION

During the last ten years, the class of nickel borocarbide compounds $\text{RNi}_2\text{B}_2\text{C}$, where $R = \text{Sc}, \text{Y}, \text{Lu}, \text{Dy}, \text{Ho}, \text{Er}, \text{Tm}$ and other rare-earth ions, has attracted considerable attention in the superconducting community [1]. This interest is caused by the unusual properties of these materials related to the rich interplay of superconductivity and magnetism, when R is a magnetic rare-earth ion. In this context, it is remarkable that the superconducting transition temperature T_c can be higher than the Neel temperature T_N as for $R = \text{Tm}$ and Er , but also comparable with T_N as for $R = \text{Ho}$ and even lower than T_N as for $R = \text{Dy}$. Non-magnetic compounds with $R = \text{Sc}, \text{Y}$ and Lu have the highest T_c values of 15 K, 15.5 K and 16.5 K, respectively. They are type II superconductors and have three-dimensional, practically isotropic electronic structure, while their crystal structure comprises alternating RC and N_2B_2 layers. Noteworthy recent experiments including tunnelling [2] and point contact measurements [3, 4] on bulk single crystals have shown that the unusual superconducting properties of nickel borocarbides exhibit strong anisotropy. In particular, a hybrid ($s + g$) wave superconducting state has been proposed [5, 6] for the compounds with $R = \text{Y}$ and Lu , characterized by four point nodes of the superconducting order parameter in the $[1, 0, 0]$ and $[0, 1, 0]$ directions. This conclusion was based on investigations of the angular dependence of

the thermal conductivity [7] and specific heat [8] under an applied external magnetic field of single crystals at low temperatures. Point-contact measurements [3] also revealed a strong gap anisotropy. In the $[100]$ direction, not only the gap is 4.5 times smaller, but also the transition temperature was found to be half (!) that in the $[001]$ direction. It is also important to note that a thorough analysis of upper critical field $H_{c2}(T)$ data for $\text{YNi}_2\text{B}_2\text{C}$ and $\text{LuNi}_2\text{B}_2\text{C}$ single crystals clearly showed that superconductivity in these compounds is strongly affected by their multiband nature [9]. In order to gain further insight into the interplay of the symmetry of superconducting order parameters, their anisotropy and multiband nature, additional studies are necessary. In the present work, direct measurements of the gap amplitude distribution have been performed on epitaxial c-axis oriented $\text{YNi}_2\text{B}_2\text{C}$ thin film using point-contact spectroscopy [10].

EXPERIMENTAL TECHNIQUE

In this paper, we present the results of point contact measurements made on a high quality $\text{YNi}_2\text{B}_2\text{C}$ film [11]. The film was prepared by pulsed laser deposition on an MgO single crystal substrate. The SC transition temperature $T_c = 15.2\text{ K}$ (with transition width $\Delta T_c = 0.3\text{ K}$) was determined from resistive measurements. The residual resistance ratio $R(300\text{ K})/R(T - T_c)$ of the film was about 8. X-ray data indicate that the film consists of small crystallites having their primary orientation with the c-axis perpendicular to the substrate surface.

The measurement cell was placed in a low cryostat, enabling measurement at a series of temperatures up to T_c and higher. Point contacts were created by touching

Present address: National Institute for Materials Science, International Center for Young Scientists, 1-1 Namiki, Tsukuba, Ibaraki 305-0044, Japan

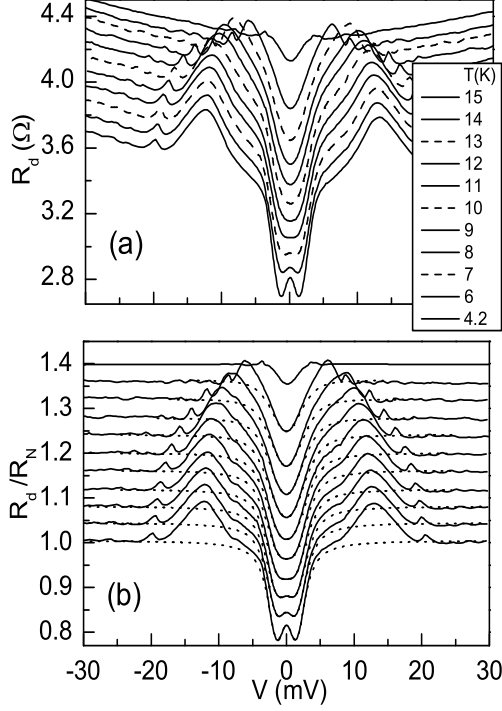


FIG. 1: (a) Differential resistance $R_d(V)$ of point contact YNi_2B_2C/Ag with normal state resistance $R_N = 3.5 \Omega$, measured at different temperatures. (b) Normalized R_d (solid) curves for this contact and those values calculated by BTK theory (dashed). The theoretical curve at 4.2 K is calculated with $\Delta = 1.67$ meV, $Z = 0.43$ and $\Delta = 0.55$ meV. The temperature dependence (T) is shown in Fig. 3(b). Curves are offset vertically from the lower curve for clarity.

sharpened Cu and Ag wires to the YNi_2B_2C surface directly within the cryostat at liquid helium temperature. An unfortunate disadvantage of this 'needle/anvil' method is the sensitivity of the contacts to mechanical vibrations and changes in temperature. As a result, only around one quarter of the prepared contacts withstood measurement above liquid helium temperature.

Using a technique of synchronous detection of weak (10–30 V) modulating signal harmonics, the first harmonic of the modulating signal V_1 [proportional to the differential resistance $R_d(V) = dV/dI(V)$] was recorded as a function of the bias voltage V .

EXPERIMENTAL RESULTS

A series of $R_d(V)$ measurements with clear double minimum features near $V = 0$ connected with the Andreev reflection of electrons at the superconductor/normal

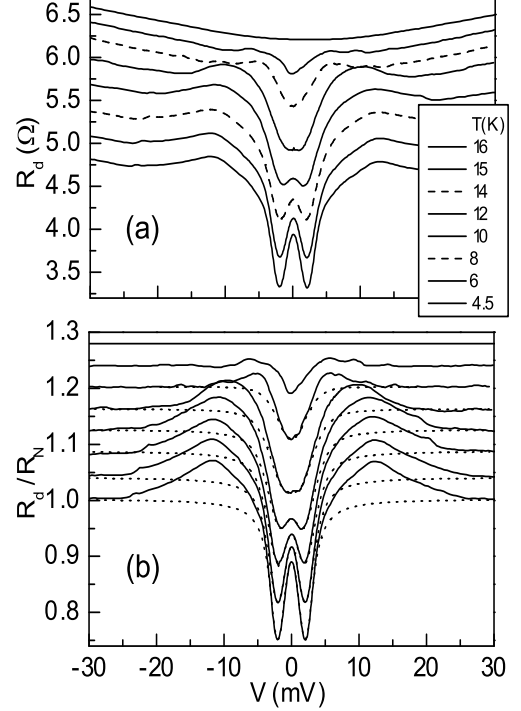


FIG. 2: (a) Differential resistance $R_d(V)$ of point contact YNi_2B_2C/Cu with normal state resistance $R_N = 4.5 \Omega$, measured at different temperatures. (b) Normalized R_d (solid) curves for this contact and those values calculated by BTK theory (dashed). The theoretical curve at 4.5 K is calculated with $\Delta = 2.24$ meV, $Z = 0.5$ and $\Delta = 0.1$ meV. The temperature dependence (T) is shown in Fig. 3(b). Curves are offset vertically from the lower curve for clarity.

metal (S/N) interface are shown in Figs. 1(a) and 2(a).

For voltages exceeding the gap value, all curves exhibit a maximum, caused, most likely, by the suppression of superconductivity in (part of) the contact. Such behavior testifies to a deviation from the spectral (ballistic) regime (i.e., the inelastic electron mean free path becomes less than or about the size of the contact) with increasing bias voltage at the contact (see [10], Chapter 3).

The size of the gap was calculated using the modified BTK theory (see [10], Chapter 3.7). The presence of a maximum in $R_d(V)$ prevented the coincidence of the calculated and measured curves throughout the voltage range; therefore an adjustment was carried out so that both curves coincided in the region of the gap ($V < 0$ and $V > 0$) and at the higher voltages beyond the maximum. Preliminary, unadjusted curves were normalized to $R_d(V; T > T_c)$. During calculation, the parameters Z and Δ were fixed or varied in small limits up to 5(10)%. The results are shown in Figs. 1(b) and 2(b). We note also that the con-

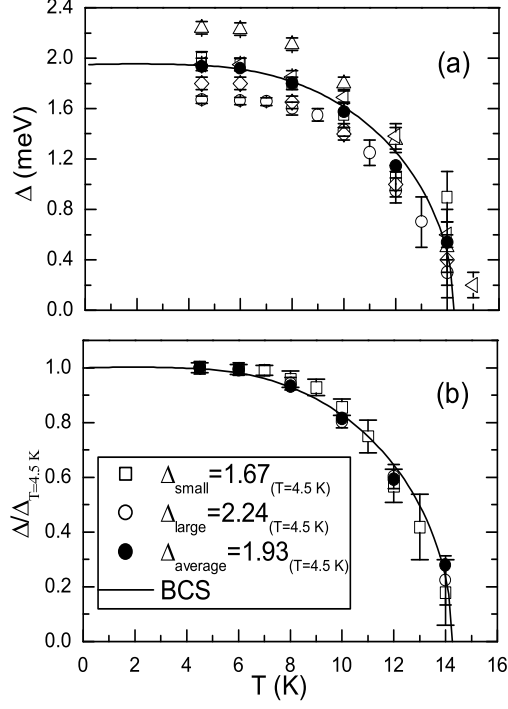


FIG. 3: (a) The temperature dependence of the gap $\Delta(T)$ obtained from the BTK fit for various different contacts (open symbols). The theoretical BCS curve is drawn to coincide with the average value of the various contacts (closed symbols). (b) The temperature dependence $\Delta(T)$ normalized to $\Delta(T = 4.5 \text{ K})$ for the minimal (open squares), maximal (open circles) and average (closed circles) gap values, along with the theoretical BCS curve.

tacts shown in Figs.1 and 2 had, respectively, the minimal and maximal gap values among all the contacts that withstood low temperature measurement.

In Fig.3(a), the dependences $\Delta(T)$ are shown for a number of different contacts, for each of which a series of $R_d(V)$ curves at different temperatures was measured. For all these contacts, the SC minimum in $R_d(V)$ disappeared at a temperature interval of 14{16 K, corresponding to the T_c value (15.2 K) of the film.

In Fig.3(b), the temperature dependences for the minimal and maximal $\Delta(T = 4.5 \text{ K})$ are shown, normalized to these values (2.24 meV and 1.67 meV, respectively). Also the normalized $\Delta(T)$ temperature dependence obtained by averaging all the contacts of Fig.3(a), and the theoretical BCS dependence are depicted. We reiterate that the complete data (measured, normalized and calculated spectra) for the smallest and largest gap are presented in Figs.1 and 2.

In total, 29 curves, on which the structure with two

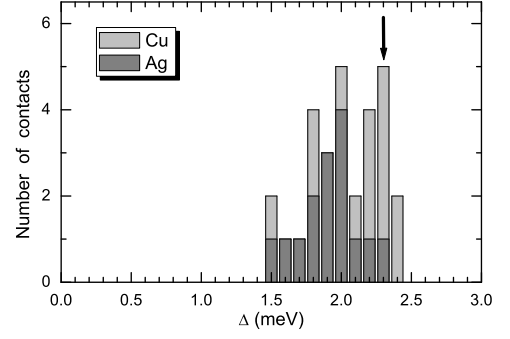


FIG. 4: Distribution of values obtained from measurement of 29 contacts with different counter electrodes Ag (15 contacts, dark bars) and Cu (14 contacts, gray bars). The arrow specifies the value corresponding to the BCS ratio $2\Delta_0/k_B T_c = 3.52$, with $T_c = 15.2 \text{ K}$.

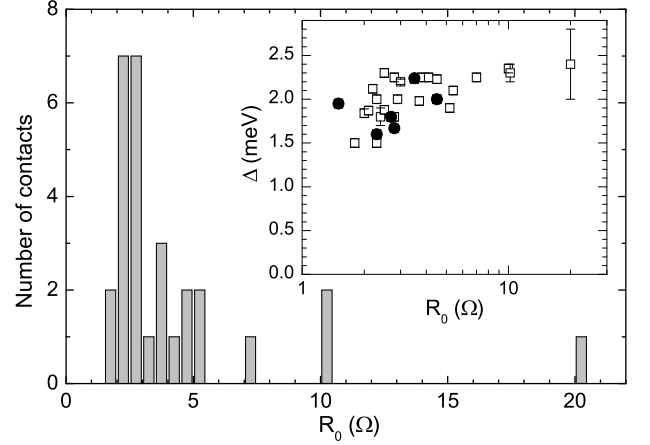


FIG. 5: Distribution of contact resistances $R_0 = R_d(V = 0, T = 4.2 \text{ K})$ for the same contacts as in Fig.4. Inset: gap values of these contacts. Solid circles designate those contacts for which a series of temperature measurements were carried out, with results shown on Fig.3(a).

minimum is clear enough to allow an unequivocal determination of Δ using the standard procedure of adjustment of theoretical curves described above, have been selected from numerous measured spectra. From the results of the calculation, the histogram in Fig.4 was constructed. Irrespective of the counter electrode used, Δ is distributed in an interval between 1.5 meV and 2.4 meV.

Half of the selected contacts had contact resistances between 2 and 3 Ω , as seen on the distribution of $N(R)$ values in Fig.5. The inset shows the Δ values obtained for contacts of different normal state resistance. Solid circles designate those contacts for which a series of tem-

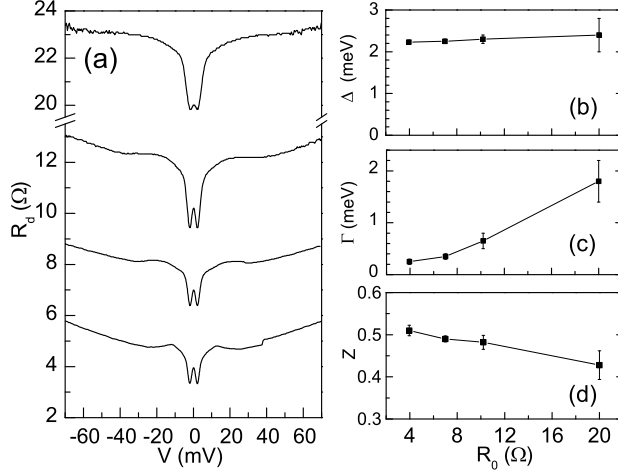


FIG. 6: (a) Differential resistance $R_d(V)$ of the same point contact $\text{YNi}_2\text{B}_2\text{C}$ (Cu measured for different $R_0 = R_d(V=0)$, $T = 4.2\text{K}$) values as a result of consecutive contact short-circuits by a current pulse. (b), (c), (d) The variation in the values Δ , Γ , and Z with R_0 .

perature measurements were carried out and superconductivity confirmed to disappear between 15K and 16K, corresponding to the T_c value of the $\text{Ni}_2\text{B}_2\text{C}$, independent of the Z value.

In Fig. 6(a), $R_d(V)$ is shown for contacts produced by consecutive electric short-circuit of the same contact from $R_N = 20$ down to $R_N = 4$. It is seen that as the contact resistance is reduced, humps start to appear to a greater degree, and the intensity of the local maximum at zero bias increases. The latter is possible to explain, proceeding from [12] where it is shown that in the diffusive regime $R_d(V)$ looks like the presence of a barrier with $Z = 0.55$ in the ballistic regime. In other words, for a clean S/N boundary without a barrier ($Z = 0$) in the diffusive regime, it is possible to observe a maximum in $R_d(V)$ at zero bias, similar to the ballistic case with $Z = 0.55$. In reality, from Fig. 6(c) it is seen that the parameter Z grows with the reduction of contact resistance, coming nearer to the value 0.55. It is necessary to note that the Δ value for these contacts is practically independent of their resistance, remaining around $2.2 \pm 0.1\text{meV}$. On the other hand, the parameter Γ grows strongly with resistance, as observed experimentally for many superconductors of different sorts (see Fig. 12.14 in [10]), although the reason for this remains under discussion.

DISCUSSION

The presented point contact measurements show a distribution of the SC gap in the electronic density of states

of an $\text{YNi}_2\text{B}_2\text{C}$ film. Important and essential is the fact that irrespective of the size of the gap, ranging from 1.5 meV to 2.4 meV, the observed critical temperature corresponds to the T_c of the $\text{Ni}_2\text{B}_2\text{C}$. This excludes the possibility of a distribution of the gap on the $\text{Ni}_2\text{B}_2\text{C}$ surface owing to its non-uniform structure. Another possible source of a gap variation is the proximity effect resulting in gap suppression at the surface. However, we assume that in this case the gap value should correlate inversely with the point contact resistance, in other words with the size of the contact: the smaller the size, the lower the gap value measured. However, this is not the case. The gap value varies even for contacts with nearly equal resistance [Fig. 5 (inset)], and has a tendency, if any, to rise with increasing resistance [Fig. 6(b)].

Hence, it is natural to first assume the presence of a gap anisotropy. Unfortunately, the use of a film does not allow measurements to be made along different crystallographic directions. However, as mentioned previously, the film is predominantly c axis oriented, and consists of small crystallites. Thus it is reasonable to expect that with contacts prepared by touching a film plane with a needle, we will mainly register a gap along the c axis. Yet, taking into account that the contribution to point contact conductivity result from some finite solid angle, the point contact axis is not well fixed along the c axis and with the possible misorientation of some crystallites our data can be interpreted as the observation of the gap anisotropy with $\Delta_{\text{max}}/\Delta_{\text{min}} = 1.6$. We also note that, as seen from Fig. 4, the ratio $2\Delta_{\text{max}}/k_B T_c$ is close to the standard BCS value of 3.52.

As to the presence of a hybrid gap with s + g wave order parameter symmetry and point nodes in certain directions, we never observed gaps less than 1.5 meV. The results of point contact measurements in [3], giving $\Delta = 0.45\text{meV}$ along the a axis, give rise to some questions. Firstly, the dependence $\Delta(T)$ for the a directions looks at least atypical; secondly, the critical temperature in this direction was found to be two times less than in the bulk; and thirdly, even for the maximal gap, $2\Delta_{\text{max}}/k_B T_c = 2.86$, much lower than the BCS value. This raises the doubt of whether to take into account that nickel borocarbides are more likely superconductors with strong coupling. We note that the single crystals investigated in [3] had a significantly lower $T_c = 14.6\text{K}$, in comparison with the value 15.5K usually quoted in the literature. Thus, an insufficient sample quality is apparently responsible for the reported "anisotropy" of the SC order parameter in [3].

Considering the role of disorder in anisotropic superconductors, nonmagnetic impurity scattering has profound effects on hybrid s + g wave superconductors with point nodes. It is mentioned in [6] that a disorder-induced quasiparticle energy gap opens up even for infinitesimal scattering rates. This may be a reason why we did not observe any nodal features in the SC gap.

However, impurity scattering also decreases the critical temperature, which is not observed in our investigations. Thus, according to [6], a disorder-induced energy gap of about 10 K (1 meV) corresponds to a T_c reduction to 13 K.

Concerning the effect of the pressure produced by point-contact formation on the gap distribution, we expect that under such a pressure the critical temperature should also vary in the same way as the gap. However, no such variation is observed, suggesting that there is no measurable effect due to pressure in this experiment.

Let's consider the question of the realization of multiband superconductivity in RNi_2B_2C ($R = Y, Lu$), considered in [9]. We cannot distinguish whether the observed gap distribution is a consequence of anisotropy or a multiband electronic structure. In this connection, we note that the authors of Ref. [4], investigating point contact spectra of a $LuNi_2B_2C$ single crystal, found that the calculated theoretical curves better describe the experimental data when a two-gap adjustment is used, although in the $R_d(V)$ curves, only one gap minimum is visible. In so doing, the relation between the maximal and minimal gap was found to be around 1.75 in the c direction and 1.5 in the ab plane. This is close to the value found by us, $\mu_{max} = \mu_{min} = 1.6$. To this it is possible to add that our preliminary data after analysis of about 60 $R_d(V)$ spectra measured on a cleaved YNi_2B_2C single crystal also show a gap distribution. In this case for 80% of the contacts the gap is distributed in the same range from 1.5 meV to 2.4 meV, while for 20% of the contacts the gap ranged more from 2.5 meV to 3.0 meV, and one can discern maxima in the entire gap distribution at 2.0 meV and 2.4 meV. Interestingly, to the experimental $dV = dI$ curve for the c direction in $LuNi_2B_2C$ in Ref. [4] (Fig. 13), the authors used a gap distribution with two peaks also around 2.0 meV and 2.5 meV.

A prominent feature of a multiband superconductor is also the specific behavior of the excess current in the point contacts. In [13] it was revealed that in the two-band superconductor MgB_2 , the excess current has a strongly pronounced positive curvature in a magnetic field. In Fig. 7, the behavior of the SC gap and the excess current in a magnetic field for one of the YNi_2B_2C contacts is shown. It can be seen that, while the behavior of the gap is similar to that of the pair potential of a type II superconductor in the vortex state and has negative curvature [Fig. 7(a), closed squares and dotted curve], the excess current has a strong positive curvature [Fig. 7(b)]. A similar behavior of the gap and the excess current in a magnetic field was observed by us for several of the investigated contacts ($R_d(V)$ have been processed for four contacts). Another consideration is that a small gap has an almost linear decrease under a magnetic field [Fig. 7(a), open squares]. This is similar to the theoretical behavior of the small gap in MgB_2 calculated in [14]. Thus, our observation of the excess current and small gap

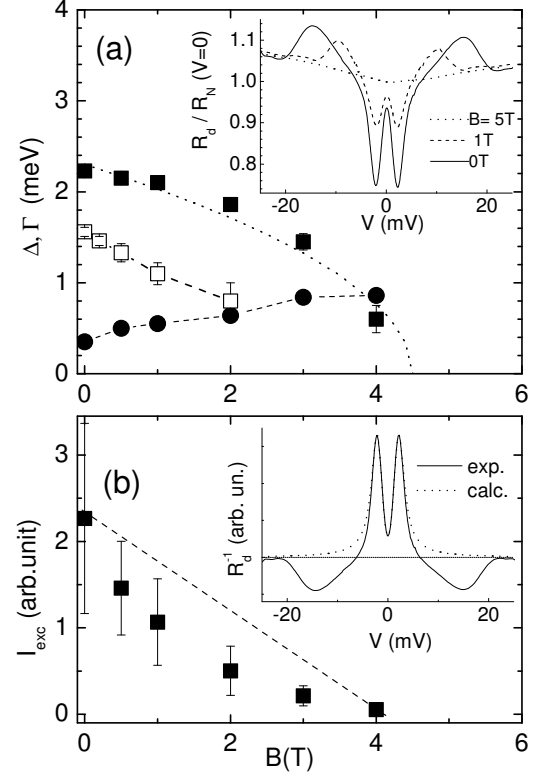


FIG. 7: (a) Calculated magnetic field dependences of (closed squares) and (closed circles) at $Z = 0.58$ for an YNi_2B_2C /Cu point contact ($R_0 = 2.8$, $T = 4.2$ K). Open squares show the magnetic field behavior of for another contact with small gap value. The dotted curve shows the behavior $\propto (1 - B/B_{c2})^{1/2}$ of the pair potential of a type II superconductor in the vortex state according to Abrikosov's theory. Dashed lines connect circles and open squares as guides to the eye. Inset: reduced experimental $R_d(V)$ in zero field and in magnetic fields of 1 T and 5 T. (b) Behavior of the excess current in a magnetic field. The inset shows symmetrized experimental and theoretical $R_d^{-1}(V)$ in zero field. The excess current was determined as the integral of the calculated $R_d^{-1}(V)$ after subtraction of the normal state conductivity (horizontal dashed line). Error bars were determined as the integral of the difference between theoretical and experimental $R_d^{-1}(V)$ curves. The greatest difference arises due to the presence of minima in the experimental $R_d^{-1}(V)$ curves at biases exceeding the gap energy.

behavior under a magnetic field may be taken in support of a multiband SC state in YNi_2B_2C .

CONCLUSION

Studies of the SC gap and its temperature dependence (T) in YNi_2B_2C have shown a distribution of values from $\mu_{min} = 1.5$ meV up to $\mu_{max} = 2.4$ meV,

however in all cases with a BCS-like (T) dependence. The observed $2\mu_{\text{ax}} = k_B T_c = 3.66$ is also close to the BCS value of 3.52, and the critical temperature in all cases corresponded to that of the \ln , thus excluding the possibility that the observations result from heterogeneity in the properties of the \ln . It is most probable that the distribution of the gap can be attributed to gap anisotropy, or to the multiband nature of the SC state in $\text{YNi}_2\text{B}_2\text{C}$. The positive curvature in the behavior of the excess current under applied magnetic field (Fig. 7(b)) tends to support the multiband scenario. Proceeding from the stated results, and also preliminary investigations of $\text{YNi}_2\text{B}_2\text{C}$ single crystals, the presence of point nodes in the SC order parameter of $\text{YNi}_2\text{B}_2\text{C}$ is considered to be unlikely. The analogous conclusion is reached also in a recent work [15] on the basis of the observation of a sudden disappearance of de Haas-van Alphen oscillations at the transition to the mixed state. Finally, in a recent preprint [16], the authors of Ref. [3] have modified their earlier claims and come to the conclusion from the analysis of the field variation of their $dV = dI$ spectra that the unconventional gap function observed in $\text{YNi}_2\text{B}_2\text{C}$ could originate from multiband superconductivity.

ACKNOWLEDGEMENTS

The support of the U.S. Civilian Research and Development Foundation for the Independent States of the Former Soviet Union (grant no. UP1-2566-KH-03), the Deutsche Forschungsgemeinschaft within SFB 463 "Rare earth transition metal compounds: structure, magnetism and transport" and of the National Academy of Sciences of Ukraine are acknowledged.

[1] K.-H. Müller and V.N. Narozhnyi, Rep. Prog. Phys. 64, 943(1008 (2001); K.-H. Müller, G. Fuchs, S.L. Drechsler and V.N. Narozhnyi, in: Magnetic and Superconduct-

- ing Properties of Rare Earth Borocarbides of the Type $\text{RNi}_2\text{B}_2\text{C}$, Handbook of Magnetic Materials, (Ed. K. H. J. Buschow), Vol. 14, pp. 199(305 (Elsevier North-Holland, 2002)).
- [2] P. Martinez-Samper, H. Suderow, S. Vieira, J. P. Brison, N. Luchier, P. Lejay, and P. C. Canfield, Phys. Rev. B 67, 014526 (2003).
- [3] P. Raychaudhuri, D. Jaiswal-Nagar, Goutam Sheet, S. Ramakrishnan, and H. Takeya, Phys. Rev. Lett. 93, 156802 (2004).
- [4] N. L. Bobrov, S. I. Beloborod'ko, L. V. Tyutrina, I. K. Yanson, D. G. Naulge, and K. D. D. Rathnayaka, Phys. Rev. B 71, 014512 (2005).
- [5] K. Maki, P. Thalmeier, and H. Won, Phys. Rev. B 65, 140502 (2002).
- [6] K. Maki, H. Won, and S. Haas, Phys. Rev. B 69, 012502 (2004).
- [7] K. Izawa, K. Kamata, Y. Nakajima, Y. Matsuda, T. Watanabe, M. Nohara, H. Takagi, P. Thalmeier, and K. Maki, Phys. Rev. Lett. 89, 137006 (2002).
- [8] Tuson Park, M. B. Salamon, Eun Mi Choi, Heon Jung Kim, and Sung-Ik Lee, Phys. Rev. Lett. 90, 177001 (2003).
- [9] S. V. Shulga, S.-L. Drechsler, G. Fuchs, K.-H. Müller, K. Winer, M. Heinecke, and K. Kug, Phys. Rev. Lett. 80, 1730 (1998).
- [10] Yu. G. Naidyuk and I. K. Yanson, Point Contact Spectroscopy, Springer Series in Solid-State Sciences, Vol. 145 (Springer, New York, 2004).
- [11] S. C. Wimbush, K. Hase, L. Schultz and B. Holzapfel, J. Phys.: Condens. Matter 13, L355 (2001).
- [12] I. I. Mazin, A. A. Golubov and B. Nadgorny, J. Appl. Phys. 89, 7576 (2001).
- [13] I. K. Yanson and Yu. G. Naidyuk, Low Temp. Phys. 30, 261 (2004); Yu. G. Naidyuk, O. E. Kvinnitskaya, I. K. Yanson, S. Lee, and S. Tajima, Solid State Commun. 133, 363 (2005).
- [14] A. E. Koshelev and A. A. Golubov, Phys. Rev. Lett. 90, 177002 (2003).
- [15] O. Ignatchik, T. Coey, J. Hagel, M. Jackel, E. Jobiliong, D. Souptel, G. Behr, and J. Wosnitza, J. of Magn. and Magn. Mat. 290-291, 424 (2005).
- [16] S. Mukhopadhyay, Goutam Sheet, P. Raychaudhuri, and H. Takeya, cond-mat/0412486.