

# Comment on "Comparison of the Cc and R3c space groups for the superlattice phase of $\text{Pb}(\text{Zr}_{0.52}\text{Ti}_{0.48})\text{O}_3$ "

J. Frantti

Materials and Structures Laboratory, Tokyo Institute of Technology,  
4259 Nagatsuta, Midori-ku, Yokohama, 226-8503, Japan

(Dated: April 14, 2024)

The two-phase (space groups Cc and Cm) structural model recently proposed for the modeling of the neutron powder diffraction pattern collected on  $\text{Pb}(\text{Zr}_x\text{Ti}_{1-x})\text{O}_3$  (PZT) sample with  $x = 0.52$  [R. Rangan, A. K. Singh, Ragini, and D. Pandey. Phys. Rev. B 71, 092101 (2005)] is shown to neglect the hkl dependent (anisotropic) line broadening. The most serious problem with this model is that it assigns octahedral tilts to a wrong phase. Instead of correctly taking the anisotropic line broadening into account, this model used low symmetry phases to minimize the residuals during Rietveld refinement. The essential features of a model taking the hkl dependent line broadening into account are summarized. It has already been reported that once the anisotropic line broadening, revealed by high resolution neutron powder diffraction instrument, is correctly taken into account the model with R3c and Cm space group symmetries describes all Bragg peaks and their intensities well [J. Frantti, S. Eriksson, S. Hull, V. Lantto, H. Rundlof, and M. K. Akihana. J. Phys.: Condens. Matter 15, 6031 (2003)]. It was further shown that the Cm + R3c model is consistent with the structural features observed at other compositions and temperatures, which is particularly important in the vicinity of the phase boundary. Also problems related to sample preparation and data collection are pointed out.

PACS numbers: 77.84.Dy 61.12.Ld 61.50.Ah 81.30.Dz

Recently, based on previously published neutron powder diffraction data<sup>1,2</sup>, a model which used two monoclinic phases (space group symmetries Cc and Cm) was proposed to describe the structure of  $\text{Pb}(\text{Zr}_x\text{Ti}_{1-x})\text{O}_3$  (PZT) with  $x = 0.52$ <sup>3</sup>. This model assigned a space group symmetries P4mm (at room temperature) or Cc (at low temperature) to the phase which was assigned to Cm symmetry in refs. 4 and 5. In addition, the phase, which traditionally has been assigned to the rhombohedral symmetry, was assigned to Cm symmetry. To understand the problems related to such a model and the reason why the use of space group Cc was previously rejected<sup>5</sup> it is necessary to summarize the crucial role of the hkl dependent line broadening for Rietveld refinement in the case of these materials. There is a high risk that erroneous space group symmetry assignments result in once this line broadening is compensated for by reducing the space group symmetry. For example, one can make the difference between measured and calculated diffraction intensities arbitrarily small by simply using space group P1 and increasing the primitive cell size until the difference vanishes below the desired value. In our opinion, a structural model which reduces the symmetries to 'model' the hkl dependent line broadening takes the disorder into account in a wrong way, since in this way the disorder is assigned to be a periodic disturbance extending through the crystal, obeying the space group symmetry. However, the hkl-dependent line broadening is an inherent property of PZT powders, and is already seen in tetragonal Ti-rich compositions. The same behaviour was observed in a closely related  $\text{Pb}(\text{Hf}_x\text{Ti}_{1-x})\text{O}_3$  (PHT) system with  $0.10 \leq x \leq 0.40$ , where the peak widths of the 001 reflections were twice as large as the widths of

h00 reflections<sup>6</sup>. It must be emphasized that no signs of symmetry lowering from the P4mm symmetry was observed in this high-resolution neutron powder diffraction study. Light scattering experiments revealed that both in the case of PZT and PHT samples deviations from the average symmetry were observed<sup>7,8,9</sup>. Although one could decrease the average symmetry to take these observations into account, a more realistic model is to assume that the average symmetry over a length scale of a few hundred nanometers is P4mm, and deviations from this symmetry occur in a local scale (of a few unit cells). The essential point here, too, is that these deviations are not periodical! It is also important to note that the Cm phase was identified by studying the peak split of the pseudocubic 110 reflections<sup>4</sup>. This peak split was beyond the resolution of the instrument used in ref. 3 and there is no way to recover the lost information. It does not matter how many 'new' refinements are carried out for the low-resolution data collected with insufficient counting time (note that neutron powder diffraction data in refs. 1,2 and 3 are the same). To solve the problem related to average symmetries it is necessary to carry out experiments with an appropriate instrument and carefully prepared sample. The role of the spatial composition variation (which in practice cannot be eliminated) in the vicinity of the phase boundary is an old and still a valid explanation for the two phase 'co-existences' and also partially explains the hkl-dependent line broadening. It was also worth of trying to find a simple model which is consistent with other compositions and temperatures<sup>5,12</sup>. These aspects are shortly reviewed below.

a. Spatial composition variation. Traditionally, the two-phase 'co-existence', observed in room temperature

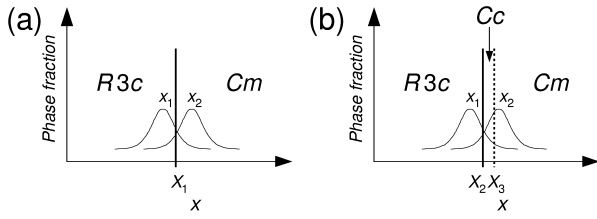


FIG. 1: The consequences of the spatial composition variation (at fixed temperature and pressure) in the case of two samples with average compositions  $x_1$  and  $x_2$  in the vicinity of (a) the phase boundary separating R3c and Cm phases (at  $x_1$ ) and (b) two phase boundaries separating R3c and Cc (at  $x_2$ ) and Cc and Cm phases (at  $x_3$ ).

PZT in the vicinity of the morphotropic phase boundary (MPB), has been explained by the composition variation. In the context of low temperature symmetries the role of spatial composition variation was discussed in refs. 5 and 12. The crystal symmetry of Zr rich PZT ceramics is R3c<sup>12,13,14</sup>, except for the compositions with  $x \approx 1$ . Since spatial composition variation cannot be completely eliminated, there must exist two phases in the vicinity of MPB. To allow the existence of Cc phase necessitates that there should be a narrow region in the  $x$ - $T$  plane where this phase is stable or metastable. Now, if we were to explain the existence of Cc phase, two phase boundaries located somewhere between  $0.52 < x < 0.54$  should be assumed to exist, see Fig. 1 (b). This in turn, once the spatial composition variation is taken into account, leads to three phase 'co-existence'. We preferred the simplest Cm + R3c model (corresponding to Fig. 1 (a)), since it was able to explain the experimental observations in simplest terms. At low temperature ( $4 \text{ K}^{12}$  or  $10 \text{ K}^5$ ) the phase fraction of the Cm phase was monotonically decreasing with  $x$  increasing from 0.52 to 0.54, which in turn implies that two-phase 'co-existence' is predominantly due to the spatial composition variation. Other factors include stresses, which probably exist in the grain boundaries. It is worth to point out that the model proposed in ref. 3 was ruled out also in a recent paper, see the last paragraph in ref. 15. After all, the only difference between our model and the model proposed in ref. 15 is that we used R3c symmetry (corresponding to two lattice parameters and four atomic coordinates), while they used Cc symmetry (corresponding to four lattice parameters and twelve atomic coordinates, if constraints are not used), a subgroup of R3c space group. Thus, the model proposed by us and the model proposed in ref. 15 assigned octahedral tilts (evidenced by superlattice reflections) to the same phase. Octahedral tilts are crucial once the structural changes versus temperature, composition or pressure are studied. Somewhat surprisingly, the space group symmetries of the two phases were rather arbitrarily interchanged in refs. 3 and 10. This model immediately runs into trouble, as the octahedral tilts are assigned to a wrong phase, see below.

In addition, there have been reports claiming that dielectric measurements support Cc phase (for example, see ref. 1). In this context we note that the samples studied in refs. 3 and 10 contained a nonidentified impurity phase(s), as was revealed by the peaks at around 28 and 35 two-theta degrees (corresponding to d spacings 3.18 Å and 2.56 Å, respectively). This implies that the composition was not well known and there is no way to avoid compositional and structural inhomogeneities. Although this non-perovskite phase was clearly observable, it was neglected in the Rietveld refinement model considered in ref. 10, which in turn results in an error in the structural parameters of the perovskite phase(s). This is related to the fact that the diffraction pattern shown in ref. 10 (reported to have  $x = 0.52$ ) is reminiscent to our diffraction pattern with  $x = 0.53$ . In contrast, our diffraction pattern with  $x = 0.52$  (see ref. 11) and the diffraction pattern of the  $x = 0.52$  sample reported in refs. 15 and 4 were reminiscent. It should also be understood that dielectric measurements do not suit for a space group determination. Although the dielectric measurements can provide valuable information in the case of single phase samples, particular care is necessary once multiphase samples are studied. Anomalies observed in a dielectric constant versus temperature measured from a two or three phase ceramic bulk samples (see ref. 17) do not provide reliable evidence that one of the phases has undergone a phase transition from Cm to Cc phase.

b. Anisotropic line broadening. The anisotropic line broadening was ascribed to the spatial composition variation resulting in 'microstrain' (i.e., Zr substitution for Ti creates local strains which in turn contributes to the hkl dependent line broadening)<sup>12</sup>. In addition, rather strong diffuse scattering is commonly observed between the h00 and 00h Bragg reflections, which was assigned to Pb ions displaced toward h110i directions. This latter feature is somewhat puzzling, as it adds intensity to certain diffraction peaks, which results in an asymmetric profile. For example, the larger and smaller d-spacings sides of the pseudo-cubic 200 and 002 reflections, respectively, gain intensity. In ref. 3 Cm phase was practically used to model the intensity not only due to the crystalline phase, but also due to the diffuse scattering and due to the main crystalline phase. Despite the increased number of refined parameters, the residuals were still rather high and the differences between different models compared were marginal (for instance,  $R_{\text{exp}}$  was lowest for the R3c + Cm model which was rejected in ref. 3).

Although a reasonable structure refinement for medium resolution data collected on PZT samples with  $x \approx 0.50$  could be obtained using a lineshape which ignores anisotropic line broadening, the situation was quite different for high resolution facilities, particularly once the data was collected on two phase samples (the present case). In such a case it was essential to use an appropriate profile function. Now, if the anisotropic line broadening is neglected, the fit in the case of certain weak peaks becomes slightly worse (as was observed to be the case

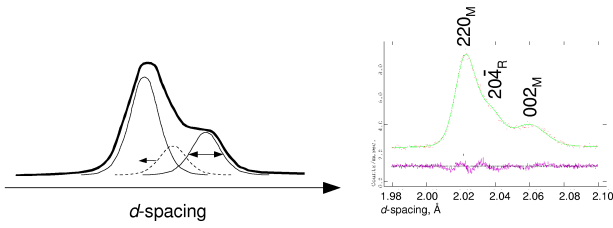


FIG. 2: Left panel: Schematic illustration of the way how the neglect of anisotropic line broadening affects the position of the rhombohedral peaks: once the rightmost peak broadens, it pushes the rhombohedral peak (middle) towards smaller d-spacing. Right panel: Observed and computed high resolution neutron powder diffraction profile collected on PZT with  $x = 0.53$  at 4 K. Pseudo-cubic 200 reflection region is shown. Note that the  $002_M$  peak (Cm phase) at around 2.06 Å is significantly broader than the  $220_M$  (Cm phase) peak at around 2.02 Å. Now, the position of the rhombohedral  $204_R$  peak depends on the way the line broadening is taken into account.

of weak superlattice reflections, which are less weighted in the refinements). The reason for this is illustrated in Fig. 2: in order to improve the fit corresponding to the strong pseudo-cubic 200 reflections, during the refinement the position of R3c reflection is shifted toward higher d-spacings, which in turn resulted in a small shift of the weak peaks at 2.44 and 1.06 Å (in a case of the data shown in ref. 3 the latter peak was almost at the level of noise and the Cc + Cm model assigns more reflections than there are data points in this region). The anisotropic line broadening was not limited to the d-spacing at around 2 Å, and similar mechanism was seen at other d-spacings.

c. Previous high resolution neutron powder diffraction results. The anisotropic line broadening was the reason to carry out a subsequent study using a high resolution neutron powder diffraction instrument (which reveals the anisotropic line broadening particularly clearly and allows a distinction between average symmetry lowering and a defect related anisotropic line broadening to be done, in contrast to the low- or medium resolution constant wavelength neutron diffraction facilities)<sup>12</sup>.

In addition, we increased Zr content,  $x = 0.54^{12}$  (although it definitely was possible to tailor reflections using the Cm + R3c model also in the case of  $x = 0.52$  and  $x = 0.53$  samples). This allowed a more reliable refinement and symmetry identification to be done by studying the changes in phase fractions versus temperature. Importantly, for these compositions it has been found that oxygen octahedra tilts increase with increasing  $x$  (ref. 14) and decreasing temperature (this feature is discussed in refs. 18 and 5). We also note that previously Cc was proposed to be space group symmetry corresponding to high isotropic pressure<sup>16</sup>, whereas our work was concentrating on the determination of space group symmetries versus composition and temperature at ambient pressure. Now, PZT sample with  $x = 0.54$  provided a test for clarifying which phase is the preferred one at low temperature. To model the peak profiles, GSAS<sup>19</sup> lineshape 4 by Stephens<sup>20</sup> was used. As was seen in ref. 12, once the crystal contracts with decreasing temperature the R3c phase was favoured (and Cm phase did not transform to Cc phase, as one could expect from the model proposed in ref. 3). Thus, when the oxygen octahedra had almost no chance to contract, they were tilt towards opposite directions along the pseudo-cubic 111 axis (tilt system  $a \parallel a \parallel a$ ). This tilt results in a decrease of the volume of cuboctahedra around Pb ions. Changes evidencing Cc symmetry (and the corresponding tilt system) were not observed. Indeed, the phase fraction of Cm phase (which was assigned to Cc symmetry in ref. 3) decreased with decreasing temperature, whereas R3c phase fraction significantly increased with decreasing temperature. This can be confirmed even by a naked eye, although the results of refinements were also given. The intensity of the peak at around 1.06 Å was increasing with decreasing temperature, which further confirmed that its origin is the phase assigned to R3c phase. Also the peak at around 1.06 Å was well fitted by R3c symmetry.

As a summary, we do not find support for Cm + Cc model proposed in ref. 3. Instead, we still consider that Cm + R3c provides a sufficient low temperature structural model for PZT with composition in the vicinity of the morphotropic phase boundary.

Electronic address: jfrantti@mltitech.ac.jp

<sup>1</sup> R. R. Anjan, S. K. Mishra, D. Pandey and K. Kennedy. Phys. Rev. B 65, 060102 (2002).

<sup>2</sup> D. M. Hatch, H. T. Stokes, R. R. Anjan, Ragini, S. K. Mishra, D. Pandey, and B. J. Kennedy, Phys. Rev. B 65, 212101 (2002).

<sup>3</sup> R. R. Anjan, A. K. Singh, Ragini, and D. Pandey. Phys. Rev. B 71, 092101 (2005).

<sup>4</sup> B. Noheda, D. E. Cox, G. Shirane, J. A. Gonzalo, L. E. Cross and S-E. Park. Appl. Phys. Lett. 74, 2059 (1999); B. Noheda, J. A. Gonzalo, L. E. Cross, R. Guo, S-E. Park, D. E. Cox, and G. Shirane. Phys. Rev. B 61, 8687 (2000).

<sup>5</sup> J. Frantti, S. Ivanov, S. Eriksson, H. Rundlof, V. Lantto, J. Lappalainen, and M. Kakihana. Phys. Rev. B 66, 064108 (2002).

<sup>6</sup> J. Frantti, Y. Fujjoka, S. Eriksson, S. Hull and M. Kakihana. Neutron powder diffraction study of  $\text{Pb}(\text{Hf}_{1-x}\text{Ti}_x)\text{O}_3$  ceramics ( $0 \leq x \leq 0.50$ ), submitted.

<sup>7</sup> J. Frantti, V. Lantto, S. Nishio and M. Kakihana. Phys. Rev. B 59, 12 (1999).

<sup>8</sup> J. Frantti, J. Lappalainen, S. Eriksson, V. Lantto, S. Nishio, M. Kakihana, S. Ivanov, and H. Rundlof. Jpn. J. Appl. Phys. 38, 5679 (1999).

<sup>9</sup> J. Frantti, Y. Fujjoka, S. Eriksson, V. Lantto, and M. Kak-

- ihana. *Journal of Electroceramics* 13, 299 (2004).
- <sup>10</sup> Ragini, R. Ranjan, S. K. Mishra, and D. Pandey, *J. Appl. Phys.* 92, 3266 (2002).
  - <sup>11</sup> J. Frantti, J. Lappalainen, S. Eriksson, V. Lantto, S. Nishio, M. Kakinana, S. Ivanov, and H. Rundlof. *Jpn. J. Appl. Phys.* 39, 5697 (2000).
  - <sup>12</sup> J. Frantti, S. Eriksson, S. Hull, V. Lantto, H. Rundlof, and M. Kakinana. *J. Phys.: Condens. Matter* 15, 6031 (2003).
  - <sup>13</sup> C. Michel, J. M. Moreau, G. D. Achenbach, R. Gerson, and W. J. James, *Solid State Commun.* 7, 865 (1969).
  - <sup>14</sup> D. L. Corker, A. M. Glazer, R. W. Whitmore, A. Stallard, and F. Fauth. *J. Phys. Condens. Matter* 10, 6251 (1998).
  - <sup>15</sup> D. E. Cox, B. Noheda, and G. Shirane. *Phys. Rev. B* 71, 134110 (2005).
  - <sup>16</sup> J. Rouquette, J. Haines, V. Bomand, M. Pintard, Ph. Pappet, W. G. Marshall, and S. Hull. *Phys. Rev. B* 71, 024112 (2005).
  - <sup>17</sup> Ragini, S. K. Mishra, D. Pandey, H. Lemmens, and G. Van Tendeloo. *Phys. Rev. B* 64, 054101 (2001).
  - <sup>18</sup> N. W. Thomas and A. Beitollahi. *Acta Crystallogr., Sect. B: Struct. Sci.* 50, 549 (1994).
  - <sup>19</sup> A. C. Larson and R. B. Von Dreele *General Structure Analysis System*, LANSCE MS-H 805, Los Alamos National Laboratory, Los Alamos, NM 87545 (2000).
  - <sup>20</sup> P. W. Stephens. *J. Appl. Crystallogr.* 32 281 (1999).