

# Non-universality in Micro-branching Instabilities in Rapid Fracture: the Role of Material Properties

Eran Bouchbinder and Itamar Procaccia

Dept. of Chemical Physics, the Weizmann Institute of Science, Rehovot 76100, Israel

In spite of the apparent similarity of micro-branching instabilities in different brittle materials, we propose that the physics determining the typical length- and time-scales characterizing the post-instability patterns differ greatly from material to material. We offer a scaling theory connecting the pattern characteristics to material properties (like molecular weight) in brittle plastics like PMMA, and stress the fundamental differences with patterns in glass which are crucially influenced by 3-dimensional dynamics. In both cases the present *ab-initio* theoretical models are still too far from reality, disregarding some fundamental physics of the phenomena.

More than a decade of relatively high precision experiments on rapid crack propagation in brittle materials has ignited the interest of the physics community [1]. It appears that one important prediction of "Linear Elasticity Fracture Mechanics" [2], stating that cracks will accelerate smoothly as they lengthen until they reach their asymptotic velocity (bounded either by the loading conditions or by the Rayleigh speed  $c_R$ ), is in fundamental contradiction with experiments. In thin brittle plates of width  $W$  (see the typical geometry in Fig. 1;  $W$  is in the  $z$  direction, with length in  $x$  and height in  $y$  much larger than  $W$ ), at some finite fraction of the Rayleigh speed, the smooth dynamics of the crack evolving in the  $x$  direction is marred by the appearance of micro-branches in the  $x-y$  plane that do not cut through the whole width  $W$ . These micro-branches have a typical length  $\lambda_b$ , a typical width  $\lambda_z \ll W$  and they appear to recur with an average periodicity. We will refer to this recurrence scale as "the scale of noisy periodicity"  $\lambda$ . The nature of this length-scale and the physics that determine it are the subjects of this Letter. In glass this scale appears to range between the measurement resolution ( $\sim 1 \mu\text{m}$ ) and a few mm [4], while in PMMA between tens and hundreds  $\mu\text{m}$  [3], depending on the material properties and the experimental conditions.

As is well known, linear elasticity fracture mechanics has no typical scale, and thus the appearance of such a scale is yet another demonstration of the need to modify this theory in the context of dynamic fracture. Indeed, there exist concepts in the classical theory of crack propagation that can be used to form a length scale. Recall that in the classical theory one asserts that as a crack of length  $L$  propagates at velocity  $v$  under loading conditions  $\sigma$ , the energy  $G(\sigma; L; v)$  released from the stressed material streams into the tip region where it is compensated by the total dissipation  $\dot{\mathcal{D}}(v)$ ,

$$G(\sigma; L; v) = \dot{\mathcal{D}}(v) : \quad (1)$$

The dissipation function  $\dot{\mathcal{D}}(v)$  is not computable from elasticity theory, but it can be measured in experiments, (essentially by using Eq. (1)). Equipped with this function and the Young modulus  $E$  of the material we can

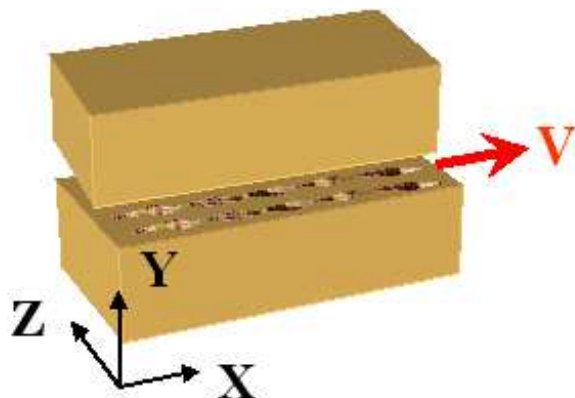


FIG. 1: Typical geometry of a dynamically generated crack, with the side branches that result from the instability leaving their mark on the faces of the crack.

form a (velocity-dependent) scale from

$$\lambda(v) = \dot{\mathcal{D}}(v)/E : \quad (2)$$

To get a rough estimate of the resulting scale, we use the data for PMMA determined in [1] near the onset of the microbranching instability:  $\dot{\mathcal{D}}(v) \sim 3000 \text{ J/m}^2$  and  $E \sim 3 \cdot 10^9 \text{ N/m}^2$ . This predicts  $\lambda(v)$  in the  $\mu\text{m}$  range; a similar estimation for glass yields a nm scale. We thus understand that the scale computed in Eq. (2) may be relevant for PMMA, but appears utterly out of range for glass, where the observed scales of noisy periodicity must be sought elsewhere, as we discuss below. Given information about the largest stress value that marks the breakdown of the linear theory, say  $\sigma_m$ , another length-scale can be constructed as

$$\lambda_m(v) = E / \sigma_m^2 : \quad (3)$$

We estimate  $\sigma_m$  by the yield stress of the material. For the materials under discussion the resulting length-scale is typically two orders of magnitude larger than (2), putting it right in the range of scales of noisy periodicity for PMMA, but still off range for glass. We continue now to assess the relevance of (2) or (3) to PMMA. Obviously, the dissipation  $\dot{\mathcal{D}}(v)$  in PMMA should be a strong

function of the molecular weight  $M$  of the polymers that make the material, due to the increased density of entanglements of the polymer chains. Indeed, a calculation of the  $M$  dependence of  $\lambda$  in quasi-static conditions exists [5], with the resulting prediction

$$(\lambda = 0) = e^{M_0/M}; \quad (4)$$

where  $M_0$  is the smallest molecular weight below which the polymers do not contribute to  $\lambda$ . On the other hand, the Young modulus  $E$  and the yield stress were shown [6, 7] to be  $M$ -independent.

The length (2) (or 3) will be dressed by dynamical effects, which we introduce in the form

$$\lambda(v) = e^{M_0/M} f(v/c_R); \quad (5)$$

To proceed, we adopt the scaling assumption that  $\lambda(v)$  is the only typical scale in the problem, characterizing the length  $\lambda_b$  of micro-branches in the  $x-y$  plane as well as  $\lambda$  in the  $x-z$  plane. In addition, we will assert that in PMMA (in contrast to glass, and see below for further discussion) the relevant length-scales are determined by a competition between the side micro-branch and the main crack, without important dynamical coupling to the third dimension. In this respect the mechanism underlying the repetitive nature of the microbranching process in PMMA is qualitatively similar to the 2-dimensional branching model developed recently in [8]. In this model, the local competition between the side branch and the main crack temporarily slows the main crack below the relevant branching velocity. When the main crack regains the critical velocity another side branching event occurs (see Fig. 7 in [8]). It was found (see Fig. 6 in [8]) that the velocity dependence of  $\lambda_b$  has the following form

$$\lambda_b(v) = \lambda_b(v_c) [1 + (v - v_c)/c_R]; \quad (6)$$

Here  $\lambda_b(v_c)$  is the finite length of the side branch which occurs at threshold and  $\lambda$  is a dimensionless coefficient. In [8] this length was introduced by hand to represent the scale over which linear elasticity theory is not applicable (the so-called process zone); here we take it as the undressed length proportional to  $\exp(-M_0/M)$ . Collecting our assumptions together we present the prediction for the scale of noisy periodicity and the length of the micro-branches in PMMA:

$$\lambda(v; M) = \lambda_b(v; M) e^{M_0/M} [1 + \frac{v - v_c}{c_R}]; \quad (7)$$

Note that if indeed the scale  $\lambda_b(v_c)$  is physically identified with the process zone, it may have a velocity dependence of its own. If this velocity dependence is linear, the prediction (7) remains unchanged.

It is possible to test this major prediction against available experiments. The influence of the mean molecular weight  $M$  on the scale of noisy periodicity in PMMA was

studied in [9] at a given average velocity. Fig. 2 displays their experimental data for  $M \log(\lambda)$  as a function of  $M$  (taken from Table 1 in [9]). The almost perfect lin-

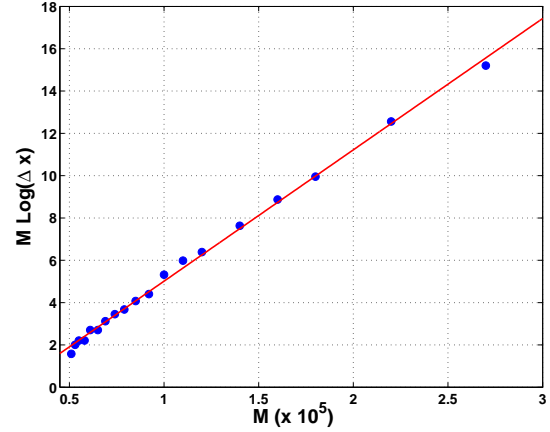


FIG. 2:  $M \log(\lambda)$  as a function of  $M$ . The filled circles are the experimental data taken from [9] (see Table 1) and the solid line is a linear fit.

earity of the graph lends a strong support to the  $M$  dependence in our scaling law. Next, the branch length at a fixed mean molecular weight as a function of the normalized mean velocity for PMMA is shown in Fig. 3. It is clear that  $\lambda_b$  is linear in  $v$  as predicted by our scaling relation. Moreover, the fit indicates the existence of a finite length  $\lambda_b(v_c) \approx 30 \mu\text{m}$  as predicted by the scaling law. This finite length is determined uniquely in this graph once  $v_c$  is known. The value of  $\lambda_b(v_c)$  is confirmed in §3.

In summary, the scale of noisy periodicity in PMMA appears to be adequately described by a scaling theory in which the main scale depends on the material properties  $E$  and possibly  $\nu$ , dressed by dynamical effects which are not fundamentally dependent on coupling to

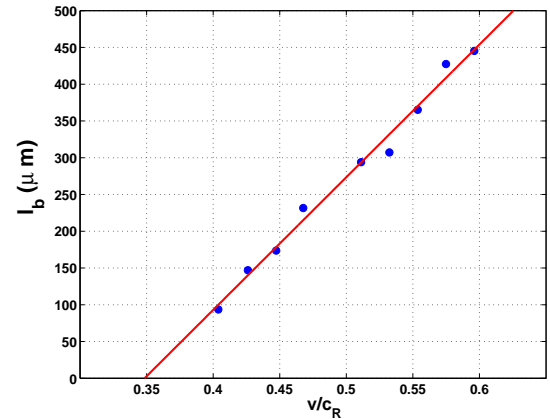


FIG. 3: The branch length  $\lambda_b$  as a function of the mean normalized velocity for PMMA. Data taken from [10]. The solid line represents the linear fit with  $\lambda_b(v_c) \approx 30 \mu\text{m}$ ,  $v_c \approx 0.365 c_R$ , and  $\lambda_b(v_c) \approx 30 \mu\text{m}$ .

dynamics in the third dimension. There is nothing like that in glass. First, we remarked before that the length-scales (2) and (3) are in 1-100 nm range, whereas the noisy periodicity in glass appears on scales up to a few mm. Moreover, we will point out now that there is no typical scale of noisy periodicity in glass experiments; the distances between micro branching events can vary over three orders of magnitude (from the measurement resolution to the scale of the width  $W$ ) and they are determined by a dynamical mechanism that rests crucially on the dynamics of the crack front in the narrow third dimension along the width  $W$ .

In glass, once a micro-branch forms at a location  $z$  along the width of the sample and with a width  $z$ , the next branching events fall very precisely along a strip of width  $z$  localized at the same location  $z$ ; see Fig. 4 as an example. The crucial phenomenon that is responsible for these highly correlated structures is the interaction of the crack front with spatial heterogeneities (regions of variable  $\nu$ ). These can generate non-decaying waves that travel with velocity  $c_{FW}$  (relative to the heterogeneity) on the front as it propagates [11]. Plane numerical simulations [12] have shown that the interaction of the front with an asperity leads to a velocity overshoot exactly ahead of the interaction site, see Fig. 5.

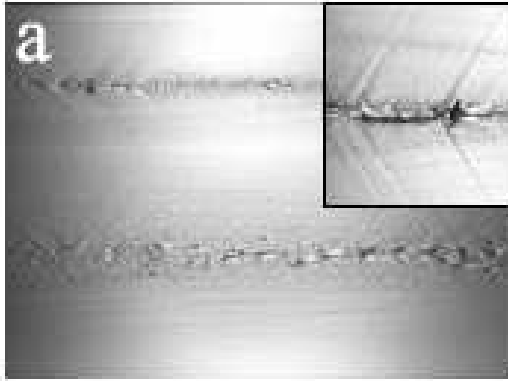


FIG. 4: The correlated micro-branches in glass samples. Each series of micro-branches is localized in a strip of width  $z$ , and has a noisy periodicity  $x' \sim 4-5 z$ . Adapted from [4].

Since the creation of a micro-branch increases locally, one expects the generation of front waves, as indeed was observed in glass and can be seen in the inset of Fig. 4. The resulting velocity overshoot just ahead of the micro-branching event was interpreted by Sharon, Cohen and Fineberg [4] as the source of the well-defined lines of micro-branches in glass. In this picture, the creation of a micro-branch reduces locally the velocity of the main crack below the micro-branching velocity, but this velocity is reached again due to the velocity overshoot just ahead. The typical time for this process is the time needed for the front wave to travel a distance of

the order of the width of the micro-branch  $z$ . Since the velocity of the front wave along the front is  $\frac{c_{FW}^2}{v^2}$  one obtains

$$\frac{z(v)}{c_{FW}^2 v^2} : \quad (8)$$

Therefore, the noisy periodicity scale  $x$  is estimated as

$$x(v) = \frac{z(v) v}{c_{FW}^2 v^2} : \quad (9)$$

Since the combination  $v = \frac{c_{FW}^2}{c_R^2} v^2$  is a slowly increasing function of  $v$  ( $0.94 c_R / c_{FW}(v) c_R$ ) in the relevant range of velocities, one expects the ratio  $x(v) = z(v)$  to be nearly constant and this is indeed the case as shown in [4], where the relation is stated to be  $x' \sim 4-5 z$ . The point that we want to stress here is that in contradistinction with PMMA, in glass there exist no typical scale for the noisy periodicity.  $x(v)$  can be anything, depending on the local asperity size that nucleated the first micro branch of size  $z(v)$ . After that the dynamics will sustain repeated micro-branches every  $x' \sim 4-5 z$ . The only thing that can happen is that  $z(v)$  might increase as a function of  $v$ , which is the last issue that we discuss.

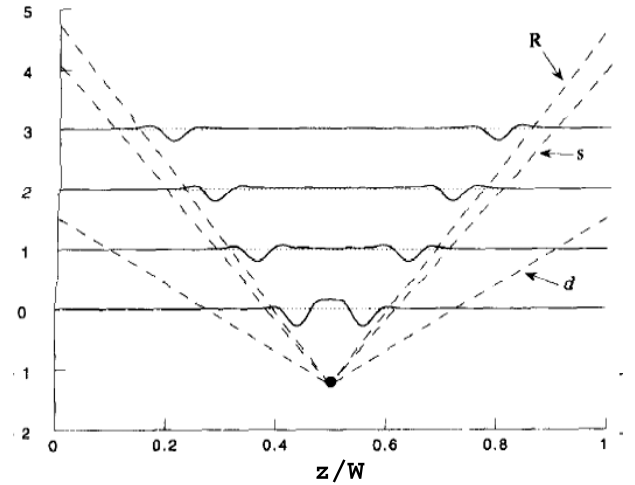


FIG. 5: The front waves generated by the interaction of the front with an asperity. The front velocity profile is plotted at constant time intervals. Note the velocity overshooting just ahead of the asperity.  $d$ ;  $s$ ;  $R$  are the cones generated by the dilatational, shear and Rayleigh waves, respectively. The relation  $c_{FW} = c_R$  is apparent. Adapted from [12].

As noted earlier, Eq. 1 predicts that cracks accelerate smoothly towards their asymptotic velocity. A crucial assumption leading to this prediction is that a single crack whose front is essentially a point (there is translational invariance in the  $z$ -axis) can expend the extra energy owing to its tip by adjusting its velocity and increasing the kinetic energy of its surroundings. This

assumption holds up to  $v_c$ , but breaks down for  $v > v_c$ . At the onset of instability a multiple crack state is formed by repetitive frustrated micro-branching events and these micro-branches break the translational invariance in the third dimension, occupying a finite width  $z \sim W$ . The essence of the instability is that the additional energy supply is expended on creating more surface area per unit crack extension, even at a constant velocity. This process introduces new dynamic variables to the problem: the number of coexisting branches  $n$ , the morphology of the branches in the  $x$ - $y$  planes and their width  $z$ . All these variables contribute to the additional energy dissipation per unit crack extension. It was shown [13] that the total surface energy created per unit crack extension is proportional to the total energy release rate, implying that in this regime the fracture energy  $\gamma(v)$  is constant, independent of the velocity. Assuming that  $z$  characterizes the width of the micro-branches as long as they exist, we can write

$$W G(v) = z(v) f(n(v); \dots) + W \quad ; \quad (10)$$

where the right hand side is a sum of the dissipative contributions from the micro-branches as well as from the main crack, respectively. The function  $f(n(v); \dots)$  depends on the number of coexisting micro-branches, their morphology and maybe other dynamic variables. The last relation can be rewritten as

$$z(v) = f(n(v); \dots) W \frac{G(v)}{1 - G(v)} \quad ; \quad (11)$$

Although  $f(n(v); \dots)$  is not known in adequate detail, making the last equation somewhat tentative, we can still draw relevant qualitative conclusion. Since  $G(v)$  is known from experiments to be a strongly increasing function of  $v$  [13], we can safely expect that  $z(v)$  is also a strongly increasing function of  $v$ . This expectation is supported by the data; the dependence of  $z$  on the mean velocity  $v$  for both PMMA and glass is shown in Fig. 6. We stress that in glass the increase in  $z(v)$  must affect the scale of noisy periodicity, whereas in PMMA it does not. In glass, the dynamics along the third dimension are strongly coupled to the dynamics in the longitudinal direction (by the front waves mechanism) and the dynamic length-scale  $z$  controls all the other length-scales. In PMMA, the dynamics along the third dimension are only weakly coupled to the dynamics in the longitudinal direction, where the length-scales are determined by material properties and the elastodynamic competition between the micro-branches and the main crack.

In summary, models of dynamic fracture that are developed based on the continuum equations supplemented by criteria for crack evolution can hope to adequately describe the dynamic instabilities only if the physics that determines the fundamental scales were incorporated. In glass it appears that without adequate treatment of the

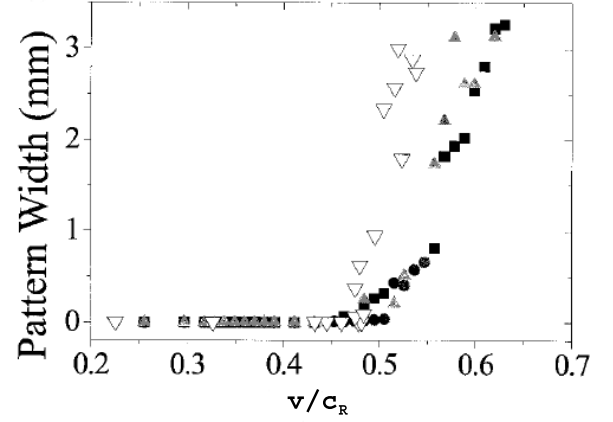


FIG. 6: The pattern width  $z$  as a function of the normalized mean velocity  $v/c_R$  for PMMA (filled symbols) and glass (empty symbols). Adapted from [10].

third dimension and the physics of the crack front, not much insight into the micro-branching process can be gained. In PMMA the coupling to the third dimension might be weaker, but one should resolve how the material parameters appear in the continuum description. Completely different scaling laws appear in these two materials due to the different mechanisms that control the scale of noisy periodicity; probably other materials may increase the richness of the phenomenology. It might be worthwhile to stress less the presence of universal features and more the interesting physics that can be learned even with simple scaling theories.

- 
- [1] see M. Marder and J. Fineberg, Phys. Rep. 313, 1 (1999) and references therein.
  - [2] L.B. Freund, Dynamic Fracture Mechanics, (Cambridge, 1998).
  - [3] E. Sharon and J. Fineberg, Phys. Rev. B 54, 7128 (1996).
  - [4] E. Sharon, G. Cohen and J. Fineberg, Phys. Rev. Lett. 88, 085503 (2002).
  - [5] A.G. Mikos and N.A. Peppas, J. Chem. Phys. 88, 1337 (1988).
  - [6] R.P. Kusy and D.T. Tumer, Polymer 17, 161 (1976).
  - [7] P.I. Vincent, Polymer 1, 425 (1960).
  - [8] E. Bouchbinder, J. Mathiesen, I. Procaccia, Phys. Rev. E, In press (2005). See also: cond-mat/0410448.
  - [9] R.P. Kusy and D.T. Tumer, Polymer 18, 391 (1977).
  - [10] E. Sharon and J. Fineberg, Phil. Mag. B 78, 243 (1998).
  - [11] S. Ramakrishnan and D.S. Fisher, Phys. Rev. Lett. 79, 877 (1997).
  - [12] J.W. Morrissey and J.R. Rice, J. Mech. Phys. Solids 46, 467 (1998).
  - [13] E. Sharon, S.P. Gross and J. Fineberg, Phys. Rev. Lett. 76, 2117 (1996).