

Half-metallic properties of atomic chains of carbon-transition metal compounds

S. Dag,¹ S. Tongay,¹ T. Yildirim,² E. Durgun,¹ R. T. Senger,¹ C. Y. Fong,³ and S. Ciraci¹,

¹Department of Physics, Bilkent University, Ankara 06800, Turkey

²NIST Center for Neutron Research, National Institute of Standards and Technology, Gaithersburg MD 20899

³Department of Physics, University of California, Davis, CA 95616, USA

(dated: December 25, 2021)

We found that magnetic ground state of one-dimensional atomic chains of carbon-transition metal compounds exhibit half-metallic properties. They are semiconductors for one spin-direction, but show metallic properties for the opposite direction. The spins are fully polarized at the Fermi level and net magnetic moment per unit cell is an integer multiple of Bohr magneton. The spin-dependent electronic structure can be engineered by changing the number of carbon and type of transition metal atoms. These chains, which are stable even at high temperature and some of which keep their spin-dependent electronic properties even under moderate axial strain, hold the promise of potential applications in nanospintronics.

PACS numbers: 61.46.+w, 72.25.-b, 75.50.Cc, 71.20.Be

Spin-dependent electronic transport has promised revolutionary applications using giant-magneto-resistance in magnetic recording and nonvolatile memories [1, 2, 3]. Half-metals (HM) [4, 5] are a class of materials, which exhibit spin-dependent electronic properties relevant to spintronics. In HMs, due to broken spin-degeneracy, energy bands $E_n(k; \uparrow)$ and $E_n(k; \downarrow)$ split and each band accommodates one electron per k -point. Furthermore, they are semiconductor for one spin direction, but show metallic properties for the opposite spin direction. Accordingly, the difference between the number of electrons of different spin-orientations in the unit cell, $N = N_{\uparrow} - N_{\downarrow}$, must be an integer and hence the spin-polarization at the Fermi level, $P = D(E_F; \uparrow) - D(E_F; \downarrow) / [D(E_F; \uparrow) + D(E_F; \downarrow)]$, is complete [5]. This situation is in contrast with the ferromagnetic metals, where both spin-directions contribute to the density of states at E_F and spin-polarization P becomes less than 100%. Even though three-dimensional (3D) ferromagnetic Heusler alloys and transition-metal oxides exhibit HM properties [6], they are not yet appropriate for spintronics because of difficulties in controlling stoichiometry and the defect levels destroying the coherent spin-transport. Zinc-blende (ZB) HMs with high magnetic moment and high Curie temperature $T_c > 400\text{K}$ (such as CrAs, and CrSb in ZB structure) have been grown only in thin-film forms [7]. More recently, it has been predicted that four new ZB crystals can be HM at or near their respective equilibrium lattice constants [8].

In this letter, we report that very simple and stable one-dimensional (1D) structures, such as linear atomic chains of carbon-transition metal compounds, i.e. $C_n(TM)$, show half-metallic properties. The prediction of half-metallic behavior in 1D atomic chains is new and of fundamental interest, in particular in the field of fermionic excitations with spin degree of freedom. Besides, the present finding may lead to potential applications in the rapidly developing field of nanospintron-

ics, such as tunnelling magnetoresistance, spin valve, and nonvolatile magnetic devices.

In earlier transport studies, the spin-direction of conduction electrons was generally disregarded, in spite of the fact that spin orientation of electrons decays much slower than their momentum [3]. Magnetic ground state of TM-adsorbed single-wall carbon nanotubes (SWNT) [9, 10], spontaneous spin-polarized electron transport through nitrite TM wires [11], and oscillatory spin-polarized conductance and spin-valve effect through nitrite carbon wires capped with Co atoms in between gold electrodes [12] have been treated recently. However, half-metallicity predicted in periodic $C_n(TM)$ is a behavior fundamentally different from those magnetic properties found in earlier systems in Ref. [9, 10, 11, 12] and is a novel feature of 1D systems that allows both semiconducting and metallic properties coexisting in the same structure.

Our predictions are obtained from the first-principles pseudopotential plane wave calculations within DFT using generalized gradient approximation (GGA) and ultrasoft pseudopotentials [13]. $C_n(TM)$ chains have been treated in supercell geometry, and Brillouin zone is sampled by 10-80 special k -points depending on the supercell size. All the atomic positions, and the supercell lattice parameter c along chain axis are optimized by minimizing the total energy, E_T^{sp} , the forces on the atoms, as well as the stress of the system calculated by spin-polarized (or spin-relaxed) GGA. Since $E = E_T^{su} - E_T^{sp}$ (where E_T^{su} is spin-unpolarized total energy) and net magnetic moment are both positive, these compound chains have ferromagnetic ground state [14]. While our study has covered a large family of $C_n(TM)$ chains, our discussion will focus on C_nCr .

Finite size linear chain of single C atom has already been synthesized experimentally [15]. The double bond between carbon atoms and doubly degenerate π -band crossing the Fermi level underlie the stability of the chain

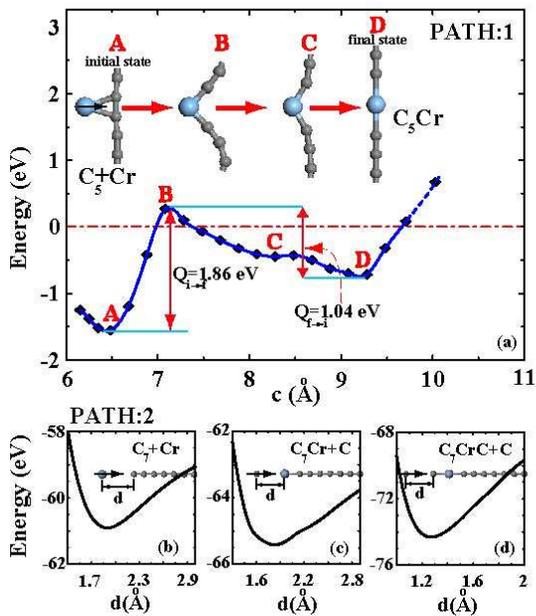


FIG. 1: Transition state analysis for two different reaction paths (a) Path-1: Variation of energy, E_T (eV), for the transition from the C_5+Cr initial state to the linear C_5Cr HM as final state: $Q_{i \rightarrow f}$ and $Q_{f \rightarrow i}$ are energy barriers involved in the transitions. Zero of energy is taken relative to the free Cr atom and free periodic C-linear chain. (b)-(d) Path-2: Variation of interaction energy with distance d between C_7 and Cr, C_7Cr and C, C_7CrC and C for adatom attaching from one end.

and its unusual electronic properties. We examine the formation of linear C_5Cr HM by performing transition state analysis along two different reaction paths. Normally, a Cr atom is attracted by C-linear chain and eventually forms a bridge bond over a C-C bond. We take this bound state (specified as C_5+Cr) as an initial state of the first reaction path for transition to the final state corresponding to the linear C_5Cr HM as illustrated in Fig. 1 (a) [16]. The energy barrier necessary to go from the initial state to the final state is $Q_{i \rightarrow f} = 1.86$ eV. Once the final state has formed, it is prevented from going back to the initial state by a significant barrier of $Q_{f \rightarrow i} = 1.04$ eV. However, the energy barrier $Q_{i \rightarrow f}$ disappears totally and hence the process becomes exothermic for the second reaction path where HM is grown from one end of the chain by attaching first Cr atom then C atoms sequentially. Each ad-atom (Cr or C) is attracted to chain and eventually becomes bound to it as shown in Fig. 1 (b-d). This analysis lets us believe that half-metallic C_n (TM) chains are not only of fundamental interest, but also can be realized experimentally.

Whether a periodic C_nCr linear chain is stable or it can transform to other structures has been examined by an extensive investigation of Born-Oppenheimer surface.

TABLE I: Results of spin-polarized first-principles calculations for C_nCr linear chains. E_T is the difference between spin-paired (non-magnetic) and spin-polarized (magnetic) total energies. c is the optimized 1D lattice parameter. ν is the total magnetic moment per unit cell in units of Bohr magneton, ν_B . M, S, and HM stand for metal, semiconductor, and half metal, respectively. By convention majority and minority spins are denoted by " and #. The numerals in the last column are the band-gap energies in eV.

1D compound	E_T (eV)	c (Å)	ν_B	Type: " (eV) # (eV)
CCr	1.8	3.7	2.0	S: " = 0.7 # = 1.0
C ₂ Cr	2.8	5.2	4.0	HM: " = M # = 3.3
C ₃ Cr	3.0	6.5	4.0	HM: " = 0.4 # = M
C ₄ Cr	3.0	7.9	4.0	HM: " = M # = 2.9
C ₅ Cr	2.5	9.0	4.0	HM: " = 0.6 # = M
C ₆ Cr	3.1	10.3	4.0	HM: " = M # = 2.4
C ₇ Cr	2.5	11.6	4.0	HM: " = 0.5 # = M

Local minima of the total energy have been searched by optimizing the structure starting from transversally displaced chain atoms for varying lattice parameters. The linear chain structure has been found to be stable and energetically favorable relative to zigzag structures. The phonon calculations of C_nCr , yielding positive phonon frequencies ($\nu_{TO}(k=0) = 89, 92, 411$ cm^{-1} ; $\nu_{LO}(k=0) = 421, 1272, 1680$ cm^{-1} for $n=3$ and $\nu_{TO}(k=0) = 13, 71, 353, 492$ cm^{-1} ; $\nu_{LO}(k=0) = 489, 1074, 1944, 2102$ cm^{-1} for $n=4$) corroborate the above analysis of stability. However, for $n=9$ some of the frequencies get negative indicating an instability for a large n . In addition, we performed high temperature ($T = 750-1000$ K) ab-initio molecular dynamics calculations using Nose thermostat, where atoms are displaced in random directions. All these tests have provided strong evidence that the linear chain structures with small n are stable. To weaken the constraints to be imposed by supercell geometry, calculations have been done by using double supercells including two primitive unit cells of the chains. Peierls instability that may cause the splitting of metallic bands at the Fermi level did not occur in C_nCr linear chain structures. Table I summarizes the calculated magnetic and electronic properties of C_nCr linear chain. We also examined how an axial strain may affect the half-metallic behavior of these chains. HM character of C_4Cr was robust under $\epsilon = 0.05$. Small band gap C_5Cr remains HM for $\epsilon = 0.05$, but is rendered a ferromagnetic metal under $\epsilon = 0.10$. While C_3Cr changes to a semiconductor under $\epsilon = 0.10$, it becomes a ferromagnetic metal with $\epsilon = 3:1$ under $\epsilon = 0.10$.

Spin-polarized electronic band structures are strongly dependent on n . For example, all C_nCr we studied are HM except CCr, which is a semiconductor. For even n , majority spin bands are metallic, but minority spin bands are semiconducting with large band gaps ($E_{g\#} \approx 3$

eV). This situation, however, is reversed for odd n , where majority spin bands become semiconducting with relatively smaller gaps ($E_g \approx 0.5$ eV), but minority bands are metallic. This even-odd n disparity is closely related to bonding patterns in different chains. For example, for odd $n = 3$, respective bond lengths are in Å $-C-1.28-C-1.28-C-1.95-Cr-$, and for even $n = 4$, $-C-1.25-C-1.33-C-1.25-C-2.1-Cr-$. It appears that, while double bonds are forming between all atoms for odd n , for even n triple and single bonds form alternatingly between C atoms, and single bonds occur between C and Cr atoms with relatively longer bond lengths [12]. Consequently, the overlap between Cr and C orbitals and hence relative energy positions of bands vary depending on whether n is even or odd. The C_nCr_1 linear chains exhibit also similar spin-dependent electronic properties. While CCO chain is a ferromagnetic metal with $\mu_B = 0.5$, C_nCr_1 chains (for $2 < n < 6$ studied in this work) are HM. They have even-odd n disparity; E_g is relatively larger for even n but decreases as n increases. Interestingly, the odd n C_nCr_1 chains, where nearest carbon atoms have spins smaller but opposite to that on Cr, exhibit a ferrimagnetic behavior.

Half-metallic electronic structure and resulting spin-dependent properties of C_nCr_1 linear chains are shown by the bands and density of states in Fig. 2. The odd-even n disparity is clearly seen. The double degenerate m -band (denoted by $m\uparrow$ for $n = 3$ or $m\downarrow$ for $n = 4$) is half-filled and determines the position of E_F . The band gap of semiconducting states, which have spin in the direction opposite to that of m -band, occurs between the filled v_1 -band and empty conduction c_1 -band. According to these bands, the equilibrium ballistic conductance of the infinite C_3Cr_1 is $G_{\#} = 2e^2/h$ for minority spin, but zero for majority spin. The calculated spin-projected total density of states (TDOS) in Fig. 2 shows the energy spectrum of majority and minority spin states in an interval 2 eV around E_F . The band gap for one spin direction, and infinite density of states at E_F for the opposite spin are clearly seen. This is a dramatically different finding than those of Ref. [9, 10, 11]. Orbital-projected local densities of states at Cr and C atoms show the orbital composition of the spin-polarized bands. The m -band is composed of Cr-3d and mainly first-neighbor C-2p orbitals at E_F , that is the p -d hybridization. The v_1 -band nearest to E_F is derived from the Cr-3d and 4s states. The empty c_1 -band originates from C-2p and Cr-3d states.

The effect of spin-orbit (SO) coupling on the HM properties of C_3Cr_1 has been calculated by using all-electron DFT (WIEN2K) code. We found the splitting is very small and E_T (with SO) - E_T (without SO) = -7.9 meV. As illustrated in Fig. 2(c), the difference between TDOSs calculated with and without SO-coupling is negligible and hence the effect is not strong enough to destroy the half-metallic properties. This conclusion obtained for $n = 3$ can apply to other chain structures in Table I,

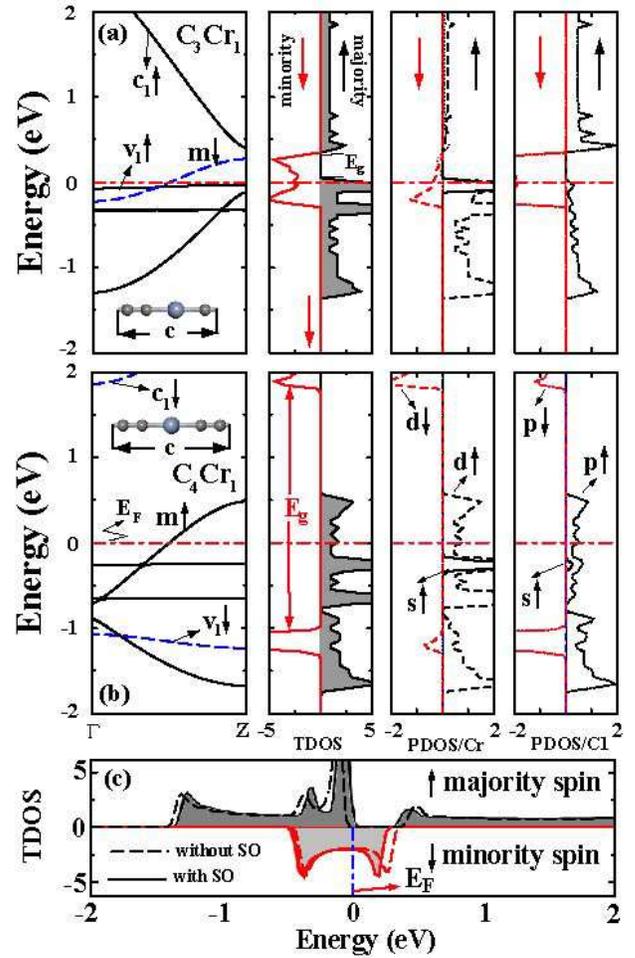


FIG. 2: (a) Energy band structure of C_3Cr_1 ; corresponding total density of states (TDOS) for majority (\uparrow) and minority (\downarrow) spins; orbital-projected local density of states at Cr atom (PDOS/Cr), at C atoms first nearest neighbor to Cr (PDOS/C1). (b) C_4Cr_1 . State densities with s, p, d orbital symmetry in PDOSs are shown by thin continuous, dotted, broken lines, respectively. Zero of energy is set at E_F . Metallic band crossing the Fermi level, highest valence and lowest conduction bands are labelled by $m\uparrow$, v_1 and c_1 , respectively. (c) Majority and minority TDOS of C_3Cr_1 calculated with and without spin-orbit coupling (SO).

since the Cr-C interaction decays fast beyond the first nearest neighbors of Cr atom.

Further insight about the electronic structure and the character of bonding can be gained by examining the charge distributions associated with selected bands shown in Fig. 3. The charge density of the metallic spin-state at E_F is obtained by averaging charges of states of m -band having energy ± 0.02 eV around E_F . They are formed from the bonding combination (or p -d hybridization) of C- $2p_{x,y}$ and Cr- $3d_{xz,yz}$ valence orbitals of C_3Cr_1 . In the case of even n ($n = 4$) it corresponds to an antibonding combination of the above orbitals with enhanced Cr-3d contribution. The charge density of v_1 -

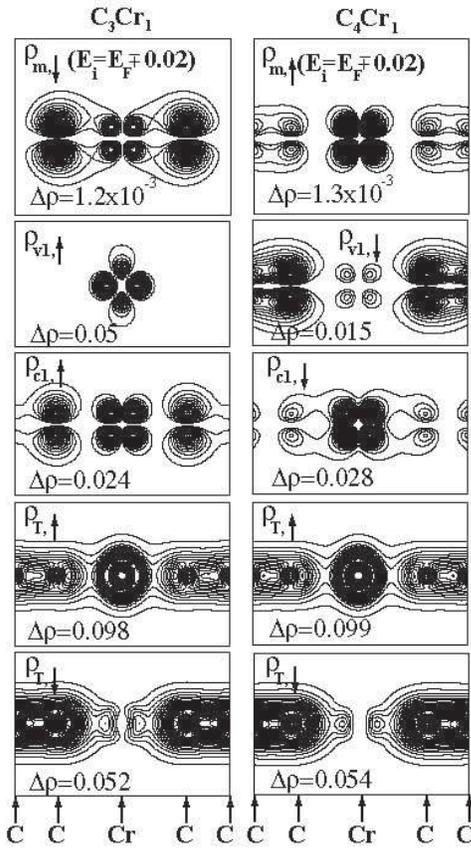


FIG. 3: Charge density contour plots of linear chains of C_3Cr_1 , C_4Cr_1 compounds on a plane through the chain axis. $\rho_{m,\uparrow/\downarrow}$ is the charge density of metallic spin-states within energy range $E_F \pm 0.02$ eV. $\rho_{v_1,\uparrow/\downarrow}$ and $\rho_{c_1,\uparrow/\downarrow}$ are the charge density of the highest valence v_1 and the lowest (empty) conduction band c_1 , respectively. $\rho_{T,\uparrow/\downarrow}$ are total charge density due to majority spin states and minority spin states, respectively. $\Delta\rho$ is contour spacing.

band is due to non-bonding Cr-4s $3d_{z^2}$ orbitals in C_3Cr_1 . For even n case, the C- $2p_{x,y}$ contribution is pronounced. Charge density of the c_1 -band suggests the antibonding combination of p-d hybridized states.

The band structure and charge density plots suggest that the p-d hybridization between neighboring C and Cr orbitals and resulting exchange splitting of bands in different spin directions give rise to the ferromagnetic ground state of the above chains. An additional ingredient, namely cylindrical symmetry of the π -bonds in the carbon chain provides conditions to result in integer number of excess spin in the unit cell which is required to achieve half-metallic behavior. The ferromagnetic ground state with values integer multiple of N_B per unit cell can be understood from a local point of view based on first Hund's rule. We take C_3Cr_1 as examples. In Fig. 2 (a), three spin-up (one non-degenerate- v_1 , one doubly degenerate) bands below E_F are derived mainly from Cr-3d orbitals. Five of six electrons on Cr (in these

corresponding bands) occupy the majority spin states to yield $N_{\uparrow} = 5$. The sixth electron occupies the p-d hybridized, doubly degenerate but only half-filled $m_{\#}$ -band yielding $N_{\downarrow} = 1$. Consequently, $N = N_{\uparrow} - N_{\downarrow} = 4$, and hence $N = 4 N_B$.

The present study predicts that linear chains of $C_n(TM)$ compounds ($TM = Cr, Ti, Mn, Fe, Co$) with specific n can show half-metallic behavior with a diversity of spin-dependent electronic properties. Here, the type and number of atoms in the compound, as well as even-odd n disparity are critical variables available to engineer nanostructures with spin-dependent properties. The electronic transport properties and the value of σ can be modified also by applied axial strain. Not only periodic structures, but also non-periodic combinations comprising HM-HM or HM-S (or M) quantum structures and superlattices can be envisaged to obtain desired device characteristics, such as spin-valve effect and spin-resonant tunnelling. Since linear carbon chains have been obtained also at the center of multi-wall carbon nanotubes [15], C_nCr chains can, in principle, be produced inside a nanotube to protect the spintronic device from the undesired external effects or oxidation. In fact, we obtained that strained C_7Cr compound chain placed inside a (8,0) SWNT can be a HM. Of course, the properties revealed in this study correspond to idealized infinite chain structures, and are subject to modifications when the chain size becomes finite. However, for finite but long chains (for example a coil of C_nTM around an insulating SWNT), the level spacings are still small to gain a band-like behavior. Also, localization of electronic states due to imperfections in 1D may not lead to serious difficulties when the localization length is larger than the length of the device. It is also noted that the properties of chains may depend on the type and detailed atomic structure of the electrodes.

In conclusion, we showed that half-metallic properties can be realized in linear chains of carbon-transition metal compounds presenting a number of exciting properties which can be of fundamental and technological interest for new generation devices. We believe that in view of recent progress made in synthesizing C atomic chains, present study will bring a new perspective in spintronics.

Electronic address: ciraci@fen.bilkent.edu.tr

- [1] G. A. Prinz, Science 282, 1660 (1998).
- [2] P. Ball, Nature (London) 404, 918 (2000).
- [3] S. A. Wolf, et al., Science 294, 1488 (2001).
- [4] R. A. de Groot, et al., Phys. Rev. Lett. 50, 2024 (1983).
- [5] W. E. Pickett and J. S. Moodera, Phys. Today 54, 39 (2001).
- [6] J.-H. Park, et al., Nature (London) 392, 794 (1998).
- [7] H. Akinaga, T. Manago, M. Shirai, Jpn. J. Appl. Phys. Part 2 39, L1118 (2000).

- [8] J.E. Pask, et al., Phys. Rev. B 67, 224420 (2003). See also W.-H. Xie, et al., Phys. Rev. Lett. 91, 037204 (2003).
- [9] E. Durgun, et al. Phys. Rev. B 67, R201401 (2003); S. Dag, et al., *ibid* 69, R121407 (2004).
- [10] C.K. Yang, J. Zhao and J.P. Lu, Phys. Rev. Lett. 90, 257203 (2003).
- [11] V. Rodrigues, et al., Phys. Rev. Lett. 91, 096801 (2003).
- [12] R. Pati, et al., Phys. Rev. B 68, 014412 (2003).
- [13] Numerical calculations have been performed by using VASP package; G. Kresse and J. Hafner, Phys. Rev. B 47, 558 (1993); G. Kresse and J. Furthmüller, *ibid* 54, 11169 (1996). Stability of optimized structures have been confirmed by independent analysis using the software package CASTEP.
- [14] Spin-relaxed structure optimization calculations starting with an initial net spin $S_T = 0$ have converged to the values $S_T = \sum_{n;k}^{\text{occ}} (S_{n;k;\uparrow} + S_{n;k;\downarrow}) > 0$. This situation excludes the possibility of an antiferromagnetic ground state.
- [15] G. Roth and H. Fischer, Organometallics 15, 5766 (1996); X. Zhao et al., Phys. Rev. Lett. 90, 187401 (2003).
- [16] $C_5 + Cr$ initial state is a bound state with $\epsilon = 5.1$ Bohr magneton and high-spin polarization. We estimate the breaking strain of the linear C_5CrHM at the axial strain of $\epsilon = 0.1$ near $E_T(c) = 0$ in Fig. 1(a).