

# Paraelectric-Ferroelectric Phase Transitions in Small Spherical Particles

O. Hudak<sup>1</sup>

Department of Aerodynamics and Simulations, Applied Physics Group,  
Faculty of Aeronautics, Technical University, Kosice

---

<sup>1</sup>e-mail: hudako@mail.pvt.sk,  
part-time work: Department of Physics, Pedagogical Faculty, Catholic University, Ru-  
zomberok

## Abstract

A transition in a spheroidal particle from the paraelectric to the ferroelectric phase as well as dynamic susceptibility are studied without approximation in the paraphase. It is assumed that the surface charge is compensated and the boundary condition for the polarisation is  $P = 0$ , i. e. with zero polarisation at the surface of the particle. There is an infinite number of resonance frequencies in the dynamic dielectric function within the quasistatic approximation. The paraphase properties of the dielectric response of the particle are discussed. The transition temperature decreases with decreasing diameter  $d$  of the particles inverse quadratically. There exists such a critical diameter that for the particles with the diameter below the critical one the ferroelectric phase is absent. Comparison of the experiment with theoretical results is carried out. Introduction of a dead layer thickness leads to a very good agreement of theory with the experiment for  $PbTiO_3$  and to a good agreement with the experiment for  $BaTiO_3$ .

# 1 Introduction

Disordered ferroelectrics and antiferroelectrics have infrared, microwave and Raman spectra with their characteristic features which are not present in the ordered ferroelectrics and antiferroelectrics. Disorder in these materials may be of a different type. Stoichiometric order-disorder type systems are the best studied materials of the mentioned type [1], [2] and [3]. Other type of order-disorder system are those materials in which two types of ions interchange their positions at high temperatures. At lower temperatures there exists a freezing of their positions. When the freezing is theoretically very slow, this may be achieved practically by an annealing process at which the ions order, see in [2] and the references therein. The low-temperature phase is the ferroelectric phase. A similar type of materials are crystal-glass microcomposites. The nonstoichiometric solid solutions in which one component is a ferroelectric type material and the other is a non-ferroelectric, or antiferroelectric type material form another class of order-disorder systems with ferroelectric or antiferroelectric properties. Their structural form or the form of clusters with different dielectric properties are usually of the nanocomposite form. New methods of the preparations of materials have lead in the last years to a possibility to obtain nanostructural type of the order-disorder materials [2].

We studied the dielectric response of microcomposites of the ferroelectric-dielectric type in our papers [4] and [5]. A two-phase composite of ferroelectric-dielectric particles was studied as concerning the dielectric response within the quasistatic approximation. Maxwell-Garnett theory, effective medium theory and Bergman representation enabled us to calculate the dielectric function for a microcomposite. The dynamic and static properties of such composites have been reported in these papers. There is present a distribution of polar modes due to their presence in the original ferroelectric component in the bulk form and due to the presence of geometrical resonances. New low-frequency peaks appear due to the phenomenon of the geometric resonance. Their properties are dependent on the distribution of ferroelectric and non-ferroelectric clusters which percolate the material. The soft mode below the percolation transition within a state where at least one infinite ferroelectric cluster is present does not change its frequency depending on the concentration of the non-ferroelectric material whatever its strength changes. The soft mode disappears above the percolation transition, where there is no infinite ferroelectric cluster present. Thus the soft mode becomes a hard mode. Let us note that presence of the multirelaxation phenomenon in the ferroelectric-dielectric composites of the type mentioned above has its origin in the presence of ferroelectric clusters with a distribution of their geometrical and topological properties. In materials of the order-disorder type with a regular crystal structure there is a possibility to find multirelaxation phenomenon due to other reasons [6], [7] and [8] where the complex dielectric function was calculated using semiempirical Bloch equations. A perturbation and a non-perturbation approaches were used to calculate a dielectric function, and the multirelaxation phenomenon was found. Its origin is due to presence of dispersion-less excitations in ferroelectric order-disorder materials with an incommensurate phase present at a given temperature. Clusters with an incommensurate modulation of the ferroelectric order parameter were observed [9] not only in dipolar glasses mentioned in [3], but also in  $Zr_{0.98}Hf_{0.02}TiO_4$  ceramics exhibiting an incommensurate-commensurate phase transition due to

occurrence of small polar-like regions (the domains within the incommensurate structure surrounded by discommensurations which appear upon cooling down from higher temperatures below some critical one). It is interesting that there exists a similarity in response of magnetic quantum systems with incommensurably modulated phases and order-disorder systems with an incommensurate phase [10]. In these magnetic systems it was shown theoretically [11] that in the quantum magnetic incommensurably modulated system exist dispersionless excitations and that their presence may explain the observed Al-NQR and thermodynamic anomalies observed in *CeAl<sub>2</sub>* [12] and [13], and in Ga-NMR study of the low-energy excitations in *NdGa<sub>2</sub>* [14] and [15].

In dielectrics the dielectric function behaviour of a composite depends not only on properties of infinite and finite clusters, but also on the particles from which the composite is formed as well as on their possible domain wall structure of the order parameter. The size effect on the ferroelectric phase transition in *PbTiO<sub>3</sub>* ultrafine particles was experimentally studied in [16], namely the size dependence of the transition temperature. The difference in the critical temperature for the bulk and for the particle with diameter  $d$  is found to be  $T_{c\infty} - T_c(d) = \frac{C}{(d-d_c)}$ , where the constant  $C$  is  $C = 588.5^\circ\text{C nm}$  and the value for the parameter of fitting called critical diameter  $d_c$  of the particle  $d_c = 12.6$  nm for *PbTiO<sub>3</sub>* was found. Note that it is not this critical diameter at which the ferroelectric phase in the particle vanishes. Here  $T_{c\infty}$  is the bulk transition temperature,  $T_c(d)$  is the particle transition temperature. Similar effects were observed (in earlier works) in KDP [17] and in *BaTiO<sub>3</sub>* [18].

In [19] the surface effects on the phase transitions in ferroelectrics are studied using a phenomenological theory describing the change of the local spontaneous polarisation in the vicinity of the free surface of a ferroelectric thin film. The film is kept between metallic electrodes. Depolarising field effects reduce the deviation of this local polarisation from its bulk value as compared to the surface effects on phase transitions in other systems. The critical exponents describing the behavior of the local polarisation in the vicinity of the Curie-Weiss temperature  $T_c(d)$  are the same as the bulk exponents. Only the critical amplitudes are changed.

The Landau theory of phase transitions in thick films is developed in [20] for a one-component order parameter. The boundary conditions at the surfaces of a film with thickness  $L$  are given by means of an extrapolation length  $\delta$ . The exact expressions are given for the critical temperature and the order parameters profile in terms of elliptic functions, and the nature of the phase transition is discussed. The dependence of the crystal structure on the particle size in *BaTiO<sub>3</sub>* is studied in [21]. The Curie-Weiss temperature of *BaTiO<sub>3</sub>* powder has been investigated in the particle size range from 0.1 to 1.0  $\mu\text{m}$ . The transformation from the ferroelectric tetragonal to the paraelectric cubic symmetry occurs at the critical particle size of 0.12  $\mu\text{m}$  at room temperature, and the Curie-Weiss temperature drops below the room temperature at the critical particle size. In [22] the size driven phase transition in ferroelectric particles is studied. The spatial distribution and size dependence of the polarisation is calculated numerically. Theoretical values for the critical diameter  $d_c$  in *BaTiO<sub>3</sub>* and *PbTiO<sub>3</sub>* are compared with experimental values. The surface layer thickness  $\delta$  depends on the particle size. The predicted critical size of the particles is smaller than that from the experiment. In [23] the size dependence of the

ferroelectric transition of small  $BaTiO_3$  particles is studied taking into account the effect of depolarisation. The depolarisation energy is reduced in a crystal that contains domains of different polarisation. Authors are considering cubic particles with alternating domains separated by  $180^\circ$  domain walls. The depolarisation energy and the domain-wall energy contributions are taken into account in the Landau-Ginzburg free-energy density. Assuming a hyperbolic tangent polarisation profile across the domain wall, the domain-wall energy and the domain-wall half thickness can be obtained by minimizing domain free energy with respect to this thickness.  $BaTiO_3$  is not a perfect insulator, therefore a Schottky space charge layer on the surface that shields the interior of the crystal from the depolarisation field is considered. The equilibrium polarisation  $P$  and the domain width  $D_w$  are found. The results show that the ferroelectric transition temperature of small particles can be substantially lower than that of the bulk transition temperature as a result of the depolarisation effect. Consequently, at a temperature below the bulk transition temperature, the dielectric constant can peak at a certain cube size  $L$ . The results agree with the existing experimental observations. According to the authors the theory can also be applied to other ferroelectric materials such as  $KH_2PO_4$  or  $PbTiO_3$ . Omitting the gradient term, [24], in the free energy expansion, the noncrystalline surface layer and depolarisation effect lead to the critical temperature dependence  $T_c(d) = T_{c\infty} - \frac{6D}{\delta a_0 d}$  where  $D$  is connected with the correlation length  $\zeta$ :  $D = \zeta^2 a_0 |T - T_c|$ ,  $a_0$  is the coefficient from the Landau expansion,  $d$  is the diameter of the particle. Thus a phenomenological study of the size effect on the phase transitions in ferroelectric particles was done. Spontaneous polarisation dependence on the diameter  $d$  in spherical particles is studied using the Landau phenomenological theory. The spatial distribution of the polarisation is obtained numerically. A size-driven phase transition is found. In [25] the thickness dependence of the dielectric susceptibility of ferroelectric thin films was studied within a phenomenological theory. If the spontaneous polarisation is reduced in the surface layer, the mean susceptibility of the film increases with the decrease of the film thickness. A size-driven phase transition will take place at the critical thickness. If the temperature-driven phase transition of the bulk is of the second-order type, the size-driven transition will be accompanied by a dielectric divergence. If it is the first-order, a finite dielectric peak will appear. If the spontaneous polarisation is enhanced in the surface layer, the mean susceptibility of the film decreases with the decrease in the film thickness. No size-driven phase transition and hence no dielectric anomaly will occur in this case. In [26] the size driven phase transition in nanocrystalline  $BaTiO_3$  was studied. Nanocrystalline powders of  $BaTiO_3$  with a narrow size distribution were produced. The powder consisted of the crystallite sizes whose dimensions ranged from 10 nm to 1  $\mu m$ . The paraelectric-ferroelectric phase transition was found to disappear below a critical crystallite size of 49 nm. In accordance with this observation a structural transition towards a cubic symmetry became apparent in the x-ray diffractograms.

The size-induced diffuse phase transition in the nanocrystalline ferroelectric  $PbTiO_3$  has been studied experimentally in [27]. The size effects were found to become important only below 100 nm (the coherently diffracting x-ray domain size). The tetragonal distortion of the unit cell related to the spontaneous polarisation decreases exponentially with size and vanishes at 7 nm.  $T_c(d)$  de-

creases gradually but the transition becomes increasingly diffuse alongside of a diminishing size from 80 to 30 nm. The ferroelectric ordering probably persists down to 7 nm.

The size effects on cells in ferroelectric films are studied in [28] within the phenomenological theory. The lateral size dependence of the Curie-Weiss temperature and the polarisation is obtained and the stability of the ferroelectricity of the cells is discussed. The phase-transition behavior of the spontaneous polarisation and susceptibility of the ferroelectric thin films is studied in [29] that is based on the Ising model in the transverse field. Modification of the exchange constant and the transverse field in the surface layer might lead to the spontaneous polarisation and the Curie-Weiss temperature changing in a different direction as well as in the same direction according [29]. The Curie-Weiss temperature of the films can be enhanced, then the temperature dependence of the spontaneous polarisation shows a tail-like structure. There exist two peaks in the susceptibility-temperature curve in this case. One is located at the Curie-Weiss temperature of the films. The intensity of this peak decreases with increasing film thickness. The other peak is around the bulk Curie-Weiss point. The intensity of this peak increases with increasing film thickness. The theory [29] gives a reasonable description of the experimental facts for the triglycine sulfate (TGS) thin films.

Surface effects and size effects for ferroelectrics with the first-order phase transition are studied in [30]. The contribution of surface to the free-energy expression was studied for the transverse Ising model with four-spin interactions taken into consideration. It was shown that a  $P^4$  term should be added to the surface terms in the free-energy expression. The surface and size effect on polarisation and Curie-Weiss temperature were studied using the newly developed free-energy expression. Experimental results were discussed using the free-energy expression. In [31] the finite size effect in ferroelectrics results in a structural instability. This leads to a limitation of physical sizes and dimensions of materials in which electric dipoles can be sustained. The size dependence on the Curie-Weiss temperature is calculated with consideration of crystallographic anisotropy. The mean-field theory gives that the limitation of the transverse critical sizes is strongly dependent upon the thickness. The limitation of the critical thickness is also closely associated with the transverse critical sizes.

In [32] a new phenomenological theory of size effects in ultrafine ferroelectric particles of  $PbTiO_3$  is discussed. This model is taking size effects on the phenomenological Landau-Ginzburg-Devonshire coefficients into consideration and can successfully explain the observed size effects on the Curie-Weiss temperature,  $c/a$  ratio, and thermal and dielectric properties of the lead-titanate-type ferroelectric particles. Theoretical and experimental results for  $PbTiO_3$  fine particles are compared and discussed. The relationship between this model and the model of Zhong et al. [24] is discussed. In [33] the size effects on ferroelectricity of ultrafine particles of  $PbTiO_3$  have been studied by high resolution transmission electron microscopy. The diameter of the ultrafine ferroelectric lead titanate particles is ranging from 20 to 2000 nm. The crystal structure, surface morphology, domain-wall structure and surface reconstruction have been studied. All the particles had tetragonal structure. The lattice constants  $c/a$  ratio and the domain size decrease with decreasing particle size. The particles became monodomain when their diameter was 4.2 - 20 nm. A domain wall width of 14Å was deduced for the  $90^\circ$  domain walls.

Grain-size effects on the ferroelectric behavior of dense nanocrystalline  $BaTiO_3$  ceramics are studied in [34]. A progressive reduction of the tetragonal distortion, the heat of transition, the Curie-Weiss temperature and the relative dielectric constant have been studied with grain size decreasing from 1200 to 50 nm. According to the authors, the correlations between the grain size, the tetragonal distortion, and the ferroelectric properties strongly support the existence of an intrinsic size effect. From the experimental trends the critical size for disappearance of ferroelectricity has been evaluated to be from 10 to 30 nm. The strong depression of the relative permittivity observed for the nanocrystalline ceramics is ascribed by the authors to the combination of the intrinsic size effect and to the size-dependent dilution effect of a grain boundary dead layer. Size effects on Curie-Weiss temperature of ferroelectric particles were studied in [35] within a model without any free adjustable parameters. The model predicts that  $T_c$  decreases with decreasing particle size. The predictions of the model are in agreement with experimental results for  $PbTiO_3$  and  $BaTiO_3$ . For similar studies see also [36].

Influence of the domain wall structure on the dielectric response in  $KH_2PO_4$  type crystals was studied in [37], where one can find also references to domain wall dynamics effects in KDP and  $CsH_2AsO_4$ . In this type of the materials the domain walls freeze-in below some temperature and a multirelaxation behaviour of the dielectric function is observed. The Landau theory of  $180^\circ$  domain walls in  $BaTiO_3$  type ferroelectric particles was studied recently in [38] for the particles of the rectangular form. It was assumed that the surface charge is completely compensated. The experimentally found temperature dependence on the size of the particle is more precisely described by a domain wall if the sixth-order term in the Landau free-energy expansion is taken into account [38]. Dielectric constant and correlation length of ferroelectric particles in the paraelectric phase was studied in [39]. The finite size of a particle influences the temperature dependence of the dielectric constant and the correlation length. The deviation from the Curie-Weiss law in the ferroelectric particles originates from the decrease of the long-range correlation. Glinchuk et al. [40] studied variationally the depolarisation and the surface tension effects for polarization, susceptibility and critical temperature  $T_c(d)$  diameter dependence for spherical particles.

In this paper we are studying other sources of the observed complicated multirelaxation behaviour of the dynamic susceptibility in ferroelectric-dielectric composites by analytical calculations. Phase transition in a spheroidal particle from the paraelectric to the ferroelectric phase as well as a dynamic susceptibility are affected by the spheroidal (more generally by ellipsoidal) shape of the ferroelectric particles. Assuming that the surface charge had been compensated, the spheroidal shape does not lead to plane polarisation waves due to the surface effect: the boundary condition in a spheroidal particle with a surface layer lead to a multirelaxation response. There is an infinite number of responding modes, thus there is also an infinite number of resonance frequencies. It is the aim of this paper to discuss namely these effects of the shape of a ferroelectric particle on its dielectric response. Firstly we describe a model which enables us to calculate a dynamic dielectric function within quasistatic approximation. Deriving dynamic equations for the order parameter, the electric polarisation vector components, we discuss the paraphase properties of the response. As a result we find multirelaxation behaviour of the dielectric susceptibility in the real representation. It is then easy to find frequency dependent form of the dielec-

tric susceptibility of a spheroidal particle. Its form enables us to find resonance frequencies, their number is infinite. Consequently the transition temperature dependence on the particle diameter and on other parameters of the model may be found easily and compared with the experimental results.

## 2 Model

Let  $x$  be a generalized dipole length of the normal polarisation mode with an effective charge  $q$ . The one-component order parameter  $P$ , electric polarisation component, has the form  $P=xq$ . Let  $m$  be an effective mass of the mode. The relaxation equation has the form which follows from the free energy  $F$  for the systems of the fourth order in the order parameter  $P$ , see in [22]:

$$F = \int dv \left[ \frac{A}{2} P^2 + \frac{B}{4} P^4 + \frac{D}{2} (\nabla P)^2 \right] + \int ds \left[ \frac{D}{2} \frac{P^2}{\delta} \right] - \int dv [E \cdot P] \quad (1)$$

The first part of the equation (1) is a volume contribution to the free energy, the second one is a surface contribution to the free energy. Last term is due to the applied electric field  $E$  acting on the electric polarisation  $P$ . Here  $A$ ,  $B$ , and  $D$  are usual parameters of the Landau free energy expansion,  $E$  is an electric field,  $\delta$  is a surface parameter defined by, see in [24]:

$$\frac{1}{\delta} = \frac{5J - 4J_s}{a_0 J} \quad (2)$$

where  $J$  is a ferroelectric interaction constant in the bulk,  $J_s$  is a ferroelectric interaction constant on the surface,  $a_0$  is the bulk lattice constant. In (2) it is assumed for simplicity that the bulk lattice structure is a cubic one. Note that the limit  $\delta = 0$  corresponds to strong (anti-) ferroelectric interactions on the surface of the particle. On the other hand for strong bulk ferro- (antiferro-) interactions  $J$  the constant  $\delta$  remains finite and nonzero. For the ferroelectric particles with  $J = J_s$  the constant  $\delta$  is independent on the characteristic size of the film. In spherical particles the constant  $\delta$  is dependent on the diameter  $d$  of the particle:

$$\frac{1}{\delta} = \frac{5}{d} + \frac{1}{\delta_m} \left[ 1 - \frac{a_0}{d} \right] \quad (3)$$

where  $\delta_m$  is the extrapolation length for  $d = \infty$ . As noted in [24], to get the spatial distribution of the polarisation it is necessary to minimise the free energy (1) for a given boundary conditions which is difficult to solve analytically. The authors of [24] found the spatial distribution of polarisation numerically. We have found this distribution analytically for very large values of the ratio  $\frac{D}{\delta}$ , for which the surface contribution to the free energy (1) is minimised by zero surface polarisation.

## 3 Equations for the Soft Mode

The dynamic equation for the generalized coordinate  $x$  has the form:



$$m \frac{\partial^2}{\partial t^2} x + \Gamma \frac{\partial}{\partial t} x = -q \left( \frac{\delta F}{\delta P} - \frac{\partial}{\partial r} \frac{\delta F}{\delta P} \right) = q E_{eff} \quad (4)$$

where  $E_{eff}$  is an effective electric field acting on the charge  $q$ , here  $P = q \cdot x$  is the polarisation dependent in the position  $r$  in the particle. Using the free energy  $F$  form from (1) we find that the equation of motion (4) has the form:

$$m \frac{\partial^2}{\partial t^2} x + \Gamma \frac{\partial}{\partial t} x = qE + q(-AP - BP^3 + D(\frac{\partial^2 P}{\partial r^2} + \frac{2}{r} \frac{\partial P}{\partial r})) \quad (5)$$

It is convenient to introduce the mass  $m^*$  related to the charge  $q$  and the relaxation constant  $\Gamma$  related to the charge  $q$ :

$$\Gamma^* = \frac{\Gamma}{q^2} \quad (6)$$

$$m^* = \frac{m}{q^2}$$

The equation of motion (5) has now the form using (6):

$$m^* \frac{\partial^2}{\partial t^2} P + \Gamma^* \frac{\partial}{\partial t} P = E - AP - BP^3 + D(\frac{\partial^2 P}{\partial r^2} + \frac{2}{r} \frac{\partial P}{\partial r}) \quad (7)$$

The form (7) of the equation of motion is the form which we will use in next sections. The boundary condition for a particle with the diameter  $d$  has the form [24]:

$$\frac{\partial P}{\partial r} + \frac{P}{\delta} = 0 \quad (8)$$

at the surface  $r = \frac{d}{2}$ . It is further assumed that the polarisation  $P(r)$  in (7) remains finite at the centre of the particle  $\lim_{r \rightarrow 0} P(r) < \infty$ . Note, that the equation (8) is an algebraic equation relating the  $P$  value at the point  $r = \frac{d}{2}$ , and the  $\frac{\partial P}{\partial r}$  value at the same point. In the limit  $\frac{\delta}{D} = 0$ , the surface boundary condition is  $P(r = \frac{d}{2}) = 0$ . This boundary condition will be used in this paper. This condition is also compatible with existence of the surface layer with zero electric polarization (dead layer) which may exist around the polarized region of the particle.

## 4 Polarisation Mode in the Paraelectric Phase

The fourth-order term in the free energy (1) may be neglected in the mode analysis if the temperature  $T$  is above the Curie-Weiss temperature  $T_c$  at which the paraelectric phase transforms to the ferroelectric one. In our model above, the free energy corresponds to a displacive type of ferroelectrics which undergo a second order phase transition described by a one dimensional order parameter  $P$ . The order-disorder case has to be treated in another way.

In the free energy  $F$  the constant  $A$  is of an obvious form  $A = a_1(T - T_c)$ , with the positive constant  $a_1 > 0$ . Let us assume that our particle of the spherical shape is under influence of the time dependent spatially homogeneous electric field  $E = E_\omega \cdot \exp(j\omega t)$  oscillating with the frequency  $\omega$ , here  $j$  is an imaginary unit. Thus we assume that the wavelength of the electric field is

much larger than the particle characteristic size. Then electric polarisation  $P = P(r) \cdot \exp(j\omega t)$  has an amplitude, complex in general, which is dependent on the position in the particle, and its time dependence is of the same type as of the external electric field. The dynamic equation of motion (7) has the form of a second order differential equation for the polarisation  $P(r)$ :

$$(-m^*\omega^2 + j\Gamma^*\omega + A)P(r) = E_\omega + D\left(\frac{\partial^2 P}{\partial r^2} + \frac{2}{r} \frac{\partial P}{\partial r}\right) \quad (9)$$

Substituting  $P(r) = \frac{1}{\sqrt{r}}u(r)$  into the equation (9), where  $u(r)$  is an unknown function, we find the following form of the equation of motion (9) for  $u(r)$  :

$$(-m^*\omega^2 + j\Gamma^*\omega + A)u(z) = E_\omega\left(\sqrt{\frac{d}{2}}\right)\sqrt{z} + \frac{D}{\left(\frac{d}{2}\right)^2}\left(\frac{\partial^2 u}{\partial r^2} + \frac{1}{z} \frac{\partial}{\partial r}u(z) - \left(\frac{1}{2}\right)^2 u(z)\right) \quad (10)$$

Here  $r = z\frac{d}{2}$  where the variable  $z$ ,  $0 \leq z \leq 1$ , was introduced. The corresponding boundary condition has a simple form. At the centre of the sphere the polarisation remains finite  $\lim_{r \rightarrow 0} \frac{u(r)}{\sqrt{r}} < \infty$ . At the surface we have  $u(z = 1) = 0$ . To solve the equation of motion (10) let us start from the well-known Bessel equation of the form [41] and [42]:

$$\frac{\partial^2 u}{\partial r^2} + \frac{1}{z} \frac{\partial}{\partial r}u(z) - \left(\frac{1}{2}\right)^2 u(z) = -b^2 u(z) \quad (11)$$

The equation (11) has as its solution the Bessel functions  $J_{\pm\frac{1}{2}}(\lambda_i z)$ , where  $b^2 \equiv \lambda_i^2$ . The root  $\lambda_i$  is defined as that point for which the Bessel function vanishes  $J_{\pm\frac{1}{2}}(\lambda_i) = 0$ .

The equation of the motion (10) for the order parameter  $P(r)$  in its transformed form  $P(r) = \frac{1}{\sqrt{r}}u(r)$  has the solution  $u(r) = \sum_{i=1}^{i=\infty} a_i J_{+\frac{1}{2}}(\lambda_i z)$  where  $z$  is expressed through  $r$  as it is given above, which is finite in the centre of the sphere  $r = 0$  due to the fact that the relevant Bessel functions  $J_{+\frac{1}{2}}(\lambda_i z)$  in the corresponding limit are finite for every  $i$ ,  $\lim_{z \rightarrow 0} \frac{J_{+\frac{1}{2}}(\lambda_i z)}{\sqrt{z}} = \sqrt{\frac{2\lambda_i}{\pi}}$ . Note that one finds  $\lim_{z \rightarrow 0} \frac{J_{-\frac{1}{2}}(\lambda_i z)}{\sqrt{z}} = \infty$ , and thus the Bessel functions  $J_{-\frac{1}{2}}(\lambda_i z)$  do not satisfy the condition of the finite solution in the centre of the sphere. It is well known, that the roots for the Bessel function  $J_{+\frac{1}{2}}(\lambda_i) = 0$  are  $\lambda_i = i\pi$ . Expanding in (10) also the square root of  $z$  into Bessel functions:

$$\sqrt{z} = \sum_{i=1}^{i=\infty} b_i J_{+\frac{1}{2}}(\lambda_i z), \quad (12)$$

where  $b_i = -\frac{\sqrt{2\pi}}{\sqrt{\lambda_i}}(-1)^i$ , we find that the expansion coefficients  $a_i$  have the form:

$$a_i = \frac{-E_\omega \sqrt{\frac{d}{2}} \left(\frac{\sqrt{2\pi}}{\sqrt{\lambda_i}}(-1)^i\right)}{-m^*\omega^2 + j\Gamma^*\omega + A + \frac{4\pi^2 D i^2}{d^2}} \quad (13)$$

The space dependence of the electric polarisation  $P(r)$  is given by:

$$P(r) = \chi(r, \omega) E_\omega \quad (14)$$

concerning the amplitude of the polarisation. Here  $\chi(r, \omega)$  is the r-dependent susceptibility:

$$\chi(r, \omega) = \frac{1}{r} \sum_{i=1}^{i=\infty} \frac{\frac{d}{\pi i} (-1)^{i+1} \sin(\frac{2\pi r i}{d})}{-m^* \omega^2 + j\Gamma^* \omega + A + \frac{4\pi^2 D i^2}{d^2}} \quad (15)$$

which is of a multirelaxation type. As we see, in (15) there is an infinite number of the oscillator-like contributions with the corresponding damping, and there exists a phase shift between the mode contributions, which is r-dependent. Note, that at the centre of the particle the susceptibility remains finite.

## 5 Dynamic and Static Susceptibility

The dynamic susceptibility  $\chi(\omega)$  for the particle as a whole is that susceptibility, which we obtain from (15) by summing up the contributions over different positions within the sphere, relating this quantity to a unit volume of the particle:

$$\chi(\omega) = \frac{1}{V} \int_0^{\frac{d}{2}} \chi(r, \omega) 4\pi r^2 dr = \sum_{i=1}^{i=\infty} \frac{\frac{6}{(\pi i)^2}}{m^* (\omega_i^2 - \omega^2) + j\Gamma^* \omega} \quad (16)$$

Here  $V = \frac{\pi d^3}{6}$  is the volume of the particle. We see that the strength of every oscillator contribution decreases in the power law, i.e. as  $i^{-2}$ , for i (an integer) increasing.

The oscillator resonance frequency  $\omega_i$  is given by:

$$\omega_i^2 = \frac{1}{m^*} \left( A + \frac{4\pi^2 i^2 D}{d^2} \right) \quad (17)$$

We see that different resonance frequencies increase as  $i^2$ , and the last term in (17) decreases as  $d^2$  with increasing diameter d. The relaxation constant remains unchanged.

Static susceptibility may be easily found from (16) and has the form:

$$\chi_{stat} = \frac{1}{V} \int_0^{\frac{d}{2}} \chi(r, \omega = 0) 4\pi r^2 dr = \sum_{i=1}^{i=\infty} \frac{\frac{6}{(\pi i)^2}}{m^* \omega_i^2} \quad (18)$$

The limits of zero frequency and of volume average are interchangeable limiting processes due to the finite volume of the particle. It can be easily seen from (18) that the static susceptibility is no more of the simple Curie-Weiss type which would correspond to the first term in the sum.

The critical transition temperature  $T_c(d)$  can be found from the lowest frequency mode, the soft mode, and it is given by:

$$T_c(d) = T_{c,\infty} - \frac{4\pi^2 D}{a_1 d^2} \quad (19)$$

It increases to its bulk value  $T_{c,\infty}$  quadratically with the increase of the particle diameter d. There is a size driven phase transition with a decreasing diameter

d. For the diameter lower than the critical diameter  $d \leq d_c \equiv 2\pi\sqrt{\frac{D}{a_1 T_{c,\infty}}}$  the ferroelectric phase vanishes.

## 6 Comparison with Experiments

We have compared the theoretical dependence (19) found in this paper for the critical temperature dependence on the diameter  $d$  of the particle with experimental dependence of the critical temperature on the particle diameter for  $PbTiO_3$  and  $BaTiO_3$  particles. Experimental results for  $PbTiO_3$  are found from the measurements in [16]. The authors of [16] used a theoretical formula  $T_{c,\infty} - T_c(d) = \frac{C}{(d-d_c)}$ , where they have found the constant  $C$ ,  $C = 588.5^\circ\text{C nm}$ , and the value for the critical diameter  $d$  of the particle  $d_c = 12.6$  nm to fit the experimental points. Thus they have found that there exists a critical diameter below which there is no ferroelectricity. Experimental results for  $BaTiO_3$  are based on the measurements in [18] and used in [24]. They were described by the theoretical formula  $T_c(d) = T_{c,\infty} - \frac{6D'}{\delta A d}$  where  $D'$  is connected with the correlation length  $\zeta$ :  $D' = \zeta^2 a_1 |T - T_c|$ ,  $a_1$  is the coefficient from the Landau expansion,  $d$  is the diameter of particle. The critical diameter was found to be 44 nm theoretically and 115 nm experimentally for  $BaTiO_3$ . The same authors have found that for  $PbTiO_3$  the value is 4.2 nm (theoretical value) and 13.8 nm (experimental value from [16]) and 9.1 nm (experimental value from [24]). It is interesting that Glinchuk et al. [40] obtained a formula for the critical temperature  $T_c(d)$  dependence on the diameter of a particle by a variational method which has the form  $T_c(d) = T_{c,\infty}(1 - \frac{d_L}{d} - \frac{d_\lambda}{d-d_c})$  where  $d_L$  is the correlation diameter renormalized by the surface tension,  $d_c$  is the correlation diameter renormalized by the surface tension and by the depolarisation field and  $d_\lambda$  is a parameter. As we can see, the surface tensions and depolarisation fields lead to the dependences of the critical temperature used in the papers above as theoretical formulas for fitting the experimental points. Our calculations in this paper of the critical temperature dependence on the particle diameter are exact. It is known that variational calculations always lead to a higher free energy than exact calculations, thus our formula (19) (depolarisation field is assumed to be zero) which leads to  $\frac{1}{d^2}$  dependence instead the Glinchuk et al  $\frac{1}{d}$  dependence, is expected to be better for neglected depolarisation effects. If the depolarisation effects are taken into account we may expect that a constant  $d_m$  in our formula (19) will be introduced in  $\frac{1}{(d-d_m)^2}$  instead of  $\frac{1}{d^2}$ , as a similar dependence is found in the Glinchuk et al. formula. This leads to the following fitting formula for the critical transition temperature  $T_c(d)$ :

$$T_c(d) = T_{c,\infty}(1 - \frac{d_o^2}{(d-d_m)^2}) \quad (20)$$

This formula is expected to correspond to the Glinchuk et al. formula [40] in some sense. In this formula, the depolarisation and surface tension effects are taken into account for diameters near the corresponding correlation diameter. Our above-given results were obtained using the exact calculation of the polarisation profile induced by an external electric field in the paraelectric phase for the large  $\frac{D}{\delta}$  limit. The dependences from (20) with  $\frac{1}{(d-d_m)^2}$  and from (19)  $\frac{1}{d^2}$  are fitted to the experimental data for  $PbTiO_3$ , see Figure (1), and for  $BaTiO_3$

, see Figure (2). Far the best fit - the curve (1), is such in which we are taking the critical temperature  $T_{c,\infty}$ , the parameter  $d_o$  and the parameter  $d_m$  as fitting parameters according to (20). We have fitted this dependence (20) also using the critical temperature as a fixed parameter taking the values from the experiment and fitting the parameter  $d_o$  and the parameter  $d_m$ . We have found that such a fit is still better than the fit using the formula (19), see the curves (2) and (3) respectively in Figure (1) and Figure (2).

Critical temperature  $T_c$  in degrees Celsius (we are using degrees Celsius according to available experimental points) dependence on diameter  $d$  of particles for  $PbTiO_3$  is in Figure (1). Theoretical curves are: curve (1) for  $T_{c,\infty}$ ,  $d_o$  and  $d_m$  as fitting parameters (we have found  $T_{c,\infty} = 511.5^\circ C$ ,  $d_o = 4.8$  nm and  $d_m = 7.3$  nm with quality of fitting procedure given by  $R^2 = 0.811$  and  $d_c = 12.1$  nm), curve (2) for  $T_{c,\infty}$  and  $d_o$  as fitting parameters with  $d_m = 0$  (we have found  $T_{c,\infty} = 519.0^\circ C$  and  $d_o = 7.5$  nm with  $R^2 = 0.8024$  and  $d_c = 7.5$  nm), curve (3) for  $d_o$  as a fitting parameter and  $d_m = 0$  (we have found  $d_o = 5.9$  nm with  $R^2 = 0.6425$  and  $d_c = d_o$ ) with  $T_{c,\infty}$  fixed to  $500.0^\circ C$ . In [16] regarding  $PbTiO_3$  ceramics the diameter corresponding to our  $d_m$  diameter is found to be 12.6 nm, compared to our dead layer width 7.3 nm in Figure (1). The critical diameter corresponding to our  $d_c$  was not evaluated in [16]. Note that the dead layer diameter (=2 x dead layer radius) is in [16] interpreted as a critical size below which ferroelectricity becomes unstable.

Critical temperature  $T_c$  in Kelvins (according to available experimental points we are using Kelvins) dependence on the diameter of particles -  $BaTiO_3$ . Theoretical curves are: curve (1) for  $T_{c,\infty}$ ,  $d_o$  and  $d_m$  as fitting parameters (we have found  $T_{c,\infty} = 390.1$  K,  $d_o = 12.1$  nm and  $d_m = 92.8$  nm with a quality of the fitting procedure given by  $R^2 = 0.9938$  and with  $d_c = 104.9$  nm), curve (2) for  $T_{c,\infty}$  and  $d_o$  as fitting parameters with  $d_m = 0$  (we have found  $T_{c,\infty} = 410.2$  K and  $d_o = 56.5$  nm with  $R^2 = 0.7768$  and  $d_c = d_o$ ), curve (3) for  $d_o$  as a fitting parameter with fixed  $T_{c,\infty} = 391.0$  K from [24] and  $d_m = 0$  nm (we have found  $d_o = 49.4$  nm with  $R^2 = 0.6940$  and  $d_c = d_o$ ). In [24] the theoretically predicted value of the critical diameter is 44 nm and experimentally found 115 nm, they should be compared to our 104.9 nm for the curve (1), 56.5 nm for the curve (2) and 49.4 nm for the curve (3). We see that our value of the critical diameter from the curve (1) is near the experimental value. Our values for curves (2) and (3) are near the theoretical value (for which there no dead layer was assumed in [24]). In [34] on dense  $BaTiO_3$  ceramics with grain size decreasing from 1200 to 50 nm, the authors have found strong support for the existence of an intrinsic size effect. From the experimental trends the critical size for disappearance of ferroelectricity has been evaluated to be from 10 nm to 30 nm. The strong depression of the relative permittivity observed for the nanocrystalline ceramics can be ascribed to the combination of the intrinsic size effect and of the size-dependent dilution effect of a grain boundary dead layer. We have found that the quantity  $d_m$  has the value 92.8 nm for the curve (1). This quantity, which contributes to the total diameter of the particle, leads to the part of the diameter which corresponds to polar region with  $d=11.9$  nm for the critical diameter  $d_c = 104.9$  nm which we have found, see Figure (2). Thus, if we identify  $d_m$  with the dead layer diameter, then we see that the critical diameter found by our fitting procedure is 3 to 10 times larger than that found experimentally.

## 7 Conclusions

A phase transition in a spheroidal particle from paraelectric to ferroelectric phase as well as dynamic susceptibility are affected by the spheroidal shape of ferroelectric particles. This shape leads to many resonance frequencies in the dynamic susceptibility. Sources of the observed complicated multirelaxation behaviour of the dynamic susceptibility in ferroelectric-dielectric composites are of a different type, the shape of particles in microcomposites is one of them. In our model in this paper we assume that the surface charges are compensated. In general, there is a different polarisation at the surface of the particle from than in the bulk. The spheroidal shape does not lead to plane polarisation waves due to the surface effect: the boundary conditions in a spheroidal particle with a surface layer lead to a multirelaxation response. We have found that for the surface boundary condition  $P = 0$  on the surface there is an infinite number of the responding modes as well as infinite number of resonance frequencies. We have found formulas which enable to discuss the effects of the ferroelectric particle shape (spheroid) on its dielectric response. First we described a model from which we have found the dynamic dielectric function within the quasistatic approximation. Dynamic equations for the order parameter, the electric polarisation vector component, were found. We discussed the paraphase properties of the dielectric response of the particle. The Cole-Cole diagram is not of the semicircle form. The static susceptibility within the paraphase is discussed. It does not have the Curie-Weiss like behaviour as in the bulk.

The transition temperature decreases with the decreasing diameter  $d$  of the particle quadratically. We discussed our theoretical results comparing them with experimental results for the critical temperature diameter dependence in  $PbTiO_3$  and in  $BaTiO_3$ . We have found that the formula  $T_c(d) = T_{c,\infty}(1 - \frac{d_o^2}{(d-d_m)^2})$  where  $T_{c,\infty}$  is a fitting parameter in general together with  $d_o$  and  $d_m$ , the last parameter is a parameter describing the dead layer thickness.

## Acknowledgement

The author wishes to express his sincere thanks to V. Dvorak, J. Petzelt and I. Rychetsky, the Department of Dielectrics, Institute of Physics AS CR, Praha, for their discussions about microcomposite materials and small particle ferroelectric properties, to D. Nuzhnyy from the same Institute for his technical help with the figures, to V. Trnovcova, Department of Physics, Faculty of Materials Science and Technology, Trnava Slovak University of Technology in Bratislava, Trnava, for discussions concerning the microcomposites during the author's stay in Trnava and to V. Sepelak from the Geotechnical Institute, SAS, Kosice for discussions on ferroics. This work was supported partially by the grant VEGA 1/3042/06. This work was supported by the Slovak Research and Development Agency under the contract No. APVV-0728-07 at the final stages of the work. The author wishes to express his sincere thanks to P. Presnajder from the Faculty of Mathematics, Physics and Informatics, Comenius University, Bratislava, for his kind support.

## References

- [1] Blinc R. and Zeks B, *Soft Modes in Ferroelectrics and Antiferroelectrics*, North-Holland, Amsterdam, 1974
- [2] Petzelt J., *J.Korean Phys.Soc.*, **32** (1998) S482 - S485
- [3] Petzelt J., Kamba S. and Gregora I., *Phase Transition*, **63** 1997 107 - 145
- [4] Rychetsky I., Hudak O. and Petzelt J., *Phase Transition*, **67** (1999) 725 - 739
- [5] Hudak O., Rychetsky I. and Petzelt J., *Ferroelectrics*, **208-209** (1998) 429 - 447
- [6] Hudak O., Dvorak V., Holakovsky J. and Petzelt J., *Physica Scripta*, **T55** (1994) 77 - 80
- [7] Hudak O., Holakovsky J., Dvorak V. and Petzelt J., *J.Phys.: Condens. Matter*, **7** (1995) 4999 - 5011
- [8] Hudak O., *J.Phys.: Condens. Matter*, **8** (1996) 257 - 272
- [9] Park Yu. and Knowles K.M., *Journal of Applied Physics*, **85** (1999) 6434 - 6439
- [10] Hudak O., Gavilano J.L., Holakovsky J., Dvorak V. and Ott H.-R., *acta physica slovacica*, **44** (1994) 269 - 274
- [11] Hudak O., Gavilano J.L. and Ott H.-R., *Z. Phys.*, **B99** (1996) 587 - 591
- [12] Gavilano J.L., Hunziker J., Hudak O., Sleator T., Hulliger F. and Ott H.-R., *Phys. Rev.*, **B47** (1993) 3438 - 3441
- [13] Hudak O., Gavilano J.L. and H.-R. Ott, *acta physica slovacica*, **46** (1996) 91 - 94
- [14] Aoki Yu., Sato H. and Sugawara H., *Physica*, **B230-B232** (1997) 770 - 772
- [15] Vonlanthen P. et al., *Eur. Phys. J.*, **B9** (1999) 15 - 20
- [16] Ishikawa K., Yoshikawa K. and Okada N., *Phys. Rev.* **B37** (1988) 5852 - 5855
- [17] Jaccard A., Kanzig W., and Peter M., *Helv. Phys. Acta*, **26** (1953) 521
- [18] Anliker M., Brugger H.R., and Kanzig W., *Helv. Phys. Acta*, **27** (1954) 99
- [19] Kretschmer R. and Binder K., *Phys. Rev.*, **B20** (1979) 1065 - 1076
- [20] Tilley D. R. and Zeks B., *Sol. St. Commun.*, **49** (1984) 823 - 828
- [21] Uchino K., Sadanaga E. and Hirose T., *Journal of the American Ceramic Society*, **72** (1989) 1555 - 1558

- [22] Wang Y.G., Zhong W.L. and Zhang P.L., Sol. State Commun., **90** (1994) 329 - 332
- [23] Shih W., Shih W.-H. and Aksay I.A., Phys. Rev., **B30** (1994) 15 575 - 15 585
- [24] Zhong W.L., Wang Y.G., Zhang P.L. and Qu B.D., Phys. Rev., **B50** (1994) 698 - 703
- [25] Zhong W. L., Qu B. D., Zhang P. L. and Wang Y. G., Phys. Rev., **B50** (1994) 12375 - 12380
- [26] Schlag S. and Eicke H.-F., Solid State Commun., **91** (1994) 883 - 887
- [27] Chattopadhyay S., Ayyub P., Palkar V.R. and Multani M., Phys. Rev., **B52** (1995) 13177 - 13183
- [28] Wang Y.G. , Zhong W.L. and Zhang P.L., Phys. Rev. **B51** (1995) 17235-17238
- [29] Qu B., Zhong W. and Zhang P., Phys. Rev. **B52** (1995) 766 - 770
- [30] Wang Y. G., Zhong W. L. and Zhang P. L., Phys. Rev. **B53** (1996) 11439 - 11443
- [31] Shaoping Lia, Eastmana J.A., Lia Z., Foster C. M., Newnamb R. E. and Cross L. E., Physics Letters **A212**(1996) 341 - 346
- [32] Jiang B. and Bursill L. A., Phys. Rev., **B60** (1999) 9978 - 9982
- [33] Jiang B., Peng J. L. and Bursill L.A., J. Appl. Phys., **87** (2000) 3462
- [34] Zhao Z., Buscaglia V., Viviani M., Buscaglia M.T., Mitoseriu L., Testino A., Nygren M., Johnsson M. and Nanni P., Phys. Rev. **B70** (2004) 024107
- [35] Jiang Q., Cui X. F. and Zhao M., Journal Applied Physics A: Materials Science and Processing **78** (2004) 703 - 704
- [36] Rychetsky I. and Hudak O., J. Phys.: Condens. Matter **9** (1997) 4955 - 4965
- [37] Hudak O. and Rychetsky I., Ferroelectrics, **176** (1996) 115 - 124
- [38] Hudak O., Microcomposite Materials of the Ferroelectric - Dielectric Type and Their Dielectric Response, 7th Intl. Conf. CO-MAT-TECH Š 99, Faculty of Materials and Technologies, Slovak Technical University, Trnava, 1999, Proceedings, 92 - 97
- [39] Zhang L., Zhong W.-L. and Hu J.-F., Solid State Commun. **116** (2000) 349 - 354
- [40] Glinchuk M.O. and Morozovskaja A.N., arXiv: cond-mat/0209491v1 2002
- [41] Korenev B.G., Vvedenie v teoriju besselevykh funkciy, Nauka, Moskva 1971
- [42] Abramowitz M and Stegun I.A., Handbook of Mathematical Functions, Applied Mathematics Series 55, National Bureau of Standards, Washington, 1964



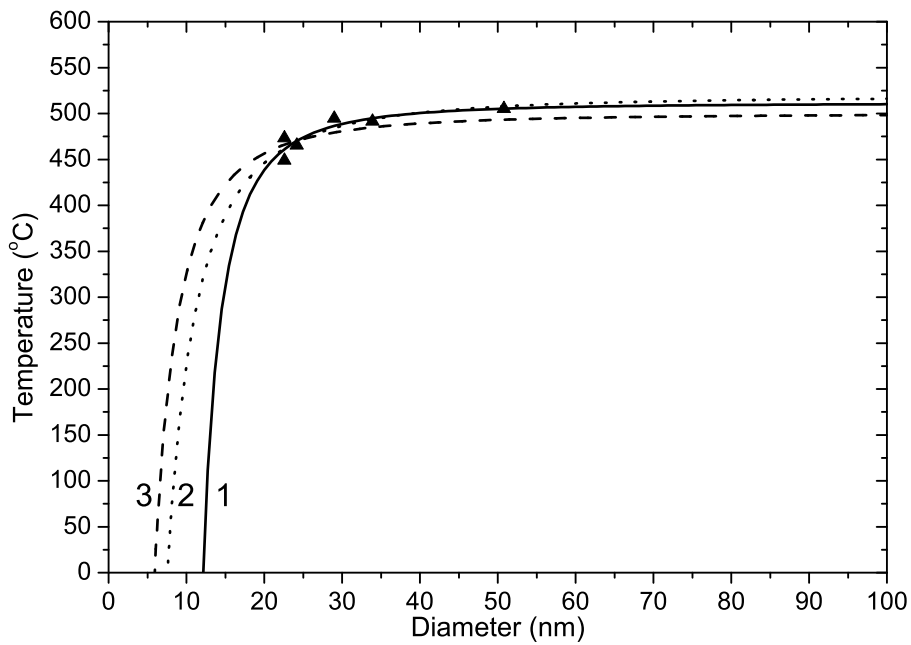


Figure 1: Critical temperature  $T_c$  in degrees Celsius (according to experimental points - full triangles) dependence on diameter of particles -  $PbTiO_3$ . Theoretical curves are: (1) for  $T_{c,\infty}$ ,  $d_o$  and  $d_m$  as fitting parameters, (2) for  $T_{c,\infty}$  and  $d_o$  as fitting parameters with  $d_m = 0$  nm, (3) for  $d_o$  as a fitting parameter with  $T_{c,\infty} = 500^\circ C$  and  $d_m = 0$  nm.

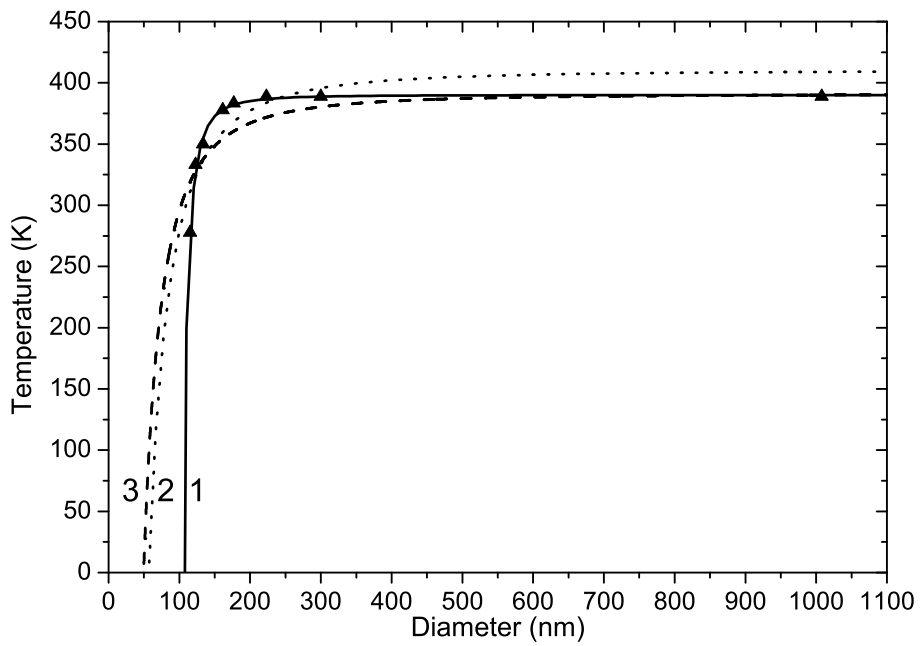


Figure 2: Critical temperature  $T_c$  in Kelvins (according to experimental points - full triangles) dependence on diameter of particles -  $BaTiO_3$ . Theoretical curves are: (1) for  $T_{c,\infty}$ ,  $d_o$  and  $d_m$  as fitting parameters, (2) for  $T_{c,\infty}$  and  $d_o$  as fitting parameters with  $d_m = 0$  nm, (3) for  $d_o$  as a fitting parameter with  $T_{c,\infty} = 391$  K and  $d_m = 0$  nm.