

# Incipient magnetism in the cubic perovskites $\text{MgCNi}_3$ and $\text{YBrh}_3$ : A comparison

P. Jiji Thomas Joseph and Prabhakar P. Singh

*Department of Physics, Indian Institute of Technology Bombay, Powai, Mumbai-400076, India*

Using density-functional-based methods, we have studied the effects of incipient magnetism in the cubic perovskites  $\text{MgCNi}_3$  and  $\text{YBrh}_3$ . Our results show that (i) at the equilibrium volume, both  $\text{MgCNi}_3$  and  $\text{YBrh}_3$  alloys remain paramagnetic and (ii) at expanded volumes, only  $\text{YBrh}_3$  shows the possibility of a ferromagnetic phase with a local magnetic moment larger than  $0.25 \mu_B$  per Rh atom.

The coexistence of magnetism and superconductivity, predicted to be incompatible [1] due to pair-breaking effects of magnetic scattering of electrons [2], has been observed in a wide variety of materials such as the cuprates [3, 4], the ruthenates [5, 6], the heavy fermion compounds [7, 8], the organic superconductors [9, 10], the borocarbides [11, 12] and the transition-metal intermetallics  $\text{ZrZn}_2$  [13].

One of the recently discovered superconducting material, the cubic perovskite  $\text{MgCNi}_3$  [14] with a superconducting transition temperature  $T_C = 8\text{K}$ , shows subtle signatures of incipient magnetism in the form of spin-fluctuations. The density of states of  $\text{MgCNi}_3$  has a strong van-Hove singularity, primarily composed of Ni 3d states, just below the Fermi energy  $E_F$  [15, 16], which suggests that the material may be close to a magnetic instability. Using the rigid band approach, one expects

0.5 holes to drive  $\text{MgCNi}_3$  to ferromagnetism [16, 17]. However, experiments find that hole-doped  $\text{MgCNi}_3$ , with the hole-doping achieved via Fe or Co substitutions in the Ni sub-lattice [18, 19, 20, 21, 22], and vacancies [23, 24] or B substitutions in the C sub-lattice [25], remains non-magnetic.

A variety of transition-metal-rich cubic perovskite materials have been synthesized [26] and tested for superconductivity. Confirmed report of superconductivity appears only for  $\text{YBrh}_3$ , for which resistivity characterization finds  $T_C$  of  $\sim 1\text{K}$  [27]. Magnetic measurements show that  $\text{YBrh}_3$  remains a Pauli paramagnet over a wide temperature range,  $42\text{ T} \sim 300\text{K}$  [27]. The density of states of  $\text{YBrh}_3$  reveals that the density of states at  $E_F$ ,  $N(E_F)$ , is dominated by the Rh 4d states, with little or no contribution of the B 2p states [28, 29]. For expanded volumes, the  $E_F$  is expected to lower in energy. Such a movement in  $E_F$  is expected to enhance  $N(E_F)$ , thus raising the possibility of satisfying the Stoner criteria. At the equilibrium volume, model calculations for  $\text{MgCNi}_3$  show that the Stoner criteria is far from being satisfied [16, 30], but is found large enough to induce spin-fluctuations.

Given that  $\text{MgCNi}_3$  and  $\text{YBrh}_3$  are perovskite superconductors, and that incipient magnetism resides in  $\text{MgCNi}_3$  in the form of spin-fluctuations [30, 31], it is interesting to compare the propensity of magnetism in the two alloys as a function of volume. The present study of ordered  $\text{MgCNi}_3$  and  $\text{YBrh}_3$  alloys is a step in that direction.

The unpolarized, spin polarized, and fixed-spin moment calculations for ordered  $\text{MgCNi}_3$  and  $\text{YBrh}_3$  alloys are carried out, self-consistently, using the Korringa-Kohn-Rostoker method in the atomic sphere approximation (KKR-ASA). The calculations are scalar-relativistic with the partial waves expanded up to  $l_{\text{max}} = 3$  inside the atomic spheres. The exchange-correlation effects are taken into account using the Perdew and Wang parametrization [32]. The core states have been recalculated after each iteration. The overlap volume resulting from the blow up of the muffin-tin spheres was less than 15%. The integration of the Green's function over the energy to evaluate moments of the density of electronic states was carried out along a semi circular contour comprising of 20 points in the complex plane. For the Brillouin zone integrations, the special k point technique was employed with 1771 k points spread in the irreducible wedge of the cubic Brillouin zone. The convergence in the charge density was achieved so that the root-mean square of moments of the occupied partial density of states becomes smaller than  $10^{-6}$ .

The calculated equilibrium lattice constants for  $\text{MgCNi}_3$  and  $\text{YBrh}_3$  are found to be  $7.138\text{\AA}$  and  $7.919\text{\AA}$ , respectively. For  $\text{MgCNi}_3$  the calculated lattice constant is consistent with the previous first-principles reports [30], but the value is underestimated by 1% when compared with the experiments [14]. Surprisingly, for  $\text{YBrh}_3$  the calculated lattice constant appears to be overestimated in comparison with the experiments [27, 33, 34], which is not so common. A previous theoretical estimate of the lattice constant of  $\text{YBrh}_3$  also finds an overestimated value [28]. Such a discrepancy also exists for  $\text{ZnCNi}_3$  alloys [35, 36]. For the latter, it is argued that the material  $\text{ZnCNi}_3$  subjected to experiments may be off-stoichiometric in C sub-lattice [36]. Thus, it can be inferred that the material  $\text{YBrh}_3$ , which is reported to be a superconductor [27], may be deficient in B content, and if so, following the case of  $\text{MgCNi}_3$  one may expect higher  $T_C$  for the stoichiometrically ordered materials.

The densities of states of  $\text{MgCNi}_3$  and  $\text{YBrh}_3$ , calculated at the respective equilibrium lattice constants, are shown in Fig.1. For both the materials, the density of states at  $E_F$  is dominated by the transition-metal states, Ni in  $\text{MgCNi}_3$  and Rh in  $\text{YBrh}_3$ . For  $\text{MgCNi}_3$ , the van-Hove singularity is well reproduced, and it is about  $0.06\text{m Ry}$  below  $E_F$ , in agreement with the earlier band-

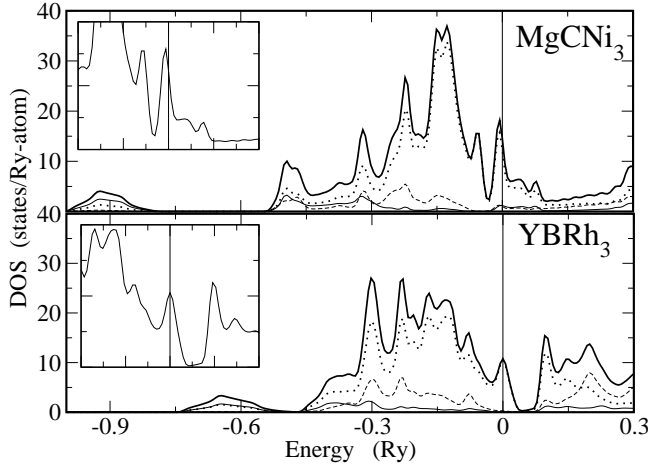


Figure 1: The total and sub-lattice resolved partial densities of states of  $\text{MgCNi}_3$  (upper panel) and  $\text{YBRh}_3$  (lower panel), calculated at their equilibrium lattice constants. The thick line represents the total density of states while dotted, dashed and thin lines represent partial densities of states for Ni(Rh), Mg(Y), and C(B). The inset is a blow up of the states near the Fermi energy which is shown as a vertical line through the energy zero.

structure reports [16]. For  $\text{YBRh}_3$ , the van-Hove singularity falls at  $E_F$ . In the itinerant model of magnetism, a high  $N(E_F)$  is essential for magnetism, and thus it appears that both  $\text{MgCNi}_3$  and  $\text{YBRh}_3$  alloys are close to ferromagnetic instability. In the case of  $\text{YBRh}_3$  the total energies of both spin polarized and unpolarized calculations at the equilibrium lattice constant remain degenerate, making  $\text{YBRh}_3$  into a paramagnetic material. The calculated paramagnetic  $N(E_F)$  for  $\text{MgCNi}_3$  and  $\text{YBRh}_3$  are 14.562 and 11.212 states/Ry atom respectively, which are consistent with the previous reports [16, 17, 28, 30, 37].

The characteristic difference in the densities of states of  $\text{MgCNi}_3$  and  $\text{YBRh}_3$  is the absence of non-metal 2p states at  $E_F$  in  $\text{YBRh}_3$ . This compares well with its iso-electronic counterpart  $\text{MgCCO}_3$ . However,  $\text{MgCCO}_3$  is found to be a weak ferromagnet with Co having a local magnetic moment of 0.33  $\mu_B$  [38, 39]. Next, we describe the effects of volume expansion on the incipient magnetism in  $\text{MgCNi}_3$  and  $\text{YBRh}_3$ .

For  $\text{MgCNi}_3$ , up to a 15% increase in lattice constant from the equilibrium showed no local magnetic moment at the Ni site. The results of our calculations are summarized in Fig.2, where we show the density of states as a function of lattice constant in  $\text{MgCNi}_3$  over an energy interval of  $-0.2 \leq E \leq 0.2$ . Though  $N(E_F)$  increases steadily with increasing lattice constant, the peak, which is characteristic of the Ni 3d bands, does not change its position on the energy scale, consistent with the observations made by Rosner et al [16]. However, the increase in  $N(E_F)$  is not sufficient to induce a magnetic phase transition in  $\text{MgCNi}_3$  even at expanded volumes.

For  $\text{YBRh}_3$ , our calculations reveal a sharp ferromag-

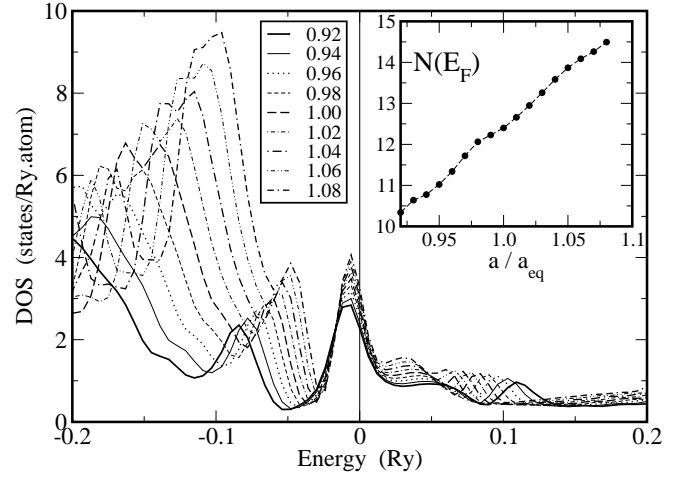


Figure 2: The total density of states of  $\text{MgCNi}_3$  for various lattice constants (as indicated in the left inset), calculated as described in the text. The density of states is shown over an energy interval  $-0.2 \leq E \leq 0.2$  with respect to the Fermi energy. The vertical line through the energy zero represents the Fermi energy. The total density of states at  $E_F$  as a function of lattice constant is shown in the right inset.

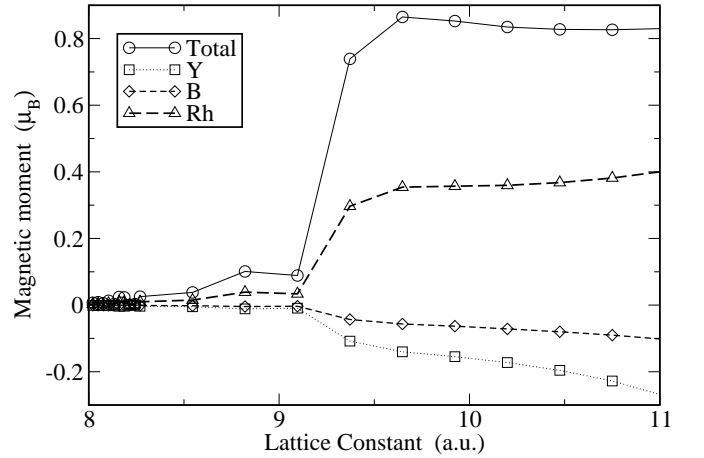


Figure 3: The total magnetic moment as well as its contributions from the Y, B and Rh sub-lattices in  $\text{YBRh}_3$  as a function of lattice constant, calculated as described in the text.

netic transition with respect to expanded lattice constants. In Fig.3, we show the total magnetization as a function of lattice constant for  $\text{YBRh}_3$ . The individual contributions to the magnetization from Y, B and Rh sub-lattices in  $\text{YBRh}_3$  are also shown in Fig.3. We find a sudden appearance of local magnetic moment larger than 0.25  $\mu_B$  per Rh atom for lattice constants larger than 15% of the equilibrium value in  $\text{YBRh}_3$ . Small magnetic moments, which are anti-ferromagnetically coupled to the magnetic moment at the Rh site, also develop at the Y and B sites due to the hybridization with the 4d states of Rh.

As a cross check to the self-consistent calculations,

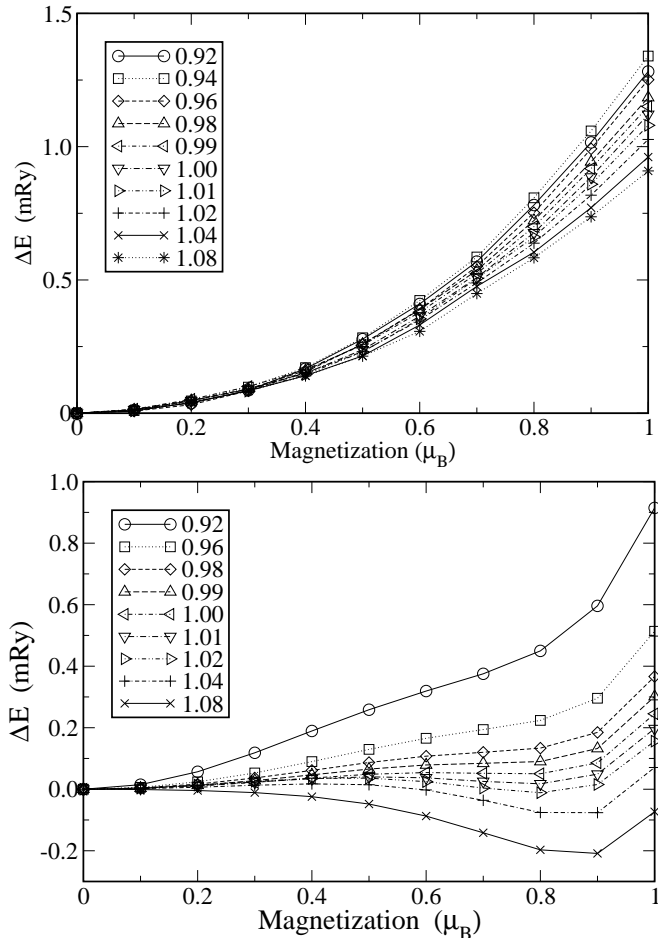


Figure 4: The Magnetic energy  $E(M)$  (in mRy) as a function of magnetization  $M$  (in  $\mu_B$ ) for  $MgCNi_3$  (upper panel) and  $YBrh_3$  (lower panel), calculated as described in the text.

as described above, we have carried out fixed-spin moment calculations [40] to estimate the magnetic energy  $E(M) = E(M) - E(0)$ , where  $E(0)$  and  $E(M)$  are the total energies for the paramagnetic phase and ferromagnetic phase with a magnetic moment  $M$  respectively, for both  $MgCNi_3$  and  $YBrh_3$  at various lattice constants.

In Fig.4, we show the calculated magnetic energy  $E(M)$  as a function of  $M$  for various lattice constants for both  $MgCNi_3$  and  $YBrh_3$ . From Fig.4, it is clear that  $MgCNi_3$  remains paramagnetic throughout, as no minimum, other than for  $M=0$ , appears in  $E(M)$  vs.  $M$  curve. However, for  $YBrh_3$  a second minimum appears in the  $E(M)$  vs.  $M$  curve, indicating a ferromagnetic transition. Hence, both self-consistent and fixed-spin moment methods show a greater propensity of magnetism in  $YBrh_3$  than in  $MgCNi_3$ . The existence of an enhanced magnetic behavior in  $YBrh_3$  is due to a weak hybridization of the metal  $d$  states with that of the non-metal  $p$  states in comparison with  $MgCNi_3$ . In  $MgCNi_3$ , one finds that the  $C 2p$  states and the  $Ni 3d$  states hybridize strongly with significant contribution to  $N(E_F)$  from the  $C$  sub-lattice.

In conclusion, first-principles, density-functional-based calculations find  $YBrh_3$  to be closer to a magnetic instability than  $MgCNi_3$  with respect to lattice constant. The enhanced propensity of magnetism in  $YBrh_3$  may be responsible for lowering the value of  $T_C$ , in spite of high density of states at  $E_F$ . The superconductor  $YBrh_3$  thus falls in the same class as the refractory compounds  $VN$ , where spin-fluctuations lower the  $T_C$  drastically.

- 
- [1] J. Bardeen, L. N. Cooper, and J. R. Schrieffer Phys. Rev. 106, 162 (1957)
  - [2] A.A. Abrikosov and L.P. Gorkov, Sov. Phys. JETP 12, 1243 (1961)
  - [3] J. G. Bednorz and K. A. Muller, Z. Phys. B 64, 189 (1986)
  - [4] M. K. Wu, J. R. Ashburn, C. J. Torng, P. H. Hor, R. L. Meng, L. Gao, Z. J. Huang, Y. Q. Wang, and C. W. Chu, Phys. Rev. Lett. 58, 908 (1987)
  - [5] Y. Maeno, H. Hashimoto, K. Yoshida, S. Nishizaki, T. Fujita, J. G. Bednorz, and F. Lichtenberg, Nature (London) 372, 572 (1994).
  - [6] W. E. Pickett, R. Weht, and A. B. Shick, Phys. Rev. Lett., 83 3713 (1999).
  - [7] S. S. Saxena, P. Agarwal, K. Ahilan, F. M. Grosche, R. K. W. Haselwimmer, N. J. Steiner, E. Pugh, I. R. Walker, S. R. Julian, P. Monthoux, G. G. Lonzarich, A. Huxley, I. Sheikin, C. Braithwaite, and J. Flouquet, Nature (London) 406, 587 (2000).
  - [8] F. Steglich, J. Aarts and H. Schaffer, Phys. Rev. Lett. 43, 1892 (1979)
  - [9] K. Bechgaard, C. S. Jacobsen, K. Mortensen, H. J. Pedersen, N. Thorup, Solid State Commun., 33, 1119-1125. (1980)
  - [10] D. Jerome, A. Mazaud, M. Ribault, J. Phys. Lett. 41, L95 (1980)
  - [11] R. Nagarajan, C. Mazumdar, Z. Hossain, S. K. Dhar, K. V. Gopalakrishnan, L. C. Gupta, C. Godart, B. D. Padalia, and R. Vijayaraghavan, Phys. Rev. Lett. 72, 274 (1994)
  - [12] R. J. Cava, H. Takagi, H. W. Zandbergen, J. J. Krajewski, W. F. Peck Jr., T. Siegrist, B. Batlogg, R. B. van Dover, R. J. Felder, K. Mizuhashi, J. O. Lee, H. Eisaki, and S. Uchida, Nature 367, 254 (1994).
  - [13] C. Pfleiderer, M. Uhlarz, S. M. Hayden, R. Vollmer, H. von Lohneysen, N. R. Bernhoeft, and G. G. Lonzarich, Nature (London) 412, 58 (2001).
  - [14] T. He, K.A. Regan, M. A. Hayward, A. P. Ramirez, Y. Wang, P. Khalifah, T. He, J.S. Slusky, N. Rogado, K.

- Inumaru, M.K. Haas, H.W. Zandbergen, N.P. Ong, and R.J. Cava, *Nature*, 411, 54 (2001)
- [15] J. H. Kim, J. S. Ahn, J. Kim, Min-Seok Park, S. I. Lee, E. J. Choi, and S.-J. Oh, *Phys. Rev. B* 66, 172507 (2002)
- [16] H. Rosner, R. Weht, M. D. Johannes, W. E. Pickett, and E. Tosatti, *Phys. Rev. Lett.* 88, 027001 (2002)
- [17] S. B. Dugdale and T. Jarlborg, *Phys. Rev. B* 64, 100508 (2001)
- [18] T. G. Kumary, J. Janaki, A. Mani, S. M. Jaya, V. S. Sastry, Y. Hariharan, T. S. Radhakrishnan, and M. C. Valsakumar, *Phys. Rev. B* 66, 064510 (2002)
- [19] T. Klimczuk and R.J. Cava, *Solid State Commun* 132, 379 (2004)
- [20] M. A. Hayward, M. K. Haas, A. P. Ramirez, T. He, K. A. Regan, N. Rogado, K. Inumaru and R. J. Cava, *Solid State Commun.* 119, 491 (2001)
- [21] M. Alzamora, D. R. Sanchez, M. Cindra and E. M. Baggio-Saitovitch, *Brazilian J. Phys* 32, 755 (2002)
- [22] A. Das and R. K. Kremer, *Phys. Rev. B* 68, 064503 (2003)
- [23] T.G. Amos, Q. Huang, J.W. Lynn, T. He, R.J. Cava, *Solid State Commun* 121, 73 (2002)
- [24] A. Ren, G. C. Che, S. L. Jia, H. Chen, Y. M. Ni, G. D. Liu and Z. X. Zhao, *Physica C* 371, 1 (2002)
- [25] T. Klimczuk, M. Avdeev, J. D. Jorgensen, R.J. Cava, *cond-mat/0412551*
- [26] R. E. Schaak, M. Avdeev, W. -L. Lee, G. Lawes, H. W. Zandbergen, J. D. Jorgensen, N. P. Ong, A. P. Ramirez and R. J. Cava, *J. Solid State Chem.* 177, 1244 (2004)
- [27] H. Takei, N. Kobayashi, H. Yamauchi, T. Shishido and T. Fukase, *J. Less Common Metals* 125, 233 (1986)
- [28] P. Ravindran, S. Sankaralingam, and R. Asokamani *Phys. Rev. B* 52, 12921 (1995)
- [29] M. Oku, T. Shishido, K. Wagatsuma, Q. Sun and Y. Kawazoe, *Journal Alloys and Compounds* 349, 206 (2003)
- [30] D. J. Singh and I. I. Mazin, *Phys. Rev. B* 64, 140507 (2001)
- [31] P. M. Singer, T. Imai, T. He, M. A. Hayward, and R. J. Cava, *Phys. Rev. Lett.* 87, 257601 (2001)
- [32] J. P. Perdew and Y. Wang, *Phys. Rev. B* 45, 13244 (1992).
- [33] T. Shishido, J. Ye, K. Kudou, S. Okada, K. Obara, T. Sugawara, M. Oku, K. Wagatsuma, H. Horiuchi and T. Fukuda, *Journal Alloys and Compounds* 291, 1999, 52 (1999)
- [34] T. Shishido, J. Ye, S. Okada, K. Kudou, K. Iizumi, M. Oku, Y. Ishizawa, T. Amano, S. Kohiki, Y. Kawazoe and K. Nakajima, *J. Alloys and Compounds* 354, 198 (2003)
- [35] M. S. Park, J. S. Giim, S. H. Park, Y. W. Lee, S. I. Lee and E. Choi, *J. Supercond. Sci. Technol.* 17, 274 (2004)
- [36] M. D. Johannes and W. E. Pickett *Phys. Rev. B* 70, 060507 (2004)
- [37] J. H. Shim, S. K. Kwon, and B. I. Min, *Phys. Rev. B* 64, 180510 (2001)
- [38] I. G. Kim, J. I. Lee, and A. J. Freeman, *Phys. Rev. B* 65, 064525 (2002)
- [39] J. L. Wang, Y. Xu, Z. Zeng, Q. Q. Zheng, H. Q. Lin, J. Appl. Phys 91, 8504 (2002)
- [40] K Schwarz and P Mohn, *J. Phys. F: Met. Phys.* 14, L129 (1984)