

Pressure-Induced Anomalous Phase Transitions and Colossal Enhancement of Piezoelectricity in PbTiO_3

Zhigang Wu and Ronald E. Cohen

Geophysical Laboratory, Carnegie Institution of Washington, Washington, DC 20015, USA

(Dated: May 1, 2019)

We find an unexpected tetragonal-to-monoclinic-to-rhombohedral-to-cubic phase transition sequence induced by pressure, and a morphotropic phase boundary in a pure compound using first-principles calculations. Huge dielectric and piezoelectric coupling constants occur in the transition regions, comparable to those observed in the new complex single-crystal solid-solution piezoelectrics such as $\text{Pb}(\text{Mg}_{1/3}\text{Nb}_{2/3})\text{O}_3$ - PbTiO_3 , which are expected to revolutionize electromechanical applications. Our results show that morphotropic phase boundaries and giant piezoelectric effects do not require intrinsic disorder, and open the possibility of studying this effect in simple systems.

PACS numbers: 77.80.-e, 77.84.-s, 63.20.-e

The classic ferroelectric PbTiO_3 has been known to have a single ferroelectric tetragonal (T) to paraelectric cubic phase transition with increased temperature [1] or pressure [2] since its discovery [3] in 1950. It seemed unlikely to discover any new ferroelectric transitions in PbTiO_3 , but we predict new ferroelectric phases under pressure. Piezoelectrics convert electric energy to mechanical energy, and vice versa. They are widely used in medical imaging, acoustic sensors and transducers, actuators, *etc* [4, 5]. PbTiO_3 has been extensively studied [1, 2, 6, 7, 8, 9, 10, 11] to understand the electronic origin of ferroelectricity. The Pb-O and Ti-O hybridization in PbTiO_3 weakens the short-range repulsions and gives rise to the ferroelectric distortion [7]. It has been found that pressure suppresses ferroelectricity since compression favours short-range repulsion, but there has been no previous work on the effect of pressure on piezoelectricity.

PbTiO_3 has a high *c*-axis strain of 6.5% (7.1%) at room (low) temperature. Under ambient pressure it undergoes a first-order phase transition at $T_c = 763$ K, and this transition is regarded as a typical displacive transition, which is associated with soft-modes [1]. The displacive phase transition temperature T_c decreases under hydrostatic pressure. A Raman study of PbTiO_3 shows that T_c reduces to 300 K and the phase transition becomes second-order at $P = 12.1$ GPa [2]. It indicates a tricritical point in the phase diagram, where the first-order phase transition changes to second-order, and it has been identified at $P = 1.75$ GPa, $T = 649$ K [12]. Increasing pressure further reduces T_c .

PbTiO_3 is an end member of $\text{Pb}(\text{Mg}_{1/3}\text{Nb}_{2/3})\text{O}_3$ - PbTiO_3 (PMN-PT) and $\text{Pb}(\text{Zn}_{1/3}\text{Nb}_{2/3})\text{O}_3$ - PbTiO_3 (PZN-PT), which have piezoelectric coefficients an order of magnitude larger than those of conventional ferroelectric simple compounds [13]. It is also an end member of PbZrO_3 - PbTiO_3 (PZT), the most widely used current piezoelectric, which is ubiquitous in modern technology. These materials have a common feature, namely the morphotropic phase boundary (MPB), and they have optimum piezoelectric efficiency near the MPB. Polar-

ization rotation [14, 15] is believed to play an important role for this extraordinary property. Close to the MPB, the energy surface for polarization is very flat so that for example a polarization along [111] direction in the rhombohedral (R) phase can be easily rotated toward the tetragonal polarization direction by applying an electric field along [001] direction, and the R phase is transformed to the T phase via the intermediate phase(s). This mechanism has been elucidated by theoretical calculations on BaTiO_3 [14] and PZT [16, 17], and by experimental findings of low symmetry phases [18, 19, 20]. The giant piezoelectric effects always do not occur along the spontaneous polarization direction [13, 15]). At ambient pressure PbTiO_3 has no such MPB because it has a rather stiff energy surface near the T phase and it has no R phase. Under high pressures the energy (enthalpy) surface is expected to be softer, and an MPB could arise.

In this Letter we address both issues of phase transitions and piezoelectricity of PbTiO_3 under hydrostatic pressures. We perform total energy as well as linear response computations, which have been proved to be highly reliable for ground state properties. We find anomalous phase transitions and giant enhancement of dielectricity and piezoelectricity near the phase transition regions induced by pressure.

We have carried out zero temperature *ab initio* computations based on density functional theory (DFT) within the local density approximation (LDA). We used the pseudopotential planewave method implemented in the ABINIT package [21]. The planewave energy cutoff is 60 Hartree, and the \mathbf{k} -point mesh for Brillouin Zone integration is of $6 \times 6 \times 6$. We used the OPIUM program [22] to generate norm-conserving pseudopotentials, which were rigorously tested against the full-potential linearized augmented planewave (LAPW) method [23]. We included semi-core states of Pb $5d^{10}$, Ti $3s^23p^64d^2$, and O $2s^2$ in valence states. We chose the LDA instead of the generalized gradient approximation (GGA) because the GGA catastrophically overestimates both equilibrium volume and strain for tetragonal PbTiO_3 [24]. On the other

TABLE I: Elastic ($c_{\mu\nu}$) and piezoelectric ($e_{i\nu}$) constants of tetragonal $P4mm$ PbTiO_3 with lattice constants $a = 3.902 \text{ \AA}$, $c = 4.155 \text{ \AA}$. $c_{\mu\nu}$ and $e_{i\nu}$ are in GPa and C/m^2 , respectively. Here FS refers to the finite strain method.

Methods	c_{11}	c_{12}	c_{13}	c_{33}	c_{44}	c_{66}	e_{31}	e_{33}	e_{15}
DFPT	230	96.2	65.2	41.9	46.6	98.8	2.06	4.41	6.63
FS	229	95.6	64.3	41.2	47.2	98.6	2.07	4.48	6.66

hand, the LDA moderately underestimates the volume (60.38 \AA^3) and strain (4.6%), and the experimental V_0 corresponds to a negative pressure $P_0 = -2.2 \text{ GPa}$.

To calculate the dielectric susceptibility χ_{ij} , elastic constants $c_{\mu\nu}$, and piezoelectric stress constants $e_{i\nu}$ (Here Latin indexes run from 1 to 3, and Greek indexes from 1 to 6), we used the density functional perturbation theory (DFPT) [25] of the linear response of strain type perturbations [26]. The DFPT is based on the systematic expansion of the variation expression of the DFT total energy in powers of parameters, such as atomic coordinates, macroscopic strain and electric field. Tensors χ and c involve second derivatives of total energy with respect to electric field and strain respectively, and tensor e is the mixed second derivative of total energy with respect to strain and electric field. Here $c_{\mu\nu} \equiv \frac{\partial \sigma_\mu}{\partial \eta_\nu}$ with σ stress and η strain. The DFPT calculates $C_{\mu\nu} = \frac{\partial^2 E}{\partial \eta_\mu \partial \eta_\nu}$ with E the total energy. Under non-zero stress (e.g. pressure), $c_{ijkl} = C_{ijkl} - \delta_{ij} \sigma_{kl}$. The elastic compliance tensor s is the reciprocal of tensor c , and the piezoelectric strain coefficients $d_{i\nu} = \sum_{\mu=1}^6 e_{i\mu} s_{\mu\nu}$. We have examined the accuracy of $c_{\mu\nu}$ and $e_{i\nu}$ obtained from the DFPT by comparing with the finite strain method. As summarized in Table I, excellent agreement between these two methods is achieved.

We constrained the symmetry to study four phases: the paraelectric cubic (C) $Pm\bar{3}m$ phase, the ferroelectric tetragonal $P4mm$, rhombohedral $R\bar{3}m$, and monoclinic (M) Cm phases. We find that the enthalpy ($H = E + PV$) difference between the T and R phases reduces rapidly with pressure and becomes very small when $P > 8 \text{ GPa}$. The lowest enthalpy corresponds to the most stable phase at that pressure. As displayed in Fig. 1(a) and 1(b), there is a T to M phase transition around 9.5 GPa ($V = 56.73 \text{ \AA}^3$), M to R around 11 GPa ($V = 56.32 \text{ \AA}^3$), and R to C around 22 GPa ($V = 53.97 \text{ \AA}^3$). The M phase for $P = 9.5 \text{ GPa}$ has its spontaneous polarization \mathbf{P}^s along the pseudocubic $[uu1]$ direction, where $u = 0.481$. The discovery of a low symmetry M phase is completely unexpected in a pure compound like PbTiO_3 , and has only been found in complex solid-solutions like PZT [18], PMN-PT [19], *etc.*

Because the enthalpy differences among these phases are very small, the above calculated pressure-induced phase transition sequence needs to be examined by directly studying energy derivative properties, such as elas-

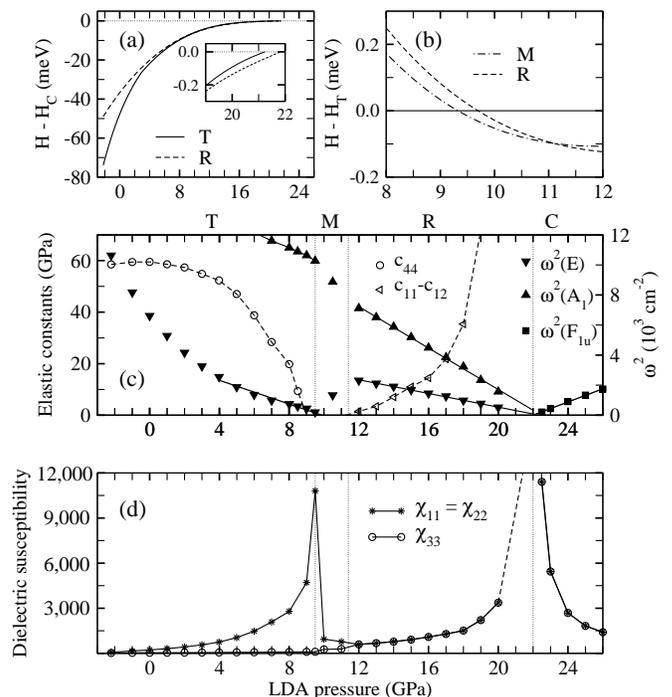


FIG. 1: Stability of various phases as a function of pressure. (a) Enthalpy difference with respect to the C phase for the T and R phases. (b) Enthalpy difference with respect to the T phase for the R and M phases. (c) Elastic constant c_{44} and $c_{11} - c_{12}$ respectively for the T and R phases, and square of the lowest optical phonon frequencies ω^2 for the T [$E(1TO)$, $A_1(1TO)$], R [$E(1TO)$, $A_1(1TO)$], and C [$F_{1u}(1TO)$] phases. (d) Dielectric susceptibility χ .

ticity, phonon frequencies, and dielectricity. The pressure dependence of elastic constants c_{44} in the T phase and $c_{11} - c_{12}$ in the R phase is shown in Fig. 1(c). Note that the cubic coordinate system is used for all cases, and elastic constants $c_{11} = c_{22} = c_{33}$ and $c_{12} = c_{13} = c_{23}$ in the R phase. We find that both c_{44} and $c_{11} - c_{12}$ approach zero around 9 and 11.5 GPa, respectively. Negative c_{44} and $c_{11} - c_{12}$ mean that the T and R phases are unstable respectively against shear and tetragonal shear strain, indicating phase transitions. The estimated phase transition pressures from elasticity anomalies agree well with the total energy results.

In tetragonal $P4mm$ PbTiO_3 , the $E(1TO)$ and $A_1(1TO)$ modes originate from the triply degenerate $F_{1u}(1TO)$ mode in the C phase. When the T-to-C phase transition occurs at high temperature and ambient pressure [1] or high pressure and room temperature [2], both the $E(1TO)$ and $A_1(1TO)$ modes soften simultaneously. However, at 0 K we find that pressure induces condensation only of the $E(1TO)$ mode around $P = 10 \text{ GPa}$ [Fig. 1(c)]. A linear combination of the doubly degenerate $E(1TO)$ modes gives rise to the transition to the M phase. For the R phase, the $E(1TO)$ and $A_1(1TO)$

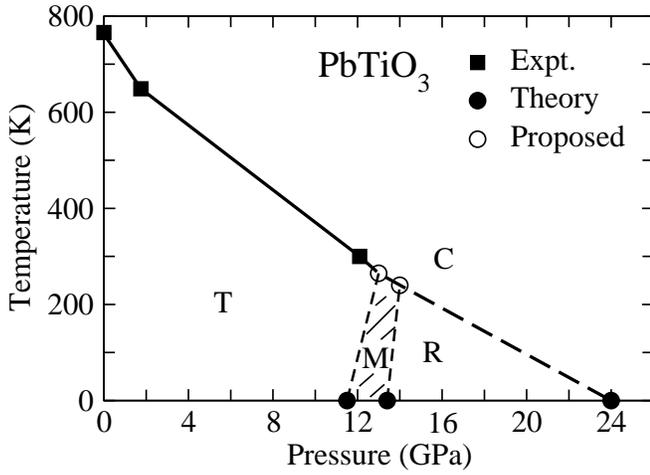


FIG. 2: Proposed (P, T) phase diagram. It combines theoretical results (solid circles) at 0 K with experimental data (solid squares) at finite temperatures. In this figure we rescaled the theoretical pressure for the experimental volume to be zero by shifting. The open circles are our guess for these two tricritical points, and an *ab initio* molecular dynamics simulation is needed to predict them accurately.

modes soften simultaneously at $P \approx 22$ GPa, going to the $F_{1u}(1TO)$ mode in the C phase. This gives rise to the R-to-C phase transition. The linearity of the square of mode frequency ω^2 vs. pressure close to phase transition indicates a Curie-Weiss pressure law. Fig. 1(d) shows that the static dielectric susceptibility χ_{11} has a maximum around 9.5 GPa, indicating a first-order transition; while it diverges at $P \approx 22$ GPa, indicating a second-order transition, as can be understood from the Lyddane-Sachs-Teller (LST) relation. For the T phase near transition pressure, $\chi_{11} = \chi_{22} \propto 1/\omega^2[E(1TO)]$, and $\chi_{33} \propto 1/\omega^2[A_1(1TO)]$. Thus χ_{11} increases rapidly around 9.5 GPa, whereas χ_{33} does not. The same analysis can be applied to the R and C phases. The phase transition pressures obtained from phonon frequencies and dielectric constants also are consistent with the total energy results, and it shows that the computed small energy differences between phases are reliable. Our first-principles calculations neglect quantum fluctuations, which could reduce the phase transition pressures [27].

We have predicted the pressure-induced phase transitions of PbTiO_3 at 0 K. Combining our results with experimental finite temperature data, we propose a schematic (P, T) phase diagram (Fig. 2), in which the intermediate M phase separates the T phase at low pressures and the R phase at higher pressures. This phase diagram bears remarkable resemblance to the (x, T) phase diagram of PZT [18], where x is the PbTiO_3 composition. The narrow M area is the MPB of PbTiO_3 , and it serves as a structure bridging the T and R phases in that its spontaneous polarization is located in the $(\bar{1}10)$ plane

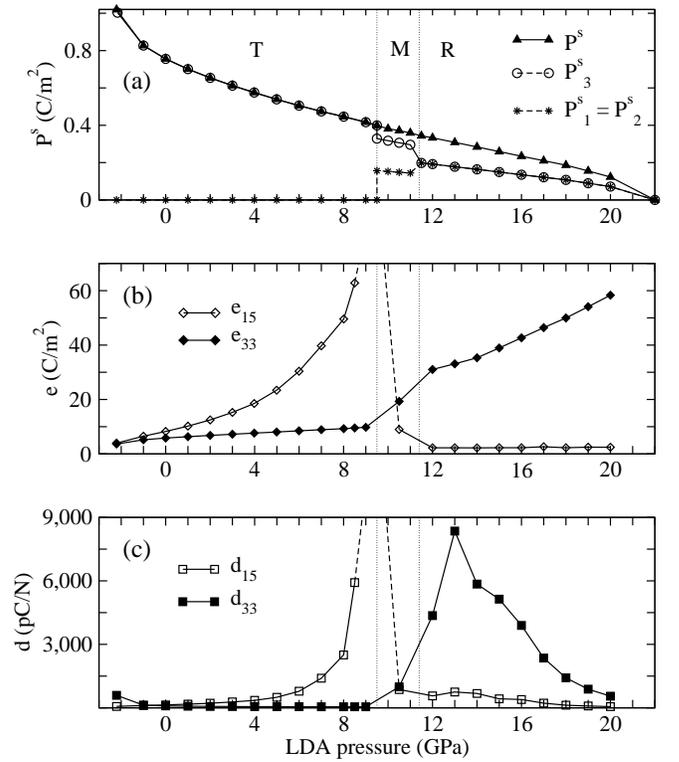


FIG. 3: Pressure dependence on piezoelectricity. (a) Spontaneous polarization \mathbf{P}^s . (b) Piezoelectric stress coefficients e_{15} and e_{33} . (c) Piezoelectric strain coefficients d_{15} and d_{33} .

and between the pseudocubic $[001]$ and $[111]$ directions, which is very similar to that in PZT.

Pressure suppresses spontaneous polarization \mathbf{P}^s [Fig. 3(a)] and the c -axis strain. Although the magnitude of \mathbf{P}^s changes continuously at the T-M transition pressure, P_1^s is discontinuous, indicating a first-order phase transition, consistent with the conclusion drawn from dielectric constants. We emphasize that when the T-to-M phase transition occurs, \mathbf{P}^s retains about half of the magnitude under zero pressure and $c/a = 1.012$. These values are comparable to those of PMN-PT [19], PZN-PT [20], and PZT [28] in the T phase close to MPB.

Fig. 3(b) and 3(c) summarize the pressure effect on piezoelectricity of PbTiO_3 . For the T phase, e_{33} increases, whereas the piezoelectric strain coefficient d_{33} decreases with pressure. The relatively large d_{33} at $P = -2.2$ GPa is due to the LDA overestimation of strain at the experimental volume. Both e_{15} and d_{15} increase with pressure, and they rise dramatically for $P > 4$ GPa when c_{44} begins to drop quickly [Fig. 1(c)]. The T phase has $d_{15} = e_{15}/c_{44}$, so that d_{15} increases even faster than e_{15} . The pressure-induced large enhancements of e_{15} and d_{15} are a result of the sharp reduction of the enthalpy difference between the T and R phases, and both e_{15} and d_{15} diverge at the T-to-M phase transition pressure. For

the R phase, both e_{15} and d_{15} are rather small, and e_{33} jumps to over 30 C/m^2 , increasing with pressure. d_{33} has huge values near the M phase and remains larger than 1500 pN/C for a broad range of pressure. The R phase under high pressure has $d_{33} \approx e_{33}/(c_{11} - c_{12})$, and the increase of $c_{11} - c_{12}$ with pressure [Fig. 1(c)] causes d_{33} to decrease with pressure, even though e_{33} rises. Note that d_{33} at 12 GPa is smaller than at 13 GPa, and it could be due to numerical uncertainties, since small variations of elastic constants c_{14} and c_{15} change elastic compliance s dramatically when $c_{11} - c_{12}$ is small. It is evident that the predicted giant piezoelectric effect of PbTiO_3 comes from non-collinear polarization rotation since the enhancement of d_{15} in the T phase and d_{33} in the R phase do not occur along the spontaneous polarization directions, and the M phase acts as a structural bridge between the T and R phases as indicated by pressure inducing polarization rotation from $[001]$ to $[111]$ directions.

We have demonstrated that pressure can induce an MPB in a simple compound PbTiO_3 , which is very similar to the composition-induced MPB in complex solid-solutions, such as PZT [18], PMN-PT [19], and PZN-PT [20]. It is critical that these ferroelectric systems near MPB have distinct phases (different patterns of atomic displacements) with very close free energies. Each local minimum is shallow and a broad global minimum exists. Low symmetry phases can be stabilized between two high symmetry phases if both of them become saddle points, and this is the origin of an MPB. Near an MPB, smooth transformation between two high symmetry phases with different polarization directions via a low symmetry phase results in strong coupling between internal degree of freedom and strain.

In PbTiO_3 , ferroelectricity arises from the competition of short-range repulsions which favor the C phase, and Coulomb forces which favor a ferroelectric phase [7]. As pressure is increased, the short-range repulsions promoting paraelectric stability increase faster than the Coulomb terms promoting ferroelectric instability. Therefore pressure favors the paraelectric phase and suppresses ferroelectricity. Because the tetragonal well-depth along $[001]$ reduces faster than the rhombohedral wells along $[111]$, under a certain pressure the T and R well-depths are equal, and the energy surface connecting the T and R phase becomes very flat. Higher order terms in the energy expression result in an intermediate M phase [29], which has slightly lower energy than both of the T and R phases, leading to a T-to-M phase transition. Further increasing pressure will make the R phase more stable than the M phase. For another important ferroelectric, BaTiO_3 , an M phase is not expected at low temperature, because the R well-depth is deeper than the T well-depth so that pressure can not induce an M phase before both well-depths disappear.

Pressure-tuning of the structural and piezoelectric

properties of PbTiO_3 promises to be an intriguing avenue for experimental study. PbTiO_3 under pressure should be the simplest possible system to study the basic physics of the MPB and piezoelectric enhancement through polarization rotation. The predicted monoclinic Cm phase (without strain and external electric field) and the MPB accompanied by giant piezoelectric effects in simple perovskite compounds have never yet been reported. Very recently, Rouquette *et al.* reported experimental evidence of polarization rotation induced by pressure in PZT [30, 31, 32]. We hope our predictions will stimulate both fundamental and technological interests to investigate ferroelectrics under hydrostatic or uniaxial pressure, and stress and pressure as means to enhance piezoelectricity.

We thank fruitful discussions with N. Choudhury and E. J. Walter. Computations were done on the Center for Piezoelectrics by Design. This work was supported by the Office of Naval Research under ONR Grants No. N00014-02-1-0506.

-
- [1] G. Burns and B. A. Scott, Phys. Rev. Lett. **25**, 167 (1973).
 - [2] J. A. Sanjurjo, E. López-Cruz, and G. Burns, Phys. Rev. B **28**, 7260 (1983).
 - [3] G. Shirane, S. Hoshino, and K. Suzuki, Phys. Rev. **80**, 1105 (1950).
 - [4] M. E. Lines and A. M. Glass, *Principles and Applications of Ferroelectrics and Related Materials* (Clarendon Press, Oxford, 1977).
 - [5] K. Uchino, *Piezoelectric actuators and ultrasonic motors* (Kluwer Academic, Boston, 1996).
 - [6] *Chemical Abstracts* reports 9924 publications on PbTiO_3 since its discovery.
 - [7] R. E. Cohen, Nature (London) **358**, 136 (1992).
 - [8] A. García and D. Vanderbilt, Phys. Rev. B **54**, 3817 (1996).
 - [9] U. V. Waghmare and K. M. Rabe, Phys. Rev. B **55**, 6161 (1997).
 - [10] G. Sághi-Szabó, R. E. Cohen, and H. Krakauer, Phys. Rev. Lett. **80**, 4321 (1998).
 - [11] Z. Wu, G. Sághi-Szabó, R. E. Cohen, and H. Krakauer, Phys. Rev. Lett. **94**, 069901 (2005).
 - [12] R. Ramirez, M. F. Lapena, and J. A. Gonzalo, Phys. Rev. B **42**, 2604 (1990).
 - [13] S. E. Park and T. R. ShROUT, J. of Appl. Phys. **82**, 1804 (1997).
 - [14] H. Fu and R. E. Cohen, Nature (London) **403**, 281 (2000).
 - [15] B. Noheda, *et al.*, Phys. Rev. Lett. **86**, 3891 (2001).
 - [16] L. Bellaiche, A. García, and D. Vanderbilt, Phys. Rev. Lett. **84**, 5427 (2000).
 - [17] Z. Wu and H. Krakauer, Phys. Rev. B **68**, 014112 (2003).
 - [18] B. Noheda, *et al.*, Appl. Phys. Lett. **74**, 2059 (1999).
 - [19] B. Noheda, D. E. Cox, G. Shirane, J. Gao, and Z.-G. Ye, Phys. Rev. B **66**, 054104 (2002).
 - [20] D. La-Orauttapong, *et al.*, Phys. Rev. B **65**, 144101

- (2002).
- [21] X. Gonze, *et al.*, *Comput. Mater. Sci.* **25**, 478 (2002).
 - [22] A. M. Rappe, K. M. Rabe, E. Kaxiras, and J. D. Joannopoulos, *Phys. Rev. B* **41**, 1227 (1990).
 - [23] D. J. Singh, *Planewaves, Pseudopotentials, and the LAPW Method* (Kluwer Academic Publishers, Boston, 1994).
 - [24] Z. Wu, R. E. Cohen, and D. J. Singh, *Phys. Rev. B* **70**, 104112 (2004).
 - [25] S. Baroni, S. de Gironcoli, A. Dal Corso, and P. Gianozzi, *Rev. Mod. Phys.* **73**, 515 (2001).
 - [26] D. R. Hamann, X. Wu, K. M. Rabe, and D. Vanderbilt, *Phys. Rev. B* **71**, 035117 (2005).
 - [27] J. Íñiguez and D. Vanderbilt, *Phys. Rev. Lett.* **89**, 115503 (2002).
 - [28] B. Noheda, *et al.*, *Phys. Rev. B* **63**, 014103 (2001).
 - [29] D. Vanderbilt and M. H. Cohen, *Phys. Rev. B* **63**, 094108 (2001).
 - [30] J. Rouquette, *et al.*, *Phys. Rev. B* **71**, 024112 (2005).
 - [31] J. Rouquette, *et al.*, *Phys. Rev. B* **70**, 014108 (2004).
 - [32] J. Rouquette, *et al.*, *Phys. Rev. B* **65**, 214102 (2002).