

Magnetic inversion symmetry breaking and ferroelectricity in TbMnO_3

M. Kenzelmann^{1,2;3}, A. B. Harris⁴, S. Jonas³, C. Broholm^{3;5}, J. Schefer²,
S. B. Kim⁶, C. L. Zhang⁶, S.-W. Cheong⁶, O. P. Vajk⁵ and J. W. Lynn⁵

- (1) Laboratory for Solid State Physics, ETH Honggerberg, CH-8093 Zurich, Switzerland
(2) Laboratory for Neutron Scattering, ETH Zurich & Paul Scherrer Institute, CH-5232 Villigen, Switzerland
(3) Department of Physics and Astronomy, Johns Hopkins University, Baltimore, Maryland 21218
(4) Department of Physics and Astronomy, University of Pennsylvania, Philadelphia, PA 19104S
(5) NIST Center for Neutron Research, National Institute of Standards and Technology, Gaithersburg, Maryland 20899
(6) Department of Physics & Astronomy, Rutgers University, 136 Frelinghuysen Rd., Piscataway, NJ 08854
(Dated: April 14, 2024)

TbMnO_3 is an orthorhombic insulator where incommensurate spin order for temperature $T_N < 41$ K is accompanied by ferroelectric order for $T < 28$ K. To understand this, we establish the magnetic structure above and below the ferroelectric transition using neutron diffraction. In the paraelectric phase, the spin structure is incommensurate and longitudinally modulated. In the ferroelectric phase, however, there is a transverse incommensurate spiral. We show that the spiral breaks spatial inversion symmetry and can account for magnetoelectricity in TbMnO_3 .

PACS numbers: 75.25.+z, 75.10.Jm, 75.40.Gb

The coexistence of antiferromagnetism and ferroelectricity in solid materials is rare, and much rarer still is a strong coupling between these two order parameters [1, 2]. In non-magnetic perovskites like BaTiO_3 , ferroelectricity is driven by a hybridization of empty d orbitals with occupied p orbitals of the octahedrally coordinated oxygen ions [3]. This mechanism requires empty d orbitals and thus cannot lead to magnetic ferroelectric materials. In materials such as BiMnO_3 , lone s^2 electron pairs can lower their energy by hybridizing with empty p orbitals [4]. While it leads to coexistence of magnetic order with electric polarization at low temperatures, the very different ordering temperatures show that the two order parameter lower the symmetry of the systems through distinctly different collective effects.

TbMnO_3 is an antiferromagnet which contains Mn^{3+} ions with occupied d orbitals and no lone s^2 cation [5]. So, as for a number of recently discovered multiferroics [6, 7, 8], neither of the mechanisms described above can explain the coexistence of magnetic and electric order. In these materials, a magnetic field of a few Tesla can switch the direction of the electric polarization [5] – proof of a strong direct coupling between the magnetic and electric polarization. Rare earth manganese oxides show a plethora of exciting phenomena which arise from competing interactions. LaMnO_3 is the parent compound to a series of materials featuring colossal magnetoresistance, and shows orbital ordering of its e_g orbital, giving rise to layered antiferromagnetic ordering. With decreasing rare-earth size, there is a tendency towards incommensurate magnetic order. Ferroelectric ground states were recently predicted for doped manganese of the type $\text{R}_{1-x}\text{Ca}_x\text{MnO}_3$, but they have not yet been observed [9]. The coexistence and strong coupling of ferroelectricity and antiferromagnetism in TbMnO_3 suggests the presence of a non-conventional coupling mechanism involv-

ing competing spin interactions, and it is thus of both practical and fundamental importance.

To develop a microscopic theory of the new coupling mechanism, unambiguous determination of the symmetry of the magnetic order is essential. In this Letter, we present neutron diffraction measurements of orthorhombic TbMnO_3 , which determine the magnetic ground states and the phase diagram as a function of temperature and a magnetic field H_{\parallel} . We find that the ferroelectric phase transition coincides with a magnetic transition from a longitudinal incommensurate structure to an incommensurate spiral structure that breaks spatial inversion symmetry. We show that a recent theory proposed for axial/non-axial parity breaking [10, 11] predicts the observed orientation of the ferroelectric polarization based on the symmetry of the magnetic structure that we report.

TbMnO_3 crystals were grown using an optical coating zone furnace. A measurement of the temperature dependence of the dielectric constant of the two samples which we studied confirmed ferroelectricity below $T = 26$ K and $T = 28$ K for sample 1 and 2, respectively. The discrepancy may result from slightly differing oxygen partial pressure during annealing. The space group is # 62, and in the Pbnm setting the lattice parameters are $a = 5.3\text{\AA}$, $b = 5.86\text{\AA}$ and $c = 7.49\text{\AA}$. The measurements were performed on two single-crystals weighing 40 mg and 220 mg, respectively, with the BT2 and SPINS spectrometers at NIST, and the TRIC S 4-circle diffractometer at PSI.

The wave-vector dependence of the diffraction intensity along the $(0; k; 1)$ direction of reciprocal space (Figs. 1 and 2) illustrates the temperature dependence of magnetic order in TbMnO_3 . Mn^{3+} spins develop long-range order at $T_N = 41$ K [12, 13]. Immediately below the transition temperature, magnetic Bragg peaks are ob-

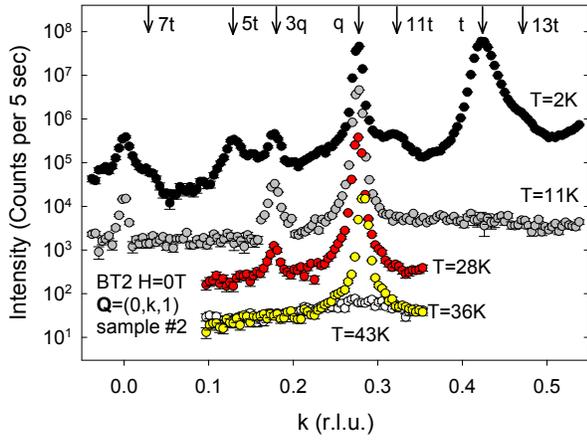


FIG. 1: Diffraction intensity along the $(0;k;1)$ direction for different temperatures (with a factor 10 offset between the sub- T_N data sets), showing fundamental and higher order Fourier components of the magnetic ordering. The 3t and 9t-order peaks associated with the Tb order occur at $k = 0.725$ and 0.175 , respectively, and are difficult to identify unambiguously due to their proximity to strong peaks.

served at $(0;1-q;1)$ and $(0;q;1)$ positions. At 35 K the magnetic order is described by a single Fourier component associated with a wave-vector $(0;q;0)$ with $q = 0.27$, and no apparent higher order Fourier components. Upon cooling below $T = 28$ K, third-order magnetic Bragg peaks $(0;1-3q;0)$ appear (Fig. 1), indicating step-like modulation of the magnetic moment. The inset to Fig. 2b shows that the wave vector continues to vary with temperature throughout the ferroelectric phase.

Below $T = 7$ K, additional magnetic peaks appear that are associated with Tb moments and indicate that their interactions favor a different ordering wave-vector than for the Mn moments. At $T = 2$ K, there is a strong peak at $(0;t;1)$ with $t = 0.425$, and several higher-order peaks as indicated in Fig. 1. The many strong odd high-order reflections indicate that the order associated with the $(0;t;0)$ wave-vector is strongly distorted (bunched structure) as expected for anisotropic rare-earth magnets. The correlation length and the incommensuration of the Tb order at low temperatures is sample dependent, as is often found in systems with phase transitions between incommensurate structures. The correlation length along the b-axis was 58 (20) and 280 (20) Å, and t was 0.41 and 0.425 in sample 1 and 2, respectively.

The magnetic structures at $T = 15$ K, and 35 K were determined from up to 922 first-order magnetic Bragg peaks each. Only first order peaks were included in the refinement as these are sufficient to determine the symmetry of the magnetic structure. Representational analysis was used to find the irreducible representations that describe the magnetic structures. The structure at $T = 35$ K in the high-temperature incommensurate (HTI) phase can be described by a single irreducible representation. The best fit with $\chi^2 = 0.86$ was ob-

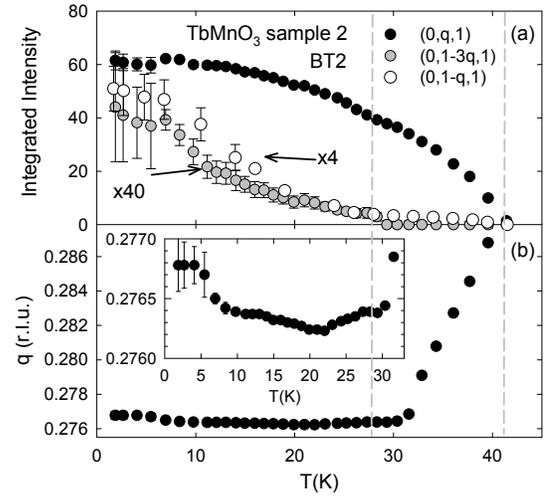


FIG. 2: (a) T-dependence of the integrated intensity of the $(0;q;1)$ Bragg peak and the associated third order peak at $(0;1-3q;1)$. (b) T-dependence of the wave-vector q , corrected for the T-dependence of the b lattice parameter, showing the absence of a lock-in transition at $T = 28$ K.

tained for a structure described by representation γ_3 , and the excellent agreement between the model and the data is shown in Fig. 3a). The magnetic structure is described by $m_3^M = (0;0(8);2;90(5);0;0(5))_B$ and $m_3^{Tb} = (0;0;0;0(4))_B$ where the subscript denotes the irreducible representation indicated in Fig. 4c. The magnetic structure is longitudinally modulated with moment along the b-axis, as illustrated in Fig. 4a and consistent with an earlier study [12]. The absence of observable higher order peaks indicates that the magnetic structure at $T = 35$ K is sinusoidally modulated.

Two irreducible representations are required to describe the magnetic structure at $T = 15$ K in the low-temperature incommensurate (LTI) phase. We found best agreement with $\chi^2 = 2.19$ for magnetic ordering involving γ_2 and γ_3 , as shown in Fig. 3b. Fits using the γ_1 and γ_3 , or the γ_3 and γ_4 representation pairs led to $\chi^2 = 14.5$ and higher, and can thus be excluded. Neglecting higher order reflections, the magnetic structure is given by $m_3^M = (0;0(5);3;9(1);0;0(7))_B$, $m_3^{Tb} = (0;0;0(1))_B$, $m_2^M = (0;0(1);0;0(8);2;8(1))_B$ and $m_2^{Tb} = (1;2(1);0(1);0)_B$. The experiment was not sensitive to the phase between the y and z-component of the Mn moment. From the size of the moment, however, we deduce that the Mn moments form an elliptical spiral. The data did not favor a phase difference between the Tb and Mn moments, so these phases remain undetermined. Symmetry splits the Tb moments into two orbits which representation theory normally treats as independent. However, as suggested by Landau theory [10], we took these two Tb amplitudes to be identical. The phase between the two orbits was found to be to 1:3(3). The greatly improved fit is evidence that the Tb sublattice carries significant magnetization in the LTI phase, pre-

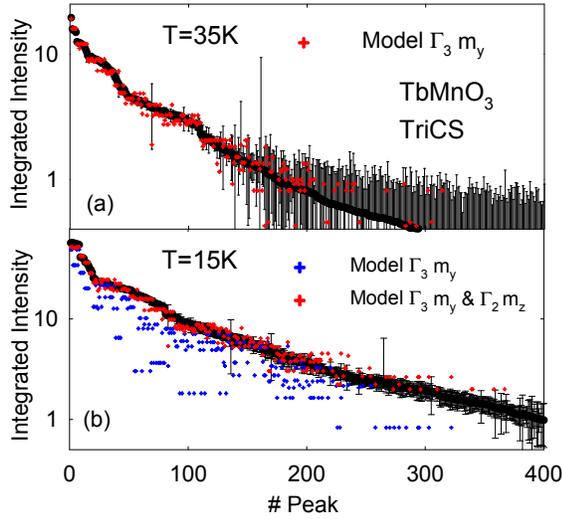


FIG. 3: Integrated intensities of magnetic Bragg peaks measured at $T = 15$ K and $T = 35$ K using TriCS are compared to various magnetic structures. Peaks are sorted by decreasing measured intensity. (a) The $T = 35$ K structure is described by a single irreducible representation, Γ_3 , and the moments point along the b -axis. (b) The $T = 15$ K magnetic structure is a spiral described by a y -component of Γ_3 and an x -component of Γ_2 with a $\pi/2$ phase shift.

sumably as a consequence of the exchange field from the ordered Mn sublattice.

Fig. 5 (a-b) shows the field dependence of the $(0; q; 1)$ magnetic Bragg reflection, which arises from the Mn spin spiral. Both the position and the intensity are field independent to within errorbar – evidence that the structure remains a spiral up to at least 6 T. Our calculations show that the intensity should drop by 7% if the z -component of Γ_2 were extinguished. In contrast, no decrease is observed to within an error bar of 2% between 0 and 6 T.

The $(0; 1 - q; 1)$ Bragg reflection shown in Fig. 5a arises from Mn Γ_3 magnetization along the a -axis and from Tb Γ_2 magnetization along the a -axis. Because the x -component of the Mn moment is small, the $(0; 1 - q; 1)$ Bragg reflection is particularly sensitive to Tb order. For $T < 28$ K the $(0; 1 - q; 1)$ intensity is suppressed by a field H_{ja} coming that the modulated Tb moment is oriented along that direction. Below the Tb ordering temperature, the field dependent magnetic Bragg intensity has a finite-field maximum (Fig. 5a), indicating a spin- flop transition.

We collected 51 magnetic Bragg peaks at $T = 4$ K and $H = 4$ T along a to determine the magnetic structure at low temperatures above the critical field for $(0; t; 0)$ Tb order (Fig. 5c). The magnetic structure can be described by Γ_2 and Γ_3 with $\Gamma_2 = 3:1$ or by Γ_1 and Γ_3 with $\Gamma_1 = 4:19$. Since a field along the a -direction disfavors antiparallel spin alignment in the same direction as in the $\Gamma_1 - \Gamma_3$ structure, we infer that the structure is given by $m_3^{Mn} = (0.3(4); 4.7(3); 0.0(5))_B$, $m_3^{Tb} =$

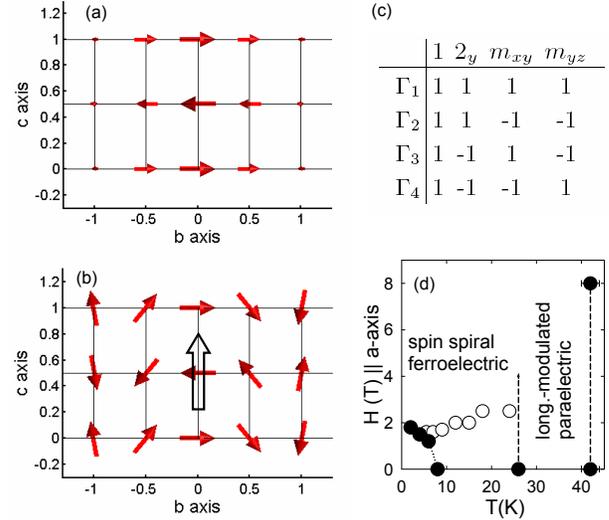


FIG. 4: Schematic of the magnetic structure at (a) $T = 35$ K and (b) $T = 15$ K, projected onto the b - c plane. Filled arrows indicate direction and magnitude of Mn moments. The longitudinally-modulated phase (a) respects inversion symmetry along the c axis, but the spiral phase (b) violates it, allowing an electric polarization (unfilled arrow). (c) Irreducible representation of the group G_k for the incommensurate magnetic structure with $k = (0; q; 0)$. (d) Phase diagram as a function of temperature and field applied along the a -axis. Full circles indicate second order phase transitions. Open circles indicate the characteristic field for reduction of magnetic $(0; 1 - q; 1)$ Bragg scattering from Tb moments by 50% from its zero-field intensity.

$(0; 0; 0; 0(3))_B$, $m_2^{Mn} = (0.0(2); 0.0(4); 3.0(3))_B$ and $m_2^{Tb} = (0.3(2); 0.0(4); 0)_B$. This result suggests that the spin spiral structure is more stable for fields along the a -axis than for fields along the b -axis [5].

Harris et al. [10, 11] recently showed that insulators with axial-non-axial parity breaking magnetic phase transitions must also be electrically polarized. Given the magnetic structure and the temperature dependence of the magnetic order parameter, the theory predicts the direction and temperature dependence of the electric polarization resulting from a symmetry allowed trilinear coupling term. In the following we show that this theory correctly accounts for the direction of the electric polarization in the LTI phase of TbMnO₃, and the absence of electric polarization in the HTI phase. The trilinear magnetoelectric coupling term P in the Landau free energy expansion is written as $V = \sum_{uv} a_{uv} \mathbf{u}(k) \cdot \mathbf{v}(k) P$. Here $\mathbf{u}(k)$ is the magnetic order parameter of irreducible representation \mathbf{u} , P is the electric polarization along the crystallographic direction and a_{uv} parametrizes the strength of the interaction between the electric and magnetic order parameters. In the HTI phase, the magnetic order is described by only one irreducible representation, Γ_3 and due to the high symmetry of the Mn moments, it is possible to define \mathbf{u} such that under inversion $\mathbf{u}(k) \rightarrow -\mathbf{u}(k)$. The trilinear coupling

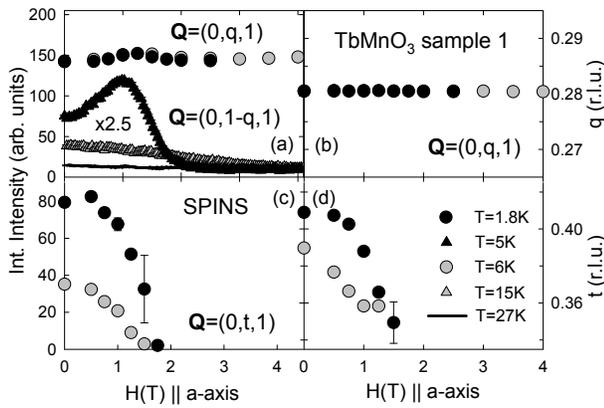


FIG. 5: Field dependence of magnetic Bragg scattering from TbMnO_3 . (a) and (b) show data for the incommensurate peaks that occur for $T < 41$ K. (a) The $(0;q,1)$ peak that is mostly sensitive to staggered magnetization on Mn sites and the $(0;1-q,1)$ peak that is sensitive to staggered magnetization on Tb sites. (c) and (d) show data for the incommensurate peaks that develop for $T < 7$ K.

thus consists only of terms such as $V = \sum_j \mathbf{a}_j \cdot \mathbf{j}_3(\mathbf{k}) \mathbf{j}_3^P$. Since interactions in a Landau expansion must have the symmetry of the paramagnetic phase, this interaction must be invariant under inversion. This requires that \mathbf{a} vanishes, so that $P = 0$ in the HTI phase. The conclusion remains valid for Tb order with no restriction on the phase between its two orbits.

For the LTI phase, which is described by \mathbf{m}_2 and \mathbf{p}_3 , there are, however, additional terms such as $V = \mathbf{b}_2 \cdot \mathbf{k} \mathbf{j}_3(\mathbf{k}) P + \text{c.c.}$, where c.c. denotes the complex conjugate. For V to be an invariant, P must transform as the product of \mathbf{m}_2 and \mathbf{j}_3 . That is, the electric polarization must be even under 1 and m_{yz} , and odd under 2_y and m_{xy} . This condition can only be satisfied for an electric polarization along the c -axis. Previous dielectric experiments have shown that the electric polarization that develops below the transition to the LTI phase is indeed oriented along the c -axis.

The coupling of the magnetic order parameter to electric polarization in TbMnO_3 [5] is similar to that in $\text{Ni}_3\text{V}_2\text{O}_8$, which adopts two different incommensurate magnetic structures [14], one of them ferroelectric and described by two irreducible representations. The correct prediction of the electric polarization for both TbMnO_3 and $\text{Ni}_3\text{V}_2\text{O}_8$ (Ref. 11) suggests that magnetoelectricity resulting from a trilinear magnetoelectric coupling term may be commonplace in insulating transition metal oxides with non-collinear incommensurate structures. Accordingly we find less compelling the suggestion [5] that the appearance of ferroelectricity is associated with an incommensurate to commensurate phase transition. Indeed, there is no evidence of a lock-in transition (see Fig. 2b) and it therefore appears to be irrelevant from the

point of view of ferroelectricity whether the modulated magnetic order is commensurate or truly incommensurate.

In summary, we have determined the magnetic structure of the paraelectric and ferroelectric phases of TbMnO_3 . We showed that the paraelectric, magnetically incommensurate phase has sinusoidally-modulated collinear magnetic order that does not break inversion symmetry. The ferroelectric phase, however, has non-collinear incommensurate magnetic order described by two irreducible representations, which explicitly breaks inversion symmetry and thus gives rise to electric polarization. The qualitative aspects of magnetoelectric effects in TbMnO_3 appear to be accounted for by a trilinear coupling term in a Landau free energy expansion as proposed by Harris et al. [10, 11]. Understanding the magnitude of the effect will require experimental as well as theoretical work to track lattice, charge, and orbital degrees of freedom through axial-non-axial parity breaking phase transition in insulators such as TbMnO_3 . Apart from the fundamental challenge, improved understanding of magnetoelectricity in these systems may help to produce materials for room-temperature applications.

We thank A. Aharony, O. Entin-Wohlman, and A. Ramirez for helpful discussions. This work was supported by the Swiss National Science Foundation under Contract No. PP002-102831. Work at Johns Hopkins University was supported by the DOE through DE-FG02-02ER45983. Work at University of Pennsylvania was supported by the U.S.-Israel Binational Science Foundation under Grant number 2000073. Work at Rutgers University was supported by the NSF-DMR-MRSEC-00-080008. This work is based on experiments performed at the Swiss spallation neutron source SINQ, Paul Scherrer Institute, Villigen, Switzerland. The work at SPINS is based upon activities supported by the National Science Foundation under Agreement No. DMR-9986442.

-
- [1] G. A. Smolenskii et al., *Sov. Phys. Usp.* 25, 475 (1982).
 - [2] H. Schmid, *Ferroelectrics* 62, 317 (1994).
 - [3] R. E. Cohen, *Nature* 358, 136 (1992).
 - [4] M. A. Tanasov et al., *J. Phys. Chem. A* 105, 5450 (2001).
 - [5] T. Kimura et al., *Nature* 426, 55 (2003).
 - [6] T. Lottermoser et al., *Nature* 430, 541 (2004).
 - [7] N. Hur et al., *Nature* 429, 392 (2004).
 - [8] S. Kobayashi et al., *J. Phys. Soc. Jpn* 73, 1593 (2004).
 - [9] D. V. Efremov et al., *Nature Materials* 3, 853 (2004).
 - [10] A. B. Harris et al., to be published.
 - [11] G. Lawes et al., *cond-mat/0503385*.
 - [12] S. Quezelle et al., *Physica B* 86-88, 916 (1977).
 - [13] R. Kajimoto et al., *Phys. Rev. B* 70, 012401 (2004).
 - [14] G. Lawes et al., *Phys. Rev. Lett.* 93, 247201 (2004).