

A critical assessment of the pairing symmetry in $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$

I.I. Mazin, M.D. Johannes

Code 6391, Naval Research Laboratory, Washington, D.C. 20375

We examine each of the symmetry-allowed pairing states of $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ and compare their properties to what is experimentally and theoretically established about the compound. In this way, we can eliminate the vast majority of states that are technically allowed and narrow the field to two, both of f-wave type states. We discuss the expected features of these states and suggest experiments that can distinguish between them. We also discuss odd-frequency gap pairing and how it relates to available experimental evidence.

$\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ is a novel superconductor which, despite a relatively low superconducting temperature¹ of only 5K, has recently attracted substantial experimental and theoretical attention. Much of the interest is driven by an as-of-yet unresolved pairing state that is presumed to be highly unusual and possibly (as we will argue in this Letter, likely) even more unconventional than the d-wave superconductivity of the cuprates or p-wave superconductivity of the ruthenates. A survey of the current literature for $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ reveals that in the two years since its discovery, various groups have proposed s-wave^{2,3,4}, p-wave $z(x + iy)^{5,6}$, d-wave $x^2 - y^2 + 2ixy^{6,7,8,9}$ and various versions of f^{4,6,10} and i-wave states, as well as an odd-frequency triplet state¹¹. To our knowledge, $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ holds the record for the greatest number of different superconducting symmetries proposed for one compound.

Synthesis of single crystal $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ is difficult and polycrystalline samples often exhibit inhomogeneities in Na distribution and H_2O accumulation^{12,13}. The compound is furthermore chemically unstable at ambient temperature and humidity¹⁴, making it difficult to handle and characterize. For these reasons, well-reproducible and reliable experimental results that could be expected to unravel the precise superconducting state have been slow to emerge. Still, there are several experimental facts that are rather well established, reproducible and which bear immediate relevance to the superconducting symmetry. Other facts that follow from confirmed knowledge about the crystal and electronic structure allow the exclusion of at least a few of the symmetry-allowed pairing states. An absence of knowledge about which states conform to symmetry requirements, which are excluded by experiment and which are physically unreasonable has frequently lead both theorists and experimentalists to concentrate on those pairing symmetries which are compatible with a specific data set or a specific theory of pairing to the detriment of a broader, consistent picture.

In this Letter, we list all the different symmetry representations that are compatible with a hexagonal crystal structure, according to the seminal work of Sigrist and Ueda¹⁵. Based on what is currently known experimentally about $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$, we discuss which states can be eliminated from consideration with a reasonable degree of confidence. We will show that surprisingly few

TABLE I: Symmetry-allowed pairing states for hexagonal symmetry

		2D	DOS	SR	
1	1	Y	N	Y	s
2	$x^2 + y^2$	Y	N	Y	s
3	z^2	N	Y	Y	s
4	$x\hat{z}^{(a)}$	Y	Y	Y	p
5	$y\hat{z}^{(a)}$	Y	Y	Y	p
6	$(x - iy)\hat{z}$	Y	N	N	p
7	$z\hat{x}$	N	Y	Y	p
8	$z\hat{y}$	N	Y	Y	p
9	$z(\hat{x} - i\hat{y})$	N	N	N	p
10	$y\hat{x} + x\hat{y}^{(b)}$	Y	N	Y	p
11	$x\hat{x} - y\hat{y}$	Y	N	Y	p
12	$(\hat{x} - i\hat{y})(x - iy)$	Y	Y	N	p
13	$x\hat{x} + y\hat{y}$	Y	N	Y	p
14	$y\hat{x} - x\hat{y}^{(c)}$	Y	N	Y	p
15	$z\hat{z}$	N	Y	Y	p
16	$x^2 - y^2^{(a)}$	Y	Y	Y	d
17	$xy^{(a)}$	Y	Y	Y	d
18	$(x - iy)^2$	Y	N	N	d
19	xz	N	Y	Y	d
20	yz	N	Y	Y	d
21	$(x - iy)z$	N	Y	N	d
22	$x(x^2 - 3y^2)\hat{z}$	Y	Y	Y	f
23	$y(y^2 - 3x^2)\hat{z}$	Y	Y	Y	f
24	$z[(x^2 - y^2)\hat{x} + 2xy\hat{y}]$	N	Y	Y	f
25	$z[(x^2 - y^2)\hat{y} + 2xy\hat{x}]$	N	Y	Y	f
26	$s\hat{x}; s\hat{y}, \text{ or } s\hat{z}$	Y	Y	Y	s

^(a) These states are excluded because of their proximity to a fully-gapped state ^(b) In Table III of Ref. 15, this state is printed with a typo, which is corrected here. ^(c) In Table VI of Ref. 15, this state is printed with a typo, which is corrected here.

candidates survive this scrutiny, and that all of these are highly unconventional and, in a sense, more exotic than either the high- T_c cuprates or the p-wave ruthenates. The list of allowed symmetries¹⁵ up to $L=3$ (i.e. up to the f-states) is given in Table I.

There are 25 states in this table, excluding the last one which will be discussed separately later. We will show that all but two of them are incompatible with the

experimental data.

First, we decide which facts are to be considered as firmly established. Some potentially very important probes, such as the temperature dependence of the Knight shift, are still controversial in the sense that different authors report contradictory results^{2,5,10,16}. We have therefore singled out three pieces of evidence on which all or practically all publications agree. These are:

Two-dimensionality. Electronic structure calculations for the hydrated compound show an anisotropy in the Fermi velocity of at least an order of magnitude¹⁷, which is supported by an experimentally measured resistive anisotropy^{18,19} of $10^3 - 10^4$, corresponding to a Fermi velocity anisotropy of 30 to 100 (the resistivity anisotropy of the unhydrated, high Na content compound, $\text{Na}_{0.75}\text{CoO}_2$; which should be substantially lower than that of $\text{Na}_{0.3}\text{CoO}_2 \cdot y\text{H}_2\text{O}$, was found²⁰ to be as high as 500), indicating that the transport along *c* is probably incoherent. This is firm evidence that the electronic structure is very strongly 2D.

As found experimentally^{21,22} and explained theoretically²³, the magnetic anisotropy of the unhydrated high-Na compound is very small, primarily because each Co couples with 7 Co atoms in neighboring layers. While there are no data on the magnetic coupling at $x = 0.3$; nor for the hydrated compound, one can estimate the reduction in magnetic coupling from the ratio of the squared Fermi velocities, which is about 20. Thus in the hydrated compound, magnetic interaction should also be 2D.

Finally, in an interesting difference from both the cuprates and ruthenates, the Co and O phonons should also be 2D in this system. Of course, water vibration need not be such, but the absence of the hydrogen isotope effect¹⁸ clearly indicates their irrelevance for the superconducting pairing.

Therefore, we conclude that the superconducting order parameter in $\text{Na}_{0.3}\text{CoO}_2 \cdot y\text{H}_2\text{O}$ should be 2D.

Absence of superconductivity-induced spontaneous magnetic moments below T_c . Some of the superconducting states listed in Table I (# 9,12) are nonunitary and have a spontaneous magnetization in the superconducting state. Others (# 6,18,21) break the time-reversal symmetry for a Cooper pair by virtue of a nonzero pair orbital moment. In both cases, the resulting nonzero local magnetic moments are supposed to be detectable¹⁵. Note that net magnetization is not present in the latter case, due to domain formation and internal Meissner screening, but crystallographic defects and grain or domain boundaries should still host nonzero local moments. One of the main arguments in favor of the axial $(x + iy)\hat{z}$ state in Sr_2RuO_4 ²⁴ was the fact that muon spectroscopy revealed the appearance of disordered static magnetic moments below T_c : The accepted interpretation of this finding is that the pairing symmetry has a nonzero orbital moment. Muon spin rotation experiments for $\text{Na}_{0.3}\text{CoO}_2 \cdot y\text{H}_2\text{O}$ have been reported^{10,25} and no indications of static moments below T_c have been found. To

our knowledge, there are no other works reporting detection or non-detection of static magnetic moments in this compound. We nevertheless feel confident to include this fact in our compendium for two reasons: i) one of the reports comes from a group¹⁰ which has performed similar measurements on other superconductors and was previously able to detect local moments in $\text{PrO}_4\text{Sb}_{12}$ ²⁶, and ii) this is a rare example of an experiment in which poor sample quality makes the effect more pronounced rather than obscuring it.

Therefore, we conclude that neither nonunitary nor $L \neq 0$ states are possible in $\text{Na}_{0.3}\text{CoO}_2 \cdot y\text{H}_2\text{O}$

Absence of a finite superconducting gap. Several experimental groups have reported experiments indirectly probing the density of states (DOS) in the superconducting phase. Such experiments, primarily calorimetry, were instrumental in clarifying the symmetry of pairing in such novel superconductors as SrRuO_4 ²⁴ and MgB_2 ²⁷. These experiments measure the temperature dependence of either specific heat^{28,29} or relaxation rates (NMR², NQR^{30,31} or SR^{10,32}). In all work that we are aware of, the authors agree that the low temperature behavior of the DOS is not exponential³³. As of yet, no group has reported measurements at temperatures low enough to allow for a reasonably confident determination of the exact temperature dependence, but most authors suggest a T^3 (line nodes) behavior for $T \lesssim 2$ K and finite-DOS linear behavior at lower T .

These results exclude states with a fully developed sizeable gap on all Fermi surfaces.

Armed with these three facts, let us now test the 25 states listed above against them. First, we eliminate all states that have, by symmetry, strong *z*-dependence of the order parameter. These are the ten states # 3, 7, 8, 9, 15, 19, 20, 21, 24, 25. Of the remaining 15 states, # 1, 2, 10, 11, 12, 13, 14, and 18 have no symmetry restriction that would require them to have node lines or points. In general, there exists the possibility of accidental rather than symmetry-induced nodes, or regions with a finite but extremely small order parameter, similar to the so-called "extended s" state, earlier considered for superconducting cuprates. In the case of $\text{Na}_{0.3}\text{CoO}_2 \cdot y\text{H}_2\text{O}$, such accidental nodes seem highly unlikely due to its specific fermiology. The Fermi surface of $\text{Na}_{0.3}\text{CoO}_2 \cdot y\text{H}_2\text{O}$ consists of one relatively small nearly circular cylinder, and, possibly (predicted by the theory, but not yet confirmed experimentally) six tiny pockets surrounding the first Fermi surface. Whether the latter actually exist or not, a pairing interaction that would be consistent with the hexagonal symmetry and at the same time enforce sign change of the order parameter on these small Fermi surfaces should itself change sign with a variation of the wave vector on the order of $0.2\{0.25\}$ of the Brillouin zone dimension. It is hardly possible to imagine a physically meaningful pairing interaction of this sort.

Finally, the SR experiment allows us to exclude the non-unitary state # 12. Note that several states that we have already excluded because they are allowed by sym-

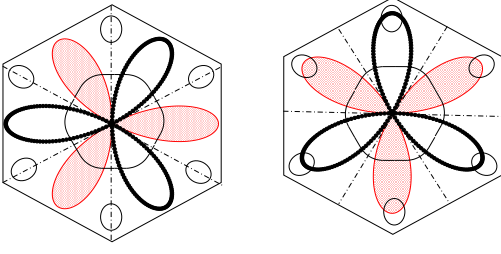


FIG. 1: A schematic of the $\text{Na}_{0.3}\text{CoO}_2 - y\text{H}_2\text{O}$ Fermi surfaces along with the two f-wave pairing states that remain after eliminating any states that are in conflict with experimental evidence. Left panel $y(y^2 - 3x^2)z$ has node lines which directly intersect the theoretically predicted e_g^0 hole pockets. Right panel The node lines of $x(x^2 - 3y^2)z$ fall between the e_g^0 pockets and therefore cause no loss of pairing energy.

metry to have a full gap, are additionally excluded as having nonzero orbital momentum. This leaves us with the six states: # 4, 5, 16, 17, 22 and 23. There is good reason to believe that the first four are not realized. As an example, we consider the first pair, xz and yz : In the linear approximation (that is, expanding the free energy to second order in the order parameter), they are degenerate with each other and with state # 6, $(x + iy)z$ (see Ref.¹⁵). Strong coupling effects, the spin-orbit interaction and other effects can, formally, tilt the energy balance in favor of these states, but only in the 4th order in the order parameter (the distinction between the states themselves appears only in the 6th order). However, all three states belong to the same symmetry representation and the first two have node lines, while $(x + iy)z$ has full gap. This should lead to a considerable difference in pairing energy that favors the fully gapped state for the same amplitude of the order parameter and makes stabilization of the other states highly questionable.

Excluding states # 4, 5, 16, and 17 on the basis of this argument, we are left with only two possible states: $x(x^2 - 3y^2)z$ and $y(y^2 - 3x^2)z$: Assuming only one Fermi surface, the a_{1g} one around the Γ point, we cannot make a further distinction between the two. However, if one accepts the Fermi surface from band structure calculations, the latter state has a node line on all e_g^0 Fermi surfaces (See Fig. 1). Given the small size of these pockets, the line nodes cause a near loss of pairing for 2/3 of all elec-

trons at the Fermi level, which is energetically unlikely. Therefore, we conclude that if the e_g^0 derived Fermi surface pockets actually exist, the most likely superconducting symmetry among all possible superconducting states with an even-frequency order parameter is the f state $x(x^2 - 3y^2)z$.

This is the main result of our paper. However, before concluding, we would like to remark that an odd-frequency triplet s_z state, proposed earlier by us¹¹, is also compatible with the criteria introduced above. It has no orbital momentum, it is unitary [as opposed to another triplet s state, $s(x - iy)z$]; it is 2D, and, despite being isotropic, it has finite DOS at zero energy, giving rise to the observed nonexponential specific heat and other DOS-sensitive quantities. As opposed to the xz and yz case above, s_x and s_y are also isotropic and thus do not have any additional disadvantage in terms of the pairing energy. The ground state in this case is defined either by the spin-orbit induced magnetic anisotropy (if the easy magnetization axis is in the plane, s_x or s_y is favored, otherwise s_z), or by the spin-orbit induced anisotropy of the pairing interaction.

Finally, we would like comment on the (still controversial) Knight shift experiments. The absence of a Knight shift decay below T_c has been taken as a decisive argument in favor of the $(x - iy)z$ state in Sr_2RuO_4 ²⁴. The f state that has emerged from our discussion also corresponds to Cooper pairs with spins in the xy plane and thus to a constant Knight shift. The same is true for the s_z state. On the other hand, s_x or s_y would show a reduced, though not exponentially reduced, Knight shift below T_c : Of the states with an even frequency gap (# 1-25), the states which, formally, should not show a Knight shift reduction below T_c along some directions are # 4, 5, 6, 15, 22 and 23.

In conclusion, we have shown that, based on established experimental evidence and a knowledge of the electronic structure of $\text{Na}_{0.3}\text{CoO}_2 - y\text{H}_2\text{O}$, many superconducting states that are allowed by symmetry can be eliminated from consideration. Of those with an even-frequency gap, only the f states, $x(x^2 - 3y^2)z$, and $y(y^2 - 3x^2)z$ are fully compatible with what is known about this compound. The former has no line nodes along the e_g^0 hole pockets and is therefore energetically favorable, given the existence of e_g^0 states at the Fermi level. In terms of odd-frequency gap states, s_x , s_y , and s_z are all consistent with experimental reports.

¹ Takada, K. et al. Superconductivity in two-dimensional CoO_2 layers. *Nature* 422, 53 (2003).

² Kobayashi, Y., Yokoi, M. & Sato, M. 59Co-NMR Knight Shift of Superconducting $\text{Na}_x\text{CoO}_2 - y\text{H}_2\text{O}$. *J. Phys. Soc. Jpn.* 72, 2453 (2003).

³ Yokoi, M. et al. Impurity Effects on the Superconducting Transition Temperature of $\text{Na}_x\text{CoO}_2 - y\text{H}_2\text{O}$. *J. Phys. Soc.*

Jap. 73, 1297 (2004).

⁴ Kuroki, K., Tanaki, Y. & Arita, R. Possible Spin-Triplet f-Wave Pairing Due to Disconnected Fermi Surfaces in $\text{Na}_x\text{CoO}_2 - y\text{H}_2\text{O}$. *Phys. Rev. Lett.* 93, 077001 (2004).

⁵ Kato, M. et al. Possible Spin-Triplet Superconductivity in $\text{Na}_x\text{CoO}_2 - y\text{H}_2\text{O}$ - 59Co-NMR Study. *cond-mat/0306036* (2004).

- ⁶ Yanase, Y., Mochizuki, M. & Ogata, M. Multi-orbital Analysis on the Superconductivity in $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$. J. Phys. Soc. Jpn. 74, 430 (2005).
- ⁷ Sa, D., Sardar, M. & Baskaran, G. Superconductivity in $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$: Protection of a $d_1 + id_2$ State by spin-charge separation. Phys. Rev. B 70, 104505 (2004).
- ⁸ Motrunich, O.I. & Lee, P.A. Possible effects of charge frustration in Na_xCoO_2 : Bandwidth suppression, charge orders, and resurrected resonating valence bond superconductivity. Phys. Rev. B 69, 214516 (2004).
- ⁹ Watanabe, T., Yokoyama, H., Tanaka, Y., Inoue, J.I. & Ogata, M. Variational Monte Carlo Studies of Pairing Symmetry for the t -J Model on a Triangular Lattice. J. Phys. Soc. Jpn. 73, 3404 (2004).
- ¹⁰ Higemoto, W. et al. Possible unconventional superconductivity in $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ probed by muon spin rotation and relaxation. Phys. Rev. B 70, 134508 (2004).
- ¹¹ Johannes, M.D., Mazin, I.I., Singh, D.J. & Papaconstantopoulos, D.A. Nesting, Spin Fluctuations, and Odd-Gap Superconductivity in $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$. PRL 93, 097005 (2004).
- ¹² Chen, D.P. et al. Single-crystal growth and investigation of Na_xCoO_2 and $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$. Phys. Rev. B 70, 024506 (2004).
- ¹³ Ueland, B.G. et al. Specific heat study of the $\text{Na}_{0.3}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ superconductor: in uence of the complex chemistry. Physica C 402, 27 (2004).
- ¹⁴ Foo, M.L. et al. Chemical instability of the cobalt oxyhydrate superconductor under ambient conditions. Solid State Commun. 127, 33 (2003).
- ¹⁵ Sigrist, M. & Ueda, K. Phenomenological theory of unconventional superconductivity. Rev. Mod. Phys. 63, 239 (1991).
- ¹⁶ Kobayashi, Y. et al. ^{59}Co NMR Knight Shift of Aligned Crystal and Polycrystalline Samples of Superconducting $\text{Na}_{0.3}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$. cond-mat/0412466 (2004).
- ¹⁷ Johannes, M.D. & Singh, D.J. Comparison of the electronic structures of hydrated and unhydrated Na_xCoO_2 : the effect of H_2O . Phys. Rev. B 70, 014507 (2004).
- ¹⁸ Jin, R., Sales, B.C., Khalifah, P. & Mandrus, D. Observation of Bulk Superconductivity in $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ and $\text{Na}_x\text{CoO}_2 \cdot y\text{D}_2\text{O}$ Powder and Single Crystals. Phys. Rev. Lett. 91, 217001 (2003).
- ¹⁹ Chou, F.C. et al. Thermodynamic and Transport Measurements of Superconducting $\text{Na}_{0.3}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ Single Crystals Prepared by Electrochemical Deintercalation. Phys. Rev. Lett. 92, 157004 (2004).
- ²⁰ Sales, B.C. et al. Magnetic, thermodynamic, and transport characterization of $\text{Na}_{0.85}\text{CoO}_2$ single crystals. Phys. Rev. B 70, 174419 (2004).
- ²¹ Bayrakci, S.P. et al. Bulk antiferromagnetism in $\text{Na}_{0.82}\text{CoO}_2$ single crystals. Phys. Rev. B 69, 100410 (2004).
- ²² Helm, L.M. et al. Three-Dimensional Spin Fluctuations in $\text{Na}_{0.75}\text{CoO}_2$. Phys. Rev. Lett. 94, 157206 (2005).
- ²³ Johannes, M.D., Mazin, I.I. & Singh, D.J. Three-dimensional magnetic interactions in Na_xCoO_2 : a first principles investigation. Phys. Rev. B 71, (in press) (2005).
- ²⁴ Mackenzie, A.P. & Maeno, Y. The superconductivity of Sr_2RuO_4 and the physics of spin-triplet pairing. Rev. Mod. Phys. 75, 657 (2003).
- ²⁵ Uemura, Y.J. et al. Unconventional superconductivity in $\text{Na}_{0.35}\text{CoO}_2 \cdot 1.3\text{D}_2\text{O}$ and proximity to a magnetically ordered phase. cond-mat/0403031 (2004).
- ²⁶ Aoki, Y. et al. Time-Reversal Symmetry-Breaking Superconductivity in Heavy Fermion $\text{PrO}_8\text{Sb}_{12}$ Detected by Muon-Spin Relaxation. Phys. Rev. Lett. 91, 067003 (2003).
- ²⁷ Mazin, I.I. & Antropov, V.P. Electronic structure, electron-phonon coupling, and multiband effects in MgB_2 . Physica C 385, 49 (2003).
- ²⁸ Yang, H.D. et al. Evidence of nodal superconductivity in $\text{Na}_{0.35}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$: A specific heat study. Phys. Rev. B 71, 020504 (2005).
- ²⁹ Oechler, N. et al. The Specific Heat of $\text{Na}_{0.3}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$: Sample-Dependent, Non-Magnetic Pair Breaking, Two Energy Gaps, and Strong Fluctuations in the Superconducting State. cond-mat/0503690 (2005).
- ³⁰ Ishida, K. et al. Unconventional Superconductivity and Nearly Ferromagnetic Spin Fluctuations in $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$. J. Phys. Soc. Jpn. 72, 3041 (2003).
- ³¹ Fujimoto, T. et al. Unconventional Superconductivity and Electron Correlations in the Cobalt Oxyhydrate $\text{Na}_{0.35}\text{CoO}_2 \cdot y\text{H}_2\text{O}$ from Nuclear Quadrupole Resonance. Phys. Rev. Lett. 92, 047004 (2004).
- ³² Kanigel, A. et al. Muon Spin Relaxation Measurements of $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$. Phys. Rev. Lett. 92, 257007 (2004).
- ³³ The authors of Ref.29 have observed exponential behavior in one of their samples (N. Phillips, private communication).