

Spin wave contribution to the nuclear spin-lattice relaxation in triplet superconductors

Timofey Rostunov¹, Antoine Georges², and Eugene Demler¹

¹*Department of Physics, Harvard University, Cambridge MA 02138*

²*Centre de Physique Theorique, Ecole Polytechnique, 91128 Palaiseau Cedex, France*

(Dated: March 23, 2022)

We discuss collective spin wave excitations in triplet superconductors with an easy axis anisotropy for the order parameter. Using a microscopic model for interacting electrons we estimate the frequency of such excitations in Bechgaard salts and ruthenate superconductors to be one and twenty GHz respectively. We introduce an effective bosonic model to describe spin-wave excitations and calculate their contribution to the nuclear spin lattice relaxation rate. We find that in the experimentally relevant regime of temperatures, this mechanism leads to the power law scaling of $1/T_1$ with temperature. For two and three dimensional systems the scaling exponents are three and five respectively. We discuss experimental manifestations of the spin wave mechanism of the nuclear spin lattice relaxation.

Nuclear magnetic resonance (NMR) is a powerful tool for analyzing ordered electron states in solids. NMR analysis has been successfully applied to study magnetic insulators (see *e.g.* [1] and references therein) as well as several classes of unconventional superconductors, including high T_c cuprates [2], heavy fermion materials [3], ruthenates [4], and organic superconductors [5]. In particular, NMR experiments have been useful for analyzing the symmetry of the SC order parameter [6] and for clarifying the structure of the phase diagram in systems with competing orders [7].

A common feature of the NMR experiments in certain families of triplet superconductors (TSC) is the power law temperature dependence of the nuclear spin lattice relaxation rate. Bechgaard salts [8], ruthenates [4], and heavy fermion materials [9] showed $1/T_1 \sim T^3$ at low temperatures and for small magnetic fields. Such behavior has usually been interpreted as a signature of nodes in the quasiparticle gap on the Fermi surface. Indeed, point and line nodes should lead to T^5 and T^3 scaling of $1/T_1$ respectively. In several cases, however, we have reasons to doubt the presence of nodes in the TSC order parameter. For example, in quasi one dimensional Bechgaard salts the natural order parameter has different signs on the two sheets of the Fermi surface and no nodal points [10]. Also in ruthenates, the order parameter that is consistent with spontaneous time reversal breaking [11] and the quasi two dimensional nature of these materials corresponds to a constant quasiparticle gap on the entire Fermi surface [12]. In this paper we consider a mechanism of the nuclear spin lattice relaxation that is not due to Bogoliubov quasiparticles but due to collective spin wave (SW) excitations of the TSC order parameter. We demonstrate that in the experimentally relevant regime of temperatures, this mechanism also leads to the power law scaling of $1/T_1$ with temperature.

Our starting point is the Moriya relation [13] for the nuclear spin lattice relaxation rate

$$\frac{1}{T T_1} = \frac{2 g_N^2 |A|^2}{(g_{\text{eff}} \mu_B)^2} \int d^d q \frac{\chi''_{\perp H}(q, \omega_N)}{\omega_N} \quad (1)$$

Here A describes the strength of hyperfine interactions between nuclear spins and conduction electrons, g_N is a gyromagnetic ratio of the nucleus, g_{eff} is an effective gyromagnetic ratio of conducting electrons, μ_B is a Bohr magneton, $\chi''_{\perp H}(q, \omega_N)$ is the imaginary part of the transverse (*i.e.* perpendicular to the magnetic field) electron spin susceptibility taken at the nuclear Larmor frequency ω_N . In the case of a perfect spin SU(2) symmetry, linearly dispersing SW excitations exist down to arbitrarily small energies. In real materials there is always spin anisotropy which gives rise to a finite gap for spin excitations, ω_0 . Below, we estimate the value of ω_0 to be tens of millikelvin for Bechgaard salts and hundreds of millikelvin for the ruthenates. This is much larger than the nuclear Larmor frequency, ω_N , but smaller than the typical temperature used in experiments. When ω_0 is much larger than ω_N , creation and annihilation of individual SWs does not affect $\chi''(\omega_N)$. However, there is a contribution due to the scattering of thermally excited SW excitations. Let $\rho(E)$ be the density of states for SW excitations and $n(E) = (\exp(E/k_B T) - 1)^{-1}$ be the Bose distribution function. From the second order perturbation theory we have $\chi''_{zz}(\omega_N) \sim \int \rho(E) \rho(E + \omega_N) [n(E) - n(E + \omega_N)] dE$. The characteristic energy scale in this integral is set by the temperature T . Since $T \gg \omega_0$ we can assume linear dispersion of SW excitations and take $\rho(E) \sim E^{d-1}$, where d is the number of spatial dimensions. Using $\omega_N \ll T$, we have $\chi''_{zz}(\omega_N) \sim \omega_N \int E^{2d-2} (-\partial n / \partial E) dE \sim T^{2d-2}$. Combining this result with the Moriya relation (1) we obtain $1/T_1 \sim T^{2d-1}$. This simple analysis does not take into account coherence factors in the expression for χ'' . Below we demonstrate that coherence factors do not modify the scaling exponent of the nuclear spin lattice relaxation rate in TSC. This is in contrast to antiferromagnetic systems that also have linearly spin waves, but in which coherence factors contribute an additional $1/T^2$ factor to $1/T_1$ [1].

For a detailed analysis of the nuclear spin lattice relaxation rate we introduce an effective model that captures

the essence of triplet superconductivity and allows us to analyze collective excitations. A simple picture of the TSC state corresponds to binding electrons into Cooper pairs with spin one and momentum zero and Bose condensing such pairs. In an effective bosonic model one can neglect details of the orbital nature of Cooper pairs and consider them as “elementary” particles. Interactions are important for the correct description of collective excitations, thus we are led to the Hubbard type model for spin one bosons [14]

$$\mathcal{H} = -t \sum_{\langle ij \rangle \sigma} (a_{i\sigma}^\dagger a_{j\sigma} + a_{j\sigma}^\dagger a_{i\sigma}) - \delta r \sum_i a_{i0}^\dagger a_{i0} + \frac{U_0}{2} \sum_i n_i(n_i - 1) + \frac{U_2}{2} \sum_i \vec{S}_i^2 - \mu \sum_i n_i \quad (2)$$

Here $a_{i\sigma}^\dagger$ creates a boson on site i with spin $\sigma = \{-1, 0, 1\}$. Operators n_i and \vec{S}_i describe the number of atoms and the total spin on site i : $n_i = \sum_\sigma a_{i\sigma}^\dagger a_{i\sigma}$, $\vec{S}_i = \sum_{\sigma, \sigma'} a_{i\sigma}^\dagger \vec{T}_{\sigma\sigma'} a_{i\sigma'}$, where $\vec{T}_{\sigma\sigma'}$ are the usual spin matrices for spin one particles. The first term in the Hamiltonian (2) describes tunneling of Cooper pairs between neighboring lattice sites i and j . An important aspect of the model (2) is the presence of two types of interaction terms. The third term in (2) depends only on the number of particles on each site and is the same as for spinless bosons. The fourth term in (2) gives spin dependence to the interaction (without breaking the spin SU(2) symmetry) and is a novel feature of spinful Cooper pairs. The sign of U_2 determines the difference between unitary ($U_2 > 0$) and nonunitary ($U_2 < 0$) triplet superconductors. It is generally believed that triplet pairing between fermions leads to unitary Cooper pairs [12]. Thus, from now on we assume that U_2 is positive. For concreteness, we consider a d dimensional ($d = 2, 3$) hypercubic lattice. Our results, however, do not depend on the precise lattice structure. The second term in equation (2) introduces easy axis anisotropy for the order parameter by making the condensation of a_0 to be energetically favorable. A state with finite $\langle a_0 \rangle$ corresponds to the unitary state of Cooper pairs with the \mathbf{d} vector pointing along the z axis (see eq. (8) for the definition of the \mathbf{d} vector).

In the mean field approximation, we take $\langle a_0 \rangle = \Psi_0$ with $|\Psi_0|^2 = (\mu + zt + \delta r)/U_0$ and $z = 2d$ being the coordination number. Without loss of generality, we can take Ψ_0 to be real. Fluctuations in the phase of a_0 correspond to the density (Bogoliubov) mode. To find SW excitations we need to consider a_\pm operators. In the Hamiltonian (2) we replace a_0 by its expectation value, take the terms quadratic in a_\pm , and perform the Bogoliubov rotation $a_{i\alpha} = \frac{1}{\sqrt{N}} \sum_{\vec{k}} a_{\vec{k}\alpha} e^{i\vec{k}\vec{r}_i}$, $a_{\vec{k}+} = u_k \gamma_{\vec{k}+} + u_k \gamma_{-\vec{k}-}^\dagger$, $a_{-\vec{k}-} = u_k \gamma_{\vec{k}+}^\dagger + v_k \gamma_{-\vec{k}-}$. Here N is the total number of lattice sites, $u_k^2 + v_k^2 = (\xi_k + \Delta)/E_k$, $2u_k v_k = -\Delta/E_k$, $\xi_k = -2t \sum_{n=1}^d \cos(k_n b) + U_0 \Psi_0^2 - \mu$. In these equations b is the lattice constant and $\Delta = U_2 \Psi_0^2$.

We obtain the diagonalized spin-wave Hamiltonian $\mathcal{H}_0 = \sum_k E_k \left(\gamma_{k+}^\dagger \gamma_{k+} + \gamma_{k-}^\dagger \gamma_{k-} \right)$ with $E_k^2 = \xi_k^2 + 2\Delta \xi_k$. Operators $\gamma_{k\pm}^\dagger$ create SW excitations with $S_z = \pm 1$. In the long wavelength limit we find $E_k^2 = \omega_0^2 + v_s^2 k^2$ with $\omega_0^2 = \delta r^2 + 2\Delta \delta r$ and $v_s^2 = 2t U_2 \Psi_0^2 a^2$.

We need to calculate the electron spin susceptibility in the direction perpendicular to the applied magnetic field. Let θ be the angle between the z axis (*i.e.* the direction of the \vec{d} vector) and the direction of the magnetic field (see Fig. 1). We have

$$\chi_{\perp H} = \sin^2 \theta \chi_{zz} + (1 + \cos^2 \theta) \chi_{xx}. \quad (3)$$

It is easy to see that χ_{xx} and χ_{zz} are given by the correlation function of SWs

$$\begin{aligned} \chi_{xx}(q, \omega) &= 2(g_{\text{eff}} \mu_B \Psi_0)^2 (u_q + v_q)^2 \sum_{\alpha\beta} D_{\alpha\beta}^R(q, \omega) \\ \chi_{zz}(q, \omega) &= (g_{\text{eff}} \mu_B)^2 \sum_{\alpha\beta} \int \frac{d^d k d\Omega}{(2\pi)^{d+1}} U_{\alpha\beta}^2(k, k+q) \times \\ &\quad D_{\alpha\alpha}^R(k+q, \Omega + \omega) D_{\beta\beta}^A(k, \Omega) \end{aligned} \quad (4)$$

where we introduced the Nambu-Gorkov type notations $D_{\alpha\beta}^{R,A}(q, \omega) = \int dt e^{i\omega t} \theta(\pm t) \langle T \Psi_{q\alpha}(t) \Psi_{q\beta}^\dagger(0) \rangle$, with $\Psi_{q\alpha} = \{\gamma_{q+}, \gamma_{-q-}^\dagger\}^T$, and $U_{\alpha\beta}(k, k') = \delta_{\alpha\beta}(v_k v_{k'} - u_k u_{k'}) + (1 - \delta_{\alpha\beta})(u_k v_{k'} - v_k u_{k'})$.

Note that there is a qualitative difference in calculating χ_{zz} and χ_{xx} . A non-uniform magnetic field in the z direction can scatter the existing thermally excited SWs. Thus we find finite imaginary part of χ_{zz} at small frequencies by considering the quadratic Bogoliubov Hamiltonian. We obtain

$$\begin{aligned} \chi_{zz}''(\omega_N, q) &= 2(g_{\text{eff}} \mu_B)^2 \frac{\omega_N}{T} b^d \int \frac{d^d k}{(2\pi)^d} \\ &\times n(E_k)(n(E_{k+q}) + 1) \delta(E_k - E_{k+q}). \end{aligned} \quad (5)$$

By contrast, a non-uniform magnetic field in the x direction can only create or annihilate SW excitations. However, energies of these excitations cannot be smaller than ω_0 . Hence, if we limit ourselves to the quadratic Hamiltonian for SWs, we find that χ_{xx}'' is identically zero for frequencies smaller than ω_0 at any temperature. To get finite χ_{xx}'' at small frequencies we need to consider interactions between SWs. Taking quartic terms in equation (2) and using definitions of SW operators, we obtain the interaction terms between SW excitations. These can be used to calculate self-energies for SW excitations as shown in Fig 2. We find [15]

$$\begin{aligned} \chi_{xx}''(q, \omega_N) &= (g_{\text{eff}} \mu_B \Psi_0)^2 \frac{\omega_N}{4\Delta T} (U_0 + 3U_2)^2 b^{2d} \\ &\times \int \frac{d^d k_1}{(2\pi)^d} \int \frac{d^d k_2}{(2\pi)^d} \frac{E_{k_1}^2 + E_{k_2}^2 + E_{k_3}^2}{E_{k_1} E_{k_2} E_{k_3}} \\ &\times (n(E_{k_1}) + 1)(n(E_{k_2}) + 1)n(E_{k_3}) \\ &\times \delta(E_{k_1} + E_{k_2} - E_{k_3}). \end{aligned} \quad (6)$$

where $\vec{k}_3 = \vec{k}_1 + \vec{k}_2$. We emphasize that equations (5) and (6) apply only in the low frequency limit $\omega_N \ll \omega_0$ which is relevant for experiments.

Expressions (5) and (6) show that in equation (3) contributions to $1/T_1$ due to χ''_{zz} and χ''_{xx} scale as T^{2d-1} and T^{3d-2} respectively. For two and three dimensional systems the χ''_{zz} contribution dominates (one can check that this conclusion remains when we include prefactors). At first glance this result appears surprising. Firstly, the real static susceptibility is finite in the direction perpendicular to the \mathbf{d} vector but is zero along it. Secondly, in the case of full SO(3) symmetry, creation and annihilation of individual SWs contribute to χ''_{xx} and χ''_{yy} at small frequencies, but have no effect on χ''_{zz} . A crucial part of our analysis is the existence of a spin gap ω_0 which is much larger than the nuclear Larmor frequency ω_N . In this case $\chi''(\omega_N)$ does not have contributions due to creation or annihilation of individual SWs. For χ''_{zz} we take thermally excited SWs and scatter them by the magnetic field. For χ''_{xx} we also need thermally excited SWs but in addition we must rely on interactions between them. SWs are pseudo-Goldstone modes. At low energies interactions between them are suppressed. This gives rise to the smallness of χ''_{xx} relative to χ''_{zz} .

To summarize, for two and three dimensional systems, we find that as long as θ is not anomalously small, the SW contribution to the nuclear spin lattice relaxation rate is given by

$$\frac{1}{T_1} = \sin^2 \theta |A|^2 g_N^2 \frac{b^d}{v_s^{2d}} \frac{S_d^2}{4\pi^2} |B_{2d-2}| T^{2d-1}, \quad (7)$$

Here $S_d = 2\pi^{d/2}/\Gamma(d/2)$ is the surface area of a unit sphere, and B_n are Bernoulli numbers, $B_2 = 1/6$, $B_4 = -1/30$. We remind the readers that equation (7) applies when $T \gg \omega_0$. At low temperatures, $T \ll \omega_0$, we expect $1/T_1$ to start decreasing exponentially, reflecting the exponential suppression in the number of thermally excited SW excitations. Equation (7) also predicts that the nuclear spin lattice relaxation rate should be very sensitive to the direction of the magnetic field. We note, however, that this argument is valid only for magnetic fields that are smaller than the so-called spin-flop magnetic field, H_{flop} . In magnetic fields larger than H_{flop} , the order parameter \vec{d} will always be perpendicular to the direction of the applied field [15].

It is useful to compare contributions to $1/T_1$ from magnons to the one from quasiparticles. For concreteness we consider a quasi two dimensional system with the TSC order parameter $\vec{d} = \Delta_0 \hat{z} k_x / k_F$, that has a line of nodes along the \hat{z} axis. The quasiparticle contribution to the NMR relaxation rate in such a state [16] is given by $1/T_{1\text{qp}} = \pi^2 |A|^2 g_N^2 b^2 m^2 T^3 / 6\Delta_0^2$. For comparison, we take equation (7) and use the BCS expressions for the velocity of SW excitations (see below). We find $T_{1\text{mag}}/T_{1\text{qp}} = \pi^2 \Delta_0^2 / \epsilon_F^2$. In a typical superconductor,

the value of the quasiparticle gap is much smaller than the electron Fermi energy. Therefore, when we have both gapless quasiparticles and SWs, the quasiparticle contribution will strongly dominate. Only when the quasiparticles are fully gapped out do the magnons provide the dominant contribution to $1/T_1$.

Now we outline the key steps of the analysis that allowed us to estimate the characteristic frequency of SW excitations in TSC. We consider a phenomenological BCS type model for interacting electrons

$$\begin{aligned} \mathcal{H} &= \sum_{k\sigma} \epsilon_k c_{k\sigma}^\dagger c_{k\sigma} - \sum_{aq} V_a^{-1}(q) d_a^\dagger(q) d_a(q) \\ d_a^\dagger(q) &= \frac{1}{2} \sum_{k\alpha\beta} V_a(q) f_k c_{k+q/2,\alpha}^\dagger (i\sigma_2 \sigma_a)_{\alpha\beta} c_{-k+q/2,\beta}^\dagger \end{aligned} \quad (8)$$

Here $d_a(q)$ are Fourier components of the TSC order parameter in the direction a ($a = x, y, z$), f_k is an orbital wavefunction (e.g. $f_k = \text{sign}(k)$ [10]), and $c_{k\sigma}^\dagger$ are electron creation operators. Parameters V_a describe electron interactions in the p-wave channel. A homogeneous unitary triplet superconducting state is the ground state of the Hamiltonian (8). Assuming easy axis anisotropy with $V^z > V^x = V^y$, we find $\langle d_z(q=0) \rangle = \Delta_0$ and $\langle d_x \rangle = \langle d_y \rangle = 0$. To find SW excitations we consider fluctuations of the TSC order parameter $d_x(r, t) = d_x^*(r, t)$. Integrating out fermions gives an effective action for SW excitations [15] $S_{\text{eff}}\{d_x\} = \int_{\omega q} D_x(q, \omega) |d_x(q, \omega)|^2$, where q and ω are the wavevector and the real frequency of the SW. For the spherically symmetric Fermi surface in d dimensions, we have $D_x(\omega, q) = \frac{1}{4} N_0 (\omega_0^2 - \omega^2 + v_s^2 q^2)$. Here N_0 is the density of states at the Fermi energy, $v_s^2 = v_F^2/d$, v_F is the Fermi velocity, and

$$\omega_0^2 = 4\Delta_0^2 N_0^{-1} (V_x^{-1} - V_z^{-1}) \quad (9)$$

Zeros of the function D_x correspond to SW excitations. In the case of spin symmetric interactions with $V_z = V_x$, SWs are Goldstone modes of broken spin symmetry and are gapless. They have linear dispersion with the velocity v_s . In the case of the easy axis anisotropy, SWs have a gap ω_0 .

As a concrete example, we consider the TSC state in Bechgaard salts. We assume that the spin anisotropic part of the interaction in this phase is the same as in the antiferromagnetic state of this material $\Delta \mathcal{H}_{\text{anis}} = \delta J_z \sum_{\langle ij \rangle} S_i^z S_j^z$. Here $\langle ij \rangle$ corresponds to the nearest neighbor sites and the spin z axis points along the crystallographic b' axis. The antiferromagnetic resonance experiments [17] suggest $\delta J_z = 0.01K$. We can express $\Delta \mathcal{H}_{\text{anis}}$ in the form similar to equation (8) with $-\delta V^z = \delta V^x = \delta V^y = \frac{1}{2} \delta J_z v_0$. Here v_0 is the volume of the unit cell. Assuming that the anisotropic term is a small correction to the spin symmetric interaction, the total interaction entering equation (8) is $V^a = V + \delta V^a$. The value of V can be estimated from the BCS equation

for the transition temperature $T_c = 1.14 \omega_{\text{BOS}} e^{-1/N_0 V}$. Here ω_{BOS} is the characteristic frequency of bosons providing electron pairing. Combining all expressions, we find

$$\frac{\omega_0}{\Delta_0} = 2(\delta J_z N_0 v_0)^{1/2} \log\left(\frac{1.14 \omega_{\text{BOS}}}{T_c}\right) \quad (10)$$

Taking $\delta J_z = 0.01 K$, $N_0 = 2 \cdot 10^{33} \text{ erg}^{-1} \text{ cm}^{-3}$, $\omega_{\text{BOS}} = 1000 K$, $T_c = 1.4 K$, $\Delta_0 = 2.5 K$, and $v_0 = 360 \text{ \AA}^3$ we obtain ω_0 around one GHz. There is a simple qualitative argument that supports our result that ω_0 for Bechgaard salts lies in the GHz range. This argument relies on a comparison of SW resonances in the antiferromagnetic and superconducting states of these materials. In quasi one-dimensional systems microscopic descriptions of the two states are similar and BCS type models and our analysis of SW excitations can be used in the antiferromagnetic phase as well. From the discussion above, we expect that the ratio of SW energies in the two phases is approximately proportional to the ratio of AF and TSC transition temperatures, i.e. around ten. In the AF phase the SW resonance frequency was measured in the tens of GHz range [17]. Hence, in the superconducting state it should be a factor of ten smaller, which brings us into the GHz range.

Similar analysis can be done for the TSC state in Sr_2RuO_4 . Sigrist and coworkers (see e.g. Ref [18]) showed that spin-orbit coupling in these materials leads to a difference in the transition temperature of various order parameters of the order of two percent. From the BCS expression for T_c we have $\delta T_c/T_c = \delta V/N_0 V^2$. Taking $\Delta_0 = 2.6 K$, from equation (9) we estimate ω_0 to be around twenty GHz.

Sr_2RuO_4 is a quasi two dimensional material. Bechgaard salts have a mixed dimensionality [19, 20] with easy, intermediate, and hard directions in transport. Hence, they may also exhibit properties of a quasi two dimensional system with respect to SW excitations. Both the ruthenates and Bechgaard salt superconductors exhibit the T^3 dependence of $1/T_1$ at low temperature. Therefore these materials should be good candidates for experimental investigation of the SW mechanism of nuclear spin lattice relaxation discussed in this paper.

In summary, we studied spin wave excitations in triplet superconductors with the easy axis spin anisotropy. We derived an explicit expression for the energy of such excitations and used it to estimate the spin wave energy in Bechgaard salts and ruthenate superconductors. We considered the effects of spin wave excitations on the nuclear spin lattice relaxation rate. We showed that in the experimentally relevant regime of temperatures, $1/T_1$ has a power law scaling with temperature, including the T^3 dependence for two dimensional systems. We showed that the spin wave mechanism predicts a dramatic decrease of $1/T_1$ for temperatures lower than the energy of spin wave excitations and leads to dependence of $1/T_1$ on the




FIG. 1: Orientation of coordinate axes, \mathbf{H} , and the \mathbf{d} vector.

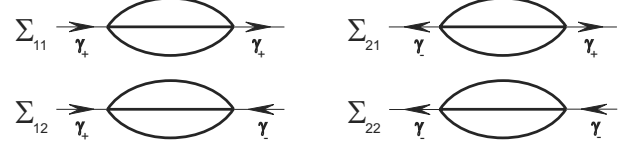


FIG. 2: Second order self-energy diagrams that give rise to scattering of spin waves. For details see [15].

direction of the applied magnetic field.

We are grateful for useful discussions with E. Altman, D. Podolsky, and A. Polkovnikov. This work was supported by the NSF grant DMR-0132874, the Sloan Foundation, and KITP UCSB.

-
- [1] D. Beeman and P. Pincus, Phys. Rev. B **166**: 359 (1968).
 - [2] A. Sakai *et.al.*, Physica C **388-389**, 251 (2003); P.M. Singer *et.al.*, Physica C **388-389**, 209 (2003); C.P. Slichter *et.al.*, J. Phys. Chem. Sol. **54**, 1439 (1993); V.F. Mitrovic *et.al.*, Phys. Rev. B **67**, 220503 (2003).
 - [3] H. Tou, K. Ishida, Y. Kitaoka, cond-mat/0308562
 - [4] K. Ishida *et.al.*, Phys. Rev. Lett. **84**, 5387 (2000).
 - [5] S. Lefebvre *et.al.*, Phys. Rev. Lett. **85**, 5420 (2000); C. Bourbonnais *et.al.*, Phys. Rev. B **33**, 7608 (1986); C. Bourbonnais *et.al.*, Phys. Rev. Lett. **62**, 1532 (1989).
 - [6] I.J. Lee *et.al.*, Phys. Rev. Lett. **88**, 017004 (2002); Y. Kitaoka *et.al.*, Physica B **281-282**, 878 (2000).
 - [7] I.J. Lee *et.al.*, Phys. Rev. Lett. **94**, 197001 (2005).
 - [8] I.J. Lee *et.al.*, Phys. Rev. B **68**, 092510 (2003); M. Taki-gawa *et.al.* in *Novel Superconductivity*, ed. by S.A. Wolf and V.Z. Kresin, Plenum, New York (1987).
 - [9] Y. Kohori *et.al.*, J. Phys. Soc. Jpn. **57**, 395 (1988).
 - [10] M. Dressel, Physica C **317**, 89 (1999).
 - [11] G.M. Luke *et.al.*, Nature **394**, 558 (1998); J.A. Duffy *et.al.*, Phys. Rev. Lett. **85**, 5412 (2000).
 - [12] A. Mackenzie and Y. Maeno, Rev. Mod. Phys. **75**, 657 (2003).
 - [13] T. Moriya, J.Phys. Soc. Jpn. **18**:516 (1963).
 - [14] E. Demler and F. Zhou, Phys. Rev. Lett. **88**:163001 (2002).
 - [15] T. Rostunov, E. Altman, and E. Demler, unpublished.
 - [16] M. Sigrist, K. Ueda, Rev. Mod. Phys. **63**, 239 (1991).
 - [17] J.B. Torrance *et.al.*, Phys. Rev. Lett. **49**, 881 (1982); M.Dumm *et.al.*, Phys. Rev. B **61**, 511 (2000); M. Dumm *et.al.*, Phys. Rev. B **62**, 6512 (2000).
 - [18] K.K. Ng, M. Sigrist, Europhys. Lett. **49**, 473 (2000).
 - [19] A. Schwartz *et.al.*, Phys. Rev. B **58**, 1261 (1998); M.

- Dressel *et.al.*, Phys. Rev. B **71**, 075104 (2005).
- [20] A.G. Lebed, Phys. Rev. B **59**, R721 (1999); A.G. Lebed, Heon-Ick Ha, and M.J. Naughton, Phys. Rev. B **71**, 132504 (2005); C.D. Vaccarella and C.A.R. Sa de Melo, Phys. Rev. B **64**, 212504 (2001).