

⁵⁹Co-NMR Knight Shift of Superconducting Three-Layer Na_xCoO₂·yH₂O

H. Watanabe, Y. Kobayashi and M. Sato*

Department of Physics, Division of Material Science, Nagoya University, Furo-cho, Chikusa-ku, Nagoya 464-8602

(accepted June 22, 2005)

The superconducting state of Na_xCoO₂·yH₂O with three CoO₂ layers in a unit cell has been studied by ⁵⁹Co-NMR. The Knight shift measured for a peak of the NMR spectra corresponding to the external magnetic field **H** along one of the principal directions within the CoO₂ plane, exhibits a rapid decrease with decreasing temperature *T* below the superconducting transition temperature *T_c*, indicating that the spin susceptibility χ_{spin} is suppressed in the superconducting phase, at least, for this field direction. Because differences of the superconducting properties are rather small between this three-layer Na_xCoO₂·yH₂O and previously reported Na_xCoO₂·yH₂O with two CoO₂ layers within a unit cell, the present result of the Knight shift studies indicates that the Cooper pairs of the former system are in the singlet state as in the latter, for which the spin susceptibility is suppressed for both directions of **H** parallel and perpendicular to the CoO₂ plane.

KEYWORDS: Na_xCoO₂·yH₂O, Superconductivity, ⁵⁹Co-NMR, Knight shift

1. Introduction

The hydrated Co oxide Na_xCoO₂·yH₂O (*x*~0.3 and *y*~1.3) having two CoO₂ layers within a unit cell, which are formed of edge-sharing CoO₆ octahedra exhibits the superconducting transition at temperature $T = T_c \sim 4.5$ K.¹⁾ Because the layers have the triangular lattice of Co atoms, roles of the geometrical frustration are, naively speaking, expected to be important for the occurrence of the superconductivity, and much attention has been paid to the system. It is also presumed that strong spin excitations are related to the superconductivity, because the spin state change is often found in Co³⁺ ions in various kinds of Co oxides.²⁻⁴⁾ Then possible exotic characters have been intensively pursued and the pairing symmetry is being hotly argued.⁵⁻¹²⁾

We have studied the ⁵⁹Co-NMR Knight shift *K* of two-layer Na_xCoO₂·yH₂O^{6,7)} and reported that it decreases with decreasing *T* below *T_c* for both directions of the applied field **H** within the *ab*-plane and parallel to the *c*-axis.⁷⁾ The result indicates that the superconducting electron pairs are in the singlet state.

In this paper, results of the ⁵⁹Co-NMR studies on another superconducting system of Na_xCoO₂·yH₂O,¹³⁻¹⁵⁾ which has three layers of edge-sharing CoO₆ octahedra within a unit cell, are presented. The *T_c* value of this three-layer Na_xCoO₂·yH₂O is ~4.5 K, nearly equal to that of two-layer Na_xCoO₂·yH₂O.

In Fig. 1, the structures of (a) P2-Na_{0.75}CoO₂ and (b) O3-NaCoO₂^{16,17)} are compared. In the figure, we can recognize that the repetition of the layer sequences of (O_A-Co-O_B-Na-O_B-Co-O_A-Na-) and (O_A'-Co-O_B'-Na-O_C'-Co-O_A'-Na-O_B'-Co-O_C'-Na-) within a unit cell are repeated, for P2-Na_{0.75}CoO₂ and (b) O3-NaCoO₂, respectively, where O_X (X=A, B, A', B' and C') distinguish the oxygen layers. The superconducting systems are prepared by de-intercalating Na atoms and then, intercalating H₂O molecules. During these processes, the stacking sequence of

P2-Na_xCoO₂ is kept unchanged, while the O3-NaCoO₂ is transformed to the P3 type one with a sequence of (-O_A'-Co-O_B'-Na-O_B'-Co-O_C'-Na-O_C'-Co-O_A'-Na-).¹⁵⁾

We have performed ⁵⁹Co-NMR studies of the powder samples of P3-Na_xCoO₂·yH₂O and compared the observed results with those of P2-Na_xCoO₂·yH₂O.

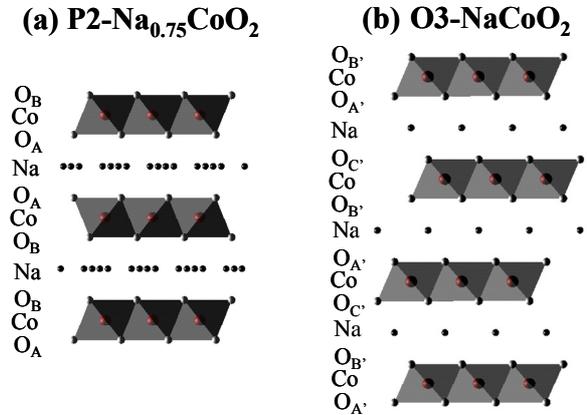


Fig. 1. Crystal structures of (a) P2-Na_{0.75}CoO₂ and (b) O3-NaCoO₂, where the Na sites are shown by the dark spheres and Co sites are within the shaded octahedra formed of the corner oxygens. In O3-NaCoO₂, the Na sites are fully occupied, while in P2-Na_{0.75}CoO₂, there are two crystallographically distinct Na sites with different occupancies.

2. Syntheses and Characterizations of the samples

Powder samples of P3-Na_xCoO₂·yH₂O were synthesized by using the procedure described in ref. 13: The mother system O3-NaCoO₂ was synthesized, by heating NaOH pellets buried in the powder of Co metal in air at 500 °C for 12 h, where we had to use the 25 % excess amount of NaOH to obtain O3-phase samples of NaCoO₂. (If the molar ratio of Na and Co is smaller than ~1.25, a significant amount of P2-Na_xCoO₂ with

*corresponding author: (e-mail: e43247a@nucc.cc.nagoya-u.ac.jp)

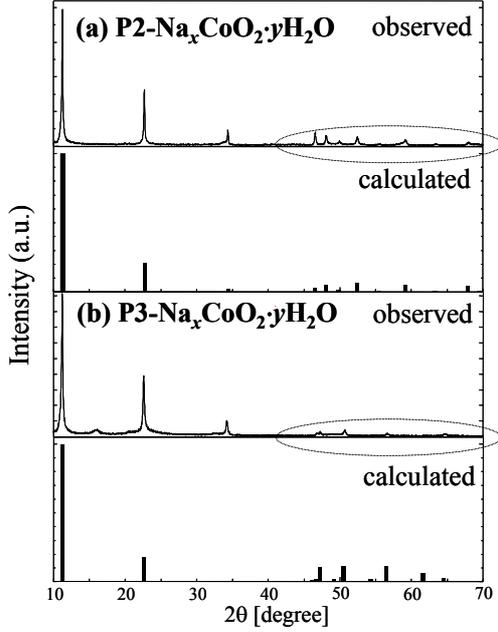


Fig. 2. The X-ray powder diffraction patterns observed for the samples of (a) P2- and (b) P3- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$ are compared with the integrated intensities calculated by using the space groups $P6_3/mmc$ and $R\bar{3}m$, respectively. The data in the high angle regions surrounded by the broken lines indicate the clear distinction between the structures of P2- and P3- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$.

$x \sim 0.75$ is found as the impurity phase.) The fused ingots were finely ground and annealed at 800°C under a N_2 flow for 16 h. In the X-ray diffraction pattern of the sample obtained by this heat treatments, we did not see any impurity phases. It is noted that the obtained O3-NaCoO_2 tends to change gradually to $\text{P2-Na}_{0.75}\text{CoO}_2$ in air. The powder was immersed in the $\text{Br}_2/\text{CH}_3\text{CN}$ solution for 5 days to de-intercalate Na atoms and then the product was washed with CH_3CN and dried in air. Finally, in order to obtain the superconducting hydrated phase with two H_2O layers between the neighboring CoO_2 planes (bilayer phase), the product was sealed in a chamber with saturated H_2O vapor at room temperature for a week.

The obtained powder sample of $\text{P3-Na}_x\text{CoO}_2.y\text{H}_2\text{O}$ was characterized as a single phase by the powder X-ray diffraction. In Figs. 2(a) and 2(b), the observed X-ray diffraction patterns of P2- and P3- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$ are compared with the calculated ones, respectively (space group $P6_3/mmc$ for the former and $R\bar{3}m$ for the latter). The preparation method of the P2- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$ can be found elsewhere.^{6,7)} We can distinguish these two phases from the peak positions in the high angle region. The lattice parameters for the samples of P3- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$ are $a = b = 2.8253(7)$ and $c = 29.423(6)$ Å, which are consistent with previously reported ones¹³⁻¹⁵⁾.

Figure 3 shows the T dependence of the magnetic susceptibility measured with the magnetic field $H = 5$ Oe for a powder sample of $\text{P3-Na}_x\text{CoO}_2.y\text{H}_2\text{O}$ used in the NMR/NQR measurements. The superconducting transition temperature T_c is about 4.5 K, which is nearly equal to that of P2- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$.

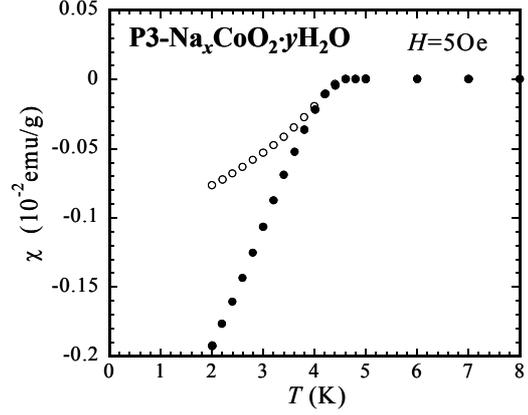


Fig. 3. Magnetic susceptibility of P3- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$ measured with the magnetic field $H = 5$ Oe. Open and solid circles are measured under the conditions of the field cooling and the zero field cooling, respectively.

^{59}Co -NMR spectra were obtained for the randomly oriented powder sample of $\text{P3-Na}_x\text{CoO}_2.y\text{H}_2\text{O}$ by the spin-echo technique using a phase coherent type pulse spectrometer. The echo intensity was recorded with the applied magnetic field changed stepwise. The nuclear longitudinal relaxation rate $1/T_1$ of ^{59}Co nuclei was measured by measuring the ^{59}Co nuclear magnetization m as a function of the time t elapsed after applying an inversion pulse in the frequency region around $3\nu_Q$, ν_Q being the electrical quadrupolar frequency (~ 4 MHz). The $\{1-m(t)/m(\infty)\}-t$ curves were found to be described by the theoretical one. Other details can be found in ref. 6.

3. Results of the NMR Studies and Discussion

Field swept spectra of ^{59}Co NMR taken at 5 K with the frequency $f = 23.566$ MHz are shown in Fig. 4 together with the result of the model calculation (broken line) obtained as described in ref. 6 for P2- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$. In the present case, the used NMR parameters are as follows. The quadrupolar frequency $\nu_Q = 4.1$ MHz, the Knight shifts $K_x = 3.2\%$, $K_y = 3.5\%$ and $K_z = 2.1\%$ for locally defined principal axes at Co sites, x , y and z , respectively and the asymmetric parameter $\eta = 0.3$. These parameters, which can well reproduce the observed spectra, are rather similar to those obtained for P2- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$.⁶⁾ Because the trigonal distortions of CoO_6 octahedra in P2- and P3- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$ are almost equal,¹⁸⁾ we can expect that the principal axis z of the latter system is parallel to the c axis, as in P2- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$. The peak indicated by the arrow in Fig. 4 corresponds to the magnetic field direction parallel to one of the principal directions (y -direction) within the ab -plane. We have measured the T -dependence of this peak at frequencies f of 23.566, 33.281 and 43.625 MHz. The value of the resonance field H_{res} determined as the peak position of the magnetic field H begins to exhibit rather rapid increase with decreasing T at the transition temperature T_c for all frequencies. This behavior is similar to that of P2- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$.^{6,7)} For example, the peak profiles observed at various temperatures for $f = 23.566$ MHz are shown in Fig. 5, where the peak values are

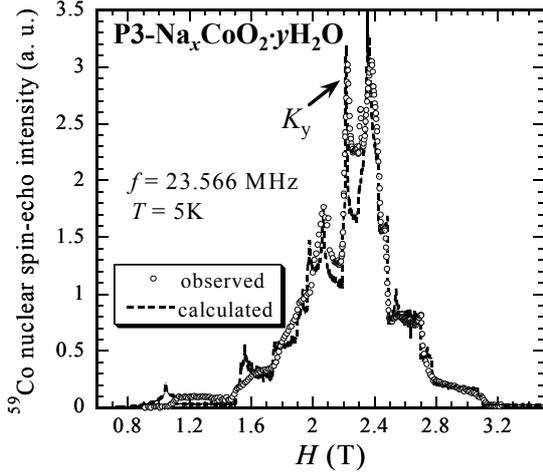


Fig. 4. Field swept ^{59}Co -NMR spectra of $\text{P3-Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ taken at 5 K with a fixed frequency of 23.566 MHz for randomly oriented powder samples. The broken line shows the powder pattern calculated by the parameters $\nu_Q = 4.1$ MHz, $K_x = 3.2$ %, $K_y = 3.5$ %, $K_z = 2.1$ % and $\eta = 0.3$.

adjusted to that shown in Fig. 4 (in Fig. 5, almost the whole part of the profiles above the dip found at the higher field side of the peak is shown and the shift of the peak toward the higher field side with decreasing T is evident). The shift occurs due to the magnetic shift and/or the effect of the second order and higher order eqQ interactions. In the present case, it is considered that the magnetic shift predominantly contributes to the observed one, because the T dependence of the shift originating from the quadrupolar interaction is considered to be negligibly small in this low temperature region.

In Fig. 6(a), the deviation of the resonance field H_{res} from the value just above T_c , $\Delta H_{\text{res}}(T) \equiv H_{\text{res}}(T) - H_{\text{res}}(T > T_c)$ observed for various frequencies (or various applied field) are shown. It is worth noting that at low temperatures the absolute value of ΔH_{res} increases with increasing H , which was also observed for $\text{P2-Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$. This field dependence of ΔH_{res} cannot be explained solely by the superconducting diamagnetism M_{dia} , because the absolute value of M_{dia} decreases with increasing H in the measured H region ($H \gg$ the lower critical field H_{c1}). Consequently, we can say that for the nonzero ΔH_{res} observed below T_c , the reduction of the spin magnetization M_{spin} is important. (The orbital contribution to the Knight shift can be considered to be T independent in this low temperature region.)

Figure 6(b) shows the T -dependence of $\Delta K(T) \equiv f\{\gamma_N H_{\text{res}}(T)\} - f\{\gamma_N H_{\text{res}}(T > T_c)\}$ for various fixed frequencies, where γ_N is the nuclear gyromagnetic ratio ($\gamma_N = 10.03$ MHz/T for ^{59}Co). If we neglect the contribution of M_{dia} , the reduction of ΔK is due to the suppression of the spin component K_{spin} of the Knight shift K . The magnitudes of ΔK for the present $\text{P3-Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ are slightly smaller than those for $\text{P2-Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$.^{6,7)} But, in both systems, K_{spin} decreases below T_c , suggesting that the superconducting electron pairs should be considered to be in the singlet state, unless the spins of Cooper pairs in the triplet state are strongly

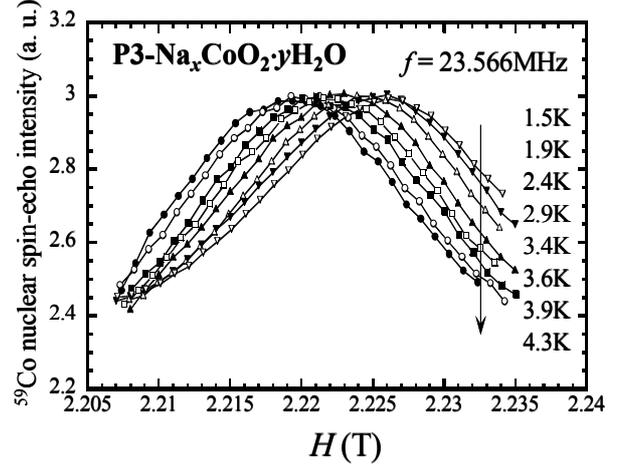


Fig. 5. Temperature dependence of the profile of the peak indicated in Fig. 4 by the arrow is shown for a fixed frequency of 23.566 MHz. The solid lines are the guides for eyes.

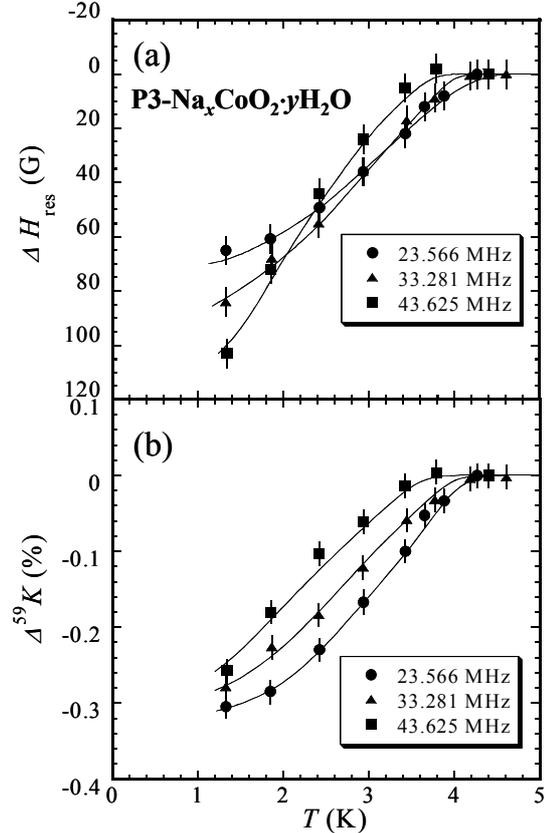


Fig. 6. (a) Deviations of the resonance field from the value just above T_c , $\Delta H_{\text{res}}(T) \equiv H_{\text{res}}(T) - H_{\text{res}}(T > T_c)$ are plotted against T for $H \parallel y$ at three fixed frequencies. (b) Deviations of the Knight shift from the value just above T_c , $\Delta K(T) \equiv f\{\gamma_N H_{\text{res}}(T)\} - f\{\gamma_N H_{\text{res}}(T > T_c)\}$ are plotted against T for various fixed frequencies, where γ_N is the nuclear gyromagnetic ratio ($\gamma_N = 10.03$ MHz/T for ^{59}Co).

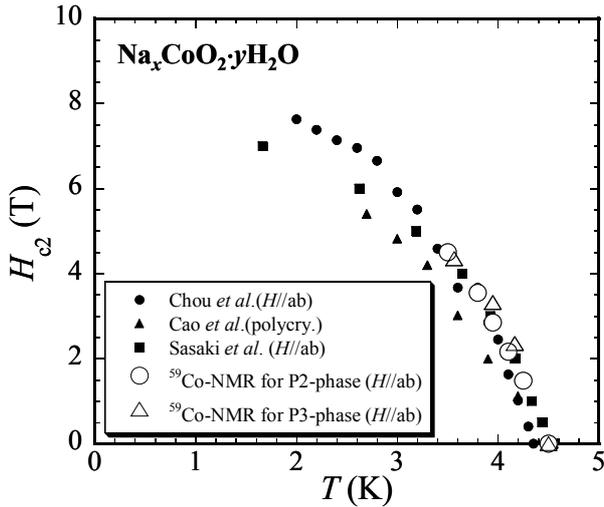


Fig. 7. T -dependence of the upper critical field H_{c2} for $H // ab$ -plane determined from the $\Delta K(H)$ - T curves of P2- and P3- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$ is shown together with the reported data of the resistivity measurements.

pinned along the c -direction. On this point, we have already reported⁷⁾ that in P2- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$, ΔK decreases (or $|\Delta K|$ increases) with decreasing T below T_c for both directions of H within the ab -plane and parallel to the c -axis. It indicates that the pairs are in the singlet state in P2- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$.

Figure 7 shows the T -dependence of the upper critical field H_{c2} estimated from $\Delta K(H)$ - T curves for P3- and P2- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$, together with those of resistivity measurements for P2- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$.^{7,19-21)} The value of $H_{c2}(T \rightarrow 0)$ is estimated to be about 8 T, which well agrees with the value expected from the Pauli paramagnetic limit $H_p = 1.84T_c$ for systems with the negligible effect of the spin-orbit coupling and with $T_c = 4.5$ K. Because the Pauli limit arises from the pair breaking by the Zeeman effect, the observed value of H_{c2} implies that the singlet superconductivity is realized in the present cobalt oxide superconductor P3- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$. Thus, we may consider that both of P2- and P3- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$ possess the same superconducting pair symmetry. For P2- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$, we have shown from the measurements of the Knight shifts that the spin susceptibility χ_{spin} is suppressed for both directions of H within and perpendicular to the ab -plane.⁷⁾ For P3- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$, we have not studied the shift for the perpendicular field, because it is difficult to grow single crystals of the mother system O3- NaCoO_2 . However, the similarity of the data shown in the present paper for H within the ab -plane implies that no significant difference exists between the behaviors of the Knight shifts of P2- and P3- superconductors. Then, we think that the singlet pairing is also realized in the present P3- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$.

In Fig. 8, the longitudinal relaxation rate, $1/T_1$ is plotted against T for ^{59}Co nuclei. In the figure, the data reported for P2- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$ ^{6,7,22,23)} are also shown. We find that both the P2- and P3- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$ systems exhibit similar T dependences of $1/T_1$ and that they do not exhibit the coherence

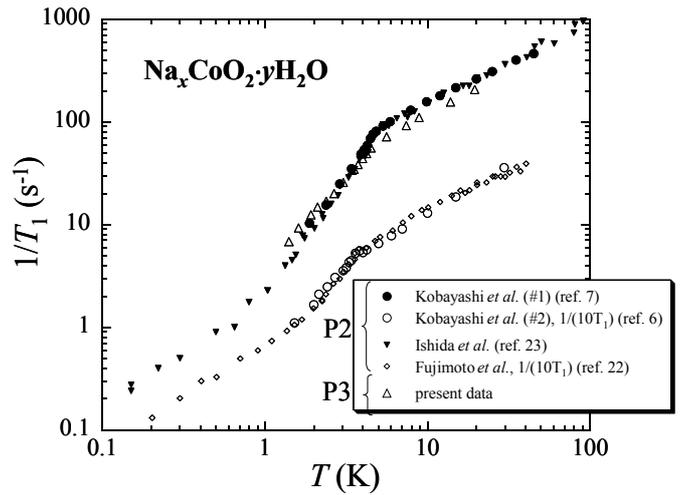


Fig. 8. Longitudinal relaxation rate $1/T_1$ of ^{59}Co nuclei are plotted against T in logarithmic scales. Several data reported for P2- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$ are also shown.

peak, confirming that their superconducting phases exhibit very similar behaviors. As has been already discussed in the preceding paper,⁷⁾ it seems to be important, for the complete understanding of the superconducting state of the hydrated Co oxides, to have a consistent explanation of the behaviors of K , $1/T_1$ and the rather small effect of non-magnetic impurities on the superconducting transition temperature T_c .⁸⁾ It remains as a future problem.

Neutron scattering studies carried out for P2- $\text{Na}_{0.82}\text{CoO}_2$ ²⁴⁾ and P2- $\text{Na}_{0.75}\text{CoO}_2$ ²⁵⁾ have shown that the interlayer magnetic interaction of the electron system is so significant that the system has the 3-dimensional nature. It is also reported that the in-plane magnetic correlation is ferromagnetic for these Na-rich systems. It has been pointed out that the origin of this significant interlayer coupling takes place through the sp^2 hybridized orbits of Na^+ and O^{2-} ions between the CoO_2 planes.²⁶⁾ Then, the neutron results stated above might indicate that the stacking way of the CoO_2 layers, which affects the interlayer coupling, is important for the determination of the physical properties of Na_xCoO_2 . However, various kinds of results obtained by NMR/NQR, neutron scattering and other studies on P2- Na_xCoO_2 indicate that the system has the low dimensional nature and the antiferromagnetic in-plane correlation of the electrons in the region of $x \leq 0.6$, as reported elsewhere.²⁷⁾ Moreover, it is expected for the superconducting systems with $x \sim 0.3$, the 2-dimensional nature is enhanced by the H_2O intercalation. Therefore, we think that the stacking way of the CoO_2 planes does not have effects on the physical properties. It is consistent with the present experimental results.

4. Summary

We have presented the results of the ^{59}Co -NMR experiments for a randomly oriented sample of P3- $\text{Na}_x\text{CoO}_2.y\text{H}_2\text{O}$. The magnitude of the Knight shift K decreases with decreasing T below T_c for the field direction H within the ab -plane. For this

reduction, the suppression of K_{spin} is essential. The value of $H_{c2}(T \rightarrow 0)$ estimated from the $\Delta K(H)-T$ curves is similar to those of $\text{P2-Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$. The structural difference between P3- and $\text{P2-Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ seems not to induce any significant differences between the superconducting properties of these two systems. In the strict sense, the present results do not completely exclude the possibility of the triplet pairing state with their spins strongly pinned along the c -axis. However, considering that ΔK_{spin} of $\text{P2-Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ decreases with decreasing T below T_c even in the case of H parallel to the c direction, it is natural to conclude that the possibility of the triplet pairing is ruled out for the present $\text{P3-Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$, too.

Acknowledgements

This work is supported by Grants-in-Aid for Scientific Research from the Japan Society for the Promotion of Science (JSPS) and by Grants-in-aid on priority areas from the Ministry of Education, Culture, Sports, Science and Technology.

References

- 1) K. Takada, H. Sakurai, E. Takayama-Muromachi, F. Izumi, R. A. Dilanian and T. Sasaki: Nature, 2003, **422**, 53.
- 2) M. Soda, Y. Yasui, T. Fujita, T. Miyashita, M. Sato and K. Kakurai: J. Phys. Soc. Jpn. **72** (2003) 1729
- 3) M. Soda, Y. Yasui, M. Ito, S. Iikubo, M. Sato and K. Kakurai: J. Phys. Soc. Jpn. **73** (2004) 464
- 4) T. Fujita, T. Miyashita, Y. Yasui, Y. Kobayashi, M. Sato, E. Nishibori, M. Sakata, Y. Shimojo, N. Igawa, Y. Ishii, K. Kakurai, T. Adachi, Y. Ohishi and M. Tanaka: J. Phys. Soc. Jpn. **73** (2004) 1987
- 5) M. Kato, C. Michioka, T. Waki, and K. Yoshimura: cond-mat/0306036
- 6) Y. Kobayashi, M. Yokoi and M. Sato: J. Phys. Soc. Jpn. **72** (2003) 2453
- 7) Y. Kobayashi, H. Watanabe, M. Yokoi, T. Moyoshi, Y. Mori, and M. Sato: J. Phys. Soc. Jpn. **74** (2005) 1800
- 8) M. Yokoi, H. Watanabe, Y. Mori, T. Moyoshi, Y. Kobayashi and M. Sato: J. Phys. Soc. Jpn. **73** (2004) 1297
- 9) K. Kuroki, Y. Tanaka and R. Arita: Phys. Rev. **B71** (2005) 024506.
- 10) Y. Yanase, M. Mochizuki and M. Ogata: J. Phys. Soc. Jpn. **74** (2005) 430
- 11) M. Mochizuki, Y. Yanase, and M. Ogata: J. Phys. Soc. Jpn. **74** (2005) 430.
- 12) H. Ikeda, Y. Nishikawa and K. Yamada: J. Phys. Soc. Jpn. **73** (2004) 17
- 13) M. L. Foo, T. Klimczuk, Lu Li, N. P. Ong, and R. J. Cava: Solid State Commun. **133** (2005) 407.
- 14) H. Sakurai, K. Takada, T. Sasaki, F. Izumi, R. A. Dilanian and E. Takayama-Muromachi: J. Phys. Soc. Jpn. **73** (2004) 2590.
- 15) K. Takada, H. Sakurai, E. Takayama-Muromachi, F. Izumi, R. A. Dilanian and T. Sasaki: Adv. Mater. **16** (2004) 21
- 16) B. L. Cushing and J. B. Wiley: J. Solid State Chem. **141**, (1998) 385
- 17) B. L. Cushing and J. B. Wiley, Synth: React. Inorg. Met.-Org. Chem., **29** (7), (1999) 1199
- 18) K. Takada, M. Osada, F. Izumi, H. Sakurai, E. Takayama-Muromachi and T. Sasaki: Chem. Matter. **17** (2005) 2034.
- 19) G. Cao, C. Feng, Y. Xu, W. Lu, J. Shen, M. Fang and Z. Xu: J. Phys. Condens. Matter **15** (2003)
- 20) T. Sasaki, P. Badica, N. Yoneyama, K. Yamada, K. Togano and N. Kobayashi; J. Phys. Soc. Jpn. **73** (2004) 1131
- 21) F. C. Chou, J. H. Cho, P. A. Lee, E. T. Abel, K. Matan and Y. S. Lee: Phys. Rev. Lett. **92** (2004) 157004
- 22) T. Fujimoto, G. Zheng, Y. Kitaoka, R. L. Meng, J. Cmaidalka and C. W. Chu: Phys. Rev. Lett. **92** (2004) 125.
- 23) K. Ishida, Y. Ihara, Y. Maeno, C. Michioka, M. Kato, K. Yoshimura, T. Takada, T. Sasaki, H. Sakurai and E. Takayama-Muromachi: J. Phys. Soc. Jpn. **72** (2003) 3041.
- 24) S.P. Bayrakci, I. Mirebeau, P. Bourges, Y. Sidis, M. Enderle, J. Mesot, D.P. Chen, C. T. Lin and B. Keimer: cond-mat/0410224.
- 25) L.M. Helme A.T. Boothroyd, R. Goldea, Prabhakaran, D.A. Tennant, A. Hiess and J. Kulda: Cond-mat/0410457.
- 26) M. D. Johannes, I.I. Mazin and D.J. Singh: cond-mat/0421663.
- 27) M. Yokoi, T. Moyoshi, Y. Kobayashi, Y. Yasui, M. Soda, M. Sato and K. Kakurai: J. Phys. Soc. Jpn. Submitted.