

^{23}Na NMR Study of Layered Superconductor $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$

H. Ohta^{a,i}, C. Michioka^a, Y. Itoh^a, K. Yoshimura^a, H. Sakurai^b,
E. Takayama-Muromachi^b, K. Takada^c, T. Sasaki^c

^aDepartment of Chemistry, Graduate School of Science, Kyoto University, Kyoto 606-8502, Japan

^bSuperconducting Materials Center, NIMS, Namiki, Tsukuba, Ibaraki, 305-0044, Japan

^cAdvanced Materials Laboratory, NIMS, Namiki, Tsukuba, Ibaraki, 305-0044, Japan

Abstract

We measured ^{23}Na -NMR spectra and nuclear spin-lattice relaxation rates ($1/T_1$) of superconducting and non-superconducting bilayer hydrate $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ ($x = 0.3; y = 1.3$). The central resonance frequency shows a small but various shift due to the difference in the shielding effect by intercalated H_2O molecules. The different shielding effect also gives a large difference in the magnitude of ^{23}Na ($1/T_1$).

Key words: Sodium cobalt oxide, Superconductivity, ^{23}Na -NMR
PACS: 71.10.Hf; 71.27.+a; 75.30.Mb

Recently, a number of investigations for the superconductivity in bilayer hydrate (BLH) sodium cobalt oxide $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ ($x = 0.3; y = 1.3$) have been done. Different properties were reported especially in NMR studies for different samples. In a report of chemical study, it is emphasized that some Na^+ ions are exchanged by H_3O^+ ions during intercalation of H_2O molecules[1]. Because of the nonstoichiometric properties in BLH, i.e. ambiguities of the amount of Na^+ , H_2O , and H_3O^+ , similar samples are hardly obtained. More chemical studies are needed to clarify the origin of the magnetism and the superconductivity of BLH.

We prepared two BLH samples by following processes[2]. Powders of Co_3O_4 and Na_2CO_3 were well mixed and heated at 800 °C for 20 hours in O_2 atmosphere. The obtained powder sample was characterized as in a single phase of $\text{Na}_{0.7}\text{CoO}_2$ by powder X-ray diffraction (XRD) measurements. Then $\text{Na}_{0.7}\text{CoO}_2$ was immersed in $\text{Br}_2/\text{CH}_3\text{CN}$ solution for several days to deintercalate Na ions. The dried powder was immersed in distilled water for 1 day. The water-

intercalated powder was put in a sealed chamber filled with 75 % of relative humidity (RH). We prepared several samples by changing the duration kept in the chamber, and frozen at about -10 °C for quenching further change. A sample named BLH1 was kept for one week in 75 % RH atmosphere, and BLH2 for 1 month.

Another two samples named BLHs1 and BLHs2 were synthesized by similar process, but not at the same time with BLH1 and BLH2. BLHs1 has already been studied in [3]. BLHs2 was a derivative of BLHs1 after about 1 year in the 75 % RH atmosphere before frozen.

Each sample was characterized to be in a single phase of the BLH by powder XRD result. The lattice constant c of BLHs1 and BLHs2 estimated by the XRD results are smaller than that of BLH1 and BLH2. This difference in c indicates that the content of H_3O^+ is different between two groups. The superconducting transition temperature T_c estimated by magnetization measurements was $T_c < 1.8$ K for BLH1 and 4.5 K for BLH2; $T_c = 4.7$ K for BLHs1 and 3 K for BLHs2.

We observed the free induction decay (FID) signals of ^{23}Na nuclei ($I = 3/2$) by NMR at 7.485 T. The Fourier transformed NMR spectra of FID signals are shown in Fig. 1. Here, ν_{ref} denotes the resonance fre-

Corresponding author. Tel: +81-75-753-3990 fax: +81-75-753-4000

Email address: shiochio@kuchem.kyoto-u.ac.jp (H. Ohta).

quency of ^{23}Na nuclei in NaCl aqueous solution at room temperature ($\nu_{\text{ref}} = 84.287 \text{ MHz}$). The satellite lines due to the nuclear quadrupole interaction may wipe out. The shift of peak resonance is very small compared with $\text{Na}_{0.7}\text{CoO}_2$ ($\nu_{\text{ref}} = 40 \text{ kHz}$) [4], and the temperature dependence of the shift is also small, suggesting a weak Co-O-Na coupling.

The recovery curves of FID signals were measured by inversion recovery method for obtaining ^{23}Na nuclear spin-lattice relaxation rate $^{23}(1/T_1)$. The temperature dependence of $^{23}(1/T_1)$ is shown in Fig. 2. The relaxation rate was estimated by the least-square fitting using the theoretical function of the central transition ($I_z = 1 \rightarrow 2$ and $1 \rightarrow 0$). While the peak shift is small and similar in each BLH as shown in Fig. 1, the absolute value of $^{23}(1/T_1)$ is markedly different. A broad peak around 100–150 K in each $^{23}(1/T_1)$ and a rapid increase above 200 K except for BLHs2 are observed. This rapid increase in $^{23}(1/T_1)$ may originate in the motion of Na^+ ions [5].

The magnitude of $^{23}(1/T_1)$ of BLH is on two or three order smaller than that of $\text{Na}_{0.7}\text{CoO}_2$ [5,6]. If the hyperfine coupling of BLH is on two or three order smaller than that of $\text{Na}_{0.7}\text{CoO}_2$ [4], the shift should be 0.05

0.5 kHz. The hyperfine coupling is thought to be shielded by the intercalated H_2O molecules. The difference in $^{23}(1/T_1)$ may be attributed to the difference of compositions of H_2O , H_3O^+ , and Na^+ , which may cause the different surroundings around a sodium ion. Since $1/T_1$ becomes slower with increasing the duration, the shielding effect is enhanced by the time duration in the chamber. We note that ^{59}Co and ^{17}O -NMR/NQR are hard to probe these difference of compositions, because Co and O nuclei are in the CoO_2 plane and outside of the layer consisting of the nonstoichiometric components. Therefore, ^{23}Na -NMR should be a strong probe to elucidate the physical properties of the BLH.

In conclusion, we measured ^{23}Na -NMR in bilayer hydrate sodium cobalt oxides, including nonsuperconducting bilayer hydrate. At the Na site, the hyperfine coupling is weakened by the intercalated H_2O molecules, and the nuclear spin-lattice relaxation shows a large difference in four samples with different superconducting temperatures.

Acknowledgment

This study was supported in part by Grants-in-Aid for Scientific Research from Japan Society for the Promotion of Science (16076210).

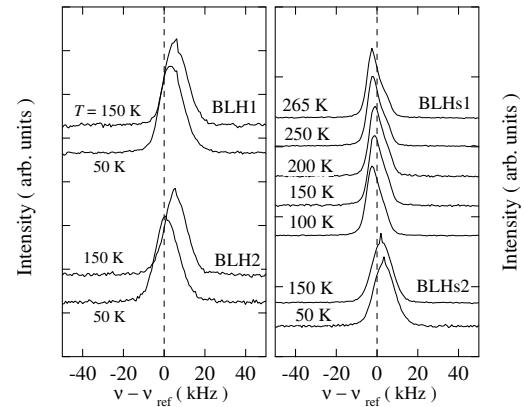


Fig. 1. ^{23}Na -NMR spectra of BLH1,2 and BLHs1,s2. ν_{ref} is the resonance frequency of ^{23}Na in NaCl aqueous solution at room temperature ($\nu_{\text{ref}} = 84.287 \text{ MHz}$). No satellite lines were observed.

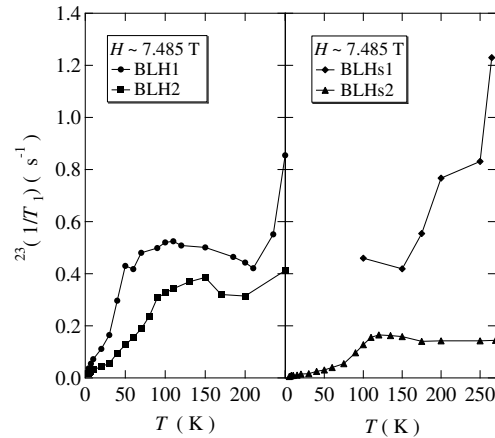


Fig. 2. Temperature dependence of $^{23}(1/T_1)$.

References

- [1] K. Takada et al, J. Mater. Chem. 14 (2004) 1448.
- [2] K. Takada et al, Nature 422 (2003) 53.
- [3] M. Kato et al, Physica B 359–361 (2005) 482.
- [4] I. R. Mukhammedshin et al, Phys. Rev. Lett. 93 (2004) 167601.
- [5] J. L. Gavilano et al, Phys. Rev. B 69 (2004) 100404(R).
- [6] Y. Ihara et al, J. Phys. Soc. Jpn 73 (2004) 2963.