

Dynamics of twist glass transition of a π -conjugated polymer investigated by NMR relaxation spectroscopy: poly(*para*-phenylene)

Naoki Asakawa,* Manabu Ohira, Koji Yazawa, and Yoshio Inoue

Department of Biomolecular Engineering, Tokyo Institute of Technology. 4259 B-55 Nagatsuta-cho, Midori-ku, Yokohama, Kanagawa 226-8501, Japan

Takakazu Yamamoto

Chemical Resources Laboratory, Tokyo Institute of Technology. 4259 Nagatsuta-cho, Midori-ku, Yokohama, Kanagawa 226-8503, Japan

(Dated: July 1, 2020)

Dynamics of Yamamoto-type poly(*para*-phenylene)[PPP] was investigated by differential scanning calorimetry(DSC) and proton solid-state NMR relaxation spectroscopy. The DSC chart shows the baseline jump without latent heat at 295K, which is due to the glass transition of the polymer. From the variable temperature proton longitudinal relaxation time(T_1) measurements, relatively short T_1 is observed over the wide temperatures range from 250K (closed to Vogel-Fulcher-Tamman temperature) to 360K, inferred the existence of cooperative critical slowing down associated with the glass transition. The frequency dependence of proton longitudinal relaxation time at 295K shows $R_1 \sim \omega^{-0.5}$ dependence, which is due to the one-dimensional diffusion-like motion of the backbone conformational modulation. The frequency dependence is held at least up to 360K. From these experiments, we were able to observe the twist glass transition of the backbone of PPP, of which critical dynamics has a universality class of the three-dimensional XY model.

PACS numbers: 82.35.Cd,82.56.-b,76.60.-k

Keywords: poly(*para*-phenylene), twist glass transition, π -conjugated polymer glass, NMR relaxation, critical dynamics

I. INTRODUCTION

”Conformon” is known as one of elementary excitations concerning molecular structure.¹ The quasiparticle in π -conjugated polymers has been of particular interest because static and dynamical aspects of the quasiparticle can closely be related to the electronic and optical properties of the polymers. Poly(*para*-phenylene)[PPP] is one of the polymers on which extensive studies have been conducted for physical properties, because of its potential functionalities such as electrical conduction or optical applications (electrical conductivity², rechargeable battery^{3,4}, electrorheology^{5,6,7,8,9,10}, electroluminescence^{11,12}). In spite of extensive studies, however, even molecular and crystal structures have not been established yet.

Particular attention has been devoted to the phase transition of π -conjugated small molecules which have the incommensurate (IC) phase (such as biphenyl^{13,14}, dichlorobiphenylsulphone¹⁵, etc.). In these phases, disordered crystals show the long range breaking of the lattice periodicity. Therefore the wavelength of the modulation is not an integral multiple of the unit cell, which means that translational symmetry is lost. In most incommensurate crystals, power-law temperature and frequency dependences on ¹H longitudinal relaxation time were observed.^{13,15} Furthermore, the relaxation rate rises dramatically around the transition temperature T_i . This is due to the fact that the longitudinal relaxation is controlled by low frequency excitations of the collective phase modes (phasons) of the order pa-

rameter(i.e., backbone twist) corresponding to the critical slowing down of molecular motion accompanying the phase transition.^{13,15,16}

As far as π -conjugated polymers are concerned, although it is well known that π -conjugated polymers shows discommensuration(so-called soliton) by carrier doping,¹⁷ there have never been reported to confirm the existence of incommensurate modulations as a purely, molecular structural problem. Recently, we have investigated the dynamics of the conformon in a regio-regulated π -conjugated polymer and found the existence of modulation waves of backbone twist in its quasiordered phase which coexists with the crystalline phase in association with the order-disorder phase transition.¹⁸ Although it is still unclear whether the modulation waves are incommensurate, the waves show anomalous dispersion of which the group velocity is approximately 10^7 time larger than the phase velocities.

In this article, we shall give attention to the conformon in a π -conjugated polymer glass and investigate the critical dynamics of twist glass transition in poly(*para*-phenylene)[PPP] mainly by nuclear magnetic resonance(NMR) relaxation spectroscopy, which deal with the frequency dependence of NMR relaxation rate in order to obtain information about dimensionality of the correlation function or spectral density function of fluctuations of local fields in a sample. So far various glassy polymers have received much attention because of their unique visco-elastic properties. While the great amount of publications concerning glassy polymers have been devoted to conventional engineering plastics or elastomers with a flexible backbone,^{19,20,21,22,23} few publica-

tions have been available for dynamics of glass transition in needle-like or plate-like polymers with rigid backbone such as π -conjugated polymers.

Among various methods for the preparation of PPP (the Kovacic method²⁸, the Yamamoto method^{29,30,31,32}, the biotechnology-based method^{33,34}, the electrolytic polymerization method³⁵), organometallic dehalogenation polycondensation of 1,4-dihalobenzene, particularly using zero-valent Ni complex³², affords PPP with well-defined linkage between the monomer units (*para*-form; no branches and cross-linked structures), and therefore the Yamamoto-type is suitable for detailed investigation of dynamics of PPP. The x-ray diffraction study of the powder sample indicates that two molecular chains are packed in an orthorhombic unit cell ($a = 0.779$ nm; $b = 0.551$ nm).³⁶ The molecular conformation is not strictly planar; namely, there is a twist between adjacent phenylene-ring planes in a molecular alternate with an angle of approximately 20° .

II. EXPERIMENTS

A. Materials

PPP was prepared by dehalogenation polycondensation of 1,4-dihalobenzene with a zero-valent nickel complex³². From the conventional element analysis, the present PPP contains 2.7 % bromine. From the value of bromine content, we estimated an average molecular weight of 2960 (DP (degree of polymerization) = 38) and 5930 (DP = 76), if one polymer chain has bromine at one terminal unit and at both terminal units, respectively.

B. DSC Measurements

DSC thermograms of PPP were recorded on a Seiko DSC 220 system connected to a SSC5300 workstation. The heating rate is 10 K/min. After the first heating scan, the sample was rapidly quenched by liquid nitrogen and then heated again at the same rate.

C. Solid-state NMR Measurements

We carried out variable temperature ^1H longitudinal relaxation time (T_1) measurements with variable frequency condition. We used the saturation-recovery method for longitudinal relaxation time (T_{1H}) measurements at ^1H resonance frequencies of 25 MHz (0.59 Tesla), 270 MHz (6.34 Tesla), and 400 MHz (9.4 Tesla) and the spin-locking method for longitudinal relaxation time in the rotating frame of a radio frequency field ($T_{1\rho}$) measurements at ^1H resonance frequency of 400 MHz with varying temperature. Varian UnityINOVA400 FT NMR spectrometer (the spectral width of 500 kHz) was used for 9.4 Tesla experiments. JEOL GSX-270 FT NMR

spectrometer (the spectral width of 100 kHz) was used for 0.59 Tesla and 6.34 Tesla experiments. For $T_{1\rho}$ measurements on a wide range of radio-frequency (rf) field, we made a home-built probe with a solenoid type micro-coil with a radius of about 1 mm and a length of about 5 mm. The intensity of rf field was over the range from 16 kHz to 106 kHz.

III. RESULTS AND DISCUSSION

A. DSC Measurements

The thermal property of PPP was examined by DSC (Fig.1). The thermograms indicate that for PPP there is a specific heat jump without latent heat near 295 K. The jump is due to a phase transition of the second kind in the crystalline PPP or due to a glass transition in the amorphous PPP.

The heat capacities of crystalline PPP oligomers (DP = 3, 4, 5, 6) have been measured by calorimetry³⁷. The thermal anomalies with latent heat were detected and attributed to a phase transition, through which an average molecular conformation changes from the planar to the twisted one on cooling. Such a finite torsional angle results from the balance between the stabilizing force of conjugation of the phenyl rings and the repulsion between nearest *ortho*-hydrogens, and this situation induces existence of a double-well potential within the molecule. For molecules with larger degrees of polymerization, a twist phase transition of the order-disorder type will bring about a thermal anomaly with latent heat. It can therefore be said that the twist phase transition will not exist in the crystalline portion of PPP. This is consistent with the fact that the temperature of the thermal anomaly we detected (295K) is much lower than that predicted for the polymer by the adiabatic specific heat measurement ($395\text{K} \pm 10\text{K}$)³⁷.

It is widely accepted that PPP is a thermally and thermooxidatively stable material^{38,39,40}. Hence, it seems to be difficult to regard the thermal anomaly as a conventional glass transition in the amorphous PPP. In order to clarify the thermal anomaly, we performed the nuclear spin relaxation measurements in the following.

B. ^1H Spin-lattice Relaxation Time Measurements

Fig.2a shows a typical profile of the longitudinal magnetization as a function of recovery time. The conventional saturation recovery method was used. We observed the signal recovery as a single exponential of the first order, but the prefactor was less than unity. For relaxation with two components, the recovery of magnetization is expressed by the following biexponential function.

$$\frac{M_0 - M(\tau)}{M_0} = A_{\text{fast}} e^{-\tau/T_1^f} + A_{\text{slow}} e^{-\tau/T_1^s} \quad (1)$$

If one component relaxes too fast to detect by the NMR receiver, the first term of the r.h.s. of Eq.1 is omitted and Eq.1 is reduced to

$$\frac{M_0 - M(\tau)}{M_0} = A_{\text{slow}} e^{-\tau/T_1^s}. \quad (2)$$

Fig.2b shows the variation of the fraction of slower component, A_{slow} , as a function of temperature. For the temperatures from 295K up to 430K, the fraction was decreased as an increase of temperature. For over 430K, we detected the sudden jump of A_{slow} , probably due to the annealing effect of the polymer. In general, mobile unpaired electrons in π -conjugated polymers can affect nuclear spin relaxations while trapped unpaired electrons does not affect the apparent nuclear spin relaxations, because the hyperfine interaction with trapped electron can be too strong to detect the nuclear spin signal by the conventional method. Further, an increase of temperature causes decrease(increase) of concentration of trapped(mobile or untrapped) unpaired electron in π -conjugated polymers, and then causes increase of A_{slow} if the relaxation is occurred by electron. Since the opposite phenomenon was observed in reality, the slower relaxation is not attributed to the relaxation by unpaired electrons, but due to molecular dynamics of sites without unpaired electron. By the variable temperature longitudinal relaxation experiments(*vide infra*, Fig.3), the slower relaxation is found to be due to fluctuations of the local field by molecular dynamics. On the other hand, the non-observed component with a faster relaxation($T_1^f > 10^4$ s) may be attributable to temporal fluctuation of the hyperfine interaction with the mobile unpaired electron.

Fig.2c shows the typical decay profile for the proton longitudinal relaxation measurements by the conventional spin-locking method.⁴¹ First, the decay profile was biexponential, which can be originated from two possibilities; one is spatially heterogeneous distribution of mobile(untrapped) electrons and the other is structural heterogeneity by the crystalline/amorphous duality. Since much faster relaxation rate would be expected for $T_{1\rho}$ than $T_1^f (> 10^4$ s) in a case of relaxation by mobile unpaired electrons, the first possibility can be ruled out. For the results of $T_{1\rho}$, we assigned the faster as the relaxation derived from the amorphous and the slower as from the crystalline portion. This is consistent with the tendency of the crossover from one-dimensional fluctuation in the crystalline portion to the higher dimension; namely, the relaxation rate becomes almost insensitive to the smaller ω .⁴² On the other hand, the amorphous portion preserves the one-dimensionality in the fluctuation of the local field. The recovery with the single exponential found in the T_1 recovery(Fig.2a) is due to the ^1H - ^1H spin diffusion between the crystalline and amorphous portions; in other words, if the spin diffusion were not there the intrinsic relaxation rate for the amorphous portion would be much larger than that for the crystalline portion.

The 400 MHz ^1H longitudinal relaxation rate (T_1^{-1}) as a function of temperature is shown in Fig.3. The in-

crease of T_1^{-1} was observed over the wide temperature range from 250K to 360K, which is due to the critical fluctuation associated with the transition.

The ^1H longitudinal relaxation rate (T_1^{-1}) at 295K as a function of the frequency is shown in Fig.4(a). The relaxation rate shows the dependence of $T_1^{-1} \propto \omega^{-0.5}$. From the fact that the decay profile of the proton longitudinal relaxation shows the single exponential of the first order(Fig.2), we could not straightforwardly attribute the frequency dependence of T_1^{-1} to the distribution of correlation time(τ_c). This relationship between T_1^{-1} and ω is also in disagreement with that predicted from the classical BPP theory⁴³. The BPP theory in which a fluctuation of local field is described as Lorentzian gives the following spectral density function,

$$J(\omega) = \frac{\tau_c}{1 + (\omega\tau_c)^2} \quad (3)$$

$$\sim \frac{1}{\omega^2\tau_c} \quad (\text{if } \omega\tau_c \gg 1). \quad (4)$$

In the region where T_1 depends on frequency ($\omega\tau_c \gg 1$), the relation $T_1^{-1} \propto \omega^{-2}$ should be realized. Therefore an alternative correlation function should be considered in order to explain the dependence obtained by our experiments.

So far there are several reports that show the $\omega^{-1/2}$ dependence of T_1^{-1} . The ideas of theories are roughly classified into two categories. First, with assuming existence of an incommensurate phase, appropriate dynamical susceptibility of the classical damped harmonic oscillator type for phason branch leads to the $\omega^{-1/2}$ dependence of longitudinal relaxation rate^{44,45}. At the same time, the theory also derives positive proportionality of T_1^{-1} to temperature. Then, this theory can be ruled out, because a decrease of T_1^{-1} was observed with an increase of temperature as shown in Fig.3.

The second theory describes the dynamical susceptibility based on a one-dimensional random walk model (details of this model are given by the reference). More generally, the frequency dependence of T_1^{-1} is different for one-, two-, and three-dimensional diffusive motions^{46,47},

$$1\text{D}: T_1^{-1} = A\tau_c^{1/2}\omega^{-1/2} \quad (5)$$

$$2\text{D}: T_1^{-1} = B\tau_c \ln(\omega) \quad (6)$$

$$3\text{D}: T_1^{-1} = C\tau_c - E\tau_c^{3/2}\omega^{1/2}. \quad (7)$$

The proportionality constants A , B , C , and E depend on the particular model of hopping motion on a given network of atomic sites. It is clear from Fig.4 that one-dimensional diffusive motion exists in PPP at our measuring frequencies. The following equation is obtained as a conclusion;

$$T_1^{-1} = M_2 f(\omega) \quad (8)$$

$$f(\omega) = \frac{1}{\sqrt{2}}\tau_c^{1/2}\omega^{-1/2} \quad (\text{if } \omega < \tau_c^{-1}), \quad (9)$$

where $f(\omega)$ is the correlation function, τ_c is the correlation time identical to the inverse of the diffusion rate, and M_2 is the second moment of the interaction that affects the relaxation.

In the case of undoped *trans*-polyacetylene, one-dimensional electron hopping affects ^1H longitudinal relaxation time^{48,49}. It is difficult in the present study to estimate the second moment by taking into account electron spin-spin interaction and hyperfine contribution, because density of free electron is not known. If mobile electrons govern the T_1 measurements, the relaxation rate should become larger with an increase in temperature⁴⁹. As shown in Fig.3, such a dependence was, however, not observed for PPP, leading us to the assumption that the spin relaxation is dominated by not electron spins but fluctuation by molecular motions; here, one-dimensional diffusive(or propagating) motion of backbone twist is the most plausible candidate. Moreover, the ^1H longitudinal relaxation rate (T_1^{-1}) at 303K, 333K, and 363K as a function of the frequency are shown in Fig.4b-d, respectively. The relaxation rates in this temperature range show the dependence of $T_1^{-1} \propto \omega^{-0.5}$. Therefore we can say that in the wide temperature range including 295 K there are the one-dimensional diffusion-like twist motion of phenylene rings along the chain.

C. ^1H Spin-lattice Relaxation Time and Correlation Time

If the diffusive motion keeps one-dimensionality in our measuring temperature range,

$$(T_1^{-1})^2 \propto \tau_c \quad (10)$$

is valid from Eq.8. As Fig.5 shows, the correlation time in the temperature range above 295 K follows the Vogel-Fulcher-Tamman equation⁵⁰

$$(T_1^{-1})^2 \propto \tau_c = \tau_0 \exp\left(\frac{B}{T - T_0}\right) \quad (11)$$

where B is constant and the Vogel-Fulcher-Tamman temperature (T_0) is found to be 255.4 K. The temperature T_0 is usually determined by analyzing the temperature dependence of the correlation time τ_c of the so-called α process using the Vogel-Fulcher-Tamman equation. The Vogel-Fulcher-Tamman temperature T_0 is observed at roughly 50 K below T_g for most amorphous polymers⁵¹. Therefore, taking into account of three factors: (i) the specific heat jump without latent heat near 295 K, (ii) the one-dimensional diffusion-like twist motion in the wide temperature range including 295 K, and (iii) the correlation time following the Vogel-Fulcher-Tamman equation in the temperature range above 295 K, we can explain that within the amorphous PPP the twist motions between adjacent phenyl rings are frozen at below 295 K without thermodynamic stability.

There is an interesting prediction to check our explanation. For hard ellipsoids of revolution M.Letz *et al.*

have calculated the phase diagram for the idealized glass transition⁵². They obtained three types of glass transition line. The first glass transition is the conventional one for spherical particles driven by the cage effect. At the second transition, which occurs for rather nonspherical particles, a glass phase is formed that consists of domains. Within each domain there is a nematic order where the center of mass motion is quasi-ergodic, whereas the interdomain orientations build an orientational glass. The third transition line occurs for nearly spherical ellipsoids where the orientational degrees of freedom with odd parity, e.g., 180° flips, freeze independently from the positions. Again, it is widely accepted that PPP is a thermally stable material^{38,39,40}. In our experiments, a conventional glass transition dominated by the cage effect was unable to exist because of high thermal stability of PPP, whereas a glass transition caused by frozen order parameter relating to the twist motions between adjacent phenyl rings can occur far below the conventional glass transition temperature.

One thing we must stress is the fact that whereas the temperature dependence of T_1^{-1} shows the typical Vogel-Fulcher-Tamman behavior, the decay profile of longitudinal relaxation measurements (Fig.2) did not show any evidences to the existence of heterogeneity of the glassy structure, namely, distribution in correlation time. In most glassy solids, distribution in the correlation time was realized and accounted by modifying the correlation function with the extended exponential function(Kohlrausch-Williams-Watts function)⁵³ or by using modifying the spectral density function with Cole-Cole,⁵⁴ Cole-Davidson,⁵⁵ Havriliak-Negami types,⁵⁶ and so on. From Fig.3, the critical slowing down was observed at temperature over the range from T_g to $T_g + 20$. This indicates that the structural relaxation rate($\tau(0)^{-1} \sim \tau_c^{-1}$) is smaller than the resonance frequency(400MHz); indeed, more precise estimation of $\tau(0)^{-1}$ is presented in Fig.6. The existence of the slower structural relaxation rate than the resonance frequency we used in this paper, must induce a singularity at the angular frequency of $\omega = \tau(0)^{-1}$ in the spectral density function, which should lead to the change in the power law. We did not observe such a change over the entire temperature range we made measurements; instead, the $\omega^{-1/2}$ dependence was almost preserved. We describe the alternative explanation for the preservation of the power law in the following.

Assuming the one-dimensional fluctuation instead of the isotropic one (Debye model) and distribution of the correlation time, the spectral density function with a discrete correlation time distribution becomes to be the following form:

$$f(\omega) = \frac{1}{\sqrt{2}}(p_0\tau_{0c}^{1/2} + p_1\tau_{1c}^{1/2} + \dots)\omega^{-1/2} \quad (12)$$

$$= \frac{1}{\sqrt{2}}\left\{\sum_i p_i\tau_{ic}^{1/2}\right\}\omega^{-1/2}, \quad (13)$$

where p_i is a probability of which structural relaxation

time is τ_{ic} . If the correlation time distribution is continuous,

$$f(\omega) = \frac{\omega^{-1/2}}{\sqrt{2}} \int_0^\infty p(\tau) \tau^{1/2} d\tau, \quad (14)$$

where $p(\tau)$ is a continuous version of p_i . From Eq.14, the $\omega^{-1/2}$ law is preserved irrespective of the structural heterogeneity and the ^1H - ^1H spin diffusion, by virtue of separation of variables, ω and τ . This situation is realistic when the one-dimensional modulation waves of backbone twist in PPP has a dispersion.

D. ^1H Spin-lattice Relaxation Time and Critical Behavior

Although the validity of the concept of dynamic scaling in glassy solids is a controversial problem in modern physics, it would be meaningful to investigate the critical dynamics of glass transition by using knowledges obtained by studies of the second order phase transition.

In this section, we analyze the results of the longitudinal relaxation time by a theory originally developed for incommensurately modulated solids.¹⁶ Here, we restrict ourselves only to make brief introduction of the theory.

By assuming a direct relaxation process of the nuclear spin system for the case in which the relaxation mechanism is due to the order parameter fluctuations and by considering the classical fluctuation-dissipation theorem, one can derive the critical contribution from the following:

$$\frac{1}{T_{1cr}} \propto W_1 \propto T \sum_k \frac{\chi''(\mathbf{k}, \omega)}{\omega}, \quad (15)$$

where $\mathbf{k} = \mathbf{q} - \mathbf{q}_p$ is the reduced wave vector and \mathbf{q}_p is the wave vector of the periodicity of the polymer chain. Here assuming that the amorphous portion of the polymer has the plate-like, linear conformation because of the relatively small molecular weight (DP=38-76), it can be thought that there exists the structural periodicity along the chain. This assumption seems to be adequate because the one-dimensional fluctuation is observed by the frequency dependent longitudinal relaxation measurements. If we think a model system of interacting pseudospins in which the interaction of the spins with the lattice vibrations induces backbone twist of the phenylene ring of PPP, the dynamical susceptibility can be written in the following:^{57,58}

$$\chi(\mathbf{k}, \omega) = \frac{\chi(\mathbf{k}, 0)}{1 + i\omega\tau(\mathbf{k})}, \quad (16)$$

where $\chi(\mathbf{k}, 0)$ is the static order parameter susceptibility. $\chi(\mathbf{k}, 0)$ depends on the wave vector according to a generalized Ornstein-Zernike representation¹⁶

$$\chi(\mathbf{k}, 0) = \frac{\chi(0, 0)}{1 + (\mathbf{k}\xi)^{2-\eta}}, \quad (17)$$

where ξ is the correlation length. In the critical region, it depends on the temperature with a critical exponent ν ($\xi \propto |T - T_g|^{-\nu}$). η is a critical exponent defining a small correction from the Ornstein-Zernike behavior at the glass transition. Supposing the validity of the van Hove theory for critical dynamics, we can obtain the following formula for the fast motion regime ($\Omega = \omega\tau(0) \gg 1$):

$$\frac{1}{T_{1cr}} \propto T^2 e^{E_a/k_B T} \frac{\chi^2(0, 0)}{\xi^3}. \quad (18)$$

Since it may be assumed the critical behavior of the quantities ξ and $\chi(0, 0)$ to diverge as $(T - T_g)^{-\nu}$ and as $(T - T_g)^{-\gamma}$ near T_g , respectively, the temperature dependence of the critical behavior is reflected by the critical exponent $\zeta = 2\gamma - 3\nu$. Therefore, the final formula can be obtained in the following:

$$\frac{1}{T_{1cr}} \propto T^2 e^{E_a/k_B T} (T - T_g)^{-\zeta}. \quad (19)$$

where E_a is an activation energy for Arrhenius-type thermally activated process without interaction and the other symbols are the usual meaning. For the slow-motion regime ($\Omega \ll 1$), the $1/T_{1cr}$ will become temperature independent.

The temperature dependence of 400MHz ^1H T_1 is shown in Fig.3 over a broad temperature interval including T_g . Since the ^1H longitudinal relaxation is mainly dominated by nuclear magnetic dipole interaction, we supposed non critical background relaxation mechanism by a two-phonon Raman process as a negligible effect.⁵⁹ Therefore, the critical relaxation rate $1/T_{1cr}$ can be evaluate from the T_1 data ($1/T_1 \approx 1/T_{1cr}$) for a wide range of temperature above T_g .

The prefactor $T^2 \exp(E_a/k_B T)$ in Equation (19) depends noncritically on the temperature. In the case of PPP, E_a corresponds to the activation energy to promote the molecule from a nonplanar to a planar state. S.Guha *et al.* obtain an activation energy $E_a = 0.04$ eV for *para* hexaphenyl via Raman scattering⁶⁰. They also calculated E_a from the difference in internal energy between the planar and nonplanar configurations of a biphenyl molecule⁶⁰. The Hartree-Fock method yields $E_a = 0.145$ eV compared to the density functional method which yields $E_a = 0.089$ eV. From the energy calculation of a PPP chain in the reference⁶¹ it is observed that $E_a = 0.065$ eV. The calculated values for the activation energy are higher for two reasons: biphenyl is shorter than hexaphenyl and calculations for both biphenyl and PPP chain are done for isolated molecules, where we expect the planarizing forces to be weaker than for hexaphenyl which is an ensemble of long molecules in a surrounding environment. Therefore in the sample of PPP (DP = 38 ~ 76) we used the activation energy E_a is likely to become smaller than 0.04 eV. Thus, the critical temperature dependence of T_{1cr} can be represented by a critical exponent ζ according to

$$\frac{1}{T_{1cr}} \approx \frac{1}{T_1} \propto T^2 (T - T_g)^{-\zeta}. \quad (20)$$

Here, we omit the prefactor $\exp(E_a/k_B T)$ which has a negligible effect on the fit value ζ in a temperature interval above T_g .

Figure 6 shows the critical temperature dependence of T_{1cr} ($\approx T_1$). At temperatures from T_g to T_g+10 the slow-motion limit behavior is observed, where $T_1 T^2$ is temperature independent. Over T_g+20 one reaches the fast-motion limit, where $T_1 T^2$ become to show a power law with a critical exponent $\zeta = 0.66$. For $T > T_g+60$ the value of $T_1 T^2$ show a steeper increase with an increase of temperature. This effect is similar to that observed by Decker *et al.*¹⁶ and may be due to the decrease of the correlation length with an increase of temperature.

This value for the experimental critical exponent $\zeta = 0.66$ can be compared with the theoretical exponent $\zeta = 0.663$ for the three-dimensional XY model derived from an elaborated field-theoretical model that goes beyond the mean-field approach⁶².

The critical exponents $\zeta = 2\gamma - 3\nu$ derived for the 3D Ising, XY, and Heisenberg models are 0.5904 ± 0.0042 , 0.6241 ± 0.0054 , and 0.6570 ± 0.0057 , respectively⁶³. However, the critical exponent $\zeta = 0.66$ derived above from our experiments differs from the prediction of the 3D XY model. Thus, the applicability of both other models cannot be strictly ruled out.

The relaxation time $\tau(0)$ of the order parameter can be derived by following equation¹⁶

$$\left(\frac{T_1}{T_1^{fml}}\right)^2 = \frac{1}{2}(\sqrt{\Omega^2 + 1} + 1). \quad (21)$$

For $T_1 T^2$ we employed the experimental data in Fig.6 while $T_1^{fml} T^2$ is calculated by using the line A. In Fig.6 also the order parameter relaxation frequency $(2\pi\tau(0))^{-1}$ calculated by using Eq.21 is plotted versus $(T - T_g)$ on a double logarithmic scale. The straight line B is a fit of the data to a power law yielding a critical exponent of $z\nu = 1.32$, which fits very well to the static susceptibility exponent $\gamma = 1.3160 \pm 0.0012$ predicted for the 3D XY model⁶³. Comparison with the corresponding theoretical γ values for the 3D Ising and Heisenberg models, 1.2402

and 1.3866, respectively. From the above analysis, the 3D-XY model is a plausible universality class for the critical dynamics of twist-glass transition in PPP.

IV. CONCLUSION

Dynamics of Yamamoto-type poly(p-phenylene)[PPP] was investigated by differential scanning calorimetry(DSC) and proton solid-state NMR relaxation spectroscopy. The DSC chart shows the baseline jump without latent heat at 295K, which is due to the twist glass transition of the polymer. From the variable temperature proton longitudinal relaxation time(T_1) measurements, we observed relatively short T_1 over the wide range from 250K (closed to Vogel-Fulcher-Tamman temperature) to 360K, inferred the existence of cooperative critical slowing down associated with the glass transition. The frequency dependence of proton longitudinal relaxation time at 295-363K shows $R_1 \sim \omega^{-0.5}$ dependence, which is due to the one-dimensional diffusion-like motion of the backbone conformational modulation. The dependence indicates that closed to T_g from the higher temperature the cooperative rearrangement region(CRR) grows in the one-dimensional manner. From the pseudospin argument, the 3D-XY model is a plausible universality class for the critical dynamics of twist-glass transition in PPP. This research is an example that have obtained the information about the universality class of twist-glass transition found in π -conjugated polymers.

Acknowledgments

This work is supported by Ministry of Education, Culture, Sports, Science and Technology(Japan) through a Grant-in-Aid for science research (No.16685012). The authors are grateful to Professor Tetsuo Asakura and Dr.Kazuo Yamauchi (Tokyo University of Agriculture and Technology) for fruitful discussions.

* Corresponding Author; Electronic address: nasakawa@bio.titech.ac.jp

¹ E.R.Andrew, Phys.Lett., **34A**, 30(1971).

² L. W. Shacklette, R. R. Chance, D. M. Ivory, G. G. Miller, and R. H. Baughman, Synth. Met., **1**, 307 (1979).

³ L. W. Shacklette, R. L. Elsenbaumer, R. R. Chance, J. M. Sowa, D. M. Ivory, C. G. Miller, and R. H. Baughman, J. Chem. Soc., Chem. Commun., 361 (1982).

⁴ M. Satoh, M. Tabata, K. Kaneto, and K. Yoshino, Jpn. J. Appl. Phys., **25**, L73 (1986).

⁵ T. Shiga, A. Okada, T. Kurauchi, Macromolecules, **26**, 6958 (1993).

⁶ J. Płocharski, H. Drabik, H. Wyciślik, and T. Ciach, Synth. Met., **88**, 139 (1997).

⁷ J. Płocharski, M. Rózański, and H. Wyciślik, Synth. Met., **102**, 1354 (1999).

⁸ I. S. Sim, J. W. Kim, H. J. Choi, C. A. Kim, and M. S. Jhon, Chem. Mater., **13**, 1243 (2001).

⁹ J. -I. Sohn, J. H. Sung, H. J. Choi, and M. S. Jhon, J. Mater. Sci., **37**, 4057 (2002).

¹⁰ J. -I. Sohn, J. H. Sung, H. J. Choi, and M. S. Jhon, J. Appl. Polym. Sci., **84**, 2397 (2002).

¹¹ G. Grem, G. Leditzky, B. Ullrich, and G. Leising, Adv. Mater., **4**, 36 (1992).

¹² G. Grem, G. Leditzky, B. Ullrich, and G. Leising, Synth. Met., **51**, 383 (1992).

¹³ S. -B. Liu and M. S. Conradi, Phys. Rev. Lett., **54**, 1287 (1985).

- ¹⁴ L.von Laue, F.Ermark, A.Gözläuser, U.Haeberlen, and U.Häcker, *J.Phys.:Condens.Matter*, **8**, 3977(1996).
- ¹⁵ R. E. de Souza, M. Engelsberg, and D. J. Pusiol, *Phys. Rev. Lett.*, **66**, 1505 (1991).
- ¹⁶ F. Decker, J. Petersson, M. Irsch, and D. Michel, *Phys. Rev. B*, **65**, 014110 (2002).
- ¹⁷ M.Winokur, Y.B.Moon, A.J.Heeger, J.Barker, D.C.Bott, and H.Shirakawa, *Phys.Rev.Lett.*, **58**, 2329(1987).
- ¹⁸ S.Mori, Y.Inoue, T.Yamamoto, and N.Asakawa, *Phys.Rev.B*, **71**, 054205(2005).
- ¹⁹ D.Richter, B.Frick, and B.Farago, *Phys.Rev.Lett.*, **61**, 2465(1988).
- ²⁰ T.Kanaya, T.Kawaguchi, and K.Kaji, *J.Chem.Phys.*, **98**, 8262(1993); T.Kanaya, T.Kawaguchi, and K.Kaji, *J.Chem.Phys.*, **104**, 3841(1996); T.Kanaya, T.Tsukushi, and K.Kaji, *Prog.Theor.Phys.Supp*, **126**, 133(1997); T.Kanaya, I.Tsukushi, and K.Kaji, *J.Bartos*, and J.Kristiak, *J.Phys.IV*, **10**, Pr7-317(2000).
- ²¹ A.P.Sokolov, E.Rossler, A.Kisliuk, and D.Quitmann, *Phys.Rev.Lett.*, **71**, 2062(1993).
- ²² E.Rossler, U.Warschewske, P.Eiermann, A.P.Sokolov, and D.Quitmann, *J.Non-Cryst.Solids*, **172-174**, 113(1994).
- ²³ A.Doβ, G.Hinze, G.Diezemann, R.Bohmer, and H.Sillescu, *Acta Polymr.* **49**, 56(1998).
- ²⁴ D. P. Murray, J. J. Dechter, L. D. Kispert, *J. Polym. Sci., Polym. Lett. Ed.*, **22**, 519 (1984).
- ²⁵ C. E. Brown, M. B. Jones, P. J. Kovacic, *J. Polym. Sci., Polym. Lett. Ed.*, **18**, 653 (1980).
- ²⁶ J. B. Miller and C. Dybowski, *Solid State Commun.*, **46**, 487 (1983).
- ²⁷ J. J. Dumais, L. W. Jelinski, M. E. Galvin, C. Debowksi, C. E. Brown, and P. Kovacic, *Macromolecules*, **22**, 612 (1989).
- ²⁸ P. Kovacic, and J. Oziomek, *J. Am. Chem. Soc.*, **85**, 454 (1963).
- ²⁹ T. Yamamoto, and A. Yamamoto, *Chem. Lett.*, 353 (1977).
- ³⁰ T. Yamamoto, Y. Hayashi, and A. Yamamoto, *Bull. Chem. Soc. Jpn.*, **51**, 2091 (1978).
- ³¹ T. Yamamoto, A. Morita, T. Maruyama, Z. -H. Zhou, T. Kanbara, and K. Snehika, *Polym. J.*, **22**, 187 (1990).
- ³² T. Yamamoto, A. Morita, Y. Miyazaki, T. Maruyama, H. Wakayama, Z. Zhou, Y. Nakamura, T. Kanbara, S. Sasaki, and K. Kubota, *Macromolecules*, **25**, 1214 (1992).
- ³³ D. G. H. Ballard, A. Courtis, I. M. Shirley, and S. C. Taylor, *J. Chem. Soc., Chem. Commun.*, 954 (1983).
- ³⁴ D. G. H. Ballard, A. Courtis, I. M. Shirley, and S. C. Taylor, *Macromolecules*, **21**, 294 (1988).
- ³⁵ M. Satoh, K. Kaneto, and K. Yoshino, *J. Chem. Soc., Chem. Commun.*, 1629 (1985).
- ³⁶ S. Sasaki, T. Yamamoto, T. Kanbara, A. Morita, and T. Yamamoto, *J. Polym. Sci., Polym. Phys. Ed.*, **30**, 293 (1992).
- ³⁷ K. Saito, Y. Yamamura, and M. Sorai, *Bull. Chem. Soc. Jpn.*, **73**, 2713 (2000).
- ³⁸ P. Kovacic and M. B. Jones, *Chem. Rev.*, **87**, 357 (1987).
- ³⁹ K. Yoshino, H. Ueno, F. Uesugi, and M. Satoh, *J. Appl. Phys.*, **61**, 1493 (1987).
- ⁴⁰ D. G. H. Ballard, A. Courtis, I. M. Shirley, and S. C. Taylor, *Macromolecules*, **21**, 294 (1988).
- ⁴¹ D.C.Ailion, in *Advances in Magnetic Resonance*, edited by J.S.Waugh(Academic Press, New York, 1971), Vol.5, 177.
- ⁴² M.A.Butler, L.R.Walker, and Z.G.Soos, *J.Chem.Phys.*, **64**, 3592, (1976).
- ⁴³ N. Bloembergen, E. M. Purcell, and R. V. Pound, *Phys. Rev.*, **73**, 679 (1948).
- ⁴⁴ S. Žumer and R. Blinc, *J. Phys. C*, **14**, 465 (1981).
- ⁴⁵ R. Zeyher and W. Finger, *Phys. Rev. Lett.*, **49**, 1833 (1982).
- ⁴⁶ A. F. McDowell, C. F. Mendelsohn, M. S. Conradi, R. C. Bowman, Jr., and A. J. Maeland, *Phys. Rev. B*, **51**, 6336 (1995).
- ⁴⁷ F. Kimmeler, G. Majer, U. Kaess, A. J. Maeland, M. S. Conradi, and A. F. McDowell, *J. Alloys Comp.*, **264**, 63 (1998).
- ⁴⁸ M. Nechtschein, F. Devreux, R.L.Greene, T.C.Clark, and G.B.Street, *Phys. Rev. Lett.*, **44**, 356 (1980).
- ⁴⁹ M. Nechtschein, F. Devreux, F. Genoud, M. Guglielmi, and K. Holczer, *Phys. Rev. B*, **27**, 61 (1983).
- ⁵⁰ H.Vogel, *Phys.Z.* **22**, 645(1921); G.S.Fulcher, *J.Am.Chem.Soc.*, **77**, 3701(1925). G.Tamman and W.Hesse, *Z.Anorg.Allg.Chem.*, **156**, 245(1926).
- ⁵¹ J. Ferry, *Viscoelastic Properties of Polymers*, 3rd ed. (Wiley, New York, 1980).
- ⁵² M. Letz, R. Schilling, and A. Latz, *Phys. Rev. E*, **62**, 5173 (2000).
- ⁵³ F.Kohlrausch, *Progg.Ann.Phys.*, **119**, 352(1863); G.Williams and D.C.Watts, *Trans. Faraday Soc.*, **66**, 80(1970).
- ⁵⁴ K.S.Cole and R.H.Cole, *J.Chem.Phys.*, **9**, 341(1941).
- ⁵⁵ D.W.Davidson and R.H.Cole, *J.Chem.Phys.*, **19**, 1484(1951).
- ⁵⁶ S.Havriliak and S.Negami, *Polymer*, **8**, 161(1967).
- ⁵⁷ G. Bonera, F. Borsa, and A. Rigamonti, *Phys. Rev. B*, **2**, 2784 (1970).
- ⁵⁸ M. Suzuki and R. Kubo, *J. Phys. Soc. Jpn.*, **24**, 51 (1968).
- ⁵⁹ A.Abragam, *Principles of Nuclear Magnetism*(Clarendon Press, Oxford, 1961).
- ⁶⁰ S. Guha, W. Graupner, R. Resel, M. Chandrasekhar, H. R. Chandrasekhar, R. Glaser, and G. Leising, *Phys. Rev. Lett.*, **82**, 3625 (1999).
- ⁶¹ C. Ambrosch-Draxl, J. A. Majewski, P. Vogl, and G. Leising, *Phys. Rev. B*, **51**, 9668 (1995).
- ⁶² B. A. Kaufmann, F. Schwabl, and U. C. Täuber, *Phys. Rev. B*, **59**, 11226 (1999).
- ⁶³ W. Gebhardt and U. Krey, *Phasenübergänge und kritische Phänomene* (Vieweg & Sohn Verlagsgesellschaft, Braunschweig, 1980).

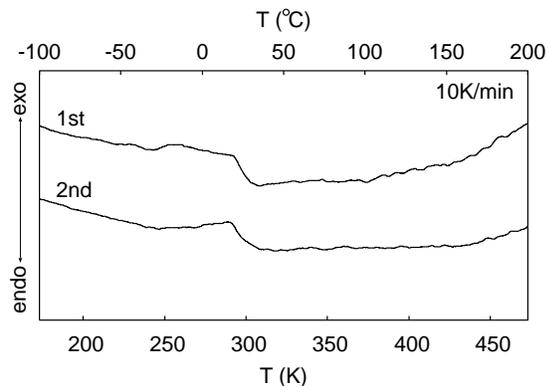


FIG. 1: DSC charts for a powder sample of PPP. The heating rate was 10 K/min. After the first heating scan, the samples were quenched by liquid nitrogen.

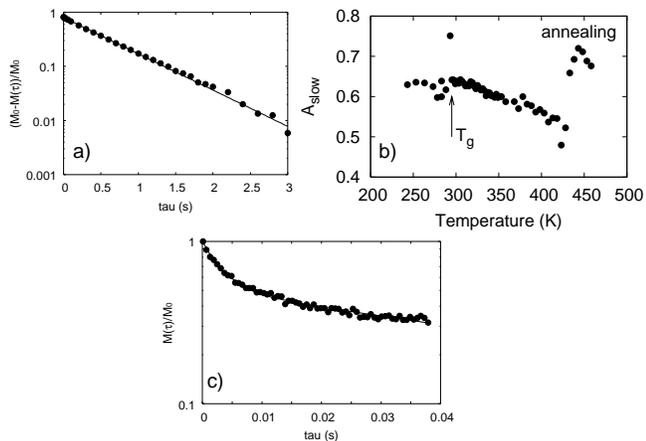


FIG. 2: A typical saturation recovery profile for PPP obtained by 400 MHz ^1H longitudinal relaxation time measurements at 295K(a) and the temperature dependence of the fraction of the longer relaxation time(b). The shorter fraction was not able to be detected because of slower analog-digital conversion rate than the relaxation rate. A typical decay profile for PPP obtained by 400 MHz ^1H longitudinal relaxation time measurements in the rotating frame at 295K(c)

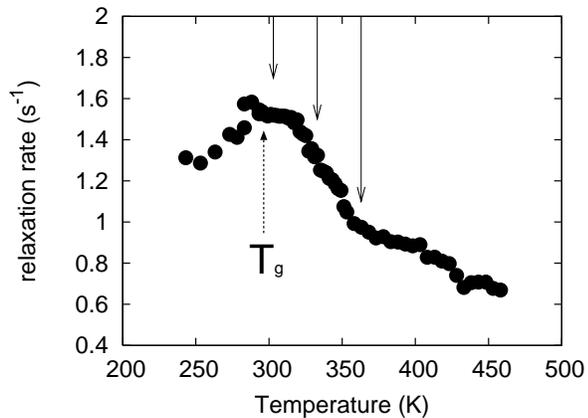


FIG. 3: The temperature dependence of 400 MHz ^1H longitudinal relaxation rate. Dotted arrow indicates 295 K. Solid arrows indicate 303K, 333K, and 363K.

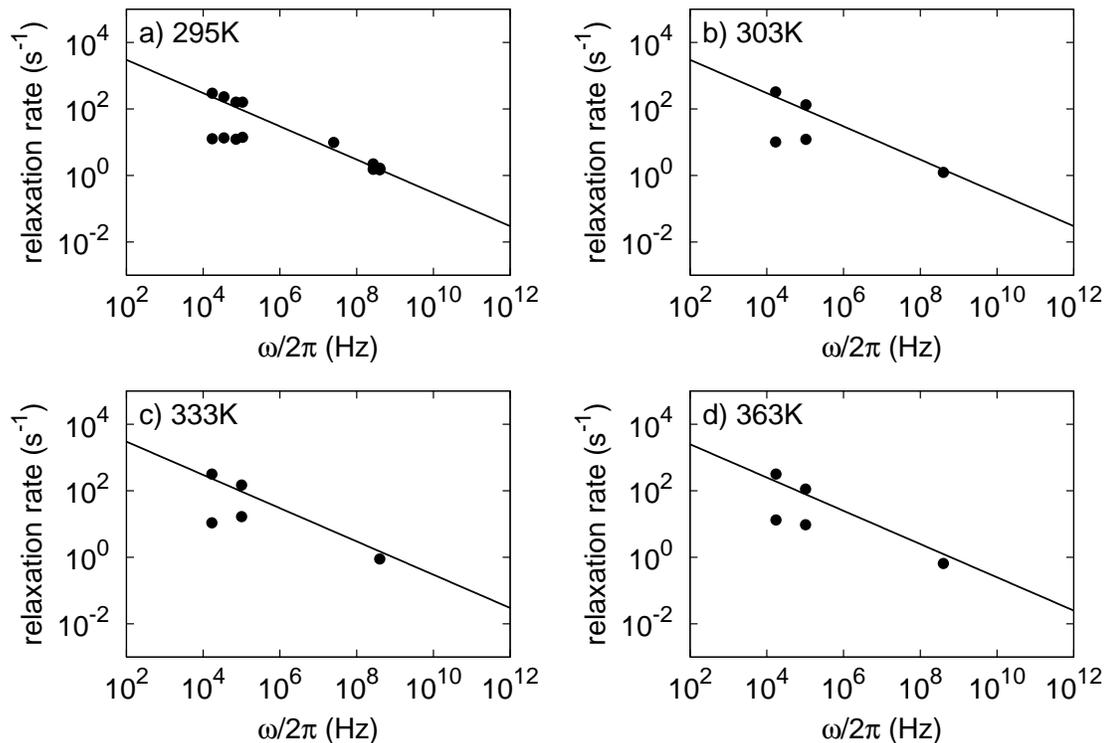


FIG. 4: The frequency dependence of ^1H longitudinal relaxation rate at 295K (a), 303K (b), 333K (c), and 363K (d). The solid lines of the $\omega^{-1/2}$ dependence is shown as a guide for eyes.

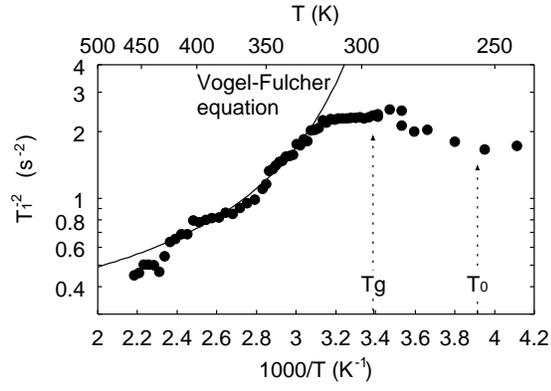


FIG. 5: The plot of 400 MHz ^1H longitudinal relaxation rate $(T_1^{-1})^2$ as a function of $1000/T$. When one-dimensional diffusion is responsible for the behavior of T_1^{-1} , $(T_1^{-1})^2$ is proportional to τ_c .

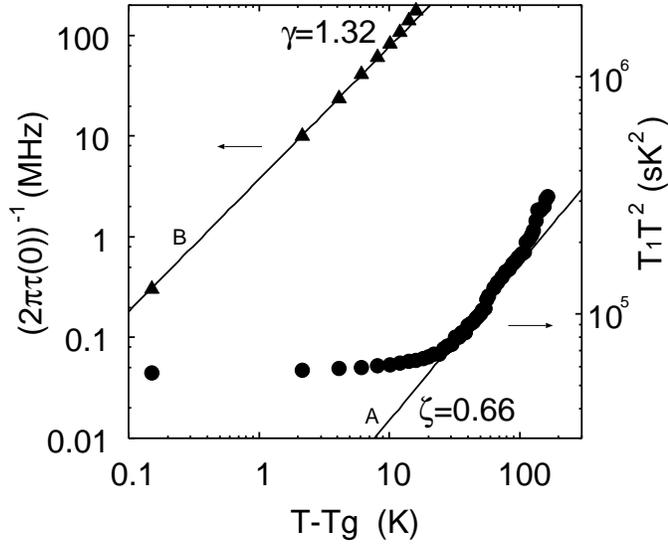


FIG. 6: The plot of T_1T^2 as a function of $T - T_g$ (right scale). Moreover, the plot of the order-parameter relaxation frequency $(2\pi\tau(0))^{-1}$ as a function of $T - T_g$ (left scale).