

Physical Meaning of the Current Vertex Corrections: DC and AC Transport Phenomena in High- T_c Superconductors

Hiroshi Kontani

Department of Physics, Nagoya University, Nagoya, 464-8602, Japan

Abstract. Famous non-Fermi liquid-like behaviors of the transport phenomena in high- T_c cuprates (R_H , $\Delta\rho/\rho$, S , v , etc) are caused by the current vertex corrections in nearly antiferromagnetic (AF) Fermi liquid, which was called the backflow by Landau. We present a simple explanation why the backflow is prominent in strongly correlated systems. In nearly AF Fermi liquid, R_H is enhanced by the backflow because it changes the effective curvature of the Fermi surfaces. Therefore, the relaxation time approximation is not applicable to a system nearby a magnetic quantum critical point (QCP).

Keywords: transport phenomena, high- T_c superconductors, current vertex correction, backflow

PACS: 72.10.-d, 78.20.Bh, 71.10.Ay

In the present article, we explain that the backflow always plays important roles in Fermi liquids. In a Fermi liquid, excited quasiparticles (QP) interact with each other. Landau showed that the QP energy at \mathbf{p} in the presence of QP excitations is expressed as [1]

$$\tilde{\epsilon}_{\mathbf{p}} = \epsilon_{\mathbf{p}} + \sum_{\mathbf{k}} f_{\mathbf{p},\mathbf{k}} \delta n_{\mathbf{k}}, \quad (1)$$

where $\epsilon_{\mathbf{p}} = \mathbf{p}^2/2m^*$ and $\delta n_{\mathbf{k}}$ represents the deviation of the QP distribution function from the ground state. $f_{\mathbf{p},\mathbf{k}}$ is the QP interaction (i.e., Landau interaction function) which arises from the electron-electron correlations. Hereafter, we consider the paramagnetic state.

First, we discuss an isotropic Fermi liquid. Here, we consider to add a QP just above the Fermi surface (FS) at \mathbf{k} as shown in Fig.1, whose lifetime τ is infinitesimally long. Then, the QP energy at \mathbf{p} shifts by $f_{\mathbf{p},\mathbf{k}}$, which induces the change of QP velocity [1]. Its summation over the FS is given by $\sum_{|\mathbf{p}| < k_F} \nabla_{\mathbf{p}} f_{\mathbf{p},\mathbf{k}} = N \oint_{\text{FS}} d p_{\parallel} f_{\mathbf{k},\mathbf{p}} \mathbf{v}_{\mathbf{p}}$, which is called the backflow by Landau. In a spherical system, the QP velocity at \mathbf{k} and the backflow are given by $\mathbf{v}_{\mathbf{k}} = \mathbf{k}/m^*$ and $\frac{1}{3}F_1 \mathbf{k}/m^*$ (F_1 being a Landau parameter), respectively. Because $1 + \frac{1}{3}F_1 = m^*/m$ due to Galilei invariance, the total current $\mathbf{J}_{\mathbf{k}}$ is \mathbf{k}/m [1]. Thus, the backflow dominates the QP velocity in a strongly correlated Fermi liquid where $m^* \gg m$.

The backflow plays an important role in DC transport phenomena. To show this fact, we study the current vertex correction in the hydrodynamic limit ($\omega\tau \ll 1$) based on the microscopic Fermi liquid theory. The resistivity of interacting electrons without umklapp scatterings should be completely zero, as consequence of the momentum conservation law. However, the relaxation time approximation (RTA) gives a finite resistivity because $\rho^{\text{RTA}} \propto \tau > 0$. Yamada and Yosida solved this discrepancy by taking the backflow (i.e., the current vertex

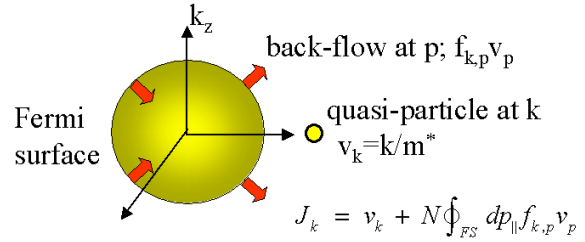


FIGURE 1. Backflow is the induced QP velocity over the FS due to other QP excitations, which is one of the most essential properties of Fermi liquids.

correction) into account; they succeeded in reproducing $\rho = 0$ in the absence of the umklapp scatterings, even when τ is finite [2].

In 1999, we found that the backflow in nearly antiferromagnetic (AF) metals plays highly nontrivial roles; the total current $\mathbf{J}_{\mathbf{k}}$ is no more parallel to the QP velocity $\mathbf{v}_{\mathbf{k}}$ due to the backflow [2, 3]. The Bethe-Salpeter equation in the microscopic Fermi liquid theory is given by

$$\vec{J}_{\mathbf{k}} = \vec{v}_{\mathbf{k}} + \oint_{\text{FS}} d k_{\parallel} \Gamma(\mathbf{k}, \mathbf{p}) \vec{J}_{\mathbf{p}}, \quad (2)$$

where $\Gamma(\mathbf{k}, \mathbf{p})$ corresponds to the Landau interaction function in the hydrodynamic limit, and k_{\parallel} is the momentum along the FS. In the FLEX approximation, $\Gamma(\mathbf{k}, \mathbf{p}) = \int d\epsilon [\text{cth}(\epsilon/2T) - \text{th}(\epsilon/2T)] \text{Im} V_{\mathbf{k}-\mathbf{p}}^{\text{FLEX}}(\epsilon) \tau_{\mathbf{p}}$ and $V_{\mathbf{k}}^{\text{FLEX}}(\epsilon) \propto \chi_{\mathbf{k}}^s(\epsilon) \propto \xi^2 (1 + \xi^2 (\mathbf{k} - \mathbf{Q})^2 - i\epsilon/\omega_{\text{sf}})^{-1}$, where $\chi_{\mathbf{k}}^s$ is the spin susceptibility; ξ is the AF correlation length and $\mathbf{Q} = (\pm\pi, \pm\pi)$. In the SCR or FLEX approximation, $\xi^2 \propto T^{-1}$ and $\xi \gg 1$ at lower temperatures. Then, $\Gamma(\mathbf{k}, \mathbf{p})$ takes a large value only when $|\mathbf{k} - \mathbf{p} - \mathbf{Q}| \lesssim \xi^{-2}$. As shown in Fig.2, a QP excitation at \mathbf{k} causes the backflow through the QP interaction

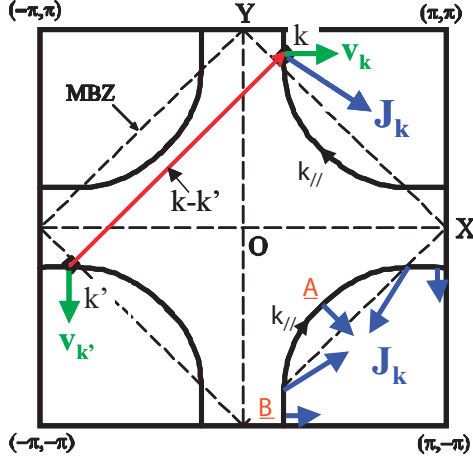


FIGURE 2. Schematic picture of $\mathbf{J}_{\mathbf{k}}$ in high- T_c cuprates. Because the excited QP at \mathbf{k} reduces the QP energy $\epsilon_{\mathbf{k}'}$ only for $\mathbf{k}' \approx \mathbf{k} + \mathbf{Q}$, the induced backflow is proportional to $\mathbf{v}_{\mathbf{k}+\mathbf{Q}}$.

Γ in eq. (2), only on the small portion of the FS around $\mathbf{k}' \approx \mathbf{k} + \mathbf{Q}$. Then, the total current becomes $\mathbf{J}_{\mathbf{k}} \propto \mathbf{v}_{\mathbf{k}} + \mathbf{v}_{\mathbf{k}'}$, so $\mathbf{J}_{\mathbf{k}}$ is not perpendicular to the FS except the points A and B, which are on the symmetric axes. In summary, the highly anisotropic Landau interaction function $\Gamma(\mathbf{k}, \mathbf{k}')$ due to the AF fluctuations causes the nontrivial \mathbf{k} -dependence of $\mathbf{J}_{\mathbf{k}}$.

We show that the nontrivial behavior of $\mathbf{J}_{\mathbf{k}}$ shown in Fig. 2 leads to the enhancement of R_H . The expression for the Hall conductivity is given by [2]

$$\sigma_{xy}^{\text{RTA}}/B_z = |e|^3 \oint_{\text{FS}} dk_{\parallel} |\vec{v}_{\mathbf{k}} \tau_{\mathbf{k}}|^2 C_{\mathbf{k}}^v, \quad (3)$$

$$\sigma_{xy}/B_z = |e|^3 \oint_{\text{FS}} dk_{\parallel} |\vec{J}_{\mathbf{k}} \tau_{\mathbf{k}}|^2 C_{\mathbf{k}}^J, \quad (4)$$

where k_{\parallel} is the momentum parallel to the FS, $C_{\mathbf{k}}^v = -\partial \theta_{\mathbf{k}}^v / \partial k_{\parallel}$, $C_{\mathbf{k}}^J = -\partial \theta_{\mathbf{k}}^J / \partial k_{\parallel}$, $\theta_{\mathbf{k}}^v = \tan^{-1}(v_{k_x}/v_{k_y})$, $\theta_{\mathbf{k}}^J = \tan^{-1}(J_{k_x}/J_{k_y})$, and $\tau_{\mathbf{k}} = 1/2\text{Im}\Sigma_{\mathbf{k}}(-i\delta)$ is the lifetime of QP. Because $C_{\mathbf{k}}^v$ represents the FS curvature (FSC) at \mathbf{k} , we recognize the well-known result of the RTA; σ_{xy} is determined by the FSC. However, this statement does not hold in nearly AF systems any more, because the "effective FSC" in eq.(4), $C_{\mathbf{k}}^J$, strongly deviates from the true FSC. In Fig. 2, $C_{\mathbf{k}}^J > 0$ around A whereas it is negative around B. In contrast, $C_{\mathbf{k}}^v > 0$ everywhere. Moreover, the "cold spot" where $\tau_{\mathbf{k}}$ takes the maximum value on the FS is around A (B) in the hole-doped (electron-doped) systems. As a result, σ_{xy} is positive (negative) in hole-doped (electron-doped) systems, as recognized in eq.(4). In fact, R_H in electron-doped systems is negative although its FSC observed by ARPES is positive. This fact cannot be explained by the idea, "deformation of the FS due to SDW transition", because $R_H < 0$ even above T_N . In Ref. [3], we solved this discrepancy by tak-

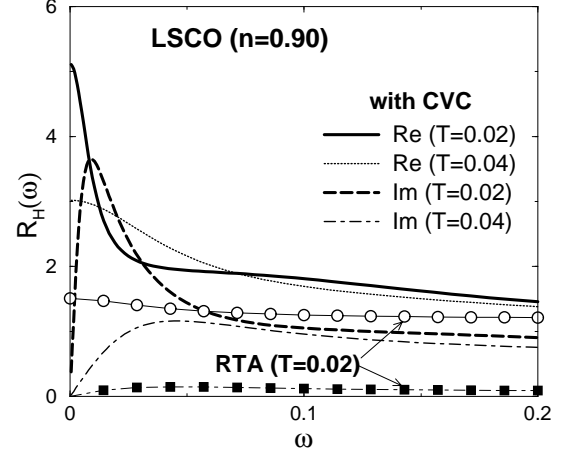


FIGURE 3. AC Hall coefficient obtained by the FLEX approximation. $R_H(\omega) \approx 1/ne$ within the RTA, whereas $R_H(\omega)$ by the conservation approximation shows a prominent ω -dependence, which is consistent with experiments.

ing the fact that the effective FSC around the cold-spot becomes negative due to the backflow. We have shown that $C_{\mathbf{k}}^J \propto \xi^2$ in both hole-doped and electron-doped systems in terms of the conserving approximation, so R_H in under-doped system is strongly enhanced at lower temperatures in proportion to T^{-1} . Moreover, characteristic frequency and temperature dependences of the AC Hall coefficient are also reproduced very well by taking the backflow into account, as shown in Fig.3 [5].

In summary, the backflow is a natural consequence of the basic Fermi liquid equation, eq.(1), and it cannot be ignored in strongly correlated systems. The total current in nearly AF metals is no more perpendicular to the FS due to the backflow, because the Landau interaction function caused by the AF fluctuations has a prominent momentum dependence. This fact means that the RTA is totally broken down. The Hall coefficient shows a strong temperature dependence because the backflow changes the "effective FSC" around the cold spot. By taking the backflow into account, we succeeded in reproducing characteristic non-Fermi liquid-like behaviors in various DC and AC transport phenomena in high- T_c cuprates, even in the pseudo-gap region [2, 3, 4].

REFERENCES

1. D. Pines and P. Nozieres, *The Theory of Quantum Liquids*, Benjamin, New York, 1966.
2. H. Kontani and K. Yamada, J. Phys. Soc. Jpn. **74**, 155 (2005), and references are therein.
3. H. Kontani et al., Phys. Rev. B **59**, 14723 (1999).
4. H. Kontani, Phys. Rev. B **67**, 014408 (2003).
5. H. Kontani, cond-mat/0507664; cond-mat/0511015.