

Photon statistics from coupled quantum dots

Brian D. Gerardot,¹ Stefan Strauf,^{1,2,*} Michiel J.A. de Dood,² Andrey M. Bychkov,^{2,†} Antonio Badolato,³ Kevin Hennessy,³ Evelyn L. Hu,^{1,3} Dirk Bouwmeester,² and Pierre M. Petroff^{1,3}

¹Materials Department, University of California Santa Barbara, CA 93106, Santa Barbara, USA

²Department of Physics, University of California Santa Barbara, CA 93106, Santa Barbara, USA

³ECE Department, University of California Santa Barbara, CA 93106, Santa Barbara, USA

We present an optical study of closely-spaced self-assembled InAs/GaAs quantum dots. The energy spectrum and correlations between photons subsequently emitted from a single pair provide not only clear evidence of coupling between the quantum dots but also insight into the coupling mechanism. Our results are in agreement with recent theories predicting that tunneling is largely suppressed between nonidentical quantum dots and that the interaction is instead dominated by dipole-dipole coupling and phonon-assisted energy transfer processes.

PACS numbers: 03.67.-a 78.67.Hc 78.55.Cr

Semiconductor quantum dots (QDs) are nanostructures that confine electrons and/or holes in all three dimensions. Excitons or single electron spins in QDs are promising candidates for the storage and manipulation of both classical and quantum bits [1]. Of particular interest for applications are semiconductor QDs in which excitons couple to photons. They display discrete energy levels [2], photon anti-bunching [3], and Rabi oscillations [4]. The coupling of two QDs has been proposed as a means to generate entangled photons and to realize quantum bit gate operations [5, 6]. The quest for qubit operations in solid-state has triggered several studies of the coupling processes in QD ensembles [7] and individual QD pairs [8, 9, 10, 11]. Theoretical investigations predict that coupling between QDs can be caused by electron and/or hole tunneling [9, 12] or by dipole-dipole interaction of excitons [6, 13, 14, 15]. Initial experiments reported large energy splittings up to 50 meV, attributed to tunnel coupling in identical QDs [9]. It is now understood that the dominant effect is the different size/strain situation of the individual QDs and that these splittings cannot be attributed to quantum mechanical coupling [10]. Refined theories that take into account the broken symmetry of nonidentical QDs predict repulsive forces between holes located on different dots, effectively preventing tunneling of excitons [16]. We present spectroscopic and photon-correlation measurements obtained from individual self-assembled InAs/GaAs QD pairs that demonstrate coupling between adjacent QDs and provide insight into the coupling mechanism and energy transfer between the QDs.

We chose to study QD pairs with a small vertical separation of 45 Å, where the coupling is expected to be pronounced. The InAs QDs were grown by molecular beam epitaxy on a (100) GaAs substrate via the Stranski-Krastanow growth mode. Strain fields above each QD form nucleation centers for QDs in a second layer, leading to vertical QD stacking. The s-shell transitions of the QD layers are carefully tuned to nearly

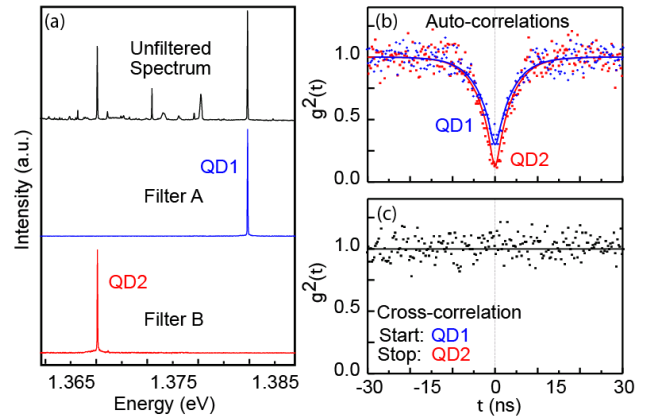


FIG. 1: (a) PL spectrum of a single layer of InAs/GaAs QDs. Interference filters were used to select two emission lines from two QDs, with lateral separation of 2 μm . (b) Photon auto-correlation for each line showing anti-bunching, $g^{(2)}(0) = 0.31$ and 0.12 for QD1 and QD2, respectively. (c) Corresponding cross-correlation showing $g^{(2)}(\tau) = 1$ for all times, indicating that the lateral QDs are uncoupled.

identical energies during the crystal growth [17, 18]. Micro-photoluminescence (PL) spectra were recorded using a 1.25 m spectrometer equipped with a charge coupled device. The QDs were non-resonantly excited at 780 nm. A solid immersion lens on the sample surface was used to improve the photon collection efficiency.

The experimental scheme is introduced by first describing measurements on a single layer of uncoupled InAs QDs [19]. The PL spectrum in Fig. 1a shows the emission of a few QDs at $T = 4$ K. The two main emission peaks correspond to the single exciton recombination of two individual QDs laterally separated by ~ 2 μm . To determine whether or not these two QDs are coupled the correlations between photons emitted from the QDs have been measured. The photons pass through a fiber beamsplitter and 1 nm frequency filters in the two output modes (k and l) before reaching single photon

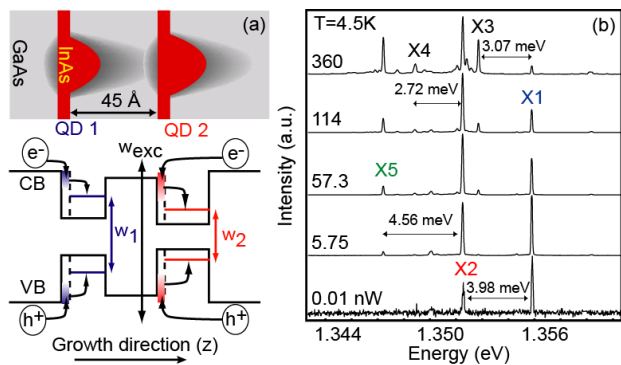


FIG. 2: (a) Schematic of the sample (top): two layers of InAs/GaAs QDs are vertically stacked with a separation of 45 Å. Schematic band diagram (bottom) of the conduction band (CB) and valence band (VB) for two stacked QDs with different transition frequencies ω_1 and ω_2 . The pump laser, with energy $\hbar\omega_{exc}$, generates carriers in the GaAs matrix, that relax into the wetting layers and from there into the QDs. (b) Typical power dependent PL spectra from an individual QD pair showing five dominant emission lines, labeled X1-X5.

detectors. Measuring the difference in arrival time between photons at each of the two detectors provides a measurement of the second-order correlation function $g_{kl}^{(2)}(\tau) = \langle I_k(t)I_l(t+\tau) \rangle / \langle I_k(t) \rangle \langle I_l(t) \rangle$, where $\langle I_k(t) \rangle$ is the expectation value of the intensity at time t . The auto-correlation function from a single QD is measured if both filters are tuned to the frequency of QD1 (or QD2). A single QD [3], just like a single atom, displays photon anti-bunching at $\tau = 0$ (Fig. 1b). For two identical but independent two-level emitters $g_{k=l}^{(2)}(0) = 0.5$. If the two emitters are non-identical, as is the situation here, a post-selection of the modes k and l can be made using different filters to measure a cross-correlation function. In this case of uncoupled QDs, emission of a photon from QD1 at $\tau = 0$ does not influence a photon emission event from QD2. Therefore, the corresponding cross-correlation function yields $g_{k \neq l}^{(2)}(\tau) = 1$ at all delay times as confirmed by the measurement shown in Fig. 1c. Coupling of two QDs would be characterized by measuring a deviation from 1 around $\tau = 0$ for $g_{k \neq l}^{(2)}(\tau)$.

As an initial characterization, pump-power dependent spectra were taken for 20 individual pairs, all showing similar properties. A schematic of the stacked QDs and corresponding band diagram is given in Fig. 2a. Under non-resonant laser excitation carriers are generated in the GaAs matrix which relax into the wetting layers and from there into the QDs. Subsequent radiative recombination leads to five dominant emission lines in the power dependent spectra labeled by X1-X5 (Fig. 2b). At low pump powers there are two dominant peaks X1 and X2 split by energy ΔE_0 that varies from 0.5 to 5.0 meV for different QD pairs. As the pump power

is increased, the peak intensities increase linearly as expected for single exciton recombination. The spectral lines X3, X4 and X5 emerge with quadratic power dependence indicative of biexcitons, while the X1 intensity diminishes. The statistics on 20 individual QD-pairs with a separation of 45 Å demonstrates that the upper limit for the coupling energy ΔE_0 is quite small, i.e. ≤ 2.6 meV on average. These small splitting energies are consistent with very recent experiments using magnetic [10] and electrical field [11] tuning, revealing anticrossing energies of 1-2 meV. Since both coupling mechanisms, electronic tunneling and dipole-dipole interaction [15], will cause an energy splitting as a function of detuning, it is not clear from such "anticrossing experiments" which mechanism will dominate the coupling.

To get insight into the coupling mechanism, we studied the temperature dependence of the peak intensities of X1 and X2 transition (Fig. 3). With increasing temperature, the X1 intensity decreases while the X2 intensity increases in such a way that the combined intensity remains constant. In addition, the measured lifetimes at 4K of the X1 and X2 states determined from auto-correlation measurements are 1.0 ns and 2.5 ns, respectively. Both observations are indicative for a directional energy transfer from QD1 to QD2 [7, 14]. This directionality excludes a direct coupling between the two levels. Coupling via the continuous wetting layer states that are ≥ 100 meV away cannot reproduce the observed strong temperature dependence. Instead, a model that couples the X1 and X2 states through a third level, that is ~ 10 meV higher in energy than X1, can be fitted to the data (solid line in Fig. 3). The model takes into account the decay rate of the QDs and uses temperature dependent absorption and emission rates for acoustic phonons in thermal equilibrium to couple the levels. Self-assembled QDs are associated with extended wetting layer states that lead to a quasi-continuous absorption background. Depending on the QD confinement potential those extended states can approach the s-shell transition energies [20]. Evidence that these states are indeed important in our InAs QDs have been recently reported [21]. Therefore, absorption of thermal energy (acoustic phonons) can bring the exciton from QD1 into resonance with an extended state of QD2 [14]. From there, the excitation will quickly relax into the s-shell leading to emission of the X2 line and thus to a directional energy transfer.

To unambiguously demonstrate that two QDs are coupled the photon correlations between each spectral line were studied. Auto-correlation measurements on individual spectral lines (X1-X5) all show strong anti-bunching as expected. The main experimental results have been obtained by cross-correlation measurements between the X1-X2, X1-X5 and X2-X5 lines, shown in Figs. 4a-c. Each cross-correlation deviates strongly from $g^{(2)}(0) = 1.0$, directly proving that the two QDs

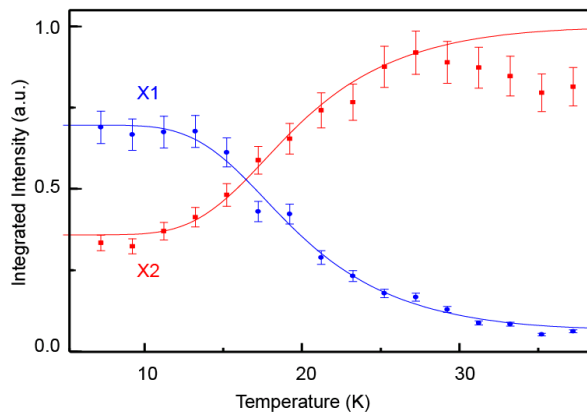


FIG. 3: PL for a pump power of 1.8 nW, of the X1 and X2 transitions versus temperature for a QD pair with $\Delta E_0 = 1.3$ meV. As the temperature is increased, the intensity from the energetically higher line, X1, is transferred to the X2 line.

form a coupled system. Below a model is proposed that provides an explanation for the observed correlations and spectral signatures.

We identify the X1(X2) line as emission from the state with one exciton localized on QD1(QD2). Note that this does include the possibility that only the hole stays localized and the electron wavefunction is spread over the double dot structure [16]. The notation of $|10\rangle$ and $|01\rangle$ is introduced for these states, where the two indices denote the number of excitons present in each QD. The states X3 and X4 emerge with quadratic power dependence at energies ~ 3 meV less than $|10\rangle$ and $|01\rangle$, respectively. As this is the typical Coulomb binding energy for biexcitons in single InAs/GaAs QDs, these states are labeled $|20\rangle$ and $|02\rangle$. In support of this assignment, measurements (not shown) of $g_{|20\rangle,|10\rangle}^{(2)}(\tau)$ and $g_{|02\rangle,|01\rangle}^{(2)}(\tau)$ exhibit the strong cascaded emission expected for biexciton to exciton states [22]. Finally, a new biexciton line X5 emerges in the spectra at lowest photon energy. We assign this to the $|11\rangle$ state with two excitons, one localized on each QD. This state occurs at lowest energy due to an attractive interdot Coulomb interaction which can be larger than the binding energy of the $|02\rangle$ and $|20\rangle$ intradot biexciton states.

To model the measured photon correlations a four-level rate equation is used that includes a ground state $|00\rangle$, two single exciton states $|10\rangle$ and $|01\rangle$, and an inter-dot biexciton state $|11\rangle$. The decay rate of the single exciton transitions Γ_X is assumed to be equal for both dots, and directional energy transfer from $|10\rangle$ to $|01\rangle$ with a rate W_T is included. The pump, included via the rate W_P , induces transitions from the ground state into the $|10\rangle$ or $|01\rangle$ states and from there into the $|11\rangle$ biexciton state. The rate equations for the system are: $\partial \vec{n} / \partial t = \mathbf{M} \cdot \vec{n}$, where the matrix \mathbf{M} is:

$$\mathbf{M} = \begin{pmatrix} -2W_P & \Gamma_X & \Gamma_X & 0 \\ W_P & -W_P - \Gamma_X & W_T & \Gamma_X \\ W_P & 0 & -W_P - \Gamma_X - W_T & \Gamma_X \\ 0 & W_P & W_P & -2\Gamma_X \end{pmatrix}$$

The column vector \vec{n} ($(n_{|00\rangle}, n_{|01\rangle}, n_{|10\rangle}, n_{|11\rangle})$) corresponds to the expectation value to be in a particular state at time t . Coherences induced through the pump field are neglected as the pump field is far off resonance. The corresponding correlation functions for the parameters $\Gamma_X = 2$ ns, $W_P = 0.75$ ns $^{-1}$ and $W_T = 5.25$ ns $^{-1}$ are shown in Fig. 4g-i and qualitatively agree with the experimental measurements. In addition, the value for the energy transfer rate is in good agreement with recent calculations assuming a phonon-assisted Coulomb transfer for two nonidentical QDs with 4-5 nm vertical separation, 2-3 meV energy separation and a lattice temperature of 4K [14]. The cross-correlation results are interpreted as follows: emission of the X1 or X2 line projects the system from the $|01\rangle$ or $|10\rangle$ to the ground state at $\tau = 0$. The X1 to X2 cross-correlation in Fig. 4a is then given by the repopulation of the $|01\rangle$ or $|10\rangle$ state [14, 23] and shows anti-bunching. The cross-correlations in Figs. 4b and 4c involve the X5 emission from the $|11\rangle$ interdot biexciton state into the $|01\rangle$ state. After spectral post-selection of the X5 emission the system is never in the $|10\rangle$ state and the X1/X5 ($|10\rangle/|11\rangle$) cross-correlation (Fig. 4b) shows pronounced anti-bunching. Conversely, cascaded emission is observed for the X2/X5 ($|01\rangle/|11\rangle$) cross-correlation in Fig. 4c, similar to the quantum cascade of a biexciton to single exciton in single QDs [22]. Note that the model predicts in addition a transition from the $|11\rangle$ to the $|10\rangle$ state, however, positive identification of this transition was hindered by the lack of intensity required for the cross-correlation measurement. While this model qualitatively explains the experimental results, it does not provide an explanation for the long recovery times of ~ 6 ns in Figs. 4a and 4c. A possible explanation is the presence of additional meta-stable states. These can be charged or dark excitons or can be formed via tunneling of the electron only, which is not distinguishable in the current experiment.

We have studied the coupling between two closely spaced self-assembled QDs with carefully tuned s-shell transitions to nearly identical energies. The results support the prediction that exciton interdot tunneling is largely suppressed due to the broken symmetry of non-identical QDs [16], and that the QD coupling is instead dominated by dipole-dipole interactions [14]. In particular, we found a direct Coulomb interaction between the permanent excitonic dipole moments (interdot biexciton), and a directional energy transfer between the QDs, even at their smallest vertical separation of 45 Å.

We acknowledge S. Anders, A. Imamoglu, R. Liu, L. Sham, J. Urayama, S. Yaida, and P. Zoller for fruit-

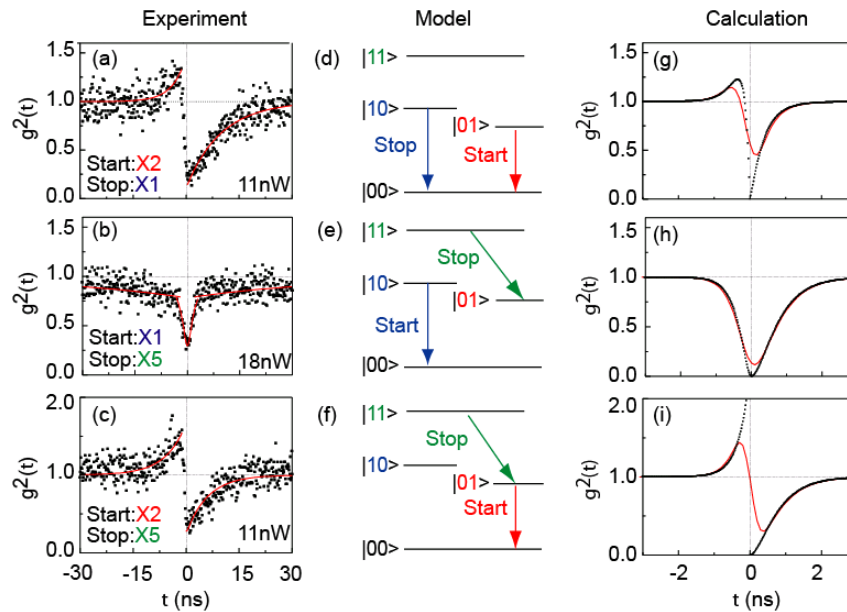


FIG. 4: Measured cross-correlation functions between the X2-X1, X1-X5 and X2-X5 lines (a-c) compared to the calculated functions between the $|01\rangle$ and $|10\rangle$, $|10\rangle$ and $|11\rangle$, and $|01\rangle$ and $|11\rangle$ states (g-i). All measurements show strong deviations from the uncoupled case $g^{(2)}(\tau) = 1$ (see Fig. 1c), with minimum values at zero delay time of 0.16 (a), 0.32 (b) and 0.25 (c). Figs. d-f show a level scheme of the states as used in the model, where $|00\rangle$ corresponds to the ground state, $|01\rangle$ and $|10\rangle$ to the single exciton states and $|11\rangle$ to the interdot biexciton state. The calculated correlation functions (dots) were convolved with a Gaussian curve that reflects the ~ 700 ps time resolution of the experimental system (lines).

ful discussions. S. Strauf acknowledges support from the Max-Kade Foundation. This research has been supported by DARPA no. MDA972-01-1-0027, NSF NIRT no. 0304678, and AFOSR no. F49620-98-1-0367 grants.

* Corresponding author: strauf@physics.ucsb.edu

† University of Cambridge, Cambridge CB3 0WA, UK

- [1] D. Loss and D. P. DiVincenzo, Phys. Rev. A **57**, 120 (1998); A. Imamoglu et al., Phys. Rev. Lett. **83**, 4204 (1999).
- [2] M. Bayer, et al., Nature **405**, 923 (2000); R. J. Warburton et al., Nature **405**, 926 (2000).
- [3] P. Michler et al., Nature **406**, 968 (2000).
- [4] T. H. Stievater et al., Phys. Rev. Lett. **87** 133603 (2001).
- [5] G. Burkard, D. Loss and D. P. DiVincenzo, Phys. Rev. B **59**, 2070 (1999); T. Calarco, A. Datta, P. Fedichev, E. Pazy and P. Zoller, Phys. Rev. A **68**, 012310 (2003).
- [6] B. W. Lovett, J. H. Reina, A. Nazir and G. A. D. Briggs, Phys. Rev. B **68**, 205319 (2003).
- [7] C. R. Kagan, C. B. Murray and M. G. Bawendi, Phys. Rev. B **54**, 8633 (1996); M. Ouyang and D. D. Awschalom, Science **301**, 1074 (2003); S. A. Crooker, J. A. Hollingsworth, S. Tretiak and V. I. Klimov, Phys. Rev. Lett. **89**, 186802 (2002).
- [8] G. Schedelbeck, W. Wegscheider, M. Bichler and G. Abstreiter, Science **278**, 1792 (1997); I. Shtrichman, C. Metzner, B. D. Gerardot, W. V. Schoenfeld and P. M. Petroff, Phys. Rev. B **65**, 081303 (2002).
- [9] M. Bayer et al., Science **291**, 451 (2001).
- [10] G. Ortner et al., Phys. Rev. B **71**, 125335 (2005).
- [11] H.J. Krenner et al., Phys. Rev. Lett. **94**, 057402 (2005); G. Ortner et al. Phys. Rev. Lett. **94**, 157401 (2005).
- [12] G. Burkard, G. Seelig and D. Loss, Phys. Rev. B **62**, 2581 (2000); F. Troiani, U. Hohenester and E. Molinari, Phys. Rev. B **65**, 161301 (2002).
- [13] E. Biolatti, R.I. Iotti, P. Zanardi, and F. Rossi, Phys. Rev. Lett **85**, 5647 (2000).
- [14] A. O. Govorov, Phys. Rev. B **71**, 155323 (2005).
- [15] A. Nazir et al., Phys. Rev. B **71**, 045334 (2005).
- [16] G. Bester, A. Zunger and J. Shumway, Phys. Rev. B **71**, 075325 (2005).
- [17] B. D. Gerardot, I. Shtrichman, D. Hebert and P. M. Petroff, J. Cryst. Gr. **252**, 44 (2003).
- [18] The InAs islands were partially covered with GaAs and annealed before complete capping to blue-shift the QD s-shell transition energy to ~ 920 nm. We used a 10 Å and 20 Å GaAs partial coverage for the first and second QD layer respectively, to tune the s-shell transitions.
- [19] The QDs are embedded in a photonic crystal membrane that enhances the photon collection efficiency. The QDs transitions are far from resonance with the cavity mode.
- [20] Y. Toda, O. Moriwaki, M. Nishioka and Y. Arakawa, Phys. Rev. Lett. **82**, 4114 (1999); A. Vasanelli, R. Ferreira and G. Bastard, Phys. Rev. Lett. **89**, 216804 (2002).
- [21] B. Urbaszek et al., Phys. Rev. B **69**, 035304 (2004); K. Karrai et al., Nature **427**, 135 (2004).
- [22] E. Moreau et al., Phys. Rev. Lett. **87**, 183601 (2001).
- [23] A. J. Berglund, A. C. Doherty and H. Mabuchi, Phys. Rev. Lett. **89**, 068101 (2002).