

Optical Conductivity and Hall Coefficient in High- T_c Superconductors: Significant Role of Current Vertex Corrections

Hiroshi KONTANI¹

¹ *Department of Physics, Nagoya University, Furo-cho, Nagoya 464-8602, Japan.*
(Dated: March 23, 2022)

We study AC conductivities in high- T_c cuprates, which offer us significant information to reveal the true electronic ground states. Based on the fluctuation-exchange (FLEX) approximation, current vertex corrections (CVC's) are correctly taken into account to satisfy the conservation laws. We find the significant role of the CVC's on the optical Hall conductivity in the presence of strong antiferromagnetic (AF) fluctuations. This fact leads to the failure of the relaxation time approximation (RTA). As a result, experimental highly unusual behaviors, (i) prominent ω and temperature dependences of $\{\text{Re}, \text{Im}\}R_H(\omega)$, and (ii) simple Drude form of $\theta_H(\omega)$ for wide range of ω , are satisfactorily reproduced. In conclusion, both DC and AC transport phenomena in (slightly under-doped) high- T_c cuprates can be explained comprehensively in terms of nearly AF Fermi liquid, if one take the CVC's into account.

Non-Fermi-liquid-like behavior in various transport phenomena in high- T_c superconductors (HTSC's) is a key clue for solving the mystery of the ground state. For example, $R_H \propto T^{-1}$ is observed in hole-doped systems below $T_0 \sim 700\text{K}$, and $|R_H| \gg 1/ne$ (n being the electron density) at lower temperatures [1]. Moreover, the magnetoresistance follows the relation $(\Delta\rho/\rho_0) \cdot \rho_0^2 \propto R_H^2 \propto T^{-2}$, which is called the modified Kohler's rule [2, 3]. A comprehensive understanding for them cannot be achieved by the relaxation time approximation (RTA) even if one assume a huge anisotropy of the relaxation time, $\tau_{\mathbf{k}}$: Although $R_H \gg 1/ne$ is derived, then $\Delta\rho/\rho_0$ increases much faster than T^{-4} so the modified Kohler's rule is broken down [4, 6].

The modified Kohler's rule is well reproduced if one take the *vertex correction for the total current* $\mathbf{J}_{\mathbf{k}}$, which is called the *back-flow* in Landau-Fermi liquid theory [5]. Due to the back-flow, $\mathbf{J}_{\mathbf{k}}$ becomes totally different from the quasiparticle velocity $\mathbf{v}_{\mathbf{k}}$ in nearly AF Fermi liquid. Reflecting this fact, relations $R_H \propto \xi^2 \propto T^{-1}$ and $\Delta\rho \cdot \rho_0 \propto \xi^4 \propto T^{-2}$ are derived, where ξ is the antiferromagnetic (AF) correlation length. In the same way, anomalous behaviors of thermoelectric power and Nernst coefficient can be explained *in the unified way* [6, 7, 8].

AC transport phenomena give us further significant information on the electronic states. In HTSC's, the extended-Drude (ED) relation given by the RTA,

$$\sigma_{xy}^0(\omega) \propto \{\sigma^0(\omega)\}^2 \propto (2\gamma_0(\omega) - iz^{-1}\omega)^{-2}, \quad (1)$$

$$\gamma_0^{-1}(\omega) = \frac{2}{\omega} \int_0^\omega d\epsilon \langle [\gamma_{\mathbf{k}}(\epsilon - \omega) + \gamma_{\mathbf{k}}(\epsilon)]^{-1} \rangle_{\text{FS}} \quad (2)$$

is strongly violated even when $\omega \ll \gamma_0$ (in the far-infrared region, $\omega \sim 50\text{cm}^{-1}$) [9]. $\gamma_{\mathbf{k}}(\omega)$ is the imaginary part of the self-energy and $z(< 1)$ is the mass-renormalization factor. The ED-relation seems to hold well in Cu and Au [10]. Note that we obtain a simple Drude form if one drop the ω -dependence of $\gamma_0(\omega)$. Another unexpected experimental fact is that the optical Hall angle $\theta_H(\omega) \equiv \sigma_{xy}(\omega)/\sigma(\omega)$ in HTSC's follows a

simple Drude form even when $\omega \gg \gamma_0$ (in the infrared region, $\omega \sim 1000\text{cm}^{-1}$), despite the fact that ω -dependence of $\tau_{\mathbf{k}}(\omega) \equiv 1/2\gamma_{\mathbf{k}}(\omega)$ violated the Drude form of $\sigma(\omega)$ [11, 12]. Previous theoretical works based on the RTA unable to give a comprehensive understanding for them [11, 12]. Thus, anomalous AC transport phenomena have been a long-standing challenge for theory.

In this article, we develop the method of calculating $\sigma(\omega)$ and $\sigma_{xy}(\omega)$ using the FLEX approximation by taking the current vertex correction (CVC) to satisfy the conservation laws. We call it the FLEX+CVC approximation. We find that $\sigma_{xy}(\omega)$ deviates from the ED-form predominantly due to CVC when AF fluctuations are strong. We succeeded in reproducing the unexpected experimental behaviors of $R_H(\omega)$ as well as $\theta_H(\omega)$ *at the same time*. Thus, anomalous AC and DC transport phenomena in HTSC's can be understood in terms of nearly AF Fermi liquid, if one take the CVC into account.

First, we study the self-energy $\Sigma_{\mathbf{k}}(\omega_n)$ in the square-lattice Hubbard model using the FLEX approximation, which is one of the self-consistent spin-fluctuation theory [13]. This method can reproduce characteristic electronic properties in slightly under-doped systems above the pseudo-gap temperature [14, 15]. We put $(t, t', t''; U) = (1, -0.1, 0.1; 5)$ and $n = 0.9$, where t , t' and t'' are hopping integrals between the nearest neighbor, the second nearest and the third nearest, respectively. The dispersion of conduction electron is $\epsilon_{\mathbf{k}} = -2t(\cos k_x + \cos k_y) - 4t' \cos k_x \cos k_y - 2t''(\cos 2k_x + \cos 2k_y)$. This set of parameters corresponds to slightly under-doped LSCO. We note that $\text{Im}\Sigma_{\mathbf{k}}(-i\delta)$ on the FS takes the minimum value around $(\pi/2, \pi/2)$, which is called the 'cold-spot' in literature [16]. Its maximum (minimum) value on the FS is 0.46 (0.081) at $T = 0.02$: The ratio of anisotropy is 5.7, which is too small to explain the enhancement of R_H ; the CVC around the cold-spot magnifies R_H [5].

Next, we study transport coefficients in the framework of the conservation approximation, by taking the CVC

into account [17]. According to the Kubo formula,

$$\sigma_{\mu\nu}(\omega) = \frac{1}{i\omega} [K_{\mu\nu}^R(\omega) - K_{\mu\nu}^R(0)], \quad (3)$$

where $K_{\mu\nu}^R(\omega)$ is the retarded correlation function, which is given by the analytic continuations of the following thermal Green functions with $\omega_l \geq 0$ [18, 19] using the numerical Padé approximation:

$$K_{xx}(i\omega_l) = -2e^2T \sum_{n,\mathbf{k}} v_{\mathbf{k}x}^0 g_{\mathbf{k}}^{n;l} \Lambda_{\mathbf{k}x}^{n;l}, \quad (4)$$

$$K_{xy}(i\omega_l) = i \cdot e^3T \sum_{n,\mathbf{k}} \sum_{\mu,\nu}^{x,y} \left[G_{\mathbf{k}}^n \overset{\leftrightarrow}{\partial}_\mu G_{\mathbf{k}}^{n+l} \right] \times \left[\Lambda_{\mathbf{k}x}^{n;l} \overset{\leftrightarrow}{\partial}_\nu \Lambda_{\mathbf{k}y}^{n;l} \right] \cdot \epsilon_{\mu\nu z}, \quad (5)$$

where $[A \overset{\leftrightarrow}{\partial}_\mu B] \equiv A \overset{\leftrightarrow}{\partial}_{k_\mu} B - B \overset{\leftrightarrow}{\partial}_{k_\mu} A$, and $\epsilon_{\mu\nu\lambda}$ is an antisymmetric tensor with $\epsilon_{xyz} = 1$. $\omega_l \equiv 2\pi Tl$ is a Matsubara frequency; here we promise l represents a integer and n is a half-integer, respectively. $G_{\mathbf{k}}^n \equiv G_{\mathbf{k}}(\omega_n)$ is the Green function and $g_{\mathbf{k}}^{n;l} \equiv G_{\mathbf{k}}^n G_{\mathbf{k}}^{n+l}$. $v_{\mathbf{k}\mu}^0 \equiv \partial \epsilon_{\mathbf{k}} / \partial k_\mu$ is the velocity of a free electron, and $\Lambda_{\mathbf{k}}^{n;l}$ is the dressed current. In the FLEX approximation, it is given by

$$\Lambda_{\mathbf{k}}^{n;l} = \mathbf{v}_{\mathbf{k}}^0 + T \sum_{n',\mathbf{p}} V_{\mathbf{k}-\mathbf{p}}(\omega_n - \omega_{n'}) \cdot g_{\mathbf{p}}^{n';l} \Lambda_{\mathbf{p}}^{n';l} \quad (6)$$

where $V_{\mathbf{k}}(\omega)$ is given in eq.(9) of ref.[5]. In eq. (6), we take the infinite series of the Maki-Tompson terms in Λ , that is, we drop all the Aslamazov-Larkin terms. This simplification is justified for DC-conductivities when the AF fluctuations for $\mathbf{Q} \approx (\pi, \pi)$ are dominant, as proved in ref.[5]. This will be also true for optical conductivities, due to the fact that the f -sum rules both for $\sigma(\omega)$ and $\sigma_{xy}(\omega)$ are well satisfied in the present study, as will be discussed below.

Padé approximation is less reliable when the function under consideration is strongly ω -dependent, and when the temperature is high because the Matsubara frequency is sparse. To obtain reliable results, both $\Sigma_{\mathbf{k}}(\omega_n)$ and $\Lambda_{\mathbf{k}}^{n;l}$ have to be converged so that the relative errors should be under 10^{-8} . Moreover, we utilize the fact that the $i\omega$ -linear term of $K_{\mu\nu}(\omega)$ is equal to the DC value of $\sigma_{\mu\nu}$, which can be obtained by the FLEX+CVC approximation with high accuracy, as performed in refs. [5, 6, 7, 8]. As a result, we succeed in deriving the $\sigma_{\mu\nu}(\omega)$ for any ω with enough accuracy.

To confirm the accuracy of numerical results, we check the following f -sum rules [20]:

$$\int_0^\infty d\omega \text{Re}\sigma(\omega) = \pi e^2 \sum_{\mathbf{k}} \frac{\partial^2 \epsilon_{\mathbf{k}}}{\partial k_x^2} n_{\mathbf{k}}, \quad (7)$$

$$\int_0^\infty d\omega \text{Re}\sigma_{xy}(\omega) = 0. \quad (8)$$

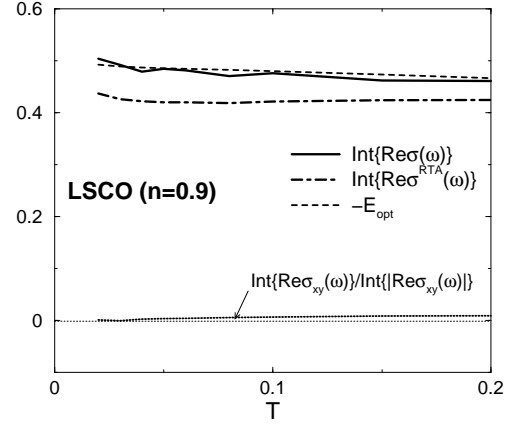


FIG. 1: f -sum rules both for $\sigma(\omega)$ and $\sigma_{xy}(\omega)$ are well satisfied if the CVC is correctly taken into account. This fact assures the reliability of the present numerical study.

Because the FLEX+CVC approximation is a conserving approximation, f -sum rules should be satisfied in the present study if numerical error is absent. In Fig.1, $\text{Int}\{\sigma(\omega)\}$ ($\text{Int}\{\sigma_{xy}(\omega)\}$) represents the numerical result for the left-hand-side of eq. (7) (eq. (8)), and $-E_{\text{opt}}$ is that for the right-hand-side of eq. (7). We see that the f -sum rules hold well, whose relative error is below 2.5%. This results assure the high reliability of the present numerical study, considering the ill accuracy of the Padé approximation for larger $|\omega|$. On the other hand, $\text{Int}\{\text{Re}\sigma^{\text{RTA}}(\omega)\}$ (without any CVC) is at least 12% smaller than the correct value, reflecting the violation of the conservation laws in the RTA.

Figure 2 shows the ω -dependences of $\sigma(\omega)$, $\sigma_{xy}(\omega)$ and $R_H(\omega)$ for several temperatures. For comparison, we also plot the results by the RTA ($\sigma^0(\omega)$, $\sigma_{xy}^0(\omega)$ and $R_H^0(\omega)$) at $T = 0.02$, which is given by dropping all the CVC's. We have checked that both $\sigma^0(\omega)$ and $\sigma_{xy}^0(\omega)$ satisfy the ED form in eq.(1) for $\omega \lesssim 0.2$ [21]. As shown in Fig.2, the CVC for $\sigma(\omega)$ is less effective (at least within the FLEX approximation), as is the case of the DC σ [5]. This fact suggests that $\sigma(\omega)$ follows the ED-form well. One can see that $\text{Re}\sigma(\omega)$ decreases with ω much slower than the Lorentzian, because $\gamma_0(\omega)$ is an increase function of ω .

In the Fermi liquid theory, the CVC is divided into (i) the back-flow, and (ii) the renormalization of $\mathbf{v}_{\mathbf{k}}$ by $d\Sigma_{\mathbf{k}}/dk$. In nearly AF systems, the conductivity is reduced by the former, whereas it is enhanced by the latter [5]. As shown in Fig.2, The latter slightly exceeds the former in the present calculation.

In contrast, $\sigma_{xy}(\omega)$ with full CVC is quite different from the RTA's result: Both ω and temperature dependences are much enhanced by CVC. $\text{Re}\sigma_{xy}(\omega)$ at $T = 0.02$ takes a large negative value for $\omega > 0.03 \sim 120\text{cm}^{-1}$, which is consistent with experimental observations [9, 11, 12]. Although $\text{Re}\sigma_{xy}^0(\omega)$ by RTA becomes

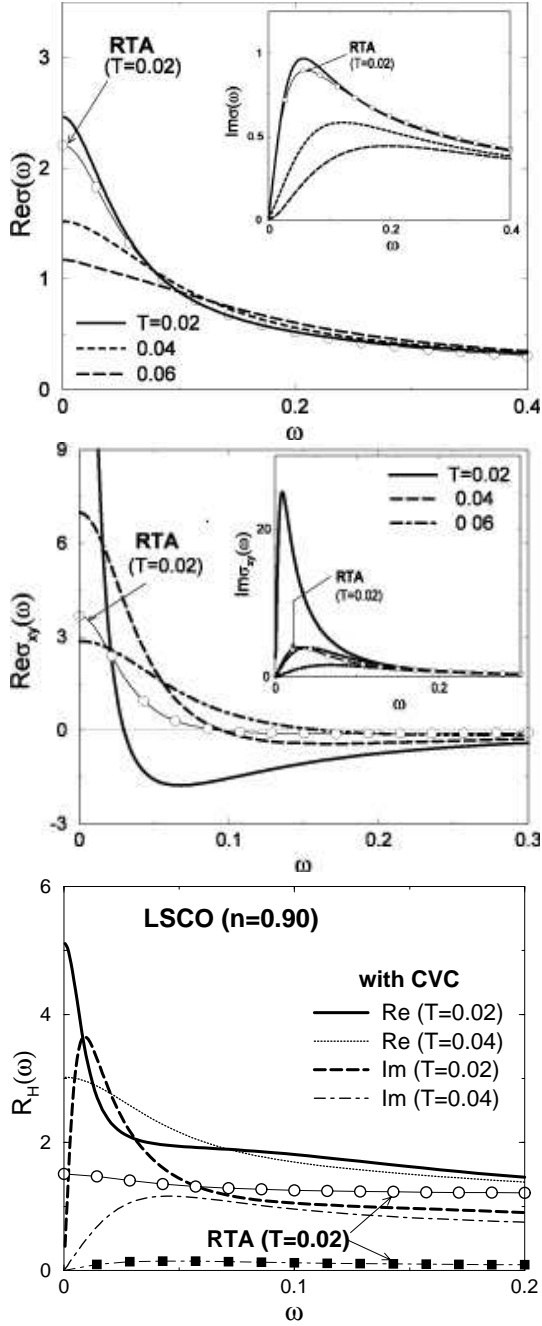


FIG. 2: $\sigma(\omega)$, $\sigma_{xy}(\omega)$ and $R_H(\omega)$ by the FLEX+CVC approximation (with CVC). $T = 0.02$ and $\omega = 0.1$ approximately correspond to 80K and 300cm^{-1} , respectively.

negative for $\omega > 0.1$, its absolute value is very small. It is naturally understood from the ED-form because $\gamma(\omega)$ increases with ω . This large dip in $\text{Re}\sigma_{xy}(\omega)$ is naturally understood in terms of the f -sum rule, eq.(8), because $\text{Re}\sigma_{xy}(0) > 0$ takes an enhanced value due to the CVC. We also stress that $\text{Im}\sigma_{xy}(\omega)/\omega|_{\omega=0}$ is strongly enhanced due to the CVC; $\text{Im}\sigma_{xy}(\omega)$ at $T = 0.02$ takes the maxi-

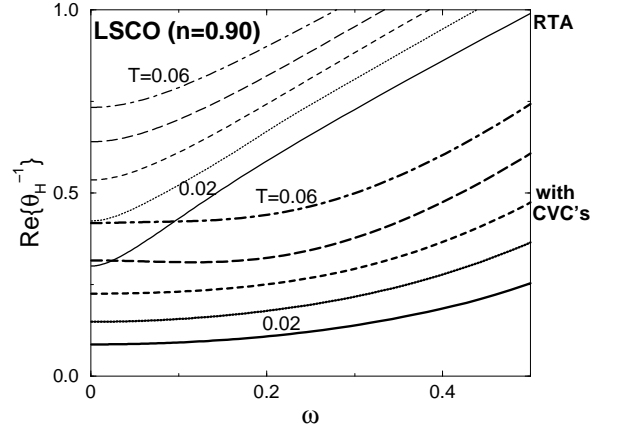


FIG. 3: ω -dependences of $\theta_H(\omega)$ given by the RTA and by the FLEX+CVC approximation.

mum value at $\omega_2 \sim 0.01$, which is about six times larger than ω_1 for $\text{Im}\sigma(\omega)$.

The violation of the ED-form is apparent in $R_H(\omega) = \sigma_{xy}(\omega)/\sigma^2(\omega)$. We see that $R_H^0(\omega)$ by the RTA, $\sigma_{xy}^0(\omega)/(\sigma^0(\omega))^2$, is almost ω -independent and its imaginary part is tiny, which means that both $\sigma_{xy}^0(\omega)$ and $\sigma^0(\omega)$ follow the ED-forms given in eq.(1). On the other hand, $R_H(\omega)$ given by the FLEX+CVC approximation shows prominent frequency as well as temperature dependences. The obtained overall behavior is similar to the experimental observation in an optimally-doped YBCO at 95K [9]. $\text{Im}R_H(\omega)$ at $T = 0.02$ takes the maximum value at $\omega_3 \sim 0.01$, which is similar to ω_2 for $\text{Im}\sigma_{xy}(\omega)$ and is six times larger than ω_1 for $\text{Im}\sigma(\omega)$. The relation $\omega_1 \gg \omega_2 \sim \omega_3$ in the present study, which is consistent with experimental observation [9, 12], cannot be reproduced by the RTA: It can be explained only when the back-flow is taken into account [21].

IR optical Hall angle $\theta_H(\omega) = \sigma_{xy}(\omega)/\sigma(\omega)$ ($\omega \lesssim 1000\text{cm}^{-1} = 1440\text{K}$) has been intensively measured by Drew et al [11, 12]. They found that the following simple Drude form is well satisfied for the Hall angle:

$$\theta_H(\omega) = \frac{\Omega_H^*}{2\gamma_H^* - i\omega}, \quad (9)$$

$$\gamma_H^* \propto T^{-d}; \quad d = 1.5 \sim 2$$

$$\Omega_H^* \propto T^0,$$

where γ_H^* and Ω_H^* are ω -independent for IR range ($\omega \lesssim 1000\text{cm}^{-1}$). This is highly nontrivial because $\gamma_0(\omega)$ in eq.(2) is approximately linear-in- ω for $\omega \gg T$ in HTSC's [22]. Ω_H^* is almost independent of ω and T , which increases as the doping decreases. These unexpected results put very severe constraints on theories of HTSC.

From now on, we show that the Drude-type form of the Hall angle is reproduced quite well by the FLEX+CVC

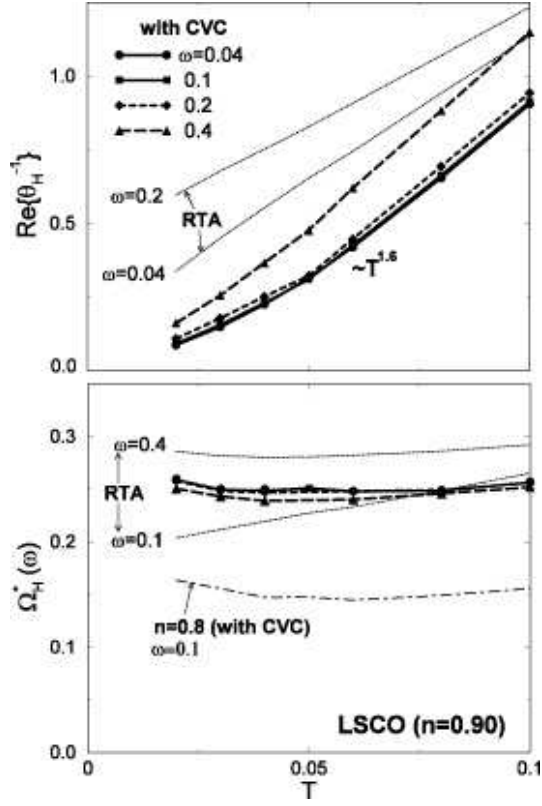


FIG. 4: Temperature dependence of $\theta_H(\omega)$ by the FLEX+CVC approximation.

approximation. Figure 3 shows the ω -dependence of $\text{Re}\{\theta_H^{-1}(\omega)\}$. Figure 4 also shows the T -dependence of $\text{Re}\{\theta_H^{-1}(\omega)\}$ and $\Omega_H^*(\omega) \equiv -\omega/\text{Im}\{\theta_H^{-1}(\omega)\}$ for several ω 's, respectively. They correspond to $2\gamma_H^*/\Omega_H^*$ and Ω_H^* , respectively, if we apply the Drude form in eq. (9). We can recognize that $\Omega_H^*(\omega)$ is almost independent of ω and T for $\omega \leq 0.4$ and $T \leq 0.1$, while it shows sizable (ω, T) -dependences within the RTA. Thus, $\text{Re}\{\theta_H^{-1}(\omega)\}$ shown in Fig.3 and in the upper panel of Fig.4 represents the (ω, T) -dependences of γ_H^* . For $\omega \leq 0.2$, γ_H^* by the FLEX+CVC approximation is almost equal to its DC value and $d = 1.6$ in eq. (9). d becomes smaller for $\omega = 0.4$. On the other hand, γ_H^* by RTA is almost linear-in- T and its ω -dependence is sizable, which is inconsistent with experiments. To summarize, experimental simple Drude-form of $\theta_H(\omega)$, which cannot be understood by the RTA, is well reproduced if one take the CVC into account. The experimental value of Ω_H^*/B for slightly under-doped YBCO and BSCCO ($n \sim 0.9$) is about $0.3[\text{cm}^{-1}\text{T}^{-1}]$, which corresponds to 0.25 in the present energy scale. It decreases to be $0.15[\text{cm}^{-1}\text{T}^{-1}]$ for optimally-doped YBCO. Thus, the doping dependence of Ω_H^* , as well as its value, are reproduced qualitatively. Similar results are obtained when the set of parameters for YBCO given in ref.[5] is used.

Now, we introduce several results given by an approximate solution of the Bethe-Salpeter equation for \mathbf{J}_k at finite frequencies [21]: The general expressions for $\sigma(\omega)/\omega|_{\omega=0}$ and $\sigma_{xy}(\omega)/\omega|_{\omega=0}$ can be derived from the Kubo formula [21]. By analysing the CVC included in them, we obtain the relation $\sigma_{xy}(\omega) \approx a(2\gamma_0)^{-1} + b \cdot iz^{-1}\omega(2\gamma_0)^{-2} + O(\omega^2)$, where $a \propto \xi^2$ and $b \propto \xi^3$ due to the CVC, whereas $a = b = 1$ in the RTA. As a result, $\sigma_{xy}(\omega)$ deviates from the ED-form due to the CVC. On the other hand, $\sigma(\omega) \approx (2\gamma_0)^{-1} + iz^{-1}\omega(2\gamma_0)^{-2}$ even if the CVC is taken. Then, we obtain relations $\text{Im}R_H(\omega)/\omega \propto z^{-1}b\gamma_0^{-1} \propto T^{-2.6}$ and $\text{Im}\theta_H^{-1}(\omega)/\omega \propto z^{-1}ba^{-2} \propto T^0$, because $\xi \propto T^{-0.4}$ and $z^{-1} \propto T^{-0.4}$ in the present FLEX approximation [21]. These relations are confirmed by the present numerical study. In addition, the cancellation of the ω -dependences of $\gamma_0(\omega)$ and CVC's result in the almost constant γ_H in eq.(9).

In summary, we have calculated the optical conductivities for HTSC's by the FLEX+CVC approximation, which had been serious problems associated intimately with the true electronic ground states in HTSC's. Experimentally observed anomalous behaviors for $\sigma(\omega)$, $\sigma_{xy}(\omega)$, $\theta_H(\omega)$ and $R_H(\omega)$ are well reproduced for enough wide range of frequencies and temperatures, without assuming any fitting parameters. They are consistent with the characteristic experimental results for HTSC's reported by Drew et al. [9, 11, 12], which cannot be reproduced by previous theoretical works based on the RTA even if one assume extremely anisotropic τ_k . The present study ensures that anomalous AC and DC transport phenomena in HTSC's can be understood in terms of nearly AF Fermi liquid state.

There remain many important issues for future study. We will calculate the optical Hall conductivity for electron-doped HTSC's [21]. We are also planning to study the optical conductivities in the pseudo-gap region based on the FLEX+T-matrix approximation, which ascribes the pseudo-gap phenomena in HTSC's to the strong superconducting fluctuations [8, 14]. We expect that the non-Drude form of the far-IR ($\omega = 20 \sim 250\text{cm}^{-1}$) Hall angle in $\text{YBa}_2\text{Cu}_3\text{O}_7$ below 150K [23] might be explained by this study.

-
- [1] J. Takeda, T. Nishikawa, and M. Sato: Physica C **231** (1994) 293.
 - [2] T. Kimura, S. Miyasaka, H. Takagi, K. Tamasaku, H. Eisaki, S. Uchida, K. Kisazawa, M. Hiroi, M. Sera, and N. Kobayashi: Phys. Rev. B **53** (1996) 8733.
 - [3] Y. Ando and T. Murayama: Phys. Rev. B **60** (1999) R6991; Y. Ando and K. Segawa: Phys. Rev. Lett. **88** (2002) 167005.
 - [4] L.B. Ioffe and A. J. Millis: Phys. Rev. B **58** (1998) 11631.
 - [5] H. Kontani, K. Kanki and K. Ueda: Phys. Rev. B **59** (1999) 14723, K. Kanki and H. Kontani: J. Phys. Soc.

- Jpn. **68** (1999) 1614.
- [6] H. Kontani: J. Phys. Soc. Jpn. **70** (2001) 1873.
 - [7] H. Kontani: J. Phys. Soc. Jpn. **70** (2001) 2840.
 - [8] H. Kontani: Phys. Rev. Lett. **89** (2003) 237003.
 - [9] S.G. Kaplan, S.Wu, H.-T.S. Lihn, H.D. Drew, Q. Li, D.B. Fenner, J.M. Phillips and S.Y. Hou: Phys. Rev. Lett. **76** (1996) 696.
 - [10] J. Cerne, D.C. Schmadel, M. Grayson, G.S. Jenkins, J.R. Simpson and H.D. Drew: Phys. Rev. B **61** (2000) 8133.
 - [11] J. Cerne, M. Grayson, D. C. Schmadel, G. S. Jenkins, H. D. Drew, R. Hughes, A. Dabkowski, J. S. Preston, and P.-J. Kung: Phys. Rev. Lett. **84** (2000) 3418.
 - [12] L. B. Rigal, D. C. Schmadel, H. D. Drew, B. Maiorov, E. Osquiguil, J. S. Preston, R. Hughes, and G. D. Gu: Phys. Rev. Lett. **93** (2004) 137002.
 - [13] N. E. Bickers and S. R. White: Phys. Rev. B **43** (1991) 8044.
 - [14] Y. Yanase, T. Jujo, T. Nomura, H. Ikeda, T. Hotta and K. Yamada: Phys. Rep. **387** (2003) 1.
 - [15] T. Moriya and K. Ueda: Adv. Physics **49** (2000) 555.
 - [16] B.P. Stojković and D. Pines: Phys. Rev. B **55** (1996) 857.
 - [17] G. Baym and L.P. Kadanoff: Phys. Rev. **124** (1961), 287.
 - [18] G. M. Eliashberg : Sov. Phys. JETP **14** (1962), 886.
 - [19] H. Kohno and K. Yamada: Prog. Theor. Phys. **80** (1988) 623.
 - [20] R. Kubo: J. Phys. Soc. Jpn. **12** (1957) 570.
 - [21] H. Kontani: unpublished.
 - [22] B.P. Stojković and D. Pines: Phys. Rev. B **56** (1997) 11931.
 - [23] M. Grayson, L. B. Rigal, D. C. Schmadel, H. D. Drew, and P.-J. Kung: Phys. Rev. Lett. **89** (2002) 037003.