

International Journal of Modern Physics B
 © World Scientific Publishing Company

Point Contact Study of the Superconducting Order Parameter in $\text{RuSr}_2\text{GdCu}_2\text{O}_8$

S. PIANO*, F. BOBBA, F. GIUBILEO, A. M. CUCOLO

*Physics Department and INFN Supermat Laboratory, University of Salerno,
 Via Salvatore Allende, I-84081 Baronissi (SA), Italy*

**samanta@sa.infn.it*

A. VECCHIONE

*Physics Department and INFN Coherencia Laboratory, University of Salerno,
 Via Salvatore Allende, I-84081 Baronissi (SA), Italy*

We have performed a detailed study of the conductance characteristics obtained by point contact junctions realized between a normal Pt/Ir tip and sintered $\text{RuSr}_2\text{GdCu}_2\text{O}_8$ (Ru-1212) samples. Indeed, this compound is subject of great interest due to the coexistence of both magnetic order and bulk superconductivity. In our experiments, the low temperature tunneling spectra reproducibly show a zero bias conductance peak that can be well reproduced by a generalized BTK model in the case of *d-wave* symmetry of the superconducting order parameter.

From the discovery of high T_c superconductors several experimental and theoretical analysis have been realized to reveal the electronic structure and to understand the pairing state of these materials. Recently a new compound of this family, the $\text{RuSr}_2\text{GdCu}_2\text{O}_8$ (Ru-1212), has raised great interest. This rutheno-cuprate superconductor is a triple perovskite material with alternating CuO_2 bilayers and RuO_2 monolayers. In addition to the superconducting transition, the rutheno-cuprate materials show magnetic order at $\sim 135\text{K}$. The magnetic order of the Ru moments is predominantly antiferromagnetic along the *c* axis¹, while a ferromagnetic component has been observed along the *a*, *b* planes². In this report we study the Point-Contact conductance characteristics obtained on Ru-1212 compound. The majority of the tunneling curves shows a zero-bias conductance peak (ZBCP), which can be modeled by assuming a *d-wave* pairing symmetry of the superconducting order parameter in this material.

The Ru-1212 pellets were melt-textured synthesized samples³. Resistivity measurements⁴ have shown a critical temperature $T_c^{\text{onset}} = 40\text{K}$ and $T_c(\rho = 0) = 25\text{K}$. To realize our experiments we used a Pt-Ir tip, chemically etched in a 37% solution of HCl and in an ultrasound bath. We have established the contact between the sample and the tip at $T = 4.2\text{K}$, and we measured the differential conductance dI/dV as a function of the voltage bias V using a conventional four-probe method and lock-in technique at 377Hz . We obtained different conductance

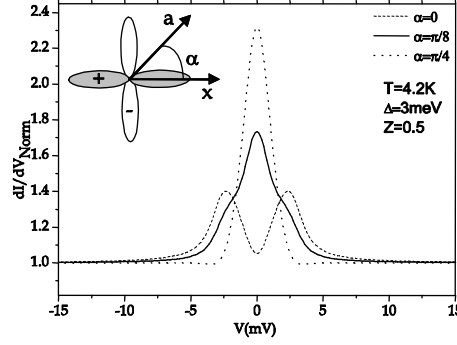


Fig. 1. Numerical simulation of *d-wave* BTK model at different values of angle α between the x -axis and a -axis of the superconductor (see inset). The fitting curve has been generated at $Z = 0.5$, $T = 4.2K$ and $\Delta = 3meV$. The dashed line represents $\alpha = 0$, the solid line $\alpha = \pi/8$ and the dotted line $\alpha = \pi/4$.

curves⁵, majority of which characterized by a triangular peak structure centered at zero bias. Sometimes this peak is greater than 2, while in other cases a variation of slope is present. These curves cannot be explained by a *s-wave* symmetry of the order parameter⁶. For this reason we explore this feature in term of a *d-wave* symmetry. Indeed, *d-wave* pairing states have an internal phase of the pairing potential which modifies the surface states due to the interface effect of the quasiparticles (*Andreev Bound States*). To take into account these effects, Tanaka and Kashiwaya⁷ modified the Blonder-Tinkham-Klapwijk (BTK) model⁸, introducing a *d-wave* symmetry of the order parameter. The BTK model describes the current-voltage characteristics of a superconductor–normal metal junction separated by a barrier of arbitrary strength, which is modelled by a dimensionless parameter Z : varying Z it is possible to go by Andreev Reflection situation (small Z) to tunneling limit ($Z \gg 1$). For an anisotropic *d-wave* superconductor, at the given energy the tunnel current depends both on the incident angle φ of electrons at the interface normal-superconductor as well as on the orientation α , that is the angle of the order parameter $\Delta_{\pm} = \Delta \cos[2(\alpha \mp \varphi)]$. It is well known that in Point Contact experiments there is no preferential direction of the quasiparticle injection into the superconductor, so the tunneling current results by an integration over all directions inside a semisphere weighted by the scattering probability term in the tunneling current formula. Moreover because our experiments deal with a polycrystalline sample, more than one grain can be touched by the tip, consequently the angle α is a pure average fitting parameter, which depends on the experimental configuration.

In Fig. 1 we show an example of the effect of the angle α on the shape of the conductance curves. We have fixed the barrier strength $Z = 0.5$ and the temperature $T = 4.2K$, and then we have assumed an order parameter, Δ , of $3meV$. We note that, by varying α , we obtain different curves. In particular for $\alpha = \pi/4$ the ZBCP reaches a maximum which is greater than 2, for $\alpha = \pi/8$ we note a shoulder in the ZBCP slope, and finally for $\alpha = 0$ we have not bound state formation being the

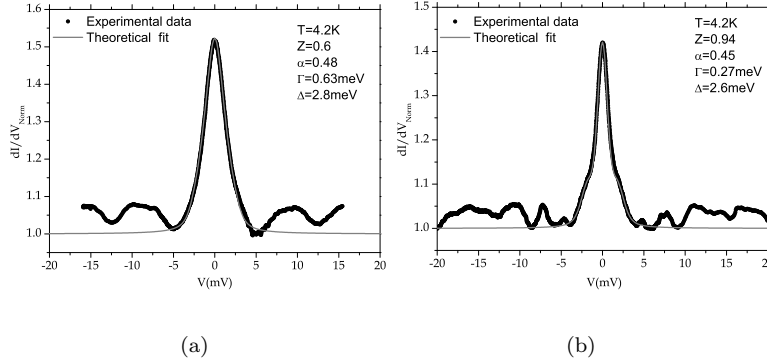


Fig. 2. dI/dV - V characteristic measured on Ru-1212/Pt-Ir point-contact junction at 4.2K. The points are experimental data. The solid line is the fit of BTK model in d -wave, the fitting parameters are: (a) $\Delta = 2.8\text{meV}$, $Z = 0.6$, $\alpha = 0.48$, $\Gamma = 0.63\text{meV}$; $\Delta = 2.6\text{meV}$, $Z = 0.94$, $\alpha = 0.45$, $\Gamma = 0.27\text{meV}$.

ZBCP absent. To understand our experimental data and to investigate the symmetry of the order parameter in $\text{RuSr}_2\text{GdCu}_2\text{O}_8$, we have fitted the $dI/dV - V$ curves with the d -wave modified BTK model⁷. In Fig. 2, two experimental conductance curves are shown together with the best fitting curves. Fitting parameters in our analysis are: the superconducting energy gap Δ , the barrier strength Z , and the angle α ; in addition to these parameters, the smearing factor Γ is introduced, which takes into account pair-breaking effects. The agreement between experimental data and theoretical model is quite satisfactory, and it yields, for the magnitude of the order parameter Δ , a value ranging between 2.6meV and 2.8meV .

In conclusion, our Point Contact spectroscopy experiments at $T = 4.2\text{K}$ on sintered $\text{RuSr}_2\text{GdCu}_2\text{O}_8$ samples exhibit unconventional superconductivity. A peak is observed at zero bias in the $dI/dV - V$ curves due to the presence of Andreev Bound States at the surface. By fitting the experimental data with a d -wave BTK model, we can estimate a superconducting energy gap $\Delta = (2.7 \pm 0.1)\text{meV}$.

References

1. J. W. Lynn, B. Keimer, C. Ulrich, C. Bernhard and J. L. Tallon, Phys. Rev. B **61**, R14964 (2000).
2. C. Bernhard *et al.*, Phys. Rev. B **59**, 14099 (1999).
3. M. Gombos, A. Vecchione, R. Ciancio, D. Sisti, S. Uthayakumar and S. Pace, Physica C **408**, 189 (2004).
4. C. Attanasio, M. Salvato, R. Ciancio, M. Gombos, S. Pace, S. Uthayakumar and A. Vecchione, Physica C **411**, 126 (2004).
5. F. Giubileo, F. Bobba, M. Gombos, S. Uthayakumar, A. Vecchione, A. I. Akimenko, and A. M. Cucolo, Int. J. Mod. Phys. B **17**, 3525 (2003).
6. S. Piano, graduation thesis (University of Salerno, 2003).
7. S. Kashiwaya, Y. Tanaka, Rep. Prog. Phys. **63**, 1641 (2000).
8. G. E. Blonder, M. Tinkham and T. M. Klapwijk, Phys. Rev. B **25**, 4515 (1982).