M ode coupling behavior of a Lennard Jones binary m ixture: a com parison between bulk and con ned phases

A. Attili^y, P. Gallo^y and M. Rovere^y,

y Dipartimento di Fisica, Universita \Roma Tre", and Democritos National Simulation Center, Via della Vasca Navale 84, 00146 Roma, Italy.

(D ated: M arch 23, 2024)

W e present a quantitative comparison at equivalent therm odynam ical conditions of bulk and con ned dynam ical properties of a Lennard Jones binary mixture upon supercooling. Both system s had been previously found to display a behavior in agreem ent with the M ode C oupling theory of the evolution of glassy dynam ics. D i erences and analogies of behavior are discussed focusing in particular on the role of hopping in reducing spatially correlated dynam ics in the con ned system with respect to the bulk.

I. IN TRODUCTION

The structural and dynam ical properties of bulk supercooled liquids are now relatively well understood in the range close to the crossover tem perature of the M ode Coupling Theory of the evolution of glassy dynamics, MCT.¹ This theory describes, in its ideal version, the relaxation mechanism of supercooled liquids as mastered by the cage e ect. The motion of atom s or molecules is restricted by the presence of nearest neighbors that surround and trap the tagged particle form ing a cage around it. W hen the cage relaxes, due to cooperative m otion, the particle di uses. Relaxation tim es of the cage diverge on approaching a tem perature T_C where, in this fram ework, the liquid undergoes a structural arrest. In most liquids this dynam ical singularity is avoided since close to T_c the hopping relaxation channel opens. The tem perature of glass transition is reached when also hopping is frozen. In this context T_c remains an important temperature that marks the ideal crossover from a regime mastered by the cage e ect to one mastered by hopping e ects. This crossover tem perature can be estim ated through an MCT analysis of dynamical properties of the liquid both with experiments and computer simulations.

Relaxation modes described by MCT are cooperative in character. Cooperativity is a basic concept in several theories and models of the glass transition. The existence of cooperative rearranging regions, CRR, intim ately related to dynam ic heterogeneities, can be a possible interpretative mechanism for the approach to the glass transition.² The extent of the CRR is expected to increases with decreasing temperature. In the presence of a restricted environment the behavior of these regions might be modiled and this might im ply a change of the dynam ical behavior. Con nement can therefore o er possible clues for a better understanding of general mechanisms for the glass transitions in the bulk. To assess the validity and the possible lim its of applicability of MCT in con nem ent can help to bridge the concepts of hopping, caging and dynam ical heterogeneities. These phenom ena appear in fact all fundam ental ingredients for the glass transition to occur. Only very faw computer simulation studies on the applicability of MCT on supercooled liquids in con ned geom etries are available.^{3,4,5,6} A detailed comparison of the dynam ics of a glass form er in the bulk and in a con ned state can give new insights in understanding the behavior of the supercooled liquids. This comparison can nonetheless be quantitatively carried out only if it is perform ed at equivalent therm odynam ical conditions.

In this paper we consider one of the m ost studied m odel for glass form er liquids, a Lennard Jones binary m ixture, LJBM, which is known to test MCT in its bulk phase⁷. We carry on a direct comparison between a set of sim ulations that we have previously published of the LJBM con ned in a disordered array of soft spheres^{8,9,10} and an equivalent bulk phase. The LJBM hosted by the m atrix is in a strong con ning environm ent where a large fraction of particles are interfacial⁸. This m icroporous m edium can be considered a model for real com pounds like silica xerogels.^{11,12,13} The con ned liquid has been found in our previous works to test MCT.^{8,9,10} R ecently them ean square displacem ent results for this system have also been found to t in the fram ework of a recently proposed m ean eld theory of the glass transition.¹⁴

A di culty to face in the comparison with the bulk is the presence of variations of the local density of the con ned LJBM as a function of temperature due to the soft sphere repulsive potential. There is not a unique way to de ne a free volum e.⁹ Therefore, in order to obtain a quantitative comparison of the dynam ical properties we performed here computer simulations of the bulk liquid along a therm odynam ical path where the (T;P) values follow the isochore obtained for the con ned system upon supercooling. This in plies that for the bulk phase analyzed in this paper the approach to T_c is not obtained along isochoric, isobaric or isotherm al paths, as usually done for bulk glass form ers.

The paper is structured as follows: in the next section

A uthor to whom correspondence should be addressed; e-m ail: gallop@ s.unirom a3.it

we present the details of the new ly perform ed bulk sin ulations, and a brief description of the previously studied con ned LJBM. The third section describes the behavior of the density correlators in the relaxation region. The fourth section explores the role of hopping in bulk com pared to con nem ent. The flh section presents an analysis of dynam ical clusters in the two system s. Last section is devoted to conclusions.

II. SIM ULATION DETAILS

W e report data analysis obtained from molecular dynam ics simulations trajectories of a Lennard-Jones 80:20 binary mixture (LJBM) de ned as in ref. 7 in the bulk phase. The LJBM state points are simulated at the sam e tem peratures and pressures of previously reported data from the sam e mixture in a con ned phase^{8,9,10}.

In the following the 80% atom s will be referred to as A and the 20% as B .

In the con ned system the LJBM was embedded in an o lattice matrix of soft spheres, labelled with S. The simulation box of the con ned system contained a rigid disordered array of N_S = 16 soft spheres. A constant volume with a selected simulation box length L = 12:6 was used. For further details referring to the con ned system see refs. 8,9,10.

Tem perature and pressure of the bulk system during cooling and equilibration procedures were controlled via a B erendsen weak coupling to therm aland pressure baths. In this case a varying box length ranging from L = 10.34 to L = 9.36 upon decreasing tem perature has been used.

For each therm odynam ical point, molecular dynam ics simulation to evaluate static and dynam ical properties, have been then perform ed in the microcanonical ensem – ble for both bulk and con ned system s.

The con ned system was studied for temperatures ranging from T = 5 to T = $0.37^{8,9,10}$ while the bulk range of temperature investigated for comparison goes from T = 5 to T = 0.48. T = 0.37 and T = 0.48 represent the low est temperatures at which we are respectively able to equilibrate the con ned and bulk system.

W e used a tim estep of 0.01 for T > 0.53 and 0.02 for T < 0.53 for the con ned system and 0.01 for T > 0.8 and 0.02 for T < 0.8 for the bulk system. The total production time of the lowest temperature investigated, T = 0.37, was of $t_{run} = 14$ m illions of timesteps. These values would correspond for liquid A rgon to T = 44.3 K and $t_{run} = 4.2$ s.

The behavior of total energy, pressure and, for the bulk, density as a function of temperature is depicted in Fig. 1. Them odynamic (T;P) points of the bulk follow the isochoric path found upon supercooling for the con ned system⁹. In the same panel we note also that upon supercooling, in the range of investigated temperatures, an increase of number density occurs in the bulk system where = 0:9 1:2. In the con ned system the density cannot be exactly calculated due to the presence

of the repulsive soft sphere potential. However a qualitative estimate of the density of the conned mixture carried out with Voronoi tessellation has been reported in ref.9. The range of densities estimated with this method for the conned system was found to be $= 0.7 \quad 1.2$, similar to that found in our equivalent bulk liquid.

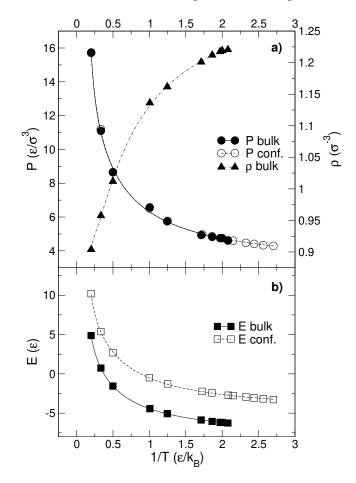


FIG.1: a) P ressure as a function of inverse temperature of both bulk and con ned⁹ system s; the corresponding bulk density is also shown. b) Total energy per atom versus inverse temperature for bulk and con ned⁹ system s. In both panels, lines depict sim ple polynom ial interpolations.

In the lower panel of F ig 1 we also reported the values of the total equilibrium energies per atom of the two system s. A similar trend is observed. As expected the energy of the con ned system is shifted above the bulk one due to the additional term of interaction with the soft spheres in the potential energy. At higher tem peratures an average increase of about 5.0 $_{\rm A}$ of the internal energy of the con ned system is found. This di erence tends to reduce asymptotically to 3.0 $_{\rm A}$ upon cooling. Over the range of tem peratures and densities investigated the bulk and the con ned liquids show no signatures of phase separation as we can deduce from the smoothness of the curves. This is consistent with a study of the liquid lim its of the bulk LJBM .¹⁵.

W e found that the main features of the pair correlation

functions and of the static structure factors of our bulk LJBM (not reported) are sim ilar to those of the con ned liquid⁹.

III. THE ALPHA-RELAXATION REGION

The slowing down of the dynamics of a supercooled liquid on approaching $T_{\rm C}\,$ can be characterized by analyzing the tem perature dependence of the single particle or self interm ediate scattering function F $^{\rm (s)}$ (Q;t), SISF, for both types of particles. In this section we report the bulk results on the SISF analysis compared to the previously obtained results for the con ned system $.^{8,9,10}$

The tem perature dependence of the bulk SISF is analyzed in the following for wave lengths corresponding to the inter-particle spacing, i.e. for $Q = Q_{MAX}$ (T), bcated at the rst peak of the static structure factors. A round these values of Q MCT features are best evident.¹ Since the positions of the di raction peak show a weak T dependence in order to pursue consistently our com parison we use for the bulk analysis the same values of $Q_{MAX;A} = 7.06$ and $Q_{MAX;B} = 5.90$ that we used in the con ned LJBM ¹⁰.

The results for A particles are reported in Fig.2 for both bulk and con ned¹⁰ systems on the same scale for a close comparison. Sim ilar results are found for B par-

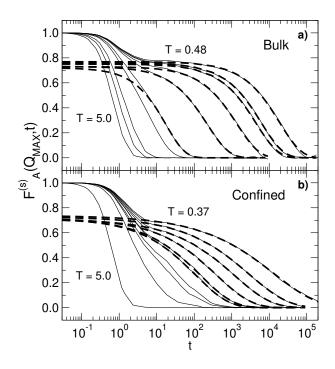


FIG.2: Self part of the interm ediate scattering function for the A particles, $F_A^{(s)} (Q_{MAX}; t)$, for di erent tem peratures for the bulk (a) and the con ned (b)¹⁰ system s. The correlators are evaluated at $Q_{MAX} = 7.06$, the position of the rst peak in the static structure factor for the A A correlation. The dashed lines are ts to KWW stretched exponential (see Eq.1), in the region of the late relaxation.

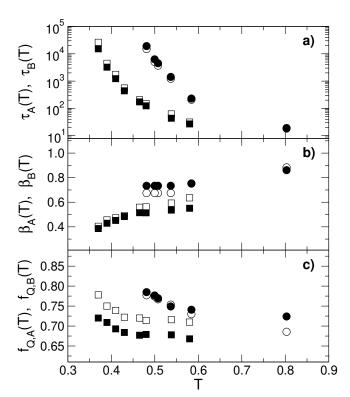


FIG.3: Fitting parameters of the KWW curves plotted in Fig.2 for both bulk and con ned system s as functions of the tem perature. Circles refer to bulk A (lled) and B (open) particles. Squares refer to con ned¹⁰ A (lled) and B (open) particles. a) Relaxation times $_{\rm A}$ (T) and $_{\rm B}$ (T). b) Stretching parameter $_{\rm A}$ (T) and $_{\rm B}$ (T). c) Form factor f_{QA} (T) and f_{QB} (T).

ticles (not reported). From the gure we recognize upon supercooling for both bulk and con ned m ixtures the onset of the MCT predicted two-step relaxation scenario. AtT_C in the idealized version of MCT this scenario leads to the bifurcation of the long time lim it of the correlator. This lim it also called non ergodicity parameter, is zero for the liquid and jumps to a nite value on crossing the MCT critical line. The existence of the plateau is related to the MCT two time fractals. The dynam ical regime that covers the approach to the plateau of the correlator is referred in literature as the relaxation regime. This regime is followed by the relaxation that starts when the correlator departs from the plateau. For long relaxation regime, the interm ediate tim es, in the late scattering function decays to zero in a non-exponential fashion.

W e note that the shape of the correlators in bulk and con ned liquids di ers. In particular at the lowest tem – peratures investigated, T = 0.48 and T = 0.37 respectively for bulk and con ned systems, the extension of the plateau rapidly grows spanning up to over three decades in the bulk, while it is much less de ned and covers only one decade in the con ned system. A fler the plateau the correlator decays much faster to zero in the bulk than in the con ned system where long time tails related to a more consistent stretching of the relaxation law can be observed.

The T dependence of the relaxation time (T), can be extracted from the ts of the F $^{\rm (s)}$ (Q;t) to the K ohlrausch-W illiam s-W atts (K W W) stretched exponential function

(t) =
$$f_Q$$
 (T) exp (t= (T)) (T); (1)

where (T) is the stretching parameter. $f_{\rm Q}$ (T) can be considered as an elective Lamb M ossbauer factor and is related to the height of the plateau.¹ In the ideal version of the theory this height coincides with the non ergodicity parameter for T $_{\rm Tc}$, $f_{\rm Q}$ (T) = $\lim_{t \geq 1}$ (t).¹

A lthough the KWW functional form is not an exact solution of MCT equations, it has been shown that it is able to reproduce remarkably well the behavior of the num erical solution evaluated from these equation, in the relaxation regim e.¹

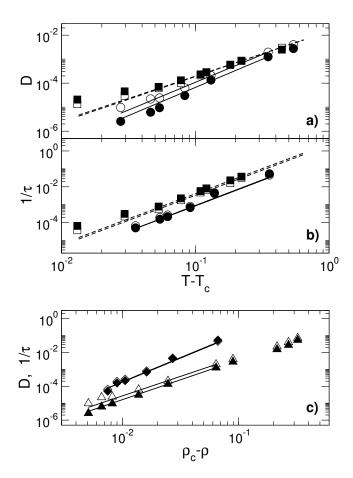


FIG.4: Power law ts of the di usion coe cients (a) and of the inverse relaxation times (b) as a function of temperature for con ned (squares) 10 and bulk (circles) liquids. In (c), only for the bulk case, analogue power law behavior of D (triangles) and (diam onds) as functions of density is shown. In all panels lled symbols refer to A particles, open symbols to B particles. The extrapolated MCT parameter, $T_{\rm C}$ and $_{\rm c}$, and exponent , are reported in Tab.I.

	Bulk Mixture		Conf. Mixture				
	А	В	А	В			
(from D)							
$T_{\rm C}$	0 : 453	0 : 453	0:356	0:356			
С	1:226	1:226					
	2:348	2 : 309	1 : 860	1:890			
(from)							
$T_{\rm C}$	0 : 445	0 : 445	0:356	0:356			
С	1:228	1:228					
	2 : 849	2 : 987	2:80	2 : 80			

TABLE I: Power-laws t parameters of bulk and con ned¹⁰ mixtures, for A and B atoms. In the upper half of the table are reported values obtained from the analysis of di usion constants D, while in the lower part values obtained from the analysis of relaxation times \cdot .

The results of the t are reported, together with the density correlators, in Fig. 2 where we can see that the agreem ent of the tting function to the correlators curves is very good.

Fitting param eters for both particle types in bulk and con ned¹⁰ systems as functions of the tem perature, are shown in Fig. 3.

As expected for system s testing MCT, the relaxation times $_{\rm A}$ (T) and $_{\rm B}$ (T) increase dram atically as the tem – perature is lowered, varying up to four order of m agnitude in the T ranges investigated. Similar trends in bulk and in connem ent^{10} are observed but we note that the relaxation times for the conned system are consistently smaller than those of the bulk. This is a clear indication of a faster dynamics due to repulsive connem ent.

The departure from the Debye exponential relaxation is quantied by the stretching parameters $_{\rm A}$ and $_{\rm B}$. These can be connected to the presence of heterogeneity in the dynam ics, due to the coexistence of dynam ical regimes characterized by a distribution of relaxation times. The stretching parameters of both systems have values close to 1 (sim ple D ebye relaxation) at high tem peratures. MCT asymptotically predicts these param eters to have a weak temperature dependence. This prediction is satis ed in the bulk liquid, where, upon decreasing the temperature, the parameter is seen to lower and to reach a constant plateau value close to 0.8, whereas, in the case of the con ned system, the parameter does not reach a constant value, but instead keeps on decreasing regularly down to 0.4 at the lowest tem perature investigated¹⁰. W e will see in the next section that the latter behavior can be related to the presence of signi cant hopping processes found in the con ned system at these tem peratures.

The T dependence of the parameter f_Q (height of the plateau) is rather weak as predicted by MCT and has a similar trend in both con ned¹⁰ and bulk systems. We found 0:70 f_Q 0:77 for the bulk with similar values

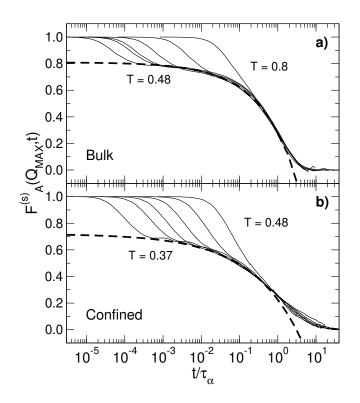


FIG.5: Self part of the interm ediate scattering function for the A particles, $F_A^{(s)}$ (Q_{MAX};t), with Q_{MAX} = 7.06, for di erent tem peratures, scaled by (obtained from a KWW t, see Fig. 3); the dashed curve is the t to a von Schweidler law de ned in Eq. 4, (see Tab. II). In (a) are presented bulk correlators at tem peratures 0:48 T 0.8, in (b) con ned correlators at tem peratures 0:37 T 0:43.¹⁰

for di erent species. For the con ned system di erent values for A and B particles were found: 0:66 f_Q 0:72 for A particles and 0:72 f_Q 0:77 for B particles.

	Bulk Mixture		Conf. Mixture	
	А	В	А	В
f_Q^c	0:81	0:81	0 : 72	0 : 80
h_{Q}	0 : 52	0:53	0:35	0 : 43
b	0 : 450	0:531	0:355	0:340
r_s^b	0:197	0:216	0:246	0:222
r ^{M SD}	0:179	0:220	0:234	0:232

TABLE II: Von Schweidler t parameters of bulk and conned 10 m ixtures, for A and B atom s.

A coording to the ideal version of M C T, the relaxation times, , as well as the di usion coe cients, D, are expected to follow asymptotically a power-law divergence as functions of temperature and density near the cross-over point (T_C; _C)

$$D; {}^{1} / (T T_{C}); D; {}^{1} / (_{C}); (2)$$

where T_c and $_c$ are respectively the cross-over tem perature and density of the theory, and is the exponent param eter. The ts to power-laws are reported in Fig. 4 overlayed to and D data found in both con ned¹⁰ and bulk systems. The coe cients D are extracted from the m ean square displacements (MSD), not reported, in the di usive regime.

W e found good agreem ent of the relations of Eq.2 with the data in the range 0.48 T 0.80 (1:16 1:22) for the bulk to be compared to 0:41 T 0:58 obtained for the con ned system 10 . These values correspond, in terms of the small parameter of the theory = ($T_{\rm C}$ T)= $T_{\rm C}$, to a relative reduction of the ideal MCT range of applicability in con nem ent of about 30% with respect to the bulk.

Results for the tting parameters are reported in table I. $T_{\rm C}$, and (for the bulk only) $_{\rm C}$, are similar for the di erent species A and B as predicted by the theory. The same crossover temperature is found from D and . In the con ned liquid $T_{\rm C}$ ' 0:36 is sensibly lower than in the bulk $T_{\rm C}$ ' 0:45.

The critical density of the bulk is slightly higher than the density simulated for the lowest temperature bulk, and also very close to the estimate of the density of the lowest temperature in the con ned system, see Sec. II.

W e note that the values of extracted from are sim ilar for both bulk and con ned mixtures, 2:8. C ontrary to the M C T predictions, the values of extracted from D di er from those extracted from both in bulk and in con ned system s. This di erence is more marked in the presence of con nem ent and a possible source of these discrepancies is the presence of hopping that will be discussed in sec. IV.

The time-temperature superposition principle, TTSP, predicted by MCT to hold asymptotically near $T_{\rm C}$, states that the shape of the correlator curves in the late

relaxation and early relaxation time regimes does not depend on temperature. Consequently the intermediate scattering functions can be written as

$$F^{(s)}(Q;t) = \hat{Q}(t=(T))$$
 (3)

where is a time scale associated to the relaxation decay of the correlation function and \hat{Q} is a master function. We used in the scaling of the SISF the (T) obtained via KWW ts.

The correlators are plotted for di erent tem peratures versus rescaled tim et=(T) in Fig.5 for A particles. The interm ediate scattering functions reported in the gure are evaluated in the same tem perature ranges used in the analysis of power-law divergence, i.e. 0.4 for the con ned mixture¹⁰ and 0.7 for the bulk one. From the gures it is seen that also for the bulk with varying density the rescaled correlator curves fall on top of each other within the the late relaxation region up to the

relaxation time range. Sim ilar results hold also for B particles (not show n).

MCT theory predicts also a precise functional form of the master function $\hat{}$ (t) in the relaxation regime. The

form is a von Schweidler (VS) power law,

$$(t) = f_{Q}^{c} \quad h_{Q} \ (t=)^{b}$$
: (4)

Best ts to our master plots are included in Fig 5 (dashed lines). Rescaled time intervals used in the ts are 10 ³ t= 10° . The values of the free param – eters, $f_0^{\,c}$, $h_{\mathbb{Q}}\,$ and b are reported in Tab. II. As it can be seen from the gures, there is a good agreem ent with the data while we observe that the prediction of MCT that b should be the same for both A and B particles is veried only in con nem ent. The better agreem ent with MCT of the con ned system might be related to packing constraint induced by the con ned geom etry and the repulsive potential that further reduce the tendency of the m ixture to phase separation. As already observed for the stretching param eter the von Schweidler exponent b low ers in con nem ent re ecting a larger distribution of the relaxation times. The critical non ergodicity parameter f_0^c o ers an estim ate of the m ean square displacem ent r_s^2 of the particles at a time $t = 1 = !_{c}$, where $!_{c}$ is the cuto frequency below which the whole alpha peak is located, i.e. the time where the relaxation starts. In fact:

$$\ln f_{Q}^{c} = \frac{(r_{s}Q)^{2}}{3} + O(Q^{4})$$
 (5)

The values of the $r_{\rm s}$ extracted both from Eq.5 are consistent with the ones obtained from the plateau of the M SD (not shown) as reported in Tab.II. We observe that A and B particles in con nement and B particle in bulk m ove on sim ilar distances while the packing of large A particles is stronger in the bulk.

W e note that the VS law has been tested to be valid for an extended range of Q around the peak of the structure factor for both con ned and bulk system $s^{7,10}$, not shown here.

IV. HOPPING EFFECTS

A. van Hove Correlation Function

To investigate the relevance of hopping e ects above $T_{\rm C}\,$ in our system s we now investigate the distribution of the average distances. This can be done by m eans of the self part of the van H ove correlation function (VHCF) de ned as

$$G^{(s)}(r;t) = \frac{1}{N} \bigvee_{i=1}^{N} (r_{i}(t) r_{i}(0) r); \quad (6)$$

This function is related to the intermediate scattering function via Fourier transform and 4 $r^2G^{(s)}(r;t)$ is the probability density for a particle of specie of being displaced of a distance r in a time intervalt.

The van Hove correlator as a function of the distance r, has been evaluated for di erent temperatures and for

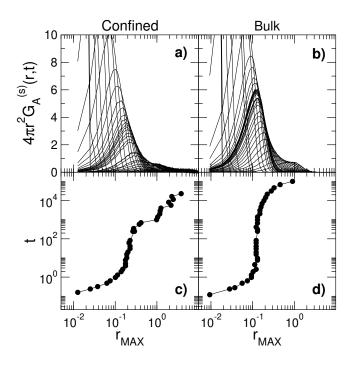


FIG. 6: Self part of the van H ove function (for A particles) evaluated at T = 0.48 for the con ned (a) and the bulk (b) system s. The range of time used is 2 10^2 t 10^5 for the bulk and 2 10^2 t 2 10^4 for the con ned system s. In panels (c) and (d) are displayed, in a double logarithm ic scale, the positions of the peaks in the van H ove function (x axis), for con ned and bulk system s respectively, versus times (y axis).

several di erent tim es, that span from the ballistic to the di usive regim e of the MSD, 10 $^2\,$ t $\,10^5$, with a t $\,2^n\,$ geom etric progression. The evaluations have been carried out for both A and B particles and for each system .

In Fig. 6 we report a comparison between the distance distributions found in the con ned and bulk LJBM (panel (a) and (b) respectively). In these plots both systems are observed at the same temperature T = 0.48, i.e. the lowest temperature simulated for the bulk liquid. From these gures we can see that in both systems the distribution shows a simple G aussian shape. The G aussian peak maxim a shift at greater distances, when the curves are sam pled at increasing delay times.

In both bulk and con ned systems the shift follows a quadratic t dependence for early times, 0.01 < t < 1, typical of the ballistic motion of the particles. For greater times than those of the ballistic regime, a time range where the curves cluster on each other as predicted by MCT starts to develop. This clustering is evidenced in the plots reported in panel (c) and (d) of Fig. 6, where the positions of the maxima in the VHCF at their corresponding times are reported in a double logarithm is scale. In the case of the bulk liquid, the time range correspond to 2 < t < 3 10³, and the curves shows a tendency to

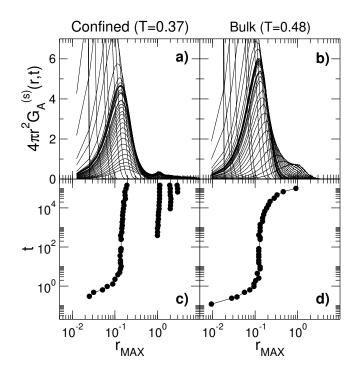


FIG. 7: Self part of the van H ove function (for A particles) evaluated at T = 0:37 for the con ned (a) and T = 0:48 for the bulk (b) system s. The range of time used is 2 10² t 10⁵ for the bulk and 2 10² t 2 10⁴ for the con ned system. In panels (c) and (d) are displayed, in a double logarithm ic scale, the positions of the peaks in the van H ove function (x axis), for con ned and bulk system respectively, versus times (y axis).

cluster at the localization radius r 0:15. At the same tem perature, for the con ned system we found a similar but less pronounced clustering in the more limited range 3 < t < 2 10^2 and at r 0.2. The position of the peak of the VHCF remains constant for the presence of oscillating particles which are trapped in their transient cages. The time ranges in which we observe this trapped dynam - ics correspond to those of the plateau seen in the SISF. We note how at this tem perature the e ect of trapped dynam ics is more accentuated in the bulk than in the con ned system.

In the study of the supercooled phase in the asymptotic region near $T_{\rm c}$ of MCT, a more signi cant comparison for the details of the dynam ical behavior is achieved by considering not absolute tem peratures, but instead tem – peratures relative to the critical tem perature, i.e. therm odynam ic conditions with the same value of the sm all parameter of the theory . This comparison is supported by the validity of the TTSP for the supercooled regime. In the previous section we demonstrated that this principle is indeed satis ed by our system s.

We now compare in Fig. 7, in the same fashion, the VHCF for the two lowest temperatures simulated in bulk and con nement. These temperatures correspond to the same distance from the respective T_c . Their value of

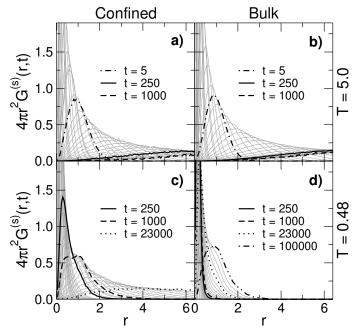


FIG. 8: Comparison between bulk and con ned systems for the self part of the van H ove correlation function $G^{s}(r;t)$ for A particles, evaluated at a high (T = 5.0) and at a low tem – perature (T = 0.48). Curves belonging to di erent times are displayed in the same plot, some of these curves are plotted with thicker lines. The four panels, adopting the same e scales, represent $G^{s}(r;t)$ for: a) con ned system, T = 5.0; b) bulk system, T = 5.0; c) con ned system, T = 0.48; d) bulk system, T = 0.48.

the small parameter is = 0.04. An interesting feature is observed for the conned case. The particles remain trapped in the frozen cage for a time longer than the bulk. E scape is guaranteed only by hopping. In this correlator in fact now three hopping peaks are clearly visible for the A particles while hopping is totally absent for this kind of particles in the bulk for the time scales of the gure.

In order to evidence the behavior of the G^(s) (r;t) at higher times (and higher distances) we show in Figs. 8, 9 and 10 a four-panel com parison of the correlators reported in a linear scale, between correlation functions for A and B atom s, bulk and con ned system s. In Fig. 8 the comparison is reported only for A particles in bulk and con nement at a high temperature and a low temperature. W hile at high tem perature the system s exhibit very sim ilar correlators at the sam e tim es, larger di erences are found at the lower tem perature, where the behavior of the van Hove correlators indicates a much greater m obility and a more evident presence of hopping of particles in the con ned system than in the bulk. In Fig. 9 the comparison is carried out at the same low temperature, T = 0.48, for both kind of particles. From the gure it can be argued that the small B particles have a larger tendency to exhibit hopping in the bulk. It is also clear that con nem ent succeeds in reducing hopping

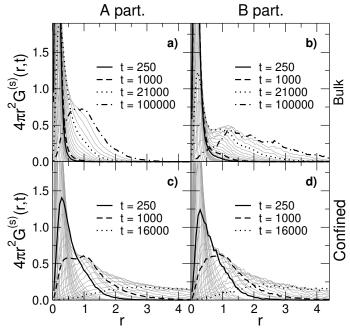


FIG. 9: C om parison between bulk and con ned system s and between di erent species of particles, for the self part of the van H ove correlation function $G^{s}(r;t)$. The correlators are evaluated at the same tem perature, T = 0.48, and for di erent times, some of these evidenced with thicker lines. The four panels, adopting the same scales, represent $G^{s}(r;t)$ for: a) bulk system, A particles; b) bulk system, B particles; c) con ned system, A particles; d) con ned system, B particles.

for B particles and to enhance hopping for A particles. The comparison carried out at the same is reported in Fig. 10. From this comparison it is even more clear than in the former gures what is the fundam ental di erence between the dynamics in the bulk and the dynamics in con nement. In the bulk we have hopping only for B particles. For these particles the phenom enon is marked, but in a quite distinct time range with respect to the time range of the caging. In con nem ent for both A and B particles we have a marked hopping already when a part of the particles is still rattling in the cage. The overall result is that dynam ics appears sim ilar for A and B particles only in con nem ent.

B. Non-Gaussian Parameter

The deviation from the G aussian behavior of G $^{(s)}$ (r;t) can be analyzed in terms of the non-G aussian parameter¹⁶:

which is the relative deviation between the r^4 (t) obtained from simulations and the value it should have if G^(s) (r;t) was Gaussian. The non Gaussian parameter

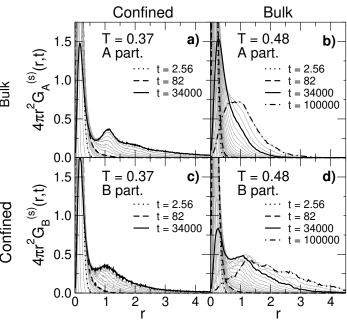


FIG. 10: Comparison between bulk and con ned⁹ systems s and between di erent species of particles, for the self part of the van H ove correlation function G^(s) (r;t). The correlators are evaluated at the same value of the sm all parameter = 0.04 of M C T, which correspond to tem peratures T = 0.48 for the bulk liquid and T = 0.37 for the con ned system. The correlator is shown in the time space region where hopping is visible, i.e. the late relaxation regime. The functions are normalized to unity. The four panels, adopting the same scales, represent G^s (r;t) for: a) con ned system, A particles; b) bulk system, A particles; c) con ned system, B particles; d) bulk system, B particles.

can be studied in order to quantify the e ects of dynam ic heterogeneity, as hopping processes, and it can also be obtained experimentally from the Q-dependence of the D ebye W aller factor.¹⁷

In gure 11, ⁽²⁾ (t) is shown as a function oft for A and B particles for di erent tem peratures. The same result for the con ned system is reported for com parison⁹. We note that the ⁽²⁾ (t) behavior for both systems is sim – ilar to that found in several other simulations on bulk liquids close to glass transition⁷: ⁽²⁾ (t) increases significantly in the late relaxation region, near the onset of the relaxation, where it reaches its maximum, then it decays to zero as t! 1. Furtherm ore, a master curve is found overlapping the individual curves in a time interval just before they attain their maximum. However we note that, in our con ned system, such master curve is considerably less de ned than in the bulk.

In the bulk system the non Gaussian parameter appears very dierent for A and B particles and never exceeds the value of 2 for A particles. This can be connected to the observed negligible hopping above T_c for A particles. In the con ned system we have instead similar parameters for A and B particles and their values grow

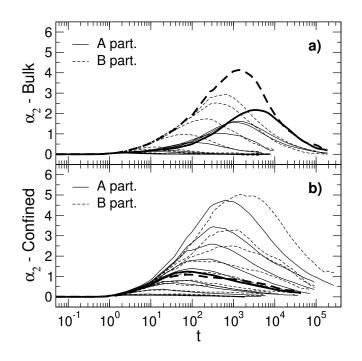


FIG. 11: The non-Gaussian parameter $A_{A}^{(2)}$ (t) (continuous lines) and $B_{B}^{(2)}$ (t) (dashed lines) for the bulk (a) and con ned⁹ (b) system s. Higher curves correspond to low er tem peratures 0.48 T 5.0 for the bulk and 0.37 T 5.0 for the con ned system s. Thicker lines in both gures are associated to the low est tem perature (T = 0.48) for the bulk.

substantially as we supercool. For the lowest tem perature investigated in con nem ent the peak heights are around 5. Hopping appears therefore to cause a much more marked deviation from gaussianity than MCT behavior and it also seem s to lead to a disappearance of the master curve.

V. CLUSTER DYNAM ICS

Extensive investigations of LJBM with a large number of particles have shown recently the important role of the cooperative m olecular m otion in the interpretation of the slow dynam ics and the behavior of the relaxation in liquids upon supercooling close to T_c .² W e expect that connem ent induces m odi cations in the CRR m echanism . We have investigated for our LJBM both in bulk and in con ned phases the possible existence of a spatially correlated dynam ics. An estim ate of the typical distance of the particles correlation can be obtained from an analysis of clusters of nearest neighbors. In our analysis two particles belong to the sam e cluster if the maxim um distance they reach from each other within a xed time t is less equal than + = 0:1. In Fig. 12 where we show the distribution functions of the size of the num ber of particles, N_p of the dynam ical clusters for di erent time ranges tused in the sam pling at di erent tem per-

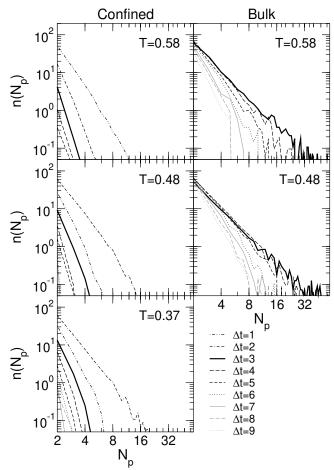


FIG.12: Distribution of the size N $_{\rm p}$ (number of particles) of the dynamical clusters found in the con ned (rst row of panels) and in the bulk (second row of panels) liquids, for the tem peratures T = 0.58, 0.48 and 0.37. Dierent curves correspond to dierent time ranges used in the sam pling (lifetime of the clusters).

atures.

W e observe that in the bulk the larger clusters, corresponding to the shorter xed times, arrive to circa 32 particles and that at the low est tem perature investigated the distribution function of the clusters remains unchanged up to t = 5. In con nem ent the maximum size of the clusters does not exceed 16 particles and persists only for a very short time also for the lowest tem perature. In the bulk a very precise analysis of these spatial correlations has been already carried out for the same LJBM . The authors use a much larger sample and are able to distinguish between mobile and immobile particles.² Both these kind of particles show a distribution of the sizes sim ilar to what found in our smaller bulk sample. Com paring our analysis of the bulk and con ned systems we observe that in con nem ent spatial correlations are strongly depressed. This can be connected to the fact that at variance with the bulk in the con ned system hopping mechanisms intervene while cages are still relaxing. The authors of ref. 2 in their study of the bulk phase of the LJBM underline in fact the importance of subsequential relaxation processes for spatially correlated dynam ics. At any given time most particles are localized in cages and a small fraction forms cooperative strings. Once rearranged these particles become caged and others become mobile. The clarication of this point needs further investigation and can be possibly connected with the behavior of the inherent structures in connement.¹⁸

VI. CONCLUSIONS

We perform ed an accurate study of the behavior of a LJBM upon supercooling. The system has been studied along the therm odynam ical path corresponding to the isochoric path of a previous study of the same liquid in con nem ent. In this way we could carry out a quantitative com parison between the two systems.

The analysis of the density correlators in the alpharelaxation region shows that the MCT predictions are satis ed by our bulk system that approaches the critical curve upon decreasing temperature with a path where the volum e is not constant.

On comparing the SISF of the bulk with the conned one we have conmed and quantied the dierences and analogies between the two systems that we did hypothize in our previous studies^{8,9,10}. In particular we have observed a dierence in the slope of the tail of the correlators and a much less de ned plateau in connement. This leads to a substantially lower value of the stretching parameter . Besides the values do not reach a constant value upon decreasing tem perature at variance with those of the bulk liquid. The crossover tem perature in the con ned case is lower with respect to bulk.

D iscrepancies with the MCT predictions for the expodeterm ining the asymptotic behavior of the renent laxation time and the di usion coe cient are found to be more marked in con nement. This can be ascribed to the hopping phenom enon that in con nem ent plays above and near $T_{\rm C}$ a more signi cant role than in the bulk. In the bulk in fact hopping e ects appear only for the smaller B particles and in a time range well distinct from the time range of the cage e ect. In con nem entwe observe hopping e ects for both species of particles in a tim e scale that coincides with the tim e scale of caging. A s a consequence MCT behavior is partially hidden. In fact the TTSP is veried also in con nement but in a much sm aller range of tem peratures, analogously to the power law behavior. Also the prediction that the exponent b extracted from the von Schweidler should be the same for A and B particles is veried only in con nement.

Hopping e ects determ ine deviation from gaussianity moremarked in connement than in bulk. The non Gaussian parameters are dierent for A and B particles in the bulk but they are very similar in connement.

Finally our comparison of the cluster dynam ics in connem ent and in bulk shows that clusters in the con ned system have smaller sizes and last shorter time than in the bulk. Further analysis of cooperativity in con ned glass form er would require to study larger system s, but present results show that in the presence of a restricted environm ent cooperativity is at least partially inhibited.

- ¹ Gotze W .and Sjogren L.Rep.Prog.Phys.55,241 (1992); Gotze W .in Liquids, Freezing and Glass Transition Eds. J.P.Hansen J.P., Levesque D., Zinn-Justin J., North Holland, Am sterdam (1991); J. Phys.: Condens. Matter 11, A1 (1999).
- ² C. Donati, S.C. G lotzer, P.H. Poole, W. Kob and S.J. Plim pton, Phys. Rev. E 60, 3107 (1999).
- ³ V.K rakoviack, Phys. Rev. Lett. 94, 065703 (2005).
- ⁴ F.Vamik, J.Baschnagel and K.Binder, Phys. Rev. E 65, 021507 (2002).
- ⁵ Gallo P., Rovere M., Spohr E., Phys. Rev. Lett. 85, 4317 (2000); J. Chem. Phys. 113, 11324 (2000).
- ⁶ P.Scheidler, W.Kob and K.Binder, Europhys. Lett. 52, 277 (2000); J.Phys.Chem.B 108, 6673 (2004).
- ⁷ Kob W . and Andersen H. C., Phys. Rev. Lett. 73, 1376(1994); Phys. Rev. E 51,4626 (1995); Phys. Rev. E 52,4134 (1995).
- ⁸ P.Gallo, R.Pellarin and M.Rovere, Europhys. Lett 57, 212 (2002).

- ⁹ Gallo P., Pellarin R. and Rovere M., Phys. Rev. E 67, 041202 (2003).
- ¹⁰ Gallo P., Pellarin R. and Rovere M., Phys. Rev. E 68, 061209 (2003).
- ¹¹ Rosinberg M.L. in New Approaches to problem s in liquid state theory. Eds. C. Caccam o, J.P. Hansen and G. Stell, Kluwer A cadem ic Publ. (1999).
- ¹² Sarkisov L. and Monson P. A. Phys. Rev. E 61, 7231 (2000).
- 13 Page K.S.and M onson P.A., Phys. Rev. E 54, R29 (1996).
- $^{14}\,$ M ichio Tokuyama, Physica A to be published (2005).
- ¹⁵ S.Sastry, Phys. Rev. Lett. 85, 590 (2000).
- ¹⁶ J.P.Boom and S.Y ip, M olecular Hydrodynam ics (D over, New York, 1980).
- ¹⁷ R.Zom, Phys. Rev. B 55, 6249 (1997).
- ¹⁸ A.Attili, P.G allo and M.R overe, Phys. Rev. E 71, 031204 (2005).