

Magnetic order in the quasi-one-dimensional spin 1/2 chain, copper pyrazine dinitrate

T. Lancaster,¹ S.J. Blundell,¹ M.L. Brooks,¹ P.J. Baker,¹ F.L. Pratt,² J.L. Manson,³ C.P. Landee,⁴ and C. Baines⁵¹ Clarendon Laboratory, Oxford University Department of Physics, Parks Road, Oxford, OX1 3PU, UK² ISIS Facility, Rutherford Appleton Laboratory, Chilton, Oxfordshire OX11 0QX, UK³ Department of Chemistry and Biochemistry, Eastern Washington University, Cheney, WA 99004, USA⁴ Department of Physics, Clark University, Worcester, Massachusetts 01610, USA⁵ Swiss Muon Source, Paul Scherrer Institut, CH-5253, PSI Villigen, Switzerland

(Dated: December 23, 2021)

We present the first evidence of magnetic order in the quasi-one-dimensional spin 1/2 molecular chain compound, copper pyrazine dinitrate $\text{Cu}(\text{C}_4\text{H}_4\text{N}_2)(\text{NO}_3)_2$. Zero field muon-spin relaxation measurements made at dilution refrigerator temperatures show oscillations in the measured asymmetry, characteristic of a quasistatic magnetic field at the muon sites. Our measurements provide convincing evidence for long range magnetic order below a temperature $T_N = 107(1)$ mK. This leads to an estimate of the interchain coupling constant of $J^0/J = 0.046$ K and to a ratio $J^0/J = 4.4 \times 10^{-3}$.

PACS numbers: 75.10.Pq, 75.50.Ee, 76.75.+i

Experimental studies of quantum many-body physics rely on the existence of simple and well characterised model systems. One such system is the linear chain Heisenberg antiferromagnet (LCHAFM) which is described by the Hamiltonian

$$H = \sum_i [JS_iS_{i+1} + g_B B \cdot S_i] \quad (1)$$

where J is the nearest neighbour exchange constant along the chain and B is an applied magnetic field. For $B = 0$, the system will not show long-range magnetic order (LRO) for $T > 0$, but will display excitations in the form of $S = 1/2$ spinons which form a gapless, two-particle continuum [1, 2]. The magnetic field B can tune the system through a quantum critical point (QCP) [3], (i.e. a zero temperature phase transition) at $B_J = 2J/g_B$ where the spin state becomes fully polarized [4, 5].

Experimental realisations of the LCHAFM have been made in several copper chain compounds, the most successful of which is copper pyrazine dinitrate $\text{Cu}(\text{C}_4\text{H}_4\text{N}_2)(\text{NO}_3)_2$ or CuPzN. This material has a relatively low value of J ($\approx 10.3(1)$ K, determined from high field magnetization and specific heat measurements [6]), ensuring the QCP is at an experimentally accessible magnetic field, but also a small ratio of intrachain to interchain exchange constants (estimated as $J^0/J < 10^{-4}$ [7]), showing that the chains are well isolated. This has allowed the magnetic field dependence of the excitations in the two-spinon continuum to be measured and led to the identification of an extended critical state [8], confirming long-standing predictions of theoretical and numerical studies [9, 10, 11]. Three-dimensional (3D) LRO has not been detected in CuPzN down to 70 mK on the basis of specific heat measurements [2]. However, as we shall demonstrate, implanted positive muons are a much more sensitive probe of 3D LRO than specific heat for the case of very anisotropic magnetic chains. In this letter we

show for the first time that CuPzN does indeed undergo a transition into a state of 3D LRO and provide an estimate of J^0/J which is larger than previously thought.

Zero-field muon-spin relaxation (ZF + SR) measurements were made on a powder sample of CuPzN using the LTF instrument at the Swiss Muon Source (SS), Paul Scherrer Institut, Villigen, Switzerland and the MUSR instrument at the ISIS facility, Rutherford Appleton Laboratory, UK. In a +SR experiment [13] spin polarised muons are implanted into the sample. The quantity of interest is the asymmetry $A(t)$, which is proportional to the spin polarization of the muon ensemble.

Example ZF + SR spectra measured using a dilution refrigerator at SS are shown in Fig.1. In spectra measured below a temperature $T = 110$ mK oscillations in the asymmetry are observed (Fig.1(a)). These oscillations are characteristic of a quasi-static local magnetic field at the muon stopping site, which causes a coherent precession of the spins of those muons with a component of their spin polarization perpendicular to this local field (expected to be 2/3 of the total polarization). The frequency of the oscillations is given by $\omega = B_i \gamma$, where γ is the muon gyromagnetic ratio ($\approx 2 \times 135.5$ MHz T^{-1}) and B_i is the average magnitude of the local magnetic field at the i th muon site. Any fluctuation in magnitude of these local fields will result in a relaxation of the oscillating signal, described by relaxation rates Γ_i . The presence of oscillations at low temperatures in CuPzN provides convincing evidence that this material is magnetically ordered below 110 mK.

Two separate frequencies were identified in the low temperature spectra, corresponding to two magnetically inequivalent muon stopping sites in the material. We note here that two muon sites have been observed in other copper pyrazine-based compounds [14]. The precession frequencies, which are proportional to the internal magnetic field as experienced by the muon, may be

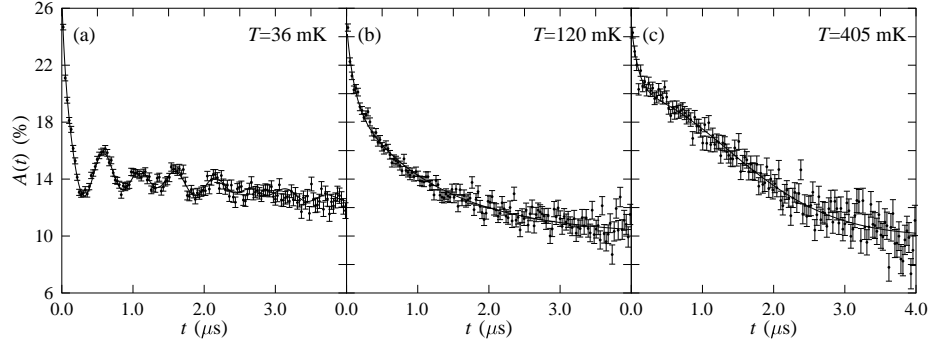


FIG. 1: ZF + SR spectra for CuPzN at three temperatures. (a) $T = 36$ mK: Oscillations are observed in the asymmetry, characteristic of long-range magnetic order. $A(t)$ is shown to Eq.(2). (b) $T = 120$ mK: the spectra are described by two components. A fast relaxing signal, probably due to the existence of a radical state, and a larger component, seen to be exponential in form. $A(t)$ is shown to Eq.(3). (c) $T = 405$ mK: The fast relaxing component is still evident, although the larger component now shows a Gaussian form. $A(t)$ is shown to Eq.(3).

viewed as an effective order parameter for these systems. In order to extract the temperature dependence of the frequencies, the low temperature data were fitted to the functional form

$$A(t) = A_1 \exp(-\gamma_1 t) \cos(2\pi\nu_1 t + \phi_1) + A_2 \exp(-\gamma_2 t) \cos(2\pi\nu_2 t + \phi_2) + A_3 \exp(-\gamma_3 t) + A_{bg} \exp(-\gamma_{bg} t); \quad (2)$$

where $A_3 \exp(-\gamma_3 t)$ accounts for the contribution from those muons with a spin component parallel to the local magnetic field. The term $A_{bg} \exp(-\gamma_{bg} t)$ reflects the small signal from those muons which stop in the silver sample holder or cryostat tail (with $\gamma_{bg} \approx 0$).

Across the measured temperature range, the two frequencies were found to be in the proportions $\nu_1 : \nu_2 = 1 : 0.65$ while the relaxation rates γ_i were found to be in the ratio $\gamma_1 : \gamma_2 = 1 : 0.75$. These quantities were fixed in these ratios during the fitting procedure. The amplitudes and phases best describing the data are given in [15]. We note that the ratio of longitudinal to transverse components is in excess of the expected value of $A_3/(A_1 + A_2) = 1/2$ (see below). Nonzero phases were also required to fit the data, as observed in previous studies of Cu-based chain compounds of this sort [14]. The magnitudes of the frequencies were fitted as a function of temperature with other parameters in Eq.(2) fixed [15]. The resulting temperature evolution of the precession frequencies is shown in Fig 2 (a).

From fits of ν_i to the form $\nu_i(T) = \nu_i(0)(1 - T/T_N)$ close to T_N , we estimate $T_N = 107(1)$ mK, leading to a value of the ratio $k_B T_N = J/J = 0.0103(1)$. The parameter

is highly sensitive to the chosen value of T_N due to the difficulty of obtaining data sufficiently close to the transition. Using $T_N = 107(1)$ mK, we estimate $J =$

$0.18(5)$, which is consistent with low dimensional (i.e. 2D Ising or 2D XY) behaviour. Fits to $\nu_i(T) = \nu_i(0)(1 - T/T_N)$ with $\nu_1 = 3$ yield $\nu_1(0) = 1.922(4)$ MHz and $\nu_2(0) = 1.257(3)$ MHz corresponding to local magnetic fields at the two muon sites of $B_1 = 141.8(3)$ G and $B_2 = 92.7(2)$ G.

Further evidence for a magnetic transition is seen in the transverse relaxation rates γ_i , which increase as the magnetic transition is approached from below (Fig 2 (b)), as would be expected for critical slowing of fluctuations near a magnetic transition. The longitudinal relaxation rate decreases as the transition is approached from below (Fig 2 (c)), suggesting that this quantity is dominated by the magnitude of the local magnetic field at the muon site.

At temperatures just above T_N the measured spectra are best described by two components (Fig 1 (b)). One is a fast relaxing contribution, with an amplitude $\approx 5\%$, likely to arise due to a fraction of the muons which initially form radical states. This component will also exist in the magnetically ordered regime, but is not resolvable from the longitudinal relaxation and partly explains why the value of A_3 is greater than that expected. The second component observed in this regime is an exponential functional form, characteristic of fast dynamics in the local magnetic field at the muon sites [6]. At higher temperatures still ($T > 400$ mK), this second component in the spectra appears Gaussian in form (Fig 1 (c)), characteristic of the early time behaviour of a Kubo Toyabe function [16] due to the magnetic field distribution of a static, disordered system, with slow dynamics preventing the characteristic recovery of the polarization at late times. It is likely that at these elevated temperatures, the electronic moments are fluctuating too fast compared to the muon time scale, and are therefore mo-

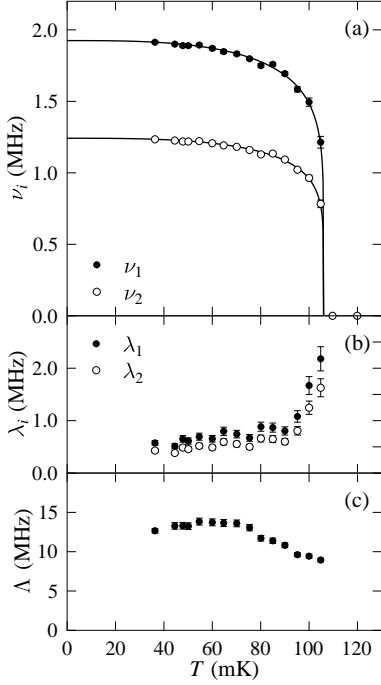


FIG. 2: Temperature evolution of the variable parameters in Eq.(2) for $T > 140$ mK. (a) Muon precession frequencies ν_i with fits shown to the expression $\nu_i(T) = \nu_i(0)(1 - (T - T_N)^2)$ (see main text). (b) Transverse relaxation rates λ_i are seen to increase as the magnetic transition is approached from below. (c) The longitudinal relaxation rate Δ , which decreases as the transition is approached from below.

tionally narrowed from the spectra. Instead the muon ensemble is depolarized by the magnetic field distribution at the muon site due to the quasi-static nuclear moments of the surrounding nuclei. This interpretation is supported by the observation that applied magnetic fields of magnitude ~ 100 G repolarize the relaxation, as expected for a static distribution (repolarization implies $\lim_{t \rightarrow 0} A(t) = A(0)$). The measured data for $T > T_N$ were therefore fitted to the function

$$A(t) = A_4 \exp(-\lambda_4 t) + A_5 \exp(-\lambda_5 t) + A_{bg} \quad (3)$$

where the stretching parameter λ_5 describes the passage from exponential to Gaussian behaviour. The results of this analysis is shown in Fig.3(a). The fact that the relaxation rate λ_5 increases sharply as the proposed transition temperature is approached from above lends further weight to the case for the existence of a magnetic transition.

In order to further investigate the high temperature behaviour of the material measurements were made in an applied longitudinal magnetic field (LF) B_L using a ^4He cryostat at the ISIS facility. The pulsed structure of the muon source at ISIS has the advantage of allowing

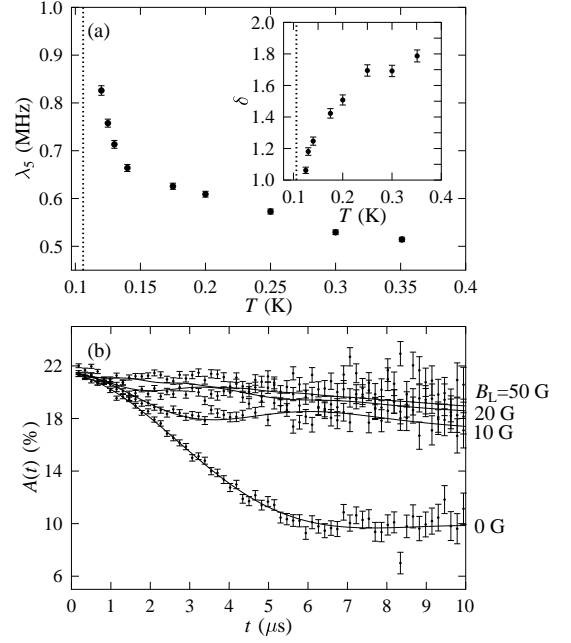


FIG. 3: (a) Results of fitting data for $T > 110$ mK to Eq.(3). (Inset: The parameter α changing from $\alpha = 1$ (exponential relaxation) to $\alpha = 2$ (Gaussian relaxation) as the dynamics move out of the muon time window with increasing temperature. Main panel: The relaxation rate λ_5 increases as the transition is approached from above. (b) LF + SR spectra made at $T = 2$ K in several applied magnetic fields B_L . Fits are shown to the LFKT function with fixed at 0.271 MHz for all fields.

the observation of the muon polarization at longer times than at a continuous source such as SS. This enables us to better characterise the data with the Kubo Toyabe function generalised for applied LFs [16]. The loss of time resolution at a pulsed source causes the fast relaxing component described above to be missing from the signal entirely. The results of these measurements, made at $T = 2$ K, are shown in Fig.3(b). The spectra are found to be approximately temperature independent in the range $2 < T < 50$ K. The application of a field repolarizes the slowly relaxing component of asymmetry for $B < 100$ G consistent with the interpretation that the relaxation at these temperatures is due to the disordered, quasistatic nuclear magnetic moments. The measured ZF and LF spectra for both materials at 2 K are well described by the longitudinal field Kubo Toyabe (LFKT) function describing the relaxation due to an ensemble of disordered magnetic moments, although the LFKT function must be multiplied by an exponential function with constant relaxation rate to account for the weak relaxation due to dynamic fluctuations [17]. This treatment has only one free parameter $\lambda_5 = \frac{\hbar B_{loc}^2}{\hbar B_{loc}^2}$, where $\hbar B_{loc}^2$ is the second moment of the average local magnetic field distribution at the muon sites in ZF. This analysis yields a

TABLE I: Parameters for copper-chain compounds Sr_2CuO_3 [21, 22], KCuF_3 [23], CPC ($= \text{Cu}(\text{py})_2\text{Cl}_2$) [19] and CuPzN ([6] and this work) with values of $j^0 = J$ estimated from Eq.(4).

	j^0/k_B (K)	T_N (K)	$k_B T_N = J$	$j^0 = J$
Sr_2CuO_3	2200	5.4	$2.5 \cdot 10^{-3}$	$9.3 \cdot 10^{-4}$
KCuF_3	406	39	$9.6 \cdot 10^{-2}$	$5.2 \cdot 10^{-2}$
CPC	26	1.1	$4.2 \cdot 10^{-2}$	$2.1 \cdot 10^{-2}$
CuPzN	10.3	0.107	$1.0 \cdot 10^{-2}$	$4.4 \cdot 10^{-3}$

value of $j^0 = 0.271 \text{ MHz}$ for CuPzN .

An efficacious method for estimating the interchain coupling J^0 in LCHAfM's has recently been developed, based on a modified random phase approximation, modelled with classical and quantum Monte Carlo simulations [8]. This approach leads to an empirical formula for the interchain coupling, given by

$$j^0/k_B = -c \frac{T_N}{4c \ln(\frac{j^0}{k_B T_N}) + \frac{1}{2} \ln \ln(\frac{j^0}{k_B T_N})}; \quad (4)$$

with $c = 2.6$ and $c = 0.233$. Substituting our value of $T_N = 107(1) \text{ mK}$ and using $J = k_B = 10.3(1) \text{ K}$, yields $j^0/k_B = 0.046 \text{ K}$ and a ratio $j^0 = J = 4.4 \cdot 10^{-3}$. The parameters describing a number of copper-chain compounds are presented in table I. Comparing values of the ratio $j^0 = J$ shows that CuPzN is approximately 26 times better isolated than copper bispyridine dichloride ($\text{Cu}(\text{py})_2\text{Cl}_2$ or CPC) [19, 20], while $j^0 = J$ for CuPzN is around one quarter of that for the best isolated LCHAfM, Sr_2CuO_3 (although this material has a QCP at a field around 200 times larger than that for CuPzN) [21, 22].

The failure of specific heat studies [2] to detect an anomaly due to the onset of 3D LRO in CuPzN down to 70 mK, may be attributed to the value of the ratio $j^0 = J$. Investigations using a stochastic series quantum Monte Carlo method [25] show that the height of the expected peak decreases with decreasing j^0 , becoming nearly linear below $j^0 = J = 0.2$. For smaller value of the ratio $j^0 = J$, the entropy change at the critical temperature is so small that it makes an undetectable contribution to the measured specific heat.

In conclusion we demonstrated the existence of long range magnetic order in the LCHAfM material CuPzN with $T_N = 107(1) \text{ mK}$. This leads to an estimate of the interchain coupling of $j^0/k_B = 0.046 \text{ K}$. For any 1D system, small values of $j^0 = J$ prevent the detection of 3D LRO with specific heat, and reduced ordered moments make the use of other techniques problematical (coupled

chain mean-field theory [24] then predicts an ordered moment size of $0.05 \mu_B$ for CuPzN). Thus we expect that muon spin may provide a particularly valuable tool for future magnetic measurements of the key parameters of highly anisotropic low-dimensional systems.

We thank W. Hayes for useful discussion. Part of this work was carried out at the Swiss Muon Source, Paul Scherrer Institute, Villigen, Switzerland and at the ISIS facility, Rutherford Appleton Laboratory, UK. This work is supported by the EPSRC, UK. T.L. acknowledges support from the European Commission under the 6th Framework Programme through the Key Action: Strengthening the European Research Area, Research Infrastructures. Contract no: R113-CT-2003-505925

Electronic address: t.lancaster1@physics.ox.ac.uk

- [1] G. Müller et al., Phys. Rev. B, 24, 1429 (1981).
- [2] M. Karbach et al. Phys. Rev. B, 55, 12510 (1997).
- [3] S. Sachdev, Quantum Phase Transitions (Cambridge University Press, Cambridge, England, 2000).
- [4] N. M. Bogoliubov, et al., Nucl. Phys. B 275, 687 (1986)
- [5] A. Fedderphann et al., Phys. Rev. B 54 7168 (1996).
- [6] P. R. Hammar et al., Phys. Rev. B, 59 1008 (1999).
- [7] J. Villain and J. M. Loveluck, J. Phys (France) Lett. 38, L77 (1977).
- [8] M. B. Stone et al., Phys. Rev. Lett., 91, 37205 (2003).
- [9] K. Lefmann and C. Rischel, Phys. Rev. B 54, 6340 (1996);
- [10] M. Karbach and G. Müller, Phys. Rev. B 62, 14871 (2000);
- [11] M. Karbach et al., Phys. Rev. B 66, 054405 (2002).
- [12] G. Menenga et al. J. Magn. Magn. Mater., 44, 89 (1984).
- [13] S. J. Blundell, Contemp. Phys. 40, 175 (1999).
- [14] T. Lancaster et al. J. Phys. Condens. Matter 16, S4563 (2004).
- [15] The fitting parameters for Eq.(2) best describing the data measured below $T = 110 \text{ mK}$ were found to be $A_1 = 1.56\%$, $\gamma_1 = 37.8$, $A_2 = 0.63\%$, $\gamma_2 = 73.5$, and $A_3 = 10.42\%$.
- [16] R. S. Hayano et al. Phys. Rev. B 20, 850 (1979).
- [17] The relaxation function multiplied by the LFKT function may be used to extract information on spin-wave dynamics in these materials; F. L. P. Ratt et al., in preparation.
- [18] C. Yasuda et al., Phys. Rev. Lett., 94, 217201 (2005).
- [19] W. Du y Jr., Phys. Rev. B, 9, 2220 (1974).
- [20] Y. Endoh et al., Phys. Rev. Lett. 32, 170 (1974).
- [21] K. M. Kojima et al., Phys. Rev. Lett., 78, 1787 (1997).
- [22] N. Motoyama et al., Phys. Rev. Lett., 76, 3212 (1996).
- [23] S. K. Satija et al. Phys. Rev. B 21, 2001 (1980).
- [24] H. J. Schulz, Phys. Rev. Lett. 77, 2790 (1996).
- [25] P. Sengupta et al. Phys. Rev. B, 68, 094423 (2003).