

Finding the structure of phosphorus in the phase IV

Takahiro Ishikawa,^{*} Hitose Nagara,[†] Koichi Kusakabe,[‡] and Naoshi Suzuki[§]
*Division of Frontier Materials Science, Graduate School of Engineering Science,
 Osaka University, Toyonaka, Osaka 560-8531, Japan*

(Dated: November 18, 2021)

We have explored the unknown structure of the phosphorus in the phase IV (P-IV phase) based on the first-principles calculations using the metadynamics simulation method. Starting from the simple cubic structure, we found a new modulated structure of a monoclinic lattice. The modulation is crucial to the stability of the structure. Refining further the structure by changing the modulation period, we have found the structure which shows the X-ray powder pattern in the best agreement with the experimental one. We can not exclude the possibility that the unknown structure of the phase IV of phosphorus is an incommensurately modulated one.

PACS numbers: 61.50.Ah, 62.50.+p, 64.70.Kb

Recent progress in high-pressure physics strengthened our recognition on the variety of structures of materials. Unexpectedly interesting structures were found in the high-pressure experiments. The modulated structure is one of curious structures often found in the high-pressure phases of elements. Improvement of the high-pressure techniques has also made it possible to specify the structure stabilized only in a narrow pressure range. The modulation of a crystal was found in the group Vb elements including As, Sb and Bi [1, 2] and in group VIb elements including S [3], Se [4] and Te [5]. Modulated structures were also reported in halogens, I [6] and Br [7].

Non availability of sufficient experimental data under very high pressure constrains high pressure study. There, people often encounter difficulties in determination of the lattice structure only from the experimental data. The theoretical approach gives alternative information on the same problem, where accuracy in the determination of a crystal structure is known to be enough, if one utilizes the first-principles calculation. However, limitation in computational resources sometimes prohibits us to perform full search of the true structure.

The phase IV of the phosphorus (P-IV) is one of the examples in which the structure has not been determined. Observation of the phase was first reported by Akahama *et al.* [8] in 1999. They showed an appearance of the simple hexagonal (sh) phase, *i.e.* the phase V (P-V), which is stabilized above 137GPa. The third phase (P-III) appearing in the sequence of pressure-induced transformations at low temperatures is the simple cubic (sc) phase. As an intermediate phase between sc and sh, the P-IV was detected in the X-ray diffraction data. Experimentally, however, the structure has not been identified. The ordinary Rietveld analysis starting from the knowledge only of the monoclinic symmetry has not been successful owing to a probable complexity of the lattice. The bcc structure (phase VI) is theoretically predicted [9] and identified at even higher pressure 262GPa [10]. We need a guess of the lattice structure or a pseudo crystal.

Several structures have been tested as candidates for the P-IV. Ahuja considered a structure of space group Imma [11]. Ehlers and Christensen studied relative stability of Ba-IV structure of P, which is a kind of modulated structure, in the pressure range from 100 to 200 GPa [12]. In spite of these intensive studies, the structure of the P-IV has not been identified.

To explore the P-IV, we adopted the following strategy in our theoretical study and used the metadynamics simulation in the first-principles calculations. This trial was done with a relatively small simulation cell to reduce the computational time. The simulation was planned, however, to be able to detect possible signal of the structural phase transformation. For the obtained structure, we checked the relative stability against the sc and sh phases. Next we considered some model structures to find more refined structure. The structural optimization was done for each model structures. The calculated X-ray powder patterns of the optimum structure are compared with that of the experimental one.

In the study of the metadynamics simulation, which was first introduced by Laio and Parrinello [13, 14], we use the Gibbs free energy (GFE) depending upon a shape of a simulation cell. Following the prescription by Martoňák [14], we consider the GFE, $G(\mathbf{h}^t) = G_o(\mathbf{h}^t) + G_g(\mathbf{h}^t)$, where $G_g(\mathbf{h}^t)$ is the artificial potential defined by the following Gaussian-type function,

$$G_g(\mathbf{h}^t) = \sum_{t' < t} \prod_{i,j} W \exp(-[\mathbf{h}^t - \mathbf{h}^{t'}]_{ij}^2 / 2\delta h^2). \quad (1)$$

The superscripts t and t' denote the current meta-step and the previous one, respectively. The quantities W and δh represent the weight and the width of the Gaussian-type function, respectively. The matrix \mathbf{h} is defined by the vectors defining the simulation cell and $\mathbf{h} = (\vec{a}, \vec{b}, \vec{c})$, where \vec{a} , \vec{b} and \vec{c} are lattice vectors. To eliminate the free rotation of the system, only the symmetric part of the matrix \mathbf{h} is updated, which reduces the number of the independent variables to 6.

The update of the matrix \mathbf{h} is made by the steepest de-

scent method using the driving force \mathbf{F} and regarding δh as stepping parameter. The driving force \mathbf{F} is obtained as the sum of the original driving force $\mathbf{F}_o = -\partial G_o / \partial \mathbf{h}$, and the Gaussian driving force $\mathbf{F}_g = -\partial G_g / \partial \mathbf{h}$. The force \mathbf{F}_o can be expressed by an internal pressure tensor \mathbf{p} , external pressure P , and the matrix \mathbf{h} [14]. One step of updating \mathbf{h} is defined as one meta-step.

At each meta-step, in order to equilibrate the system and to estimate \mathbf{p} , the conventional molecular dynamics (MD) simulations have to be done with the shape of the simulation cell fixed. The internal pressure tensor and the atomic positions at each meta-step can be taken from the output of any constant-pressure MD codes of the first-principles calculation [15].

The above artificial potential means that if the current \mathbf{h} has been visited time after time, which occurs when the system is fluctuating around the local minimum of the GFE surface, G_g accumulates to a large value and the well is gradually filled with the artificial potential G_g .

For the simulation of phosphorus, we used the density functional theory in a local density approximation and a norm-conserving pseudopotential, where we employed the expression of Perdew and Zunger [16] for the exchange and correlation energy functional. We checked the pseudopotential comparing the calculated equation of states with the experiments in other phases [8, 9, 10]. We started with the cubic simulation cell whose edge was 4.26 Å and 8 phosphorus atoms are set at the positions which make the sc lattice. We performed the k-space integration using $8 \times 8 \times 8$ mesh points in the first Brillouin zone and set the energy cut-off of the plane wave basis at 40 Ry. We set the external pressure at 120 GPa in the conventional constant-pressure MD, since the P-IV is observed at this pressure. In order to equilibrate the system, we ran this MD simulation for 200 steps at each meta-step and we calculated the average internal pressure tensor from the latter half of 100 steps. In order to perform this metadynamics simulation, we used the cluster machines.

Figure 1 shows the evolution of the cell volume and the three angles among the lattice vectors of the simulation cell. First we ran the simulations with the Gaussian potential off, by setting $W = 0$ mRy, for 38 meta-steps in order to check whether the sc structure is stable or not. During these initial meta-steps, the values of the angles and the volume were nearly maintained at those of the sc lattice. This means that the sc structure resides on a local minimum and it is separated from the other local minima by some barriers. We note that the metadynamics simulation with the Gaussian-type potential switched off is nearly equivalent to the conventional variable-cell MD simulations.

In order to explore the metastable structures beyond the potential barrier we switched the Gaussian-type potential on at 39th meta-step with W of 1 mRy and δh of 20 mÅ. As a result, one of the three angles started

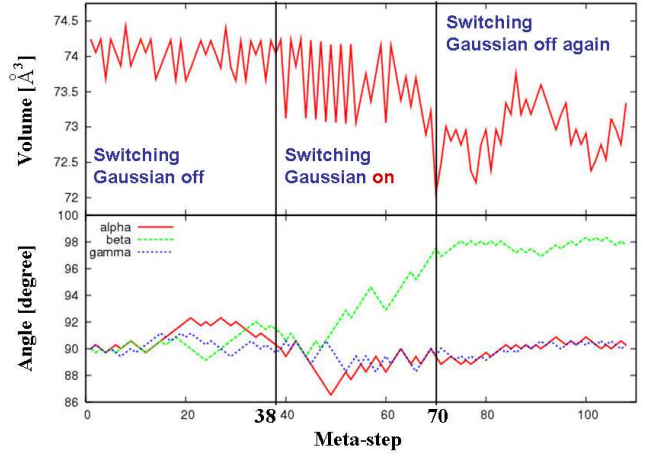


FIG. 1: Evolution of the simulation cell volume and the angles among lattice vectors. The Gaussian-type potential was switched on at 39th meta-step and off again after 71st meta-step.

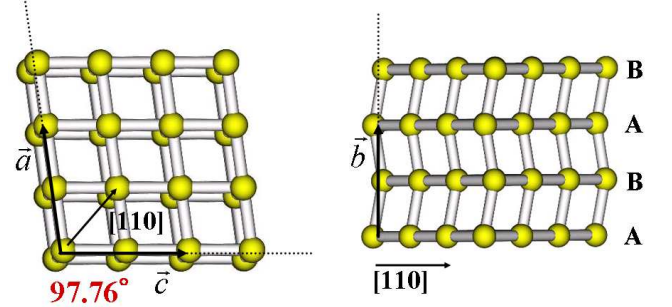


FIG. 2: A structure obtained by the first-principles metadynamics simulation. \vec{a} , \vec{b} and \vec{c} are lattice vectors of the simulation cell, and $a = 4.22$ Å, $b = 4.15$ Å, $c = 4.22$ Å, $\alpha = 90.86^\circ$, $\beta = 97.76^\circ$ and $\gamma = 90.26^\circ$. When we look at the ac plane along the b -axis, the planes are displaced alternatively in the direction $[110]$.

to increase after around 50th meta-step and the volume began to decrease dramatically. After those changes, we switched the Gaussian-type potential off at 71st meta-steps again in order to check whether the system had already surmounted the barrier and had moved to a neighboring local minimum. If the system had not crossed the barrier yet, the angle and the volume would have returned to the starting values of the sc lattice, which are approximately 90° and 74 Å³, respectively. After 71th meta-step, however, the volume fluctuated around 73 Å³ and three angles also continued to fluctuate around 90° , 98° and 90° . This behavior shows that the sc structure transformed into another metastable one.

Figure 2 shows the structure obtained by the above run, where \vec{a} , \vec{b} and \vec{c} are the lattice vectors of the simulation cell. This structure has a unit cell with the lattice parameters $a = 4.22$ Å, $b = 4.15$ Å, $c = 4.22$ Å, $\alpha = 90.86^\circ$, $\beta = 97.76^\circ$ and $\gamma = 90.26^\circ$. The left hand

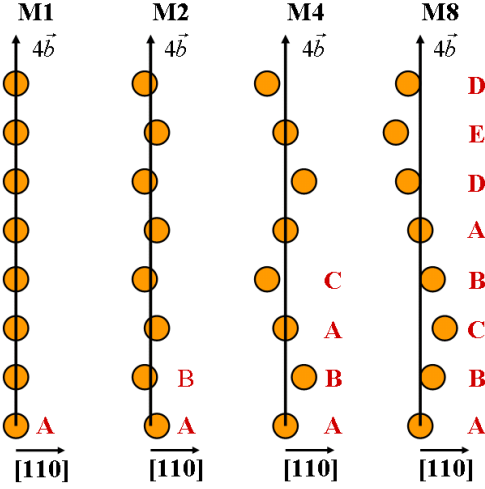


FIG. 3: Modulated structures with different modulation periods along the b -axis. The pattern M1 is of a non-modulated structure, and M2 the structure obtained by our metadynamics simulation (ABAB...). The modulation periods of M4 (ABAC...) and M8 (ABCBADED...) patterns are twice and four times as long as that of the M2, respectively.

TABLE I: Comparison of the total energies per atom for a non-modulated structure (M1) and three modulated structures (M2, M4 and M8). We used the unit cell with the lattice vectors, $\vec{a}/2$, $4\vec{b}$ and $\vec{c}/2$ in the calculation of the total energy for all of these four structures.

Structure	Total energy [Ry/atom]
M1	-13.1624
M2	-13.1638
M4	-13.1642
M8	-13.1637

side figure is the projection onto the ac plane. It shows the distortion of the simulation cell from the cubic into the cell with an angle 97.76° . When we look the lattice from a side, we find a zigzag modulation of the ac plane along the b -axis with displacement in the direction of $[110]$ as is shown in the ABAB.. in the right hand side figure. This is an important feature. The ABAB... modulation pattern is crucial for the stability of the distortion of the angle β . When we removed the zigzag modulation pattern and performed the simulation for the relaxation of the structure, we observed that the structure returned to the initial sc structure.

The structure obtained by the metadynamics is a modulation pattern with period consisting of two planes. Our simulation, however, was performed using the system with 8-atoms in a simulation cell, and with the periodic boundary condition. Hence there remains a question that the small simulation cell may limit the modulation period to a shorter one. In fact, the X-ray powder pattern of the zigzag modulated structure and that of the experimental

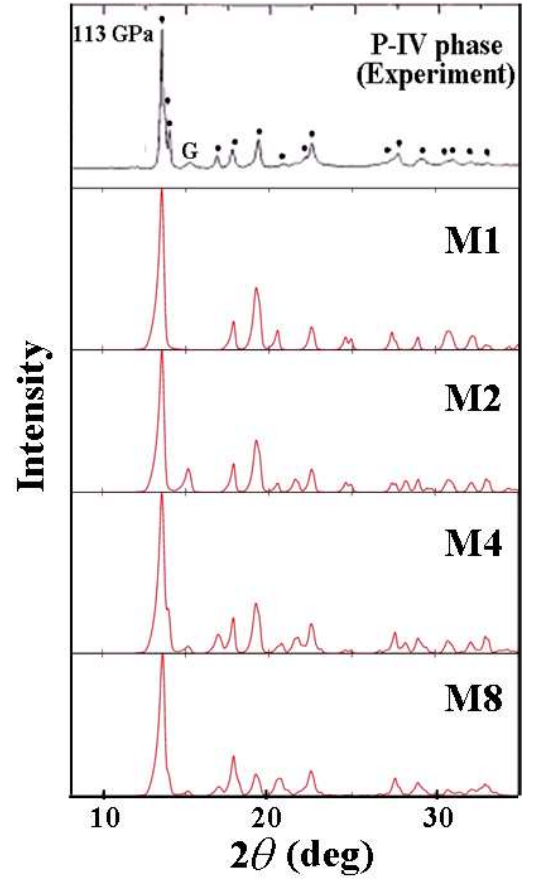


FIG. 4: Comparison of the experimentally obtained X-ray powder pattern of the P-IV [8] with those of the M1, M2, M4 and M8 modulated structures. Theoretical powder patterns of our structures are obtained by the use of RIETAN-2000 [17]. In the experimental pattern of the P-IV, peaks are indicated by dots and G represents diffraction by a metal gasket.

one show some discrepancies. To answer this question, we tried some more first-principles calculations for the refinement of the structure.

We extended our study to two more structures which have commensurate modulations: an ABAC... and an ABCBADED... The modulation period of the ABAC... and that of the ABCBADED... are twice and four times as long as that of the ABAB..., respectively. These structures are denoted as M4 and M8 and shown in Fig. 3. The pattern M1 is a non-modulated structure, and M2 is the structure obtained by the metadynamics simulation. We calculated the total energies and the X-ray powder patterns.

To compare the total energy among these structures, we used the same unit cell with the lattice vectors, $\vec{a}/2$, $4\vec{b}$ and $\vec{c}/2$, where \vec{a} , \vec{b} and \vec{c} are those of the simulation cell obtained by the metadynamics simulation. The 8 atoms were located only along the b axis in the unit cell with displacements corresponding to the modulation pattern (Fig. 3). This choice of the unit cell avoids the numerical

errors coming from the use of the different size of the unit cells. For the k-space integration, we used $16 \times 4 \times 16$ mesh points in the first Brillouin zone. Amplitude of modulation for each structure was optimized by the relaxation of the atomic positions.

Calculated total energies are listed in Table I. All modulated structures, M2, M4, and M8 have lower energy per atom than the unmodulated structure, M1, which shows any modulation periods from M2 to M8 are more favorable than the M1. Among the above three modulated structures, the energy of the M4 is the lowest in our study of the commensurate approximation. Though the enthalpy of the M4 is very close to that of the sc, it is in fact lower than that of the sc at 120GPa, according to our results. If we plot the total energy as a function of the modulation period and optimize the period as was done by Ehlers *et al.* [12], an incommensurately modulated structure is expected.

In figure 4 we compare the X-ray powder patterns of our structures with that of the experimental one. The experimental pattern of the P-IV (top figure) was obtained from Akahama *et al.*'s [8]. It shows the feature that the splits of the strongest peak at $2\theta = 13^\circ$ and the three peaks in the range from $2\theta = 17^\circ$ to 19° are observed. In our M2 structure, these features are missing and unnecessary peaks exist at $2\theta = 15^\circ$ and 25° . However, this disagreement is much improved with increase of the modulation period. Intensities of the unnecessary peak at $2\theta = 15^\circ$ in the M2 structure, which was brought about by the zigzag modulation, and another unnecessary one at $2\theta = 25^\circ$ in the same M2 structure, which appeared owing to the distortion of the simulation cell from the cubic, are decreased in the M4 and M8 structures and the split of the strongest peak appears also in the M4 and M8 structure. About the intensity of the three peaks in the range from $2\theta = 17^\circ$ to 19° , the X-ray powder pattern of the M4 shows most improved agreement with the experimental one among the 4 patterns studied. From the comparison of the total energies and the X-ray powder patterns, we conclude that the modulation period is close to that of the M4 structure in the P-IV.

In this study, we explored the structure of phosphorus in the phase IV using the first-principles metadynamics simulation and identified the new structure. This structure is the monoclinic with the modulation pattern. Furthermore we found the refined structure showing the best agreement with the X-ray powder pattern. Although we have not fully studied the possibility of the incommensurate modulation, we conclude that phosphorus takes the modulated structure with possible incommensurate modulation. The simple idea of Akahama *et al.* [8] stating that the structure of the P-IV may be on the path from the sc to sh via monoclinic distortion along the [110] direction is partly supported because the unmodulated structure is of space group $P2$ and of one atom per unit

cell. The structure of the P-IV is not so complicated as one suggested by and Ehlers *et al.* [12]. The modulation stabilizes the monoclinic distortion of the lattice. It is highly probable that the Vb, VIb, and VIIb group elements commonly show modulated structures in a narrow pressure range when they undergo the pressure induced structural transition between simple stable structures.

The authors thank Dr. Nakamoto and Dr. Morimoto for valuable discussion on the X-ray powder patterns. Computations were done on the machines at the Institute for Molecular Science, Okazaki, Aichi, Japan. This work was partially supported by a Grant-in-Aid for Scientific Research in Priority Areas "Development of New Quantum Simulators and Quantum Design" (Nos.17064006 and 17064013) and by a Computational Nanoscience program "Grid Application Research in Nanoscience-National Research Grid Initiative (NAREGI)" of The Ministry of Education, Culture, Sports, Science, and Technology, Japan.

* Electronic address: ishikawa@aquarius.mp.es.osaka-u.ac.jp

† Electronic address: nagara@mp.es.osaka-u.ac.jp

‡ Electronic address: kabe@mp.es.osaka-u.ac.jp

§ Electronic address: suzuki@mp.es.osaka-u.ac.jp

- [1] M. I. McMahon, O. Degtyareva, and R. J. Nelmes, Phys. Rev. Lett. **85**, 4896 (2000).
- [2] U. Shwartz, L. Akselrud, H. Rosner, A. Ormeci, Y. Grin, and M. Hanfland, Phys. Rev. B **67**, 214101 (2003).
- [3] C. Hejny, L. F. Lundegaard, S. Falconi, and M. I. McMahon, Phys. Rev. B **71**, 20101 (2005).
- [4] M. I. McMahon, C. Hejny, J. S. Loveday, and L. F. Lundegaard, Phys. Rev. B **70**, 54101 (2004).
- [5] C. Hejny and M. I. McMahon, Phys. Rev. Lett. **91**, 215502 (2003).
- [6] K. Takemura, K. Sato, H. Fujihisa, and M. Onoda, Nature **423**, 971 (2003).
- [7] T. Kume, T. Hiraoka, Y. Ohya, S. Sasaki, and H. Shimizu, Phys. Rev. Lett. **94**, 065506 (2005).
- [8] Y. Akahama, M. Kobayashi, and H. Kawamura, Phys. Rev. B **59**, 8520 (1999).
- [9] I. Hamada, T. Oda, and N. Suzuki, XXXXXXXX **nn**, **** (00).
- [10] Y. Akahama and H. Kawamura, Phys. Rev. B **61**, 3139 (00).
- [11] R. Ahuja, Phys. Status Solidi B **235**, 282 (2003).
- [12] F. J. H. Ehlers and N. E. Christensen, Phys. Rev. B **69**, 214112 (2004).
- [13] A. Laio and M. Parrinello, Proc. Natl. Acad. Sci. U.S.A. **99**, 12562 (2002).
- [14] R. Martoňák, A. Laio, and M. Parrinello, Phys. Rev. Lett. **90**, 75503 (2003).
- [15] S. Baroni, A. D. Corso, S. de Gironcoli, and P. Giannozzi, We used the PWSCF code which is available from: <http://www.pwscf.org/>.
- [16] J. P. Perdew and A. Zunger, Phys. Rev. B **23**, 5048 (1981).
- [17] F. Izumi and T. Ikeda, Mater. Sci. Forum **321-324**, 198 (2000).