

M agnetic- eld-induced sw itching between ferroelectric phases in orthorhom bic-distortion-controlled RM nO₃

K .Noda, M .Akaki, T .K ikuchi, D .A kahoshi, and H .K uwahara

D epartm ent of Physics, Sophia University

Chiyoda-ku, Tokyo 102-8554, Japan

(D ated: M arch 23, 2024)

Abstract

W e have investigated the dielectric and m agnetic properties of $\text{Eu}_{0.595}\text{Y}_{0.405}\text{MnO}_3$ without the presence of the 4f m agnetic m om ents of the rare earth ions, and have found two ferroelectric phases with polarization along the a and c axes in a zero m agnetic eld. A m agnetic eld induced sw itching from one to the other ferroelectric phase took place in which the direction of ferroelectric polarization changed from the a axis to the c axis by the application of m agnetic elds parallel to the a axis. In contrast to the case of TbMnO_3 , in which the 4f m om ents of Tb^{3+} ions play an important role in such a ferroelectric phase sw itching, the m agnetic- eld-induced sw itching between ferroelectric phases in $\text{Eu}_{0.595}\text{Y}_{0.405}\text{MnO}_3$ does not originate from the m agnetic transition of the rare-earth 4f m om ents, but from that of the Mn 3d spins.

PACS num bers: 71.45.Gm , 77.84.Bw , 77.80.Fm , 75.30.-m , 75.50.Ee

The first observation of the magnetoelectric effect was carried out for Cr_2O_3 in 1960.[1] Through the 1960s and 1970s, many magnetoelectric materials were discovered, such as Ti_2O_3 , RAlO_3 , RPO_4 (R is a heavy rare earth ion), and so on.[2, 3, 4, 5] Unfortunately, the magnetoelectric effects in such materials are too small for use in electronic devices. Since the recent discovery of the "magnetic-field-induced electric polarization flop" (MEPF) in TbMnO_3 , [6] the magnetoelectric effect has attracted revived interest. Even among the manganese based oxides, several magnetoelectric materials have been found and studied extensively, including GdMnO_3 , $\text{Gd}_{1-x}\text{Tb}_x\text{MnO}_3$ ($0 < x < 1$), DyMnO_3 , TbMn_2O_5 , and DyMn_2O_5 . [7, 8, 9, 10, 11] The relatively large magnetoelectric effect demonstrated in TbMnO_3 is believed to originate from the strong d - d exchange interaction between the Mn 3d spins and the Tb 4f moments and from the magnetic frustration due to the large orthorhombic distortion. It is widely accepted also that, in other orthorhombic RMnO_3 compounds, the magnetic transition of the rare-earth 4f moments plays an important role in the magnetoelectric effect. However, the origin of the magnetoelectric effect in manganites has not yet been completely accounted for by the above simple scenario. Therefore, to ascertain whether the rare-earth 4f moments are essential to produce such a peculiar magnetoelectric effect as MEPF, we have investigated this effect in orthorhombic RMnO_3 without the presence of the 4f magnetic moments of rare earth ions. For the R-site ion, we chose an admixture of Eu^{3+} and Y^{3+} ions to remove or minimize the influence of the 4f moments; in addition, we controlled the average ionic radius of the R site so that it was the same as that of TbMnO_3 . The Eu^{3+} ion is thought to have no 4f moments because of the fact that the total angular momentum $J = 0$, while the Y^{3+} ion does not have 4f electrons. The subject compound, $\text{Eu}_{0.595}\text{Y}_{0.405}\text{MnO}_3$ ($(\text{Eu,Y})\text{MnO}_3$), was, therefore, expected to be free from 4f moments. Our results revealed a magnetic-field-induced switching between ferroelectric phases in $(\text{Eu,Y})\text{MnO}_3$. In this paper, we discuss the role of Mn 3d spins in such a phase switching in this compound.

We prepared $\text{Eu}_{0.595}\text{Y}_{0.405}\text{MnO}_3$, whose average ionic radius of the R site is the same as that of TbMnO_3 . The compositional ratio of the Eu^{3+} to Y^{3+} ions was obtained by a calculation based on the Shannon's ionic radius table.[12] The single crystal sample was grown by the coating zone method. We performed x-ray-diffraction and rocking curve measurements on the resulting crystal at room temperature, and confirmed that it showed the single phase with the orthorhombic Pbnm structure without any impurity phases such

as hexagonal one or any phase segregation. All specimens used in this study were cut along the crystallographic principal axes into a rectangular shape by means of an x-ray back-reflection Laue technique. The measurements of the temperature dependence of the dielectric constant and the spontaneous ferroelectric polarization in magnetic fields were carried out in a temperature-controllable cryostat equipped with a superconducting magnet that provided a field up to 8 T. The dielectric constant was determined with an LCR meter (Agilent, 4284A). After the sample had been cooled under a poling electric field of 300–500 kV/m, the spontaneous electric polarization was obtained by the accumulation of a pyroelectric current while it was heated at a rate of 4 K/min. The magnetization and specific heat were measured using a commercial apparatus (Quantum Design, PPM S).

We show in Fig. 1 the temperature dependence of the dielectric constant along the a (ϵ_a) and c (ϵ_c) axes [(a), (d)], and the spontaneous ferroelectric polarization along the a (P_a) and c (P_c) axes [(b), (e)]. In addition, we include the magnetization (M) in magnetic fields parallel to the a axis (H_a), and the temperature dependence of the magnetization in the field parallel to each axis (f). First, we will discuss the overall magnetic behavior in a magnetic field of 0.5 T. As clearly seen in Fig. 1 (c), the normalized magnetizations in 0.5 T and 1 T are almost coincident, a result which indicates that, below 1 T, the magnetization changes linearly with the magnetic field. Therefore, the temperature dependence of the magnetization shown in Fig. 1 (f) follows almost the same trend as that in a zero magnetic field.

Other RMnO_3 crystals related to this study are known to have an anisotropic magnetic structure: either a layered (A-type) or a commensurate/incommensurate antiferromagnetic structure.[7, 9, 13, 14, 15] The present compound $(\text{Eu}, \text{Y})\text{MnO}_3$ also shows a remarkable anisotropic magnetization below 47 K, above which temperature a common paramagnetic behavior is observed along all axes. Below 47 K, the magnetization parallel to the b axis steeply decreases, while in the temperature range from 47 K to 25 K, the magnetization along the a (M_a) and c (M_c) axes remains almost constant. This result implies that the antiferromagnetic order in which the b axis is a magnetic easy axis appears below 47 K. At 25 K, a very subtle decrease in M_a and M_c is detected. With a further decrease in temperature, M_a and M_c show the opposite behavior below 23 K: the former fell, and the latter rose again.

These results suggest that $(\text{Eu}, \text{Y})\text{MnO}_3$ has three magnetic transitions: (1) a paramagnetic to antiferromagnetic (perhaps something like a layered antiferromagnetic) transition

at 47K ; (2) an unknown magnetic transition at 25K , corresponding to the peak in χ_c , discussed later; and (3) a canted antiferromagnetic transition with weak ferromagnetism along the c axis at 23K , where the Mn 3d spins along the b axis tilt toward the c axis. Furthermore, as expected, the 4f moments of Eu^{3+} seem to be quenched at low temperatures in this compound, because the paramagnetic rise and/or anomaly in magnetization, due to 4f moments observed in other RMnO_3 compounds, has not been discerned here. The results of specific-heat measurements also support this conclusion: the Schottky anomaly arising from the split levels of the 4f multiplet, also is not detected at low temperatures.

Now, we turn to a discussion of the temperature dependence of χ_a and χ_c [Figs. 1 (a) and (d)]. Below 2T, χ_a shows a large peak around 23K in the H_a . In the case of $H_a = 3\text{T}$, the peak is lowered and broadened, and is shifted to a lower temperature of 19K ; in addition, and a new anomaly appears around 25K . Furthermore, in $H_a = 6\text{T}$, the peak disappears and the anomaly observed in 3T remains as a small inflection around 25K . On the other hand, in the case of χ_c , two peaks are observed in a zero magnetic field: in H_a , the small peak at 23K in 0T shifts toward lower temperatures, and disappears, in a manner similar to the case of the χ_a peak, while the sharp peak at 25K in 0T shifts toward a little higher temperatures. The behavior of these two χ_c peaks is in good agreement with the peak and anomaly (inflection) of χ_a . The temperatures where the two χ_c peaks are observed in a zero magnetic field correspond to the magnetic transition temperatures; the peak at the higher temperature of 25K corresponds to (2), and the other, at the lower temperature of 23K , to (3).

Next, we focus on the results pertaining to the spontaneous ferroelectric polarization in H_a . Figures 1 (b) and (e) show the temperature dependence of P_a and P_c , respectively. In a zero magnetic field, P_a emerges at 23K , and P_a (and also P_c) can be reversed by a DC electric field, results which provide clear evidence for a ferroelectric phase transition. By application of H_a , the ferroelectric phase with P_a (FE_a) is suppressed toward lower temperatures and finally disappears. The transition temperature of P_a corresponds well with the peak position of χ_a (or with the small broad peak of χ_c). On the other hand, in the case of P_c , another ferroelectric phase with P_c (FE_c) exists only between 23K and 25K in a zero magnetic field. With increasing H_a , FE_c is expanding toward lower temperatures and finally FE_c becomes dominant at the lowest temperature, concomitantly with the suppression of FE_a ($H = 4\text{T}$); these findings indicate that a magnetic-field-induced switching from FE_a to FE_c occurred.

The FE_c also extends toward a little higher temperatures, and the transition temperatures for the appearance and disappearance of P_c coincide, respectively, with the sharp and broad peak positions of χ_c (or with the small inelastic and broad peak positions of χ_a). The results obtained mean that first FE_c appears at 25K, and then, below 23K, FE_c is replaced by FE_a , in a zero magnetic field (See also Fig. 3). The ferroelectric transition temperatures for FE_c and FE_a are in accord with the magnetic transition temperatures of (2) and (3), respectively. In the case of $H_a \neq 0$, FE_c develops toward lower temperatures, while FE_a is suppressed with an increasing H_a . The transition temperature of the phase switching between FE_a and FE_c in H_a also agrees well with the magnetic transition temperature, as clearly demonstrated in Fig. 1 (c). We have found that the succession of ferroelectric transitions in a zero magnetic field with decreasing temperature is as follows: the paraelectric phase $\rightarrow FE_c \rightarrow FE_a$. Moreover, the FE_a and FE_c can be controlled by the application of H_a .

In order to further investigate the phase switching between FE_a and FE_c caused by the application of H_a , we performed isothermal measurements of P_a , P_c , and M_a as a function of the magnetic field strength (Fig. 2). The crossover from P_a to P_c in H_a is clearly demonstrated in Figs. 2 (a) and (b): for example, at 5K, P_a abruptly drops around 4T where P_c rapidly rises up. The magnetic-field-induced switching between FE_a and FE_c has a certain finite phase-boundary at about 0.5T, in which P_a and P_c coexist (See also Fig. 3). As shown in Fig. 2 (c), $M_a / \mu_0 H_a$ also displays a striking peak around the switching field corresponding to the phase boundary. The value of $M_a / \mu_0 H_a$ shows a step-like increase as H_a rose below and above the switching field, which indicates that the direction of the weak ferromagnetic moments (the field-induced canting component) changed from the c axis to the a axis in H_a . These results suggest that the increase of the magnetic moment parallel to the a axis is closely related to the expansion of FE_c in higher magnetic fields.

We present in Fig. 3 the magnetoelectric phase diagram obtained for $(Eu,Y)MnO_3$ in the temperature and magnetic field plane. The switching demonstrated between the ferroelectric phases in $(Eu,Y)MnO_3$ originates from the magnetic transition of Mn 3d spins alone in sharp contrast to the magnetoelectric effect found in other ferroelectric manganites such as $TbMnO_3$ in which the 4f moments are essential. Moreover, the ME PF in $TbMnO_3$ emerges at the magnetic transition temperature of the Tb 4f moments and shifts toward higher temperatures with increasing magnetic field. However, the observed phase switching in $(Eu,Y)MnO_3$ occurs at the canted-antiferromagnetic-transition temperature of the Mn 3d

spins and shifts toward lower temperatures. This fact also reflects the difference between the magnetoelectric effects with and without the 4f moments.



In summary, we have studied the dielectric and magnetic properties of a $\text{Eu}_{0.595}\text{Y}_{0.405}\text{MnO}_3$ single crystal. We have found that this compound has two distinct ferroelectric phases that have P_a ($T < 23\text{K}$) and P_c ($23\text{K} < T < 25\text{K}$) in a zero magnetic field. In addition, we have demonstrated a magnetic-field-induced switching between these ferroelectric phases. In the present case, the direction of ferroelectric polarization is changed from the a axis to the c axis by application of H_a , a switch which is in the quite opposite direction in the case of TbMnO_3 . In contrast to TbMnO_3 or other multiferroic manganites, $(\text{Eu},\text{Y})\text{MnO}_3$ does not have 4f moments; therefore, the observed magnetic-field-induced switching between ferroelectric phases is attributed to the magnetic transition of the Mn 3d spins alone. The microscopic origin of this ferroelectric phase transition has not yet been clarified. However, the observed successive ferroelectric phase transition in $(\text{Eu},\text{Y})\text{MnO}_3$ without 4f magnetic moments should provide an improved understanding of the mechanism of the magnetoelectric effect not only in manganites but also in other multiferroic materials.


-
- [1] D. N. Astrov et al., Sov. Phys. {JETP 11, 708 (1960).
- [2] B. I. Alshin et al., Sov. Phys. {JETP 17, 809 (1963).
- [3] L. M. Holmes et al., Phys. Rev. B 5, 147 (1972).
- [4] R. M. Homrich et al., Phys. Rev. B 16, 1112 (1977).
- [5] G. T. Rado et al., Phys. Rev. Lett. 23, 644 (1969).
- [6] T. Kinura et al., Nature 426, 55 (2003).
- [7] H. Kuwahara et al., Physica B 359–361, 1279 (2005).
- [8] K. Noda et al., IEEE Trans. Magn. (in press; cond-mat/0412148).
- [9] T. Goto et al., Phys. Rev. Lett. 92, 257201 (2004).
- [10] N. Hur et al., Nature 429, 392 (2004).
- [11] D. Higashiyama et al., Phys. Rev. B 70, 174405 (2004).
- [12] R. D. Shannon, Acta Crystallogr. Sect. A 32, 751 (1976).
- [13] T. Kinura et al., Phys. Rev. B 67, 180401 (2003).
- [14] R. Kajimoto et al., Phys. Rev. B 70, 012401 (2004).
- [15] T. Kinura et al., Phys. Rev. B 71, 224425 (2005).

FIG . 1: Temperature dependence of dielectric constant along the a (a) and c (d) axes and ferroelectric polarization along the a (b) and c (e) axes in magnetic fields parallel to the a axis. Part (c) shows the temperature dependence of the magnetization parallel to the a axis normalized by the magnetic field intensity. The temperature dependence of the magnetization parallel to each axis in a field of 0.5T is shown in (f). For clarity, only the data in a warming scan are plotted.

FIG . 2: Magnetic field dependence of ferroelectric polarization along a (top panel) and c (middle) axes at several fixed temperatures. The bottom panel shows the gradient of the $M-H$ curve. Magnetic fields are applied parallel to the a axis. For clarity, only the data in the field-decreasing scan are plotted.

FIG . 3: The magnetoelectric phase diagram for $\text{Eu}_{0.595}\text{Y}_{0.405}\text{MnO}_3$ in magnetic fields parallel to the a axis.

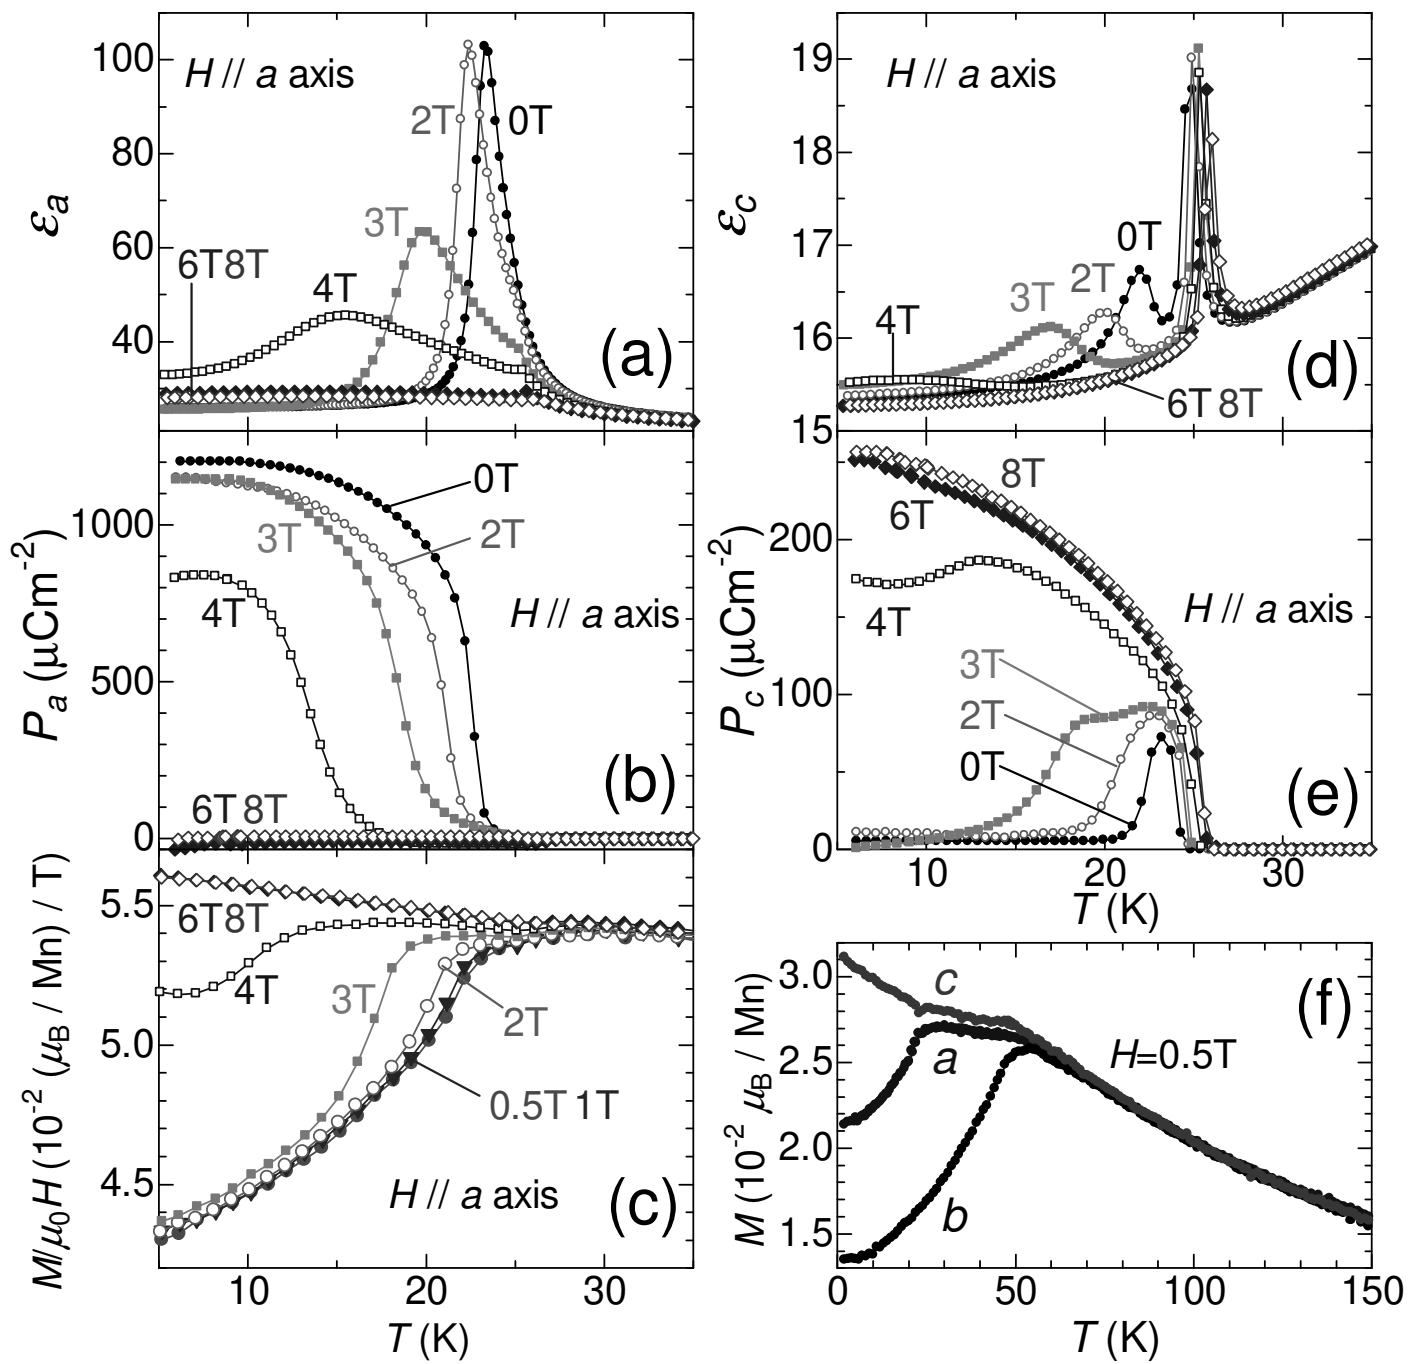

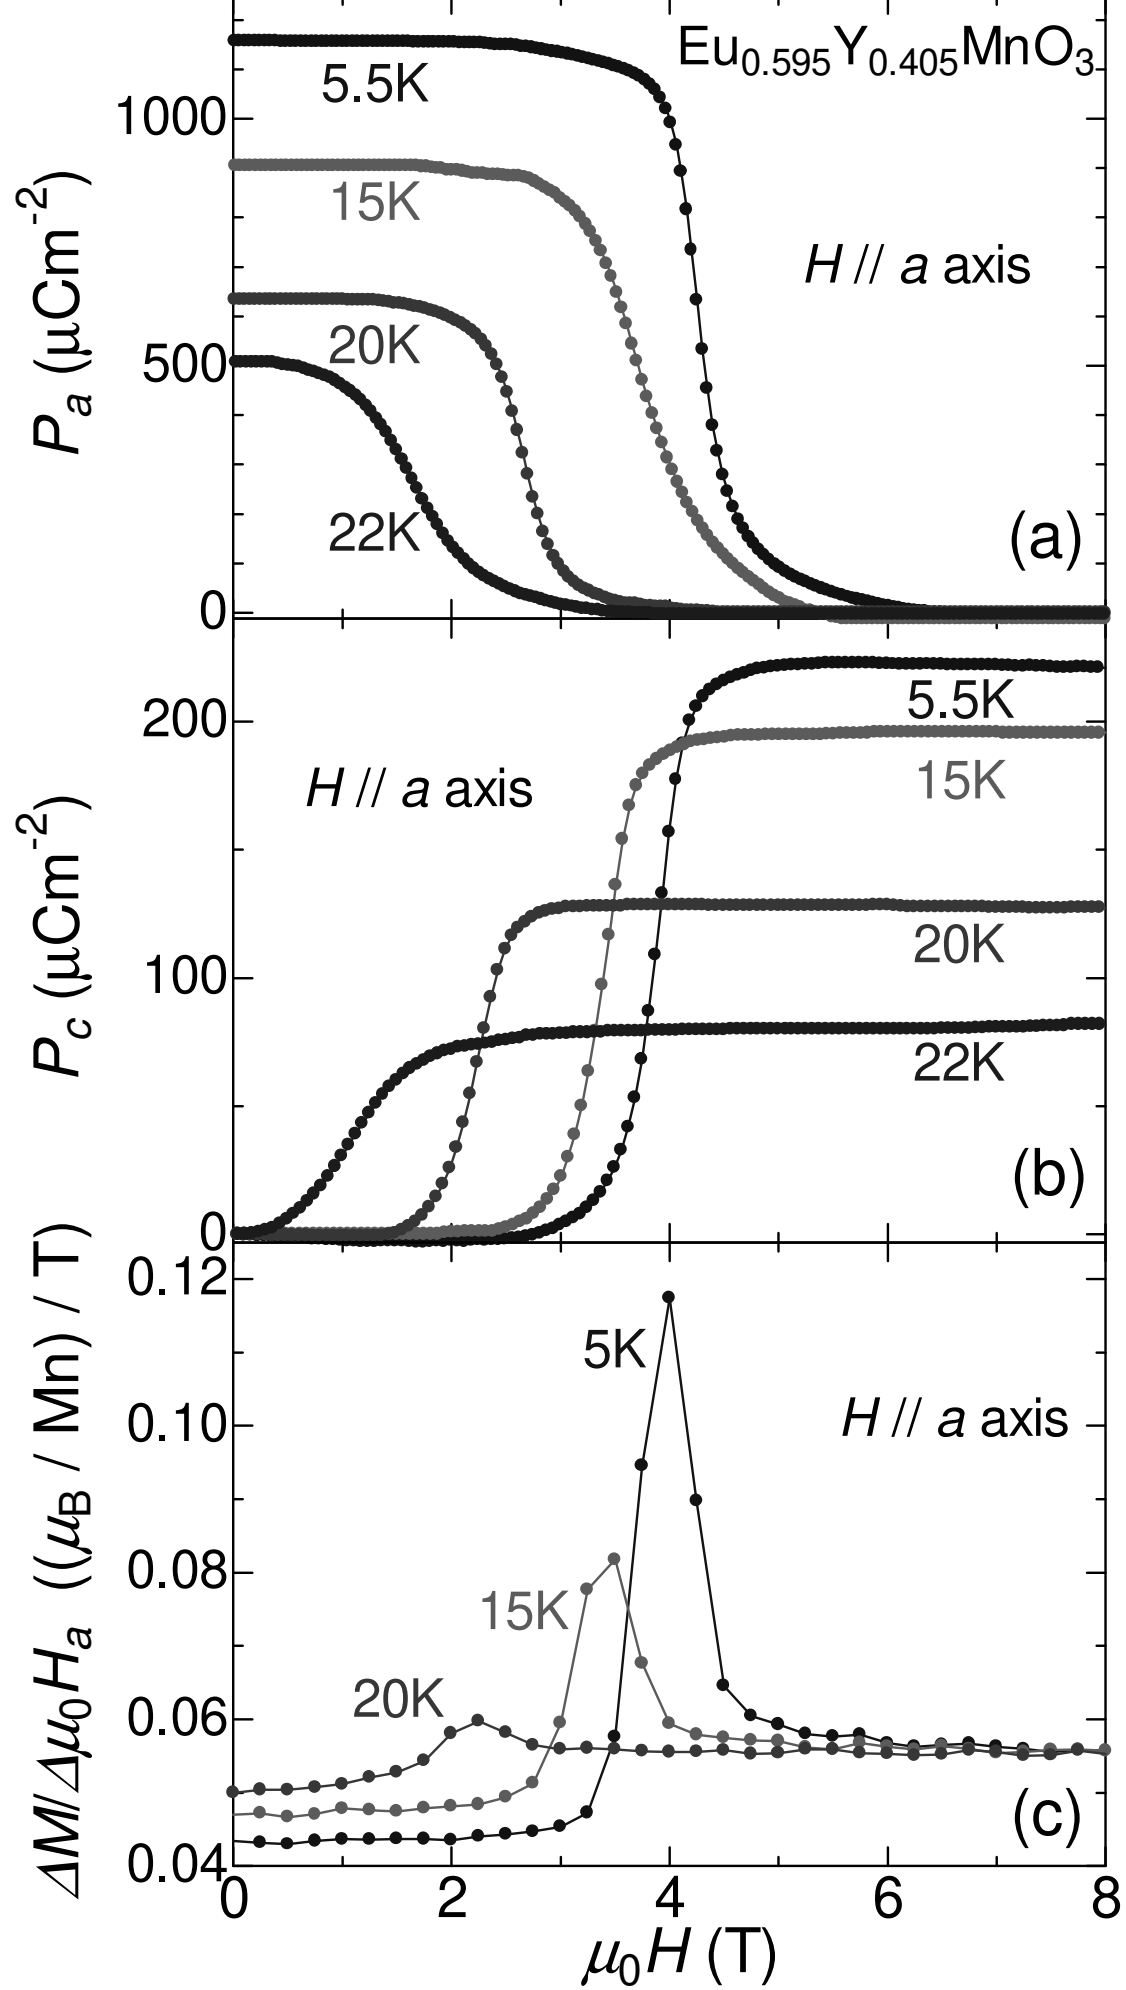

$\text{Eu}_{0.595}\text{Y}_{0.405}\text{MnO}_3$ $H//a$ axis

