

Superconducting Junctions with Ferromagnetic, Antiferromagnetic or Charge-Density-Wave Interlayers

Yuri Barash*, I. V. Bobkova*, Brian M. Andersen[†], T. Kopp** and P. J. Hirschfeld[†]

**Institute of Solid State Physics, Russian Academy of Sciences, Chernogolovka, Moscow reg., 142432 Russia*

[†]*Department of Physics, University of Florida, Gainesville, FL 32611 USA*

***Center for Electronic Correlations and Magnetism, University of Augsburg, D-86135 Augsburg, Germany*

Abstract. Spectra and spin structures of Andreev interface states and the Josephson current are investigated theoretically in junctions between clean superconductors (SC) with ordered interlayers. The Josephson current through the ferromagnet-insulator-ferromagnet interlayer can exhibit a nonmonotonic dependence on the misorientation angle. The characteristic behavior takes place if the π state is the equilibrium state of the junction in the particular case of parallel magnetizations. We find a novel channel of quasiparticle reflection (Q reflection) from the simplest two-sublattice antiferromagnet (AF) on a bipartite lattice. As a combined effect of Andreev and Q reflections, Andreev states arise at the AF/SC interface. When the Q reflection dominates the specular one, Andreev bound states have almost zero energy on AF/s-wave SC interfaces, whereas they lie near the edge of the continuous spectrum for AF/d-wave SC boundaries. For an s-wave SC/AF/s-wave SC junction, the bound states are found to split and carry the supercurrent. Our analytical results are based on a novel quasiclassical approach, which applies to interfaces involving itinerant antiferromagnets. Similar effects can take place on interfaces of superconductors with charge density wave materials (CDW), including the possible d-density wave state (DDW) of the cuprates.

Superconducting heterostructures involving ferro- and/or antiferromagnets manifest unusual properties associated with spin effects, and are of both fundamental interest and important for technological applications. Superconductor-ferromagnet-superconductor (SC/F/SC) junctions are known to display $0 - \pi$ transitions with varying the temperature or the interlayer width. We have demonstrated theoretically that the $0 - \pi$ transition can show up also at fixed temperature and interlayer width in superconducting junctions with a three-layer FIF interface, as a function of the misorientation angle between the magnetizations of two F layers separated by the insulating barrier [1]. The dependence of the Josephson current on the misorientation angle φ becomes especially simple in the tunneling limit, when the critical current takes the form $J_c(T, \varphi) = J_c^{(p)}(T) \cos^2(\varphi/2) + J_c^{(a)}(T) \sin^2(\varphi/2)$. Here $J_c^{(p)}(T)$ & $J_c^{(a)}(T)$ are critical currents in tunnel junctions with parallel and antiparallel orientations of the exchange fields in the three-layer interface. The $0 - \pi$ transition can take place with varying φ , if $J_c^{(p)}(T)$ and $J_c^{(a)}(T)$ have opposite signs. This is the case when the junction with parallel magnetizations is in the π -state, since always $J_c^{(a)}(T) > 0$. The transition results in a nonmonotonic dependence of $|J(T, \varphi)|$ on φ . This effect can be used for switching the junction from the zero state to the π state by varying the misorientation angle.

The angle is changed in the FIF interlayer with applied magnetic field, if it is larger than the coercive force in one of the F layers and less than in the other layer.

Many fundamental and practical problems involve interfaces with antiferromagnets. In particular, many of the properties of HTSC cuprate materials probably arise from a competition between antiferromagnetic and superconducting order, and many situations involve such natural or fabricated boundaries. We have studied interfaces between itinerant antiferromagnets and normal metals or superconductors and demonstrated that a new spin-dependent channel of quasiparticle reflection, the so-called Q reflection, occurs on the interfaces [2]. Parallel to the interface, the momentum component of low-energy normal-metal quasiparticles changes by Q_y in a Q reflection event, where \mathbf{Q} is the wave-vector of the antiferromagnetic pattern and y is the direction parallel to the interface. Assuming comparatively small Fermi velocity mismatches and taking into account the nesting condition $E_F(\mathbf{p} + \mathbf{Q}) = -E_F(\mathbf{p})$ in itinerant antiferromagnets, one can see within the mean-field tight-binding model on the half-filled square lattice that normal metal quasiparticles with energies less than or comparable to the antiferromagnetic gap change their momenta by \mathbf{Q} and reverse the signs of their velocities in a Q reflection event. Consequently, such quasiparticles experience spin-dependent retroreflection at antiferromagnet-normal metal (AF/N) transparent interfaces.

Quasiparticle bound states below the AF and SC gaps at AF/SC interfaces arise as a combined effect of Andreev and Q reflections. Among a variety of subgap states, low-energy states $E_B \ll \min\{m, \Delta\}$ are of special interest since they can result in low-temperature anomalies in the Josephson critical current, as well as low-bias anomalies in the conductance. Here m and Δ are the sublattice electronic magnetization and the superconducting s -wave or d -wave order parameters. In the absence of the interface potential h , the dispersive bound state energies at the (110) and (100) AF - s -wave superconductor (AF/sSC) interfaces can be represented as $E_b(\mathbf{k}_F) = \pm \Delta_s \sqrt{R_{sp}(\mathbf{k}_F)}$. Here $R_{sp}(\mathbf{k}_F)$ is the normal state reflection coefficient for specular reflection from the interface, which occurs even in the absence of any interface potentials due to a mismatch of Fermi velocities in the AF and the sSC. Since normal-metal states are presumably identical in the left and right halfspaces, under the conditions $\Delta \ll m, t$, the mismatch in the model controls the parameter m/t . If the magnetic order parameter m is much less than the hopping matrix element t , Q reflection dominates $R_{sp}(\mathbf{k}_F) \ll 1$, and bound state energies almost coincide with the Fermi level $|E_b| \ll \Delta_s \leq m$. In particular, for the (110) interface on the square lattice we find $R_{sp}(\mathbf{k}_F) = \left[1 + \left(\sqrt{2}v_{F,\perp}(\mathbf{k}_F)/am\right)^2\right]^{-1}$, where a is the lattice spacing and $v_{F,\perp}(\mathbf{k}_F)$ the normal-state Fermi velocity component along the boundary normal. In Fig. 1 we plot the quasiparticle spectrum as obtained

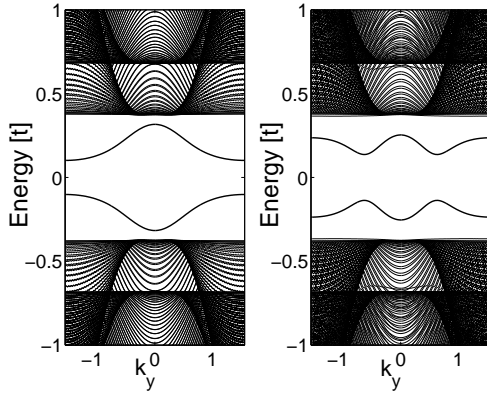


FIGURE 1. Eigenvalues for the (100) AF/sSC interface as a function of $k_y a$ (a is the lattice constant) for (a) $\mu = 0.0$ and $h = 0.0$ and (b) $h = 2.0t$. Order parameter values in the bulk: $\Delta_{s,b} = 0.4t$, $m_b = 0.7t$. Here, one sees explicitly the presence and dispersion of the bound state band inside the gap.

from the selfconsistent eigenvalues of the Bogoliubov-de Gennes equations. Interface bound states show up inside the main gap of the spectrum as a distinct band, which disperses with the momentum component k_y along the interface. The two gap edges seen in Fig. 1 are associated with the superconducting (lesser) and the antiferromag-

netic (larger) gaps. Interface potentials h present near the interface tend to suppress the bound states resulting from Q -reflection and move their positions towards the gap edge. In the regime where h is of the order of t , we find that the main effect of the specular reflection channel is to cause a stronger dispersion of the bound state energy. One can identify additional extrema in the wave vector dependence of the bound state energy $E(k_y)$. A typical example is seen in Fig. 1 where $h = 2.0t$. The new stationary points in the dispersion lead to additional LDOS peaks near the interface.

Dispersive bound state energies on an antiferromagnetic - d -wave superconductor interface (AF/dSC) can be represented as $E_b(\mathbf{k}_F) = \pm \Delta_d(\mathbf{k}_F) \sqrt{R_Q(\mathbf{k}_F)}$. They lie near the edges of the continuous spectrum, when Q reflection dominates. This contrasts with the case of a (110) surface of a dSC confined with an impenetrable wall, where zero-energy Andreev states are formed.

For an sSC/AF/sSC junction, due to a finite width l of the AF interlayer, the low-energy bound states are split and carry the supercurrent. If no potential barriers are present on the boundaries, and $l \ll \xi_s$, $\Delta_s \ll m \ll t$, we find the following energies for interface states: $\varepsilon_B = \pm \sqrt{D} |\Delta_s \cos(\chi/2)|$, where χ is the order parameter phase difference, $D(k_y) = 4K(k_y)(K(k_y) + 1)^{-2}$ is the transparency of the N/AF/N junction and $K(k_y) = \exp(2ml/|v_{F,x}(k_y)|)$. For large interlayer width, $K, D \ll 1$, there are low-energy states in the junction which result in low-temperature anomalous behavior of the critical current.

Similar effects for CDW/SC interfaces have been studied recently in [3]. Subgap Andreev states arise at CDW/dSC and DDW/sSC interfaces. At the same time there are no subgap states at CDW/sSC interfaces due to the absence of interface-induced pair-breaking processes. The interface states also do not arise at DDW/dSC interfaces since pair-breaking effects from DDW and dSC compensate each other in this case. In dSC/CDW/dSC and sSC/DDW/sSC Josephson junctions, the interface low-energy bound states are split and strongly influence the Josephson current.

This work was supported by grant NSF-INT-0340536 (I.V.B., P.J.H., and Yu.S.B.), and by ONR grant N00014-04-0060 (P.J.H and B.M.A). I.V.B. and Yu.S.B. also acknowledge the support by grant RFBR 05-02-17175. T.K. thanks the support by the DFG through SFB 484, DAAD D/03/36760 and BMBF 13N6918A.

REFERENCES

1. Yu. S. Barash, I. V. Bobkova, and T. Kopp, *Phys. Rev. B* **66**, 140503 (2002).
2. I. V. Bobkova, P. J. Hirschfeld, and Yu. S. Barash, *Phys. Rev. Lett.* **94**, 037005 (2005).

3. I. V. Bobkova, Yu. S. Barash, *Phys. Rev. B* **71**, 144510 (2005).