

Experimental determination of the non-extensive entropic parameter q

M.S. Reis and V.S. Amaral

Departamento de Física and CICECO, Universidade de Aveiro, 3810-193 Aveiro, Portugal

R.S. Sarthour and I.S. Oliveira

Centro Brasileiro de Pesquisas Físicas, Rua Dr. Xavier Sigaud 150 Urca, 22290-180 Rio de Janeiro-RJ, Brasil

(Dated: March 23, 2024)

We show how to extract the q parameter from experimental data, considering an inhomogeneous magnetic system composed by many Maxwell-Boltzmann homogeneous parts, which after integration over the whole system recover the Tsallis non-extensivity. Analyzing the cluster distribution of $\text{La}_{0.7}\text{Sr}_{0.3}\text{MnO}_3$ manganite, obtained through scanning tunnelling spectroscopy, we measure the q parameter and predict the bulk magnetization with good accuracy. The connection between the Griffiths phase and non-extensivity is also considered. We conclude that the entropic parameter embodies information about the dynamics, the key role to describe complex systems.

PACS numbers:

Keywords: Tsallis statistics; manganites; scanning tunnelling spectroscopy; Griffiths phase; diluted magnetic system

It is widely accepted that the statistical description of a system should be based on its dynamics; however, it is an information that indeed does not lie in the Boltzmann entropy. This fact opens a path for new and different statistics other than the Boltzmann one. In this direction, Tsallis thermostatics has been strongly used in a number of different contexts¹. This framework is applicable to systems which, broadly speaking, present at least one of the following properties: (i) long-range interactions, (ii) long-time memory, (iii) fractality and (iv) intrinsic inhomogeneity^{1,2}. Manganese oxides, or simply manganites, seem to embody three out of these four ingredients: they present Coulomb long-range interactions^{3,4,5}, clusters with fractal shapes^{6,7} and intrinsic inhomogeneity^{6,8,9,10,11}. Indeed, a sequence of previous publications^{12,13,14}, has shown that the magnetic properties of manganites can be properly described within a mean-field approximation using Tsallis statistics.

In the present Letter, through an analogy to the works of Beck¹⁵ and Beck and Cohen¹⁶, we consider an inhomogeneous magnetic system composed by many homogeneous parts with different sizes, each one of them described by the Maxwell-Boltzmann statistics. By averaging the magnetization over the whole system, we recover the Tsallis non-extensivity. From this point of view, an analytical relationship between the q parameter and the moments of the distribution was obtained. The robustness of the present model was tested using Scanning Tunnelling Spectroscopy (STS) conductance maps, where the q parameter could be obtained and, consequently, the bulk magnetization predicted. In order to strengthen the connections between inhomogeneity and non-extensivity, it is shown that the description of manganites using Griffiths phase^{17,18} is related to the non-extensive treatment, which contains the dynamics of the system.

We start considering a magnetic system formed by small regions, or clusters of Maxwell-Boltzmann bits,

each of them with magnetization M given by the simple Langevin function¹⁹. The clusters are distributed in size, and therefore in their net magnetic moment. Thus, let $f(\cdot)$ be the distribution of magnetic moment of the clusters. The average magnetization of the sample will be given by:

$$\langle M \rangle = \int_0^{\infty} M f(M) dM \quad (1)$$

Our goal is to connect the above expression to the non-extensive magnetization, that is calculated in Ref.^{14,20}:

$$M_q = \frac{\mu_{ne}}{(2-q)} \coth_q x \quad (2)$$

where $x = \mu_{ne} H / kT$, \coth_q is the generalized q -hyperbolic co-tangent²¹, $2-q < 1$ is the Tsallis entropic parameter and μ_{ne} means the magnetic moment of each non-extensive cluster. The non-extensive correlations lie inside each cluster, whereas the interactions inter-clusters remain extensive. This guarantees that the total magnetization will be additive¹⁴.

Microscopic analysis: From Eqs.1 and 2, the average and non-extensive magnetic susceptibilities can be derived: $\langle M \rangle = \langle M \rangle / 3kT$ and $M_q = M_q / 3kT$, as well as the saturation values of the magnetization: $\langle M \rangle_{\text{sat}} = \langle M \rangle$ and $M_{q,\text{sat}} = M_q / (2-q)$. Thus, equating those limits ($\langle M \rangle = \langle M \rangle$ and $\langle M \rangle_{\text{sat}} = M_{q,\text{sat}}$), we find a microscopic analytical expression to the q parameter, in the sense that it is related to a microscopic information (distribution of magnetic moments):

$$q(2-q)^2 = \frac{\langle M^2 \rangle}{\langle M \rangle^2} \quad (3)$$

where $\langle M \rangle$ and $\langle M^2 \rangle$ are the first and second moments of the distribution $f(\cdot)$, respectively. This result is valid for any $f(\cdot)$, and is analogous to that obtained by Beck¹⁵ and Beck and Cohen¹⁶ in other contexts.

Macroscopic analysis: From Eq. 2 we can obtain a macroscopic analytical expression for the q parameter (similarly to what was done in¹⁴), in the sense that it is now related to macroscopic quantities:

$$q(2 - q)^2 = \frac{3kT}{M_{\text{sat}}^2} \quad (4)$$

where χ and M_{sat} are the experimental magnetic susceptibility and saturation value, respectively. Note that for an homogenous superparamagnetic-like system, $q = 1$.

Experimental connection with the microscopic analysis: The colossal magnetoresistance (CMR) effect⁸, usually observed on manganites, has been explained in terms of intrinsic inhomogeneities^{6,8,9}, which lead to the formation of insulating and conducting domains within a single sample, i.e., electronic phase separation in a chemically homogeneous sample. The inhomogeneities alter the local electronic and magnetic properties of the sample and should therefore be visible via STS^{9,22,23} or Magnetic Force Microscopy (MFM)^{24,25}.

Becker and co-workers⁹ measured STS in a $\text{La}_{0.7}\text{Sr}_{0.3}\text{MnO}_3/\text{MgO}$ thin film and visualized a domain structure of conducting (ferromagnetic) and insulating (paramagnetic) regions with nanometric size. This manganite has a transition from a metallic phase (below T_C) to an insulating phase (above T_C), with a strong phase coexistence/competition around T_C 330 K. The STS conductance maps obtained by those authors at 87 K, 150 K and 278 K are reproduced in figure 1(a). From these 1-bit images (black regions mean insulating/paramagnetic phase and white regions stand for conducting/ferromagnetic phase), we have determined the distribution of clusters size. Considering that the cluster size, measured in *pixels*, is proportional to the magnetic moment of the cluster, Eq. 3 can be re-written as:

$$\frac{h^2 i}{h^2 i^2} = \frac{h^2 i}{h^2 i^2} = q(2 - q)^2 \quad (5)$$

The conductance map at 278 K has a distribution of clusters as presented in figure 1(a), and, using Eq. 5 we obtain from the data $q = 2.95$.

With this value of q , the total magnetization of the system can be predicted, by considering the mean-field approximation into the generalized magnetization (Eq.2), where $x = 3m_q = t$, $m_q = M_q = n_e$, $t = T = T_C^{(1)}$ and $T_C^{(1)} = 298\text{K}$ ¹² (see refs.^{12,14} for details concerning the mean-field approximation applied to the non-extensive magnetization). This procedure results in a satisfactory agreement between the predicted reduced magnetization ($m_q = 0.25$) and the experimental one, obtained measuring the bulk magnetization⁹, as presented in figure 1(b). The images at 87 K and 150 K were not analyzed, since the clusters have already percolated.

The procedure above described shows how to extract the q parameter from experimental data, and then how to apply the obtained q parameter to predict macroscopic

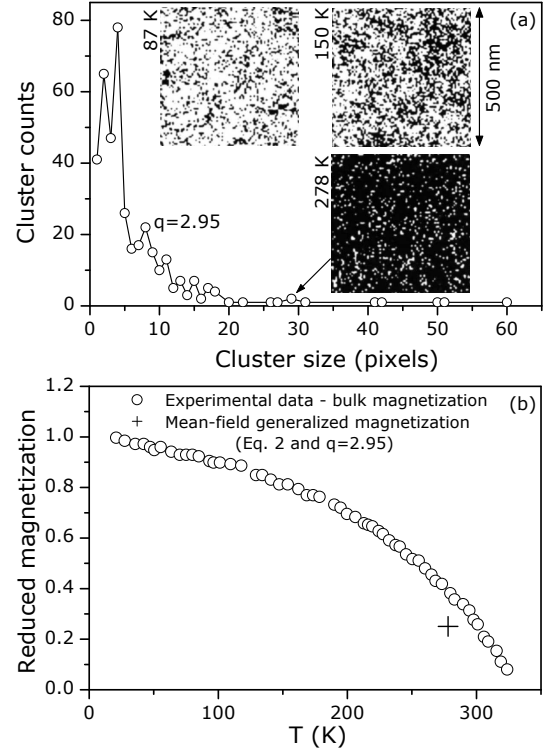


FIG. 1: (a) Scanning tunnelling spectroscopy images on $\text{La}_{0.7}\text{Sr}_{0.3}\text{MnO}_3/\text{MgO}$ manganite thin film, after Becker *et al.*⁹. White regions mean conducting (ferromagnetic) clusters and the black regions stand for insulating (paramagnetic) phase. The main graphic is the cluster size distribution of the image at 278 K, proportional to the cluster magnetic moment distribution, where, using Eq.5, $q = 2.95$ could be directly obtained. (b) Using the mean-field (reduced) generalized magnetization (Eq.2: + symbol), we could predict the bulk magnetization, in a satisfactory agreement with the measured one (○ symbol), in a reduced scale $M = M(18\text{ K})$ ⁹.

quantities of the system. In addition, these results exemplify the relation between non-extensivity and microscopic inhomogeneities. Finally, it is important to stress that q is related to the dynamics of the system, since it measures the distribution of magnetic moments, that contains the dynamics.

Experimental connections with the macroscopic analysis: $\text{Pr}_{0.05}\text{Ca}_{0.95}\text{MnO}_3$ ($T_C = 110\text{ K}$), LaMnO_3 ($T_C = 138\text{ K}$) and $\text{La}_{0.7}\text{Ca}_{0.3}\text{MnO}_3$ ($T_C = 225\text{ K}$) are interesting examples of manganites. The inverse susceptibility as a function of temperature presents a strong downturn around T_C . These samples were prepared and measured as reported in Refs^{26,27}, except the La-Ca manganite, where the experimental susceptibility was reproduced from Ref¹⁸.

The lower panels of figure 2 (○ symbols) present the q parameter obtained from the macroscopic analysis; using Eq. 4, the measured magnetic susceptibility (experimental data presented in the upper panels of figure 2) and the magnetic saturation value for the above cited mangan-

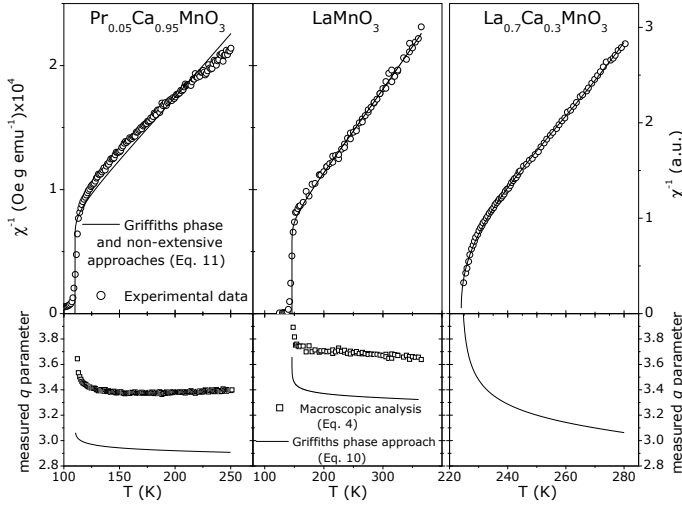


FIG. 2: Upper panels: Experimental (open circles) and theoretical (solid line-Eq. 11) temperature dependence of the inverse susceptibility for the La_{0.7}Ca_{0.3}MnO₃ (after Salamon *et al.*¹⁸), LaMnO₃ and Pr_{0.05}Ca_{0.95}MnO₃ manganites. Lower panels: measured q parameter from the macroscopic analysis and Griffiths phase approach.

ites (Pr-manganite: 8.9 emu/g and La-manganite: 8.5 emu/g). This procedure was not done for the La-Ca manganite, since Ref.¹⁸ does not provide the corresponding absolute values for the magnetic susceptibility.

Connections with Griffiths phase: An extensive number of papers^{28,29,30,31,32} (and references therein) deal with the dynamics of random magnetic systems, with special attention for a diluted Ising ferromagnet. The systems of interest are obtained by starting with an ordinary Ising model, which contains spins located on the vertices of a regular lattice. For a bond dilution, the nearest-neighbor interactions J_{ij} are independent random variables taking the values J and 0 with probabilities p and $1 - p$, respectively. For a site dilution, $J_{ij} = J c_i c_j$, where $c_{i,j} = 1$ or 0 , with probabilities p and $1 - p$, respectively. This diluted ferromagnet is in the Griffiths phase^{17,18,30,31,32} if its temperature is between the critical temperature $T_c(p)$ and the critical temperature $T_G = T_c(1)$ of a pure/non-diluted system. In figure 3, the dilution p -temperature T plane sketches this scenario.

Salamon and co-workers^{17,18} have used the idea of Griffiths singularity to study manganites, considering a distribution of the inverse magnetic susceptibility:

$$f(\chi) = \frac{A^{c-1} \exp(-A\chi)}{(c-1; A=T)} \quad (6)$$

to explain the sharp downturn in the $h^{-1}(T)$ curve (behavior usually observed in manganites, as displayed in the upper panels of figure 2). In the expression above, c is a parameter of the distribution, χ stands for the In-

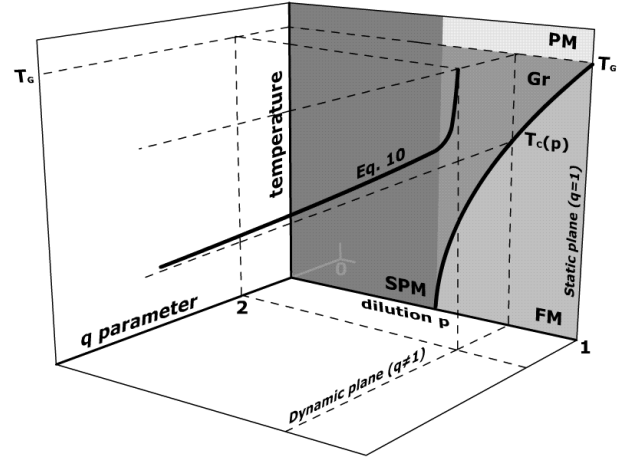


FIG. 3: Connections between Griffiths phase and non-extensivity, in a q - p - T space. p - T plane: usual magnetic phase diagram for a site/bond diluted magnetic system, where: SPM-superparamagnetic-like phase, PM-paramagnetic phase, FM-ferromagnetic phase and Gr-Griffiths phase. This plane contains the critical temperature T_c and dilution p , basic (and static) information about the system. q - T plane contains information related to the dynamics of the system, through Eq. 10. See text for details.

complete Gamma Function and

$$A = a \frac{\frac{T}{T_G} - 1}{1 - \frac{T}{T_G}} \quad (7)$$

where a is a free parameter, $\alpha = 0.38$ is a critical exponent for the pure system, assumed to be a 3D Heisenberg-like, and T_G is the Griffiths temperature^{17,18,30,31,32}. From Eq. 6 one can find the inverse average susceptibility³³:

$$h^{-1} = A \frac{(c-1; A=T)}{(c; A=T)} \quad (8)$$

that fits the strong downturn usually found on manganites.

The Curie Law $\chi = 1/3kT$ of a small Maxwell-Boltzmann region tells us that inhomogeneities in χ can arise from distributions of either χ or T (or both). Thus, we can obtain from Eq.6 a corresponding distribution of magnetic moments:

$$f(\chi) = \frac{A^{c-1}}{3T} \frac{2 - 2c - 3}{(c-1; A=T)} \exp\left(-\frac{A}{3T}\right) \quad (9)$$

and, consequently, the q parameter:

$$\frac{h^{-2}}{h^{-1}} = \frac{(c; A=T) - (c-1; A=T)}{(c-1=2; A=T)^2} = q(2-q)^2 \quad (10)$$

This result shows that, since h^{-1} and h^{-2} are both temperature dependent, one can expect that q will also be

T-dependent. This is expected, since the distribution of magnetic moments changes as a function of temperature, changing also the q parameter. Indeed, it can be observed in the STS images presented in figure 1(a), reinforcing the idea that q is related to the dynamics of the system.

From the above, one can write the non-extensive magnetic susceptibility:

$$\chi_q = \frac{q^2}{3kT} = \frac{q(2-q)^2 h^2 i^2}{3kT} = \frac{h^2 i^2}{3kT} = h^2 i^2 \quad (11)$$

that is equal to the average one. It is important to note that, once we know $f(\cdot)$, the value of q can be directly obtained, and, consequently, χ_q . The present approach, as well as those presented previously, *does not* consider the entropic index q as a fitting parameter, but as a known quantity, previously determined and direct related to the inhomogeneity and dynamics of the system.

The model above described (Eq. 11) is presented in the upper panels of figure 2. To obtain those results, the distribution of magnetic moments $f(\cdot)$ presented in Eq. 9 has the following parameters: $c = -0.04$, $a = 0.002$ K and $T_G = 510$ K, for $\text{Pr}_{0.05}\text{Ca}_{0.95}\text{MnO}_3$; $c = 0.01$, $a = 4.7 \times 10^{-8}$ K and $T_G = 555$ K, for LaMnO_3 ; and $c = 0.32$, $a = 0.066$ K and $T_G = 335$ K, for $\text{La}_{0.7}\text{Ca}_{0.3}\text{MnO}_3$. These parameters for the La-Ca manganite are considerable different from those presented in Ref.¹⁸, due to the remarkable difference between the fit presented by those authors and that one sketched in figure 2. The entropic index q (lower panels of figure 2) *is not* a free parameter and could be obtained *a priori*, using Eqs. 3 and 9. It is important to stress the agreement between the *measured* q *parameter* using the macroscopic analysis, and the present approach.

The connection between Griffiths phase and non-extensivity can be visualized considering the q param-

eter as another dimension; an independent variable in a q - p - T space, as sketched in figure 3. Analogously to the Curie temperature, a dilution p characterizes a diluted magnetic system, since these (static) quantities are unique for a certain system. If we know only p and $T_C(p)$, it is not possible to achieve the dynamics of this diluted magnetic system. For instance, given a dilution p , and consequently a Curie temperature $T_C(p)$, there are $\frac{N}{pN}$ different ways to dispose these spins, considering a site dilution problem with N available positions in the lattice. Different distributions of spins imply different dynamics and, consequently, different macroscopic quantities, like magnetization. In this sense, these quantities (p and $T_C(p)$) are static. On the other hand, the results presented in this Letter shown how the q parameter is related to the dynamics of the system and, once known q , the dynamics is consequently determined. Thus, we propose that the p - T plane at $q = 1$ is a static plane, whereas the q - T plane (Eq. 10), for a certain value of p (or $T_C(p)$) takes account the dynamics of the system.

Summarizing, in the present Letter we shown that the q parameter measures the inhomogeneity and dynamics of a given inhomogeneous magnetic system. From the measured q obtained from scanning tunnelling spectroscopy on manganites (a microscopic information), one can predict a thermodynamic quantity, the bulk magnetization (a macroscopic information); the entropic parameter contains the dynamics, connecting the microscopic and macroscopic information. The present model was also successfully applied to other manganites (bulk and thin films) and melt-spun granular alloys, reinforcing the conclusions made.

We acknowledge CAPES-Brasil, CNPq-Brasil and GRICES-Portugal. We are also thankful to P.B. Tavares, A.M.L. Lopes, M.P. Albuquerque and A.R. Gesualdi for valuable discussions.

Electronic address: marior@fis.ua.pt

- ¹ For a complete and updated list of references, see the web site: tsallis.cat.cbpf.br/biblio.htm.
- ² C. Tsallis, *Nonextensive Statistical Mechanics and Its Applications* (Springer-Verlag, Heidelberg, 2001), chap. Nonextensive Statistical Mechanics and Thermodynamics: Historical Background and Present Status, eds. S. Abe and Y. Okamoto.
- ³ J. Lorenzana, C. Castellani, and C. D. Castro, Phys. Rev. B **64**, 235127 (2001).
- ⁴ J. Lorenzana, C. Castellani, and C. D. Castro, Phys. Rev. B **64**, 235128 (2001).
- ⁵ A. Moreo, S. Yunoki, and E. Dagotto, Science **283**, 2034 (1999).
- ⁶ E. Dagotto, T. Hotta, and A. Moreo, Phys. Rep. **344**, 1 (2001).
- ⁷ M. Ausloos, L. Hubert, S. Dorbolo, A. Gilabert, and R. Cloots, Phys. Rev. B **66**, 174436 (2002).
- ⁸ E. Dagotto, *Nanoscale phase separation and colossal mag-*

netoresistance: The physics of manganites and related compounds. (Springer-Verlag, Heidelberg, 2003).

- ⁹ T. Becker, C. Streng, Y. Luo, V. Moshnyaga, B. Damaschke, N. Shannon, and K. Samwer, Phys. Rev. Lett. **89**, 237203 (2002).
- ¹⁰ S. Kumar and P. Majumdar, Phys. Rev. Lett. **92**, 126602 (2004).
- ¹¹ K. H. Ahn, T. Lookman, and A. R. Bishop, Nature **428**, 401 (2004).
- ¹² M. S. Reis, J. C. C. Freitas, M. T. D. Orlando, E. K. Lenzi, and I. S. Oliveira, Europhys. Lett. **58**, 42 (2002).
- ¹³ M. S. Reis, J. P. Araújo, V. S. Amaral, E. K. Lenzi, and I. S. Oliveira, Phys. Rev. B **66**, 134417 (2002).
- ¹⁴ M. S. Reis, V. S. Amaral, J. P. Araújo, and I. S. Oliveira, Phys. Rev. B **68**, 014404 (2003).
- ¹⁵ C. Beck, Phys. Rev. Lett. **87**, 180601 (2001).
- ¹⁶ C. Beck and E. G. D. Cohen, Physica A **322**, 267 (2003).
- ¹⁷ M. B. Salamon, P. Lin, and S. H. Chun, Phys. Rev. Lett. **88**, 197203 (2002).

- ¹⁸ M. Salamon and S. Chun, Phys. Rev. B **68**, 014411 (2003).
- ¹⁹ A. P. Guimarães, *Magnetism and Magnetic Resonance in Solids* (John Wiley, New York, 1998).
- ²⁰ In our previous work¹⁴, we derived the two-branched Generalized Langevin Function. However, further calculations lead us to a more concise and general expression, valid for any real value of q and x (Eq.2).
- ²¹ E. P. Borges, J. Phys. A: Math. Gen. **31**, 5281 (1998).
- ²² C. Renner, G. Aeppli, B. Kim, Y. Soh, and S. Cheong, Nature **416**, 518 (2002).
- ²³ M. Fath, S. Freisem, A. A. Menovsky, Y. Tomioka, J. Aarts, and J. A. Mydosh, Science **285**, 1540 (1999).
- ²⁴ Q. Lu, C. Chen, and A. deLozanne, Science **276**, 2006 (1997).
- ²⁵ L. Zhang, C. Israel, A. Biswas, R. L. Greene, and A. deLozanne, Science **298**, 805 (2002).
- ²⁶ M. S. Reis, V. S. Amaral, J. P. Araújo, P. B. Tavares, A. M. Gomes, and I. S. Oliveira, Phys. Rev. B **71**, 144413 (2005).
- ²⁷ A. M. L. Lopes, J. P. Araujo, E. Rita, J. G. Correia, V. S. Amaral, R. Suryanarayanan, and ISOLDE, J. Magn. Magn. Mater. **272**, E1671 (2004).
- ²⁸ G. Mazzeo and R. Kuhn, Phys. Rev. E **60**, 3823 (1999).
- ²⁹ M. Thorpe and A. McGurn, Phys. Rev. B **20**, 2142 (1979).
- ³⁰ A. Bray and G. Rodgers, Phys. Rev. B **38**, 11461 (1988).
- ³¹ A. Bray, Phys. Rev. Lett. **59**, 586 (1987).
- ³² A. Bray, Phys. Rev. Lett. **60**, 720 (1988).
- ³³ In a different fashion as presented by Salamon and co-workers^{17,18}, we derived an analytical and closed expression to the inverse average susceptibility.