

Studies of $R_2Ti_2O_7$ ($R=Gd$ and Yb); new results

P. Dalmas de Réotier ^a, V. Glazkov ^a, C. Marin ^a, A. Yaouanc ^a,
P.C.M. Gubbens ^b, S. Sakarya ^b, P. Bonville ^{c, d}, A. Amato ^d,
C. Baines ^d, and P.J.C. King ^e

^a*CEA/DSM, Département de Recherche Fondamentale sur la Matière Condensée,
F-38054 Grenoble Cedex 9, France*

^b*Department of Radiation, Radionuclides & Reactors, Delft University of
Technology, 2629 JB Delft, The Netherlands*

^c*CEA/DSM, Département de Recherche sur l'Etat Condensé, les Atomes et les
Molécules, F-91191 Gif sur Yvette, France*

^d*Laboratory for Muon-Spin Spectroscopy, Paul Scherrer Institute, 5232
Villigen-PSI, Switzerland*

^e*ISIS Facility, Rutherford Appleton Laboratory, Chilton, Oxfordshire OX11 0QX,
United Kingdom*

Abstract

Specific heat and muon spin rotation and relaxation data are presented for two geometrically frustrated systems: $Gd_2Ti_2O_7$ which antiferromagnetically orders and $Yb_2Ti_2O_7$ which presents dynamical short range correlations at low temperature. The muon data help to characterize the spin dynamics of these two compounds.

Key words: Magnetism, frustration, pyrochlore.

Geometrically derived magnetic frustration arises when the spatial arrangement of the spins is such that it prevents the simultaneous minimization of all interaction energies [1]. Compounds of interest for the investigation of frustration are, for example, the crystallographically ordered pyrochlore structure compounds $R_2Ti_2O_7$ where the rare earth ions (R) form a sub-lattice of corner sharing tetrahedra.

We shall focus on two pyrochlore compounds $Gd_2Ti_2O_7$ and $Yb_2Ti_2O_7$. Reports of experimental data concerning these two systems were already published by some of us, see Refs. [2,3,4,5]. A summary of the muon spin rotation

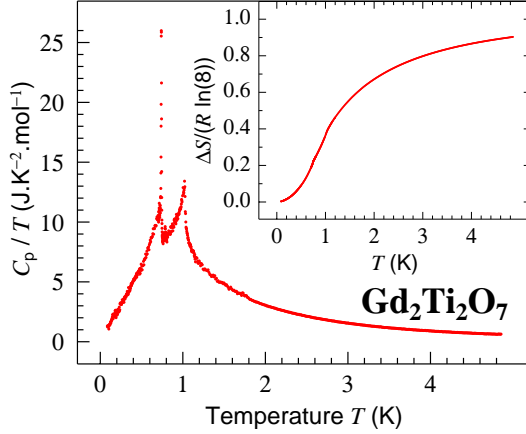


Fig. 1. Thermal dependence of the specific heat divided by the temperature measured for a crystal of $\text{Gd}_2\text{Ti}_2\text{O}_7$. The data are presented per mole of Gd. The maxima of the specific heat at $T_{c1} = 1.02$ K and $T_{c2} = 0.74$ K are the signatures of the magnetic phase transitions. The insert displays the computed entropy variation as a function of the temperature between $\simeq 85$ mK and 5 K.

and relaxation (μSR) data has been recently provided [6]. Here we report unpublished data obtained from specific heat and μSR measurements. The latter measurements were either performed at the ISIS μSR facility in UK or at the Swiss Muon Source of the Paul Scherrer Institute in Switzerland. We stress that the specific heat measurements are essential to test the sample quality in geometrically frustrated systems. For example, in the case of $\text{Gd}_2\text{Ti}_2\text{O}_7$, the heat treatment affects the specific heat data in two ways. First it notably increases the intensity of the signal and second it slightly decreases the temperature of the two peaks corresponding to the magnetic transitions. As far as μSR spectra are concerned, the values for the measured local fields are noticeably changed by the heat treatment.

In a first step we consider $\text{Gd}_2\text{Ti}_2\text{O}_7$. Figure 1 shows the specific heat measurements and the variation of entropy which is deduced from these data. The entropy variation up to $\simeq 5$ K is only 90 % of its expected value for a spin $7/2$ system. This missing entropy is probably related to the persistent spin dynamics observed in this system deep in the ordered state [2]. The specific heat structure observed at $T_{c1} \simeq 1.02$ K for $\text{Gd}_2\text{Ti}_2\text{O}_7$ corresponds to a long-range magnetic ordering of the Gd magnetic moments as shown by the spontaneous muon spin precession detected below T_{c1} in zero-field. In fact, we observe two Bessel-like oscillations, each characterized by the maximum field at the muon site, B_{max} ; see Fig. 2. Note that the transition at $T_{c2} \simeq 0.74$ K is hardly visible in the temperature dependence of B_{max} . This is not surprising since the difference between the magnetic structures adopted by $\text{Gd}_2\text{Ti}_2\text{O}_7$ above and below T_{c2} is small: the change concerns only a quarter of the Gd^{3+} moments which are disordered above T_{c2} and very weakly ordered below [7].

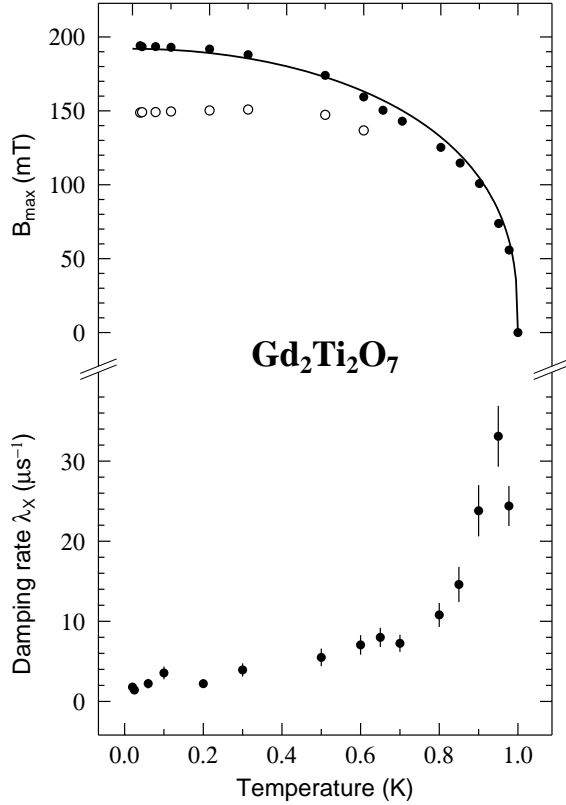


Fig. 2. Temperature dependence of B_{\max} measured for $\text{Gd}_2\text{Ti}_2\text{O}_7$ (two fields per temperature point can be resolved up to 0.6 K and only one field at higher temperatures) and the associated exponential damping rate λ_X for the higher B_{\max} value. The damping rate is negligible for the smaller B_{\max} . The line is the result of a fit for the larger field with $B_{\max}(T) \propto [1 - (T/T_{c1})^\alpha]^\beta$, setting $\alpha = 2$ and $\beta = 0.365$ as expected for a 3D Heisenberg antiferromagnet characterized by a second order phase transition at $T = T_{c1}$. The fit is numerically reasonable and physically justified since B_{\max} is expected to track the order parameter. The contact field term, which might have a temperature dependence different from that of the order parameter, should indeed be negligible for an insulating compound such as $\text{Gd}_2\text{Ti}_2\text{O}_7$.

Although the thermal behavior of the spin-lattice relaxation, λ_Z , at high temperature is not directly related to the frustrated nature of the compounds of interest, it is still of interest. We present $\lambda_Z(T)$ above T_{c1} for $\text{Gd}_2\text{Ti}_2\text{O}_7$ in Fig. 3. When the temperature is decreased from room temperature towards T_{c1} , $\lambda_Z(T)$ first slightly decreases and reaches a local minimum around 10 K, before the slowing down of the spin dynamics causes a marked increase of $\lambda_Z(T)$ when approaching T_{c1} . The initial slight decrease is the signature of the antiferromagnetic spin correlations which build up in $\text{Gd}_2\text{Ti}_2\text{O}_7$ as the system is cooled down. It is fitted to a model in which the spin correlation function is expanded versus $(k_B T)^{-1}$ [6,3] (see line in Fig. 3).

A remarkable output of most μSR measurements for geometrically frustrated magnetic materials has been the observation of persistent spin dynamics at

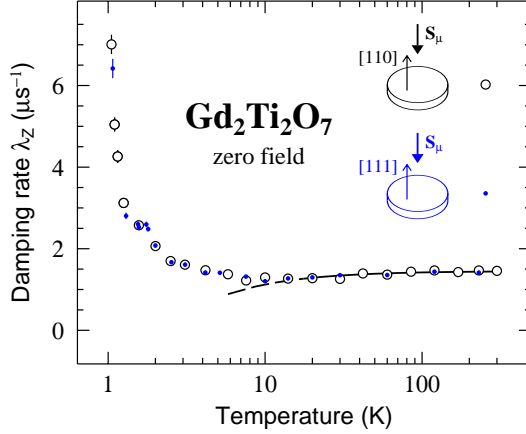


Fig. 3. The spin-lattice relaxation rate λ_Z versus temperature measured in the paramagnetic phase for crystals of $\text{Gd}_2\text{Ti}_2\text{O}_7$. The data have been recorded for two orientations of the initial muon polarization, parallel to either a [111] or [110] crystallographic axis: they show no difference. The line is the result of a fit with $\lambda_Z(T) = \lambda_Z^{(ss)}(1 + T_0/T)$ where $\lambda_Z^{(ss)} = 1.45(37) \mu\text{s}^{-1}$ and $T_0 = -2.3(6)$ K. The further increase of λ_Z as the sample is cooled down below $\simeq 10$ K reflects the slowing down of the magnetic fluctuations when approaching T_{c1} from above. This effect is not accounted for by the model.

low temperature. That dynamics has recently been shown to be the signature of a large density of states at low energy characterized by a gap linear in temperature [2]. The persistent dynamics is usually recognized by the observation of a finite value for λ_Z . This is the case for $\text{Gd}_2\text{Ti}_2\text{O}_7$ [2]. If the spin dynamics is particularly slow, $P_Z(t)$ is no longer stretched-like but Kubo-Toyabe-like. This type of relaxation function was found in $\text{Yb}_2\text{Ti}_2\text{O}_7$ [4] below the temperature of the specific heat peak shown in Fig. 4. The spin dynamics is then revealed by the finite slope of $P_Z(t)$ at large time. In order to ascertain the interpretation of the $\text{Yb}_2\text{Ti}_2\text{O}_7$ spectra, we have investigated their field dependence. As shown in Fig. 5, the relaxation is quenched by a longitudinal field. The fits presented as full lines in this figure are done using the function $a_0 P_Z(t) = a_1 P_{\text{GBG}}(t) + a_2$ where $P_{\text{GBG}}(t)$ is the Gaussian-broadened Gaussian function [8] and the second term (a_2) represents the background signal which mainly arises from muons stopped in the silver sample holder. A conventional Kubo-Toyabe function instead of $P_{\text{GBG}}(t)$ does not properly account for the data. This is illustrated by the dashed line in Fig. 5 which is the best fit for the spectrum recorded in a 2 mT longitudinal using the Kubo-Toyabe function: the dashed line curve differs notably from the data for $t \leq 1 \mu\text{s}$. It means that the muon spins detect a field distribution influenced by disorder. This probably results from the geometrical frustration of the magnetic interactions. We also note that a dynamical spin-glass model [9] does not either provide a fit of the early times data as good as the $P_{\text{GBG}}(t)$ function.

The model behind this Gaussian-broadened Gaussian function assumes that

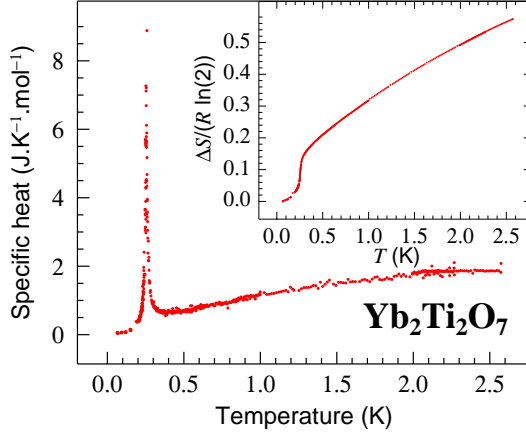


Fig. 4. Specific heat variation for the powder sample of $\text{Yb}_2\text{Ti}_2\text{O}_7$ which was used in a previously published study [4]. The data are plotted per mole of Yb. The maximum of the peak is around 0.25 K, which is the temperature of a sharp change in the spin dynamics [4]. The insert shows the entropy variation deduced from the specific heat data.

the muons see different environments, each of them being characterized by a dynamical Kubo-Toyabe function associated with a field width Δ/γ_μ . To account for the slight differences between the environments, Δ is then assumed to be Gaussian distributed with a mean-value Δ_0 and a width w . The common parameters for the five spectra presented in Fig. 5 are the initial asymmetries of the μSR signals related to the sample and the background, respectively $a_1 = 0.170$ and $a_2 = 0.065$, $\Delta_0 = 4.9 \mu\text{s}^{-1}$ ($\Delta_0/\gamma_\mu = 5.7 \text{ mT}$), the correlation frequency of the field at the muon $\nu = 0.85 \text{ MHz}$ and $w/\Delta_0 = 0.38$. Only the field values are changed. As expected from the important effect of modest fields in the shape of the μSR spectra, ν is found in the megahertz range. The remarkable result is that the fits work only if we take the values for the field smaller than the actual applied field. We have $B_{\text{meas}} = 2.5, 5.0, 9.2, 17.2$ and 36 mT instead of $B_{\text{ext}} = 10, 20, 50, 100$ and 200 mT respectively. This remarkably feature has already been encountered for a Kagome-like material [10]. It has been attributed to the intermittent nature of the spin dynamics. In our case the ratio $B_{\text{meas}}/B_{\text{ext}}$ depends on B_{ext} which would imply that the applied field affects the system. We note that Δ_0/γ_μ is reduced compared to the high temperature field width of 80 mT [11] measured above the specific heat anomaly at $\simeq 0.25 \text{ K}$. This reduction is consistent with the sporadic nature of the field at the muon. More work is yet needed for an interpretation of the magnitude of this reduction.

Financial support from the Netherlands Organization for Scientific Research (NWO) and the European Union (EU) is gratefully acknowledged.

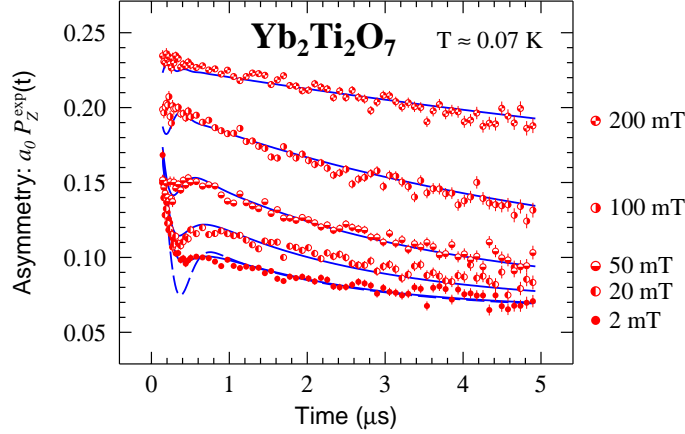


Fig. 5. Effect of a longitudinal magnetic field on the longitudinal polarization function $P_Z(t)$ recorded in $\text{Yb}_2\text{Ti}_2\text{O}_7$ at low temperature. The spectra are presented in absolute scale, *i.e.* they are not shifted vertically. The different lines are results of fits described in the main text.

References

- [1] A.P. Ramirez, *Handbook of Magnetic Materials*, Vol 13, edited by K.H.J. Buschow (Elsevier, Amsterdam, 2001).
- [2] A. Yaouanc *et al.*, Phys. Rev. Lett. **95** (2005) 047203.
- [3] P. Dalmas de Réotier *et al.*, Hyperfine Interactions, in press.
- [4] J.A. Hodges *et al.*, Phys. Rev. Lett. 88 (2002) 077204.
- [5] P. Bonville *et al.*, Hyperfine Interactions, 156-157 (2004) 103.
- [6] P. Dalmas de Réotier, P.C.M. Gubbens and A. Yaouanc, J. Phys.: Condens. Matter 16 (2004) S4687.
- [7] J.R. Stewart *et al.*, J. Phys.: Condens. Matter 16 (2004) L321.
- [8] D.R. Noakes and G.M. Kalvius, Phys. Rev. B 56 (1997) 2352.
- [9] Y.J. Uemura *et al.*, Phys. Rev. B 31 (1985) 546.
- [10] Y.J. Uemura *et al.*, Phys. Rev. Lett. 73 (1994) 3306.
- [11] A. Yaouanc *et al.*, Physica B 326 (2003) 456.