

Incommensurate DDW order

Ivailo Dimov and Chetan Nayak

Department of Physics and Astronomy, University of California at Los Angeles, Los Angeles, California 90095-1547, USA

(Dated: December 23, 2021)

We consider various incommensurate (IC) order parameters for electrons on a square lattice which reduce to $d_{x^2-y^2}$ -density wave (DDW) order when the ordering wavevector $\mathbf{Q} \rightarrow (\pi, \pi)$. We describe the associated charge and current distributions and their experimental signatures. Such orders can arise at the mean-field level in extended Hubbard models. We compare the phase diagrams of these models with experiments in the underdoped cuprates, where (1) DDW order is a possible explanation of the pseudogap, and (2) there are experimental indications of incommensurability. We find various types of IC DDW and discuss their possible relevance to the physics of the cuprates. Our main finding is that IC DDW order is generally accompanied by superconducting order, but the magnitude of the IC wavevector can be small. A comparison with the analogous AF-ICSDW transition is given.

PACS numbers:

I. INTRODUCTION

When a commensurate one-dimensional charge density wave (CDW) is doped, the resulting charges may be viewed as defects in the CDW. If the interactions between them are sufficiently strong compared to their effective kinetic energy, then they will form an ordered lattice (which can be stabilized by a crossover to 3D order if there are many 1D chains coupled together) of defects and the CDW will become incommensurate with the lattice. This can be more energetically favorable than simply doping holes into the rigid band formed in the presence of CDW order at a fixed wavevector. The reason is that, in the latter case, we must pay the single-particle energy gap of the CDW. In a two-dimensional $d_{x^2-y^2}$ -density wave (DDW) state, however, there are nodes in the order parameter, so it is relatively painless for doped holes to simply go to the nodes, which expand into Fermi pockets (in quasi-1D systems, however, this might not be possible, so doping must lead to incommensurability¹). However, this cannot continue indefinitely if the DDW state is stabilized by approximate nesting, since the Fermi surface (FS) would eventually move away from the nesting wavevector. Thus, incommensurate DDW order is a strong possibility, at least over some range of hole dopings. In this paper, we explore this possibility.

Near half-filling, the Hubbard model, the $t - J$ model, and generalizations of these appear to have many phases which are nearby in energy^{1,2}. Thus, small perturbations can strongly influence the competition between them. Consequently, it should not be too surprising that experiments on the cuprate superconductors have also uncovered evidence for a cornucopia of phases, particularly on the underdoped side of the phase diagram, which appear in particular materials and for certain values of the doping level, temperature, magnetic field, etc.³. Depending on the interfacial energies between these phases, one way in which their competition can be resolved is through the formation of stripes⁴ or other inhomogeneous pat-

terns of microscale phase-separation. Neutron scattering and scanning tunneling microscopy experiments point towards this possibility^{5,6}. Furthermore, as the cuprates are doped, their Fermi surfaces evolve away from the commensurate nesting wavevector (π, π) , so we would expect translational symmetry-breaking order parameters to occur at incommensurate wavevectors. Hence, it would seem important for any theory of the pseudogap to incorporate the tendency towards incommensuration, which we take as further impetus to study incommensurate (IC) order parameters related to DDW order.

In this paper we consider various ways in which $d_{x^2-y^2}$ -density wave (DDW) order can go incommensurate. Before turning to this discussion, we review the reasons for expecting DDW order to occur in the pseudogap regime of the cuprates. It has been suggested^{7,8} that competition between DDW order and d -wave superconductivity (DSC) can explain many of the anomalous properties of the pseudogap⁹. The DDW order parameter is given by

$$\langle c_{\mathbf{k}\sigma}^\dagger c_{\mathbf{k}+\mathbf{Q}\sigma} \rangle = i\Phi f(\mathbf{k}) \quad (1)$$

with $f(\mathbf{k}) = \cos(k_x) - \cos(k_y)$ and a *commensurate* (C) ordering wavevector $\mathbf{Q} = (\pi, \pi)$. The particle-hole condensate in (1) breaks translation by one lattice spacing, parity, and time-reversal but is invariant under the combination of any two of the above symmetries. In real space it is represented by currents which alternate from one plaquette to the next.

One motivation for considering DDW order is to explain¹⁰ the abrupt depletion of the superfluid density below the critical $x_c \approx 0.19$ in Bi2212 and similar dopings in other materials^{11,12}. Because the order has a d -wave momentum dependence, its onset would explain ARPES measurements above T_c in the pseudogap¹³. Furthermore, since DDW is a spin-singlet condensate, it would also explain the suppression of the spin susceptibility in NMR measurements and opening of a spin gap in inelastic neutron scattering⁷. Also, the depletion of the c -axis conductivity¹⁴, whose contribution mostly comes from the antinodal regions, would also be naturally ex-

plained by the development of DDW order, which gaps these regions. Direct attempts to measure DDW order through neutron scattering have neither ruled it out¹⁵ nor unambiguously verified its presence, but there are intriguing suggestions that it may be present¹⁶. Thus, it is natural to ask whether DDW order is compatible with incommensurability. (For a discussion of the experimental signatures of DDW order, the reader is referred to the literature^{7,10,13,17,18,19,20,21}. The case of DDW in $La_{2-x}Ba_xCuO_4$ is discussed in²². For numerical evidence of the existence of DDW in other systems, one is referred to²³.)

The plan of our paper is as follows. In section II we develop some preliminary intuition about the energetics of IC density wave order by analyzing the DDW susceptibility of a Fermi liquid (both the nested and non-nested cases). In section III we review some of the theory of commensurate (C) DDW order and show various ways to make it incommensurate. We also suggest the kind of microscopic physics that could lead to C and IC DDW, and in addition discuss possible experimental signatures of IC DDW. Finally, in section IV, we compute the mean-field phase diagrams of an extended Hubbard model. Our main results are that (a) IC DDW develops for a wide range of parameters, but (b) the IC wavevectors can be very small. Their relevance to the cuprates may, at most, be for a rather narrow set of dopings. We also offer a physical explanation of our results, which sheds some light on the nature of C-IC DDW transition in extended Hubbard models. We note that similar incommensurate order has been found in refs.^{24,25}.

II. SUSCEPTIBILITY NEAR HALF-FILLING

The easiest way to see that IC DDW phases could arise in effective models (which, in this paper, will, in turn, emerge from microscopic extended Hubbard models with correlated hopping terms²⁶; see section III C for details) is to consider the bare susceptibility as a function of the incommensurability wavevector \mathbf{q} , where $\mathbf{Q} = (\pi, \pi) + \mathbf{q}$:

$$\chi_0(\mathbf{q}) = \frac{1}{2\pi^2} \int_{\mathbf{k}} (f(\mathbf{k}))^2 \frac{n_F(\epsilon_{\mathbf{k}+\mathbf{Q}} - \mu) - n_F(\epsilon_{\mathbf{k}} - \mu)}{\epsilon_{\mathbf{k}} - \epsilon_{\mathbf{k}+\mathbf{Q}}}. \quad (2)$$

where $f(\mathbf{k})$ is defined after eq. 1. Here, for simplicity, DDW is considered without the presence of any other order. In eq. 2, n_F is the Fermi occupation number, and the energy dispersion contains nearest, t , and next-nearest neighbor, t' , hopping parameters, $\epsilon_{\mathbf{k}} = -2t(\cos k_x + \cos k_y) - 4t' \cos k_x \cos k_y$. The DDW equivalent of the Stoner criterion is satisfied when the right-hand-side of this equation approaches the inverse of the pertinent coupling $1/g$. This observation allows us to interpret the positions of the peaks of $\chi_0(\mathbf{q})$ as the wavevectors at which DDW order is likely to occur as we lower the temperature. A similar analysis was done by Schulz²⁷ for the case of AF and IC SDW order in the Hubbard model

close to half-filling, where perfect nesting at half-filling was assumed. In fact, his results can be recovered by let-

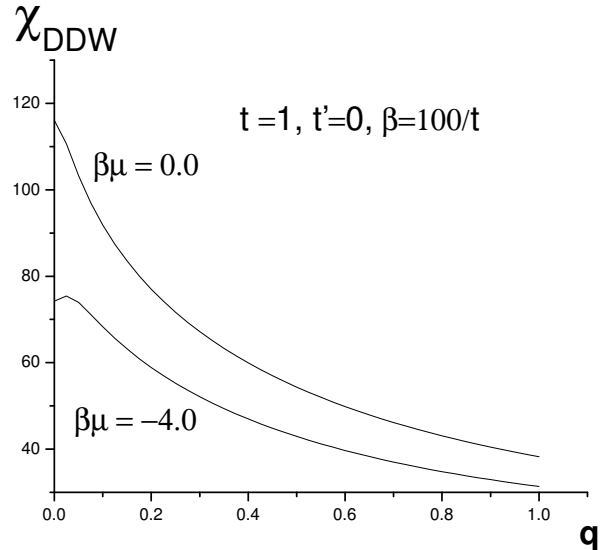


FIG. 1: Susceptibility to DDW order. Away from half-filling, the peak of $\chi_0(\mathbf{q})$ is at nonzero \mathbf{q} . Here, q is measured along the zone diagonal in units of $(\pi/a, \pi/a)$, where a is the lattice spacing.

ting $f(\mathbf{k}) \rightarrow 1$ in (2) if we set $t' = 0$.

The support of $(f(\mathbf{k}))^2$ in the integrand in (2) is at $(0, \pi)$ and symmetry-related antinodal points of the FS since this is where the DDW order parameter is large. However, since these points are also the location of van Hove singularities, the regions around them also dominate the AF susceptibility. Thus, at least in the $t' = 0$ case, one expects that whenever an IC SDW instability occurs, an IC instability for DDW should also occur. Indeed, for both orders, the peak of $\chi_0(\mathbf{q})$ occurs at $\mathbf{q} \neq 0$ for low enough temperatures and sufficiently away from half-filling, e.g. if $|\mu\beta| \geq \mathcal{O}(1)$, as shown in Fig. 1. Note that the same analysis repeated with any other density wave or spin-density wave order would yield an IC instability as long as the dominant channels of the modulation coincide with Fermi surface points which give large contributions to the susceptibility. For instance, a p_x -density wave⁸ with wavevector $\mathbf{Q} = (0, \pi) + \mathbf{q}$ has a peak in χ_0 for $\mathbf{q} \neq 0$ away from half filling at $T \simeq 0$, in the case $t' = 0$.

A natural question to ask is: to what extent does the IC DDW instability mimic the IC SDW one? To answer this, one needs to consider specific models as we do in III C. However, two differences can be anticipated even beforehand. First, the DDW order parameter has nodes, while the AF order parameter does not. Second, in a more realistic model, one must consider competition with DSC, which also could change features of the tran-

sition to IC state. A better understanding of IC DDW order parameter is necessary to better understand the situation away from half-filling.

III. C VS. IC ORDER

A. C Order parameter

Given that the susceptibility (2) points towards an IC instability, the next issue is what IC DDW order would look like. Before addressing this question, let us first summarize some features of the C-case.⁸ In the C case, a general singlet particle-hole condensate can be written as (neglecting the $\mathbf{k} = \mathbf{k}'$ contribution):

$$\langle c_{\mathbf{k}'}^{\alpha\dagger} c_{\alpha,\mathbf{k}} \rangle = i\Phi f(\mathbf{k}) \delta_{\alpha}^{\alpha'} \delta_{\mathbf{k}',\mathbf{k}+\mathbf{Q}}. \quad (3)$$

Here, Φ is the magnitude of the order parameter. The wavevector $2\mathbf{Q}$ is a reciprocal lattice vector. The spin index α included above will be omitted in the future for simplicity unless clarity requires otherwise. In (3), the form factor $f(\mathbf{k})$, which can transform non-trivially under the point group of the 2-D lattice, is related to the angular momentum of the particle-hole condensate. For DDW order, $f(\mathbf{k}) = \cos k_x - \cos k_y$ which corresponds to $l = 2$ and $d_{x^2-y^2}$ symmetry. A p_x -density-wave with $\mathbf{Q} = (0, \pi)$ has $f(\mathbf{k}) = \sin k_x$, which corresponds to $l = 1$. In real space, (3) becomes

$$\langle c_{\mathbf{r}'}^{\dagger} c_{\mathbf{r}} \rangle = \mathcal{V}(\mathbf{r}, \mathbf{r}') \Phi \cos(\mathbf{Q} \cdot \mathbf{r}) \quad (4)$$

where the vertices \mathcal{V} of the orders discussed above are given by

$$\begin{aligned} -i\mathcal{V}^{\text{DDW}}(\mathbf{r}, \mathbf{r}') &= \delta_{\mathbf{r}',\mathbf{r}+\hat{x}\mathbf{a}} + \delta_{\mathbf{r}',\mathbf{r}-\hat{x}\mathbf{a}} - \delta_{\mathbf{r}',\mathbf{r}+\hat{y}\mathbf{a}} - \delta_{\mathbf{r}',\mathbf{r}-\hat{y}\mathbf{a}} \\ -i\mathcal{V}^{p_x\text{DW}}(\mathbf{r}, \mathbf{r}') &= \delta_{\mathbf{r}',\mathbf{r}+\hat{x}\mathbf{a}} - \delta_{\mathbf{r}',\mathbf{r}-\hat{x}\mathbf{a}}. \end{aligned} \quad (5)$$

Note that the factors of i in \mathcal{V}^{DDW} and $\mathcal{V}^{p_x\text{DW}}$ signify that the corresponding phases break time-reversal, e.g. current flows along the bonds. Positive/negative signs in (5) represent current going in/out of the vertex. Translation invariance, by default, is broken by any density wave order since there is a preferred vector \mathbf{Q} , but in the C case, invariance under a *subset* of the lattice group is retained. DDW order, for example, is invariant under translation by linear combinations of even reciprocal lattice vectors along each bond direction. The current along the bonds is given by:

$$\mathbf{j}_{\mathbf{r} \leftrightarrow \mathbf{r}+\hat{s}\mathbf{a}} = it(\langle c_{\mathbf{r}}^{\dagger} c_{\mathbf{r}+\hat{s}\mathbf{a}} \rangle - \langle c_{\mathbf{r}+\hat{s}\mathbf{a}}^{\dagger} c_{\mathbf{r}} \rangle) \quad (6)$$

Here \hat{s} is along either the \hat{x} - or \hat{y} -direction. Because of the equivalence of \mathbf{Q} and $-\mathbf{Q}$ in the C case, the current is simply $\mathbf{j}_{\mathbf{r} \leftrightarrow \mathbf{r}+\hat{s}\mathbf{a}} \sim \cos(\mathbf{Q} \cdot \hat{s}\mathbf{a}) \sim \langle c_{\mathbf{r}}^{\dagger} c_{\mathbf{r}+\hat{s}\mathbf{a}} \rangle$. In the DDW case this results in an alternating plaquette current/checkerboard magnetic field patterns.⁸

B. IC Order Parameter

To obtain an IC version of DDW order, one first notes that DDW is chiral and hence breaks the Ising symmetry which reverses all the clockwise plaquette currents into counter-clockwise and vice versa. Therefore one can construct anti-phase domain walls as in Fig.2. A simple caricature of a bond-oriented domain wall is given in Fig.2a. Its real space representation is

$$\langle c_{\mathbf{r}'}^{\dagger} c_{\mathbf{r}} \rangle = \mathcal{V}^{\text{DDW}}(\mathbf{r}, \mathbf{r}') \Phi \cos \mathbf{Q} \cdot \mathbf{r} \times (2\Theta(r_x) - 1) + \mathcal{V}^{\text{IC}} \quad (7)$$

where $\Theta(x)$ is the step function, so

$$2\Theta(x) - 1 = \sum_n A_{2n+1} \sin\left(\frac{(2n+1)\pi x}{L}\right) \quad (8)$$

with $A_{2n+1} = 4/\pi(2n+1)$. At the midpoint of the domain wall, the currents in the x -direction vanish while the currents in the y -direction are halved. The diagonal domain wall depicted in figure 2b has a similar representation. Note that because of the halving of the y -direction currents at the midpoint of the bond-domain wall in (7), we need to include the term:

$$\mathcal{V}^{\text{IC}} = \mathcal{V}^{\text{R}}(\mathbf{r}, \mathbf{r}') \delta_{r_x,0} + \mathcal{V}^{\text{L}}(\mathbf{r}, \mathbf{r}') \delta_{r_x,1} \quad (9)$$

where the new vertices $\mathcal{V}^{\text{L,R}}$ are given by:

$$\begin{aligned} -i\mathcal{V}^{\text{L}} &= \delta_{\mathbf{r}',\mathbf{r}-\hat{x}\mathbf{a}} - \frac{1}{2}\delta_{\mathbf{r}',\mathbf{r}+\hat{y}\mathbf{a}} - \frac{1}{2}\delta_{\mathbf{r}',\mathbf{r}-\hat{y}\mathbf{a}} \\ -i\mathcal{V}^{\text{R}} &= \delta_{\mathbf{r}',\mathbf{r}+\hat{x}\mathbf{a}} - \frac{1}{2}\delta_{\mathbf{r}',\mathbf{r}+\hat{y}\mathbf{a}} - \frac{1}{2}\delta_{\mathbf{r}',\mathbf{r}-\hat{y}\mathbf{a}}. \end{aligned} \quad (10)$$

Such vertices seem necessary for IC transitions of current density waves. One could imagine situations in which the transition to a disordered state is driven by thermal proliferation of such vertices, similar to earlier analysis of the 6-vertex model²⁸. Although the analysis of such a transition is an interesting topic on its own, we will not pursue it in this paper. We are more interested in the energetics of the IC phase, so a long-wavelength mean-field treatment is sufficient.

To analyze the C-IC transition, one then considers an array of alternating domain walls with average separation L . Then, in the single harmonic approximation one retains only the $n = 0$ term in (8) and identifies $q = \pi/L$ with the incommensurability wavevector. The new short-range vertex contributions (10) are also neglected in the lowest harmonic approximation. The neglect of higher harmonics should not change the transition temperature²⁹ or the value of the critical doping for the onset of IC order since Φ is small and the corrections are of higher order in Φ . An incommensurate instability in a clean system occurs when L becomes finite. (In a disordered system, it occurs when $L < L_d$, where L_d is a characteristic length scale for the disorder.)

Within the single harmonic approximation, an array of anti-phase domain walls with separation

$|\mathbf{q}| = |\mathbf{Q} - (\pi, \pi)| = \pi/L$, looks simpler in momentum space:

$$\langle c_{\mathbf{k}'}^\dagger c_{\mathbf{k}} \rangle = i \frac{\Phi}{2} f(\mathbf{k}) (\delta_{\mathbf{k}', \mathbf{k}+\mathbf{Q}} + \delta_{\mathbf{k}', \mathbf{k}-\mathbf{Q}}). \quad (11)$$

Note that in the limit $|\mathbf{q}| \rightarrow 0$, the above reduces to (3). One could have guessed the result (11) by writing $2\delta_{\mathbf{k}', \mathbf{k}+\mathbf{Q}} = \delta_{\mathbf{k}', \mathbf{k}+\mathbf{Q}} + \delta_{\mathbf{k}', \mathbf{k}-\mathbf{Q}}$ in the commensurate case, and then let \mathbf{Q} go incommensurate. This suggests other ways to get IC order. In particular the oddness of DDW order with respect to rotations by $\pi/2$ and transpositions about, say, the (π, π) direction lead to the following example of a DDW *checkerboard pattern*:

$$\langle c_{\mathbf{k}'}^\dagger c_{\mathbf{k}} \rangle = \frac{i}{4} \Phi f(\mathbf{k}) (\delta_{\mathbf{k}', \mathbf{k}+\mathbf{Q}} + \delta_{\mathbf{k}', \mathbf{k}-\mathbf{Q}}) - \{\mathbf{Q} \rightarrow \mathcal{O}(\mathbf{Q})\} \quad (12)$$

where the operation $\mathcal{O}(\mathbf{Q})$ can be either a transposition, or a rotation by $\pi/2$. The checkerboard pattern in (12) corresponds to simply superimposing two domain walls rotated by $\pi/2$ with respect to each other.

In a similar spirit, one could also investigate the possibility of *non-topological* domain walls³⁰, e.g. IC domains as the above, superimposed with an uniform order, so the overall order parameter does not change chirality. However, as we will see in Sec. IV, much of the physics of the C-IC transition will already be transparent from the simpler choices (11) and (12) of order parameter.

Finally, note that within the single harmonic approximation, (11) and (12) are current-conserving only to lowest order in q . For the purpose of clarifying the energetics of the IC order close to the C-IC transition, or in the cases where the magnitude of the incommensurability is small, this lowest order approximation is good enough. Our numerical results, Sec. IV, *a posteriori* show that we are in such regime.

C. Microscopic Models

We will consider the above order parameters in the context of the following Hamiltonian²⁶:

$$\begin{aligned} \mathcal{H} = & -t_{ij} \sum_{\langle i,j \rangle} (c_{i\sigma}^\dagger c_{j\sigma} + \text{h.c.}) - t_c \sum_{\substack{\langle i,j \rangle, \langle i',j \rangle \\ i \neq i'}} c_{i\sigma}^\dagger c_{j\sigma} c_{j\sigma}^\dagger c_{i'\sigma} \\ & + U \sum_i n_{i\uparrow} n_{i\downarrow} + V \sum_{\langle i,j \rangle} n_i n_j \end{aligned} \quad (13)$$

In this formula, t_{ij} is hopping with $t_{ij} = t$ for nearest neighbors, $t_{ij} = t'$ for next nearest neighbors and $t_{ij} = 0$ otherwise. t_c is a correlated hopping term which simultaneously hops an electron from site j to site i and hops an electron from i' into the vacated site j . The on-site and nearest-neighbor repulsions are, respectively, U and V . The indices i, j signify lattice sites and σ the spin.

We will consider this Hamiltonian at the mean-field level. At this level, the energetics of DDW order is the

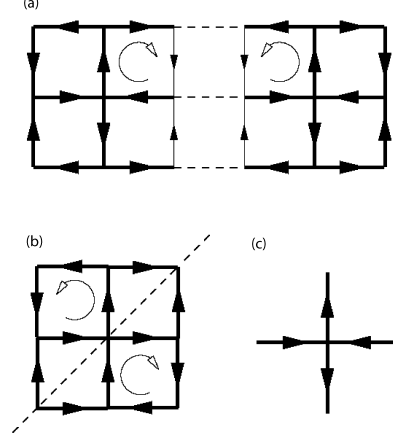


FIG. 2: (a) Bond-oriented DDW domain wall. (b) Diagonal DDW domain wall. (c) Current vertex of DDW. There is no current on dashed lines. Arrowless currents are regions of increased kinetic energy. Thick arrows represent one (arbitrary) unit of current. Thin lines represent half a unit of current.

same as for a ‘BCS-reduced’ Hamiltonian for DDW order of the form:

$$\mathcal{H}_{DDW} = -g_{DDW} \int_{\mathbf{k}, \mathbf{k}'} f(\mathbf{k}) f(\mathbf{k}') c_{\mathbf{k}+\mathbf{Q}\sigma}^\dagger c_{\mathbf{k}\sigma} c_{\mathbf{k}'\sigma'}^\dagger c_{\mathbf{k}'+\mathbf{Q}\sigma'}, \quad (14)$$

with $g_{DDW} = 24t_c + 8V$. A similar reduced Hamiltonian for *d*-wave superconductivity has $g_{DSC} = 12t_c - 8V$. Note that the processes responsible for both DSC and DDW are essentially kinetic.

A Hamiltonian of the form (13) has one important virtue: it has a *d*-wave superconducting ground state over a range of dopings (and an antiferromagnetic ground state at half-filling). Since this is the *sine qua non* for any description of the cuprates, we believe that this is a good starting point. One may object that correlated hopping terms have to be put in by hand in a microscopic Hamiltonian. However, they naturally arise even from the one-band Hubbard model away from half-filling, where their contribution can be computed in t/U perturbation theory:

$$t_c \simeq x \frac{t^3}{U^2} \quad (15)$$

At dopings $x = 0.1$, for $t/U \sim 0.2$, we would have $g_{DDW} = 2g_{DSC} \sim 0.1t = J/2$. Thus, not far away from half-filling, correlated hopping terms are certainly not negligible.

D. Mean Field Theory

Let us generalize the mean field description of C DDW to the IC case. The path we will take is similar to that in Sec. IIIB, where we wrote down the *commensurate* order parameter without making use of the $\mathbf{Q} \rightarrow -\mathbf{Q}$ symmetry, and as a result the generalization to incommensurate \mathbf{Q} was straightforward. We thus obtain a functional $\mathcal{F}(\mu, \Delta_i, \mathbf{q})$, equation (20), whose minimization yields self-consistently both the order parameters Δ_i and the deviation from commensurability $\mathbf{q} = \mathbf{Q} - (\pi, \pi)$. The only subtlety, as we discuss at the end of this section, is that although \mathcal{F} reduces to the mean-field free energy in the C phase, in the IC phase it is *not* the free energy even within the single harmonic approximation. Instead, minimization of \mathcal{F} is equivalent to a variational search of the ground state.

Our derivations generalize the treatment of Nayak and Pivovarov²⁶ of competition of C DDW with DSC and possibly AF. The C DDW mean field Hamiltonian we start with is:

$$\mathcal{H}_{\text{DDW}} = \int_{\mathbf{k} \in \text{RBZ}} \left\{ i \frac{W_{\mathbf{k}}}{2} c_{\mathbf{k}\sigma}^\dagger c_{\mathbf{k}+\mathbf{Q}\sigma} + \mathbf{Q} \rightarrow -\mathbf{Q} \right\} + \{\text{h.c.}\} \quad (16)$$

where $W_{\mathbf{k}} = \frac{W_0}{2} f(\mathbf{k})$.

Note that in (16) the $\mathbf{Q} \rightarrow -\mathbf{Q}$ symmetry for *incommensurate* \mathbf{Q} is not equivalent to the Hermiticity of the Hamiltonian due to the \mathbf{k} -dependence of $W_{\mathbf{k}}$ (e.g. $\langle c_{\mathbf{k}}^\dagger c_{\mathbf{k}+\mathbf{Q}} \rangle = iW_{\mathbf{k}} \neq \langle c_{\mathbf{k}}^\dagger c_{\mathbf{k}-\mathbf{Q}} \rangle^* = -iW_{\mathbf{k}-\mathbf{Q}}$ for IC \mathbf{Q}). This is unlike the case of AF order, where the interaction is simply

$$\mathcal{H}_{\text{AF}} = \int_{\mathbf{k} \in \text{RBZ}} \phi (c_{\mathbf{k}\uparrow}^\dagger c_{\mathbf{k}+\mathbf{Q}\uparrow} - c_{\mathbf{k}\downarrow}^\dagger c_{\mathbf{k}+\mathbf{Q}\downarrow}) + \text{h.c.} \quad (17)$$

and we have $\langle c_{\mathbf{k}\sigma}^\dagger \tau_3^{\sigma\sigma'} c_{\mathbf{k}+\mathbf{Q}\sigma'} \rangle = \phi = \langle c_{\mathbf{k}\sigma}^\dagger \tau_3^{\sigma\sigma'} c_{\mathbf{k}-\mathbf{Q}\sigma'} \rangle^*$.

In order to check with earlier results on the C-IC transition of AF order in the *weak coupling* Hubbard model²⁷ (see Sec. II), we will also include a term like (17) in our full reduced Hamiltonian. Of course, in the strong coupling, $U > t$, limit, one is not justified in treating AF as a Fermi surface instability, especially close to half filling.

A $t-J$ description is more appropriate in this case. However, as mentioned in Sec. IIIC, both DDW and DSC are essentially kinetic in origin within the extended Hubbard model, so even in the strong onsite repulsion limit, there is a good justification to use mean field theory to describe their competition away from half filling.

In the C case, the standard DSC term in our reduced Hamiltonian is:

$$\mathcal{H}_{\text{DSC}} = \int_{\mathbf{k} \in \text{RBZ}} \Delta_k c_{\mathbf{k}\uparrow}^\dagger c_{-\mathbf{k}\downarrow}^\dagger + \text{h.c.} \quad (18)$$

where $\Delta_{\mathbf{k}} = \frac{\Delta_0}{2} f(\mathbf{k})$. Using a Nambu basis $\Psi_{\mathbf{k}} \equiv (c_{\mathbf{k}\uparrow}^\dagger, c_{\mathbf{k}+\mathbf{Q}\uparrow}^\dagger, c_{-\mathbf{k}\downarrow}, c_{-\mathbf{k}-\mathbf{Q}\downarrow})$, the full Hamiltonian $\mathcal{H} = \mathcal{H}_{\text{kin}} + \mathcal{H}_{\text{AF}} + \mathcal{H}_{\text{DDW}} + \mathcal{H}_{\text{DSC}}$ can be rewritten as $\mathcal{H} - \mu N = \int_{\text{RBZ}} \Psi_{\mathbf{k}}^\dagger \cdot \mathbf{A} \cdot \Psi_{\mathbf{k}}$ where:

$$\mathbf{A} \equiv \begin{pmatrix} \epsilon_{\mathbf{k}} - \mu & iG_{\mathbf{k}} + \phi & \Delta_{\mathbf{k}} & 0 \\ c.c. & \epsilon_{\mathbf{k}+\mathbf{Q}} - \mu & 0 & \Delta_{-\mathbf{k}-\mathbf{Q}} \\ c.c. & 0 & -\epsilon_{\mathbf{k}} + \mu & -iG_{-\mathbf{k}-\mathbf{Q}} + \phi \\ 0 & c.c. & c.c. & -\epsilon_{\mathbf{k}+\mathbf{Q}} + \mu \end{pmatrix} \quad (19)$$

with $G_{\mathbf{k}} = (W_{\mathbf{k}} - W_{\mathbf{k}+\mathbf{Q}})/2$. The action derived from the above Hamiltonian yields, upon integrating the Fermions out, the free energy in the ordered state:

$$\mathcal{F}_{\mathbf{q}} = \mathcal{F}_{\text{quad}} + \sum_{s=\pm 1} \int_{\mathbf{k} \in \text{RBZ}} \left\{ (s\epsilon_{\mathbf{k}} - \mu) - \frac{2}{\beta} \ln 2 \cosh\left(\frac{\beta E_s}{2}\right) \right\} \quad (20)$$

with $\pm E_s$, $s = \pm 1$ the energy eigenvalues of (19), and

$$\mathcal{F}_{\text{quad}} = \frac{\phi^2}{g_{\text{SDW}}} + \frac{W_0^2}{g_{\text{DDW}}} + \frac{\Delta_0^2}{g_{\text{DSC}}}. \quad (21)$$

If we assume $\mathbf{Q} \rightarrow -\mathbf{Q}$ symmetry, E_s would be given by:

$$E_s(\mathbf{k}) = \sqrt{\Delta_{\mathbf{k}}^2 + [\mu - \epsilon_+(\mathbf{k}) + s\sqrt{\bar{\Phi}_{\mathbf{k}}^2 + \epsilon_-^2(\mathbf{k})}]^2} \quad (22)$$

where $\epsilon_{\pm}(\mathbf{k}) \equiv (\epsilon_{\mathbf{k}} \pm \epsilon_{\mathbf{k}+\mathbf{Q}})/2$ and $\bar{\Phi}_{\mathbf{k}}^2 \equiv W_{\mathbf{k}}^2 + \phi^2$.

However, in the IC case, $\mathbf{Q} \rightarrow -\mathbf{Q}$ need not hold, in which case the above would generalize to:

$$E_s(\mathbf{k}) = \{f_+^2(\mathbf{k})\Delta_{\text{DSC}}^2 + (\mu - \epsilon_+(\mathbf{k}))^2 + \bar{\Phi}_{\mathbf{k}}^2 + \epsilon_-^2(\mathbf{k}) + s\sqrt{4(\mu - \epsilon_+(\mathbf{k}))^2(\bar{\Phi}_{\mathbf{k}}^2 + \epsilon_-^2(\mathbf{k})) + D_{\mathbf{q}}(\Delta_{\text{DSC}}^2, \bar{\Phi}_{\mathbf{k}}^2, \epsilon_{\mathbf{k}}, \mu)}\}^{\frac{1}{2}}, \quad (23)$$

$$D_{\mathbf{q}} \equiv [4\tilde{f}_{\mathbf{k}}\bar{\Phi}_{\mathbf{k}}^2 + f_-^2(\mathbf{k})\{(\epsilon_{\mathbf{k}} - \mu)^2 - (\epsilon_{\mathbf{k}+\mathbf{Q}} - \mu)^2\}]\Delta_{\text{DSC}}^2 + f_-^4(\mathbf{k})\Delta_{\text{DSC}}^4.$$

The effect of a nonzero incommensurability \mathbf{q} can be seen not only in the appearance of the terms $f_{\pm}^2(\mathbf{k}) \equiv (f^2(\mathbf{k}) \pm f^2(\mathbf{k} + \mathbf{Q}))/2$ and $\tilde{f}_{\mathbf{k}} \equiv (f(\mathbf{k}) + f(\mathbf{k} + \mathbf{Q}))/2$, but also in the DSC-and doping-dependent function $D_{\mathbf{q}}$.

Our final step before letting \mathbf{Q} be incommensurate is

to pass the integration in (20) from RBZ to BZ:

$$\mathcal{F} - \mathcal{F}_{\text{quad}} = \int_{\text{RBZ}} f_s(\mu, \beta, \Delta_i) = \frac{1}{2} \int_{\text{BZ}} f_s(\mu, \beta, \Delta_i) \quad (24)$$

Once we convert the RBZ integrals to BZ integrals as in (24), we numerically minimize (see Sec. IV) the resulting ‘free energy’ with respect to both the order parameters Δ_i and the deviation from commensurability q .

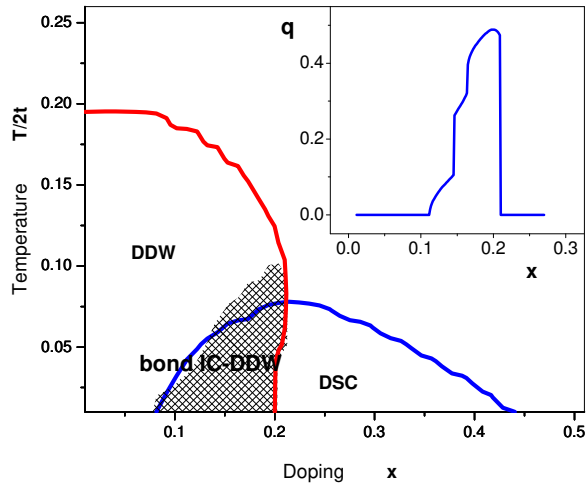


FIG. 3: Phase diagram of DDW competing with DSC. Both $g_{\text{DDW}} = 0.05\text{eV}$ and $g_{\text{DSC}} = 0.03\text{eV}$ are large (compare to Figs. 5 and 6) $t = 0.5\text{eV}$. The next nearest neighbor hopping, $t' = -0.05\text{eV}$, is small compared to typical values fitted to ARPES³¹, but IC order was nevertheless robust away from half-filling. Inset: IC wavevector q at $T = 0.01\text{eV}$ as a function of doping. Wavevectors are in units of π/a , where a is the lattice spacing.

It must be emphasized that the expression to be minimized in Sec. IV is *not* the true free energy of the system if \mathbf{Q} is incommensurate. One way to see this is to note that the eigenvalues (23) are not invariant under $\mathbf{k} \rightarrow -\mathbf{k}$ if $\mathbf{Q} \neq (\pi, \pi)$ and therefore they cannot be interpreted as band energies. In a C-IC transition, the excitations split into a generally uncountably many bands even within the single harmonic approximation²⁹. Therefore, the problem of finding the mean-field free energy is notoriously difficult even in the single harmonic limit. The calculation we are doing, on the other hand, is essentially a mean-field variational search for the ground state, and not for the excitations. A similar calculation was done by Schulz²⁷ for the case of the C-IC transition of the weak-coupling Hubbard model close to half-filling. By continuity of the true free energy²⁹, one expects that the resulting variational estimates for $q = |\mathbf{q}|$ would be accurate only close to the C-IC transition, where q is small.

IV. NUMERICAL RESULTS

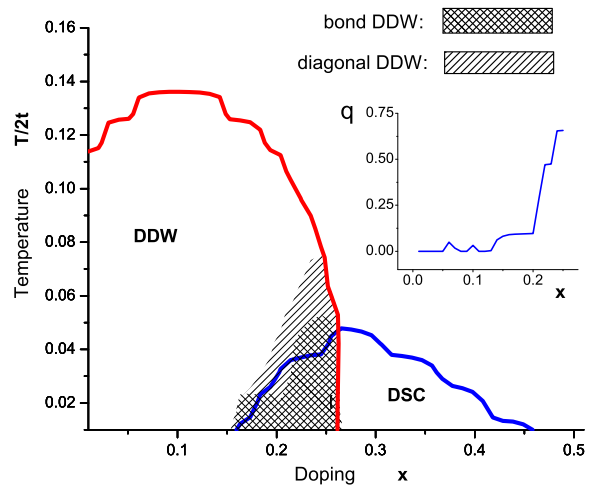


FIG. 4: Again $g_{\text{DDW}} = 0.04\text{eV}$, $g_{\text{DSC}} = 0.02\text{eV}$ are ‘large’ (note temperature scale) similar to Fig. 3, with $t = 0.5\text{eV}$. However this time we take a more realistic $t' = -0.12\text{eV}$. Again IC order is robust at dopings relevant for the pseudogap. Inset: IC wavevector q at $T = 0.01\text{eV}$ as a function of doping. See Fig. 10 for a more detailed view of q (and also Fig. 9 for the case of $t' = -0.06\text{eV}$).

To obtain the phase diagrams for the models in (20), for various fixed dopings x and temperatures T , we minimize $\mathcal{F} = \mathcal{F}(\Delta_i, q)$ with respect to both the order parameters Δ_i (as was done previously in the C-case²⁶) and the IC wavevector magnitude q . Each choice of IC order parameter (e.g. bond or diagonal) corresponds to a separate minimization procedure. To distinguish which IC order dominates at a particular point in (x, T) space, we compared the free energies of the orders considered, and chose the IC phase of minimal energy. Note that, as given in (20), the free energy is a function of μ , so to obtain the dependence on the doping x , we first perform a Legendre transformation and minimize instead $\mathcal{F}(x) = \mathcal{F}(\mu(x)) + \mu(x)N$ where the chemical potential is obtained from $1 - x = \partial f / \partial \mu$ with $f = \mathcal{F}/N_0$.

Our approach is slightly different than that previously used in the C-case²⁶. There, the competition between AF, DDW and DSC was analyzed, and some sensitivity on the details of the microscopics was found. Phase diagrams resembling that of the cuprates were obtained. The general trend was that any phase diagram which included d -wave superconductivity also had DDW order competing with it. By changing the bare coupling constants, rather different phase diagrams could be obtained and these generally did not have superconductivity.

In our treatment here, we do not consider the competition with AF order, which is not a Fermi surface instability anyway in the context of the cuprate superconductivity.

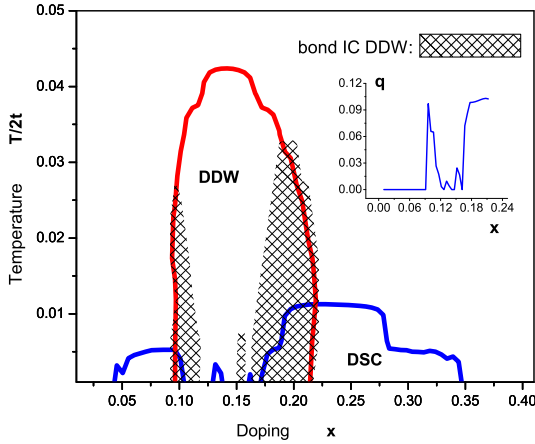


FIG. 5: $t = 0.5\text{eV}$, $g_{\text{DDW}} = 0.025\text{eV}$, $g_{\text{DSC}} = 0.01\text{eV}$. The next nearest neighbor hopping, $t' = -0.12\text{eV}$. Note the appearance of DSC proximate to ‘magic’ dopings. Inset: the IC wavevector $q(x)$ at $T = 0.001\text{eV}$. See Fig.11 for comparison between $q(x)$ and $\mu(x)$.

tors. In (20), we still include AF, but only in order to check with previous results²⁷ of IC AF order away from half filling in the *weak coupling* $g_{\text{AF}} < t$ limit. On the other hand, the AF order appearing at half filling in the cuprates is a strong coupling phenomenon. A reduced Hamiltonian (17) is the wrong starting point at half filling in the limit $U > t$.

Therefore, we only consider competition between DDW and DSC and look for IC order in this case. All the phase diagrams constructed this way are robust in the sense that DDW and DSC are found to coexist at mean field level for almost all reasonable values of the coupling constants.

Sample phase diagrams are shown in Figs. 3-6. In all of them, IC order is present at dopings $0.15 \lesssim x \lesssim 0.2$ where DDW and DSC compete. In the first two of these figures, we vary t' at relatively high g_{DDW} and g_{DSC} , while in the last two we explore the phase diagram for more realistic DDW and DSC couplings (compare the temperature scales to those in the cuprates). Note the complexity of Figs. 5, Figs. 6 compared to Figs. 3, Figs. 4. At realistic couplings, the IC wavevector profile is complicated, and furthermore DSC order appears in more than one doping region within the DDW dome. In fact, the appearance of incommensurability seems correlated with the appearance of DSC. A more systematic analysis to be discussed below reveals that generally the types of C-IC transitions that were produced in our phase diagrams fall into two categories: (a) those which correspond to motion of the bare Fermi surface away from commensurate nesting (shaded regions); (b) those which appear near certain ‘magic’ filling fractions. Case (a) is similar to the famil-

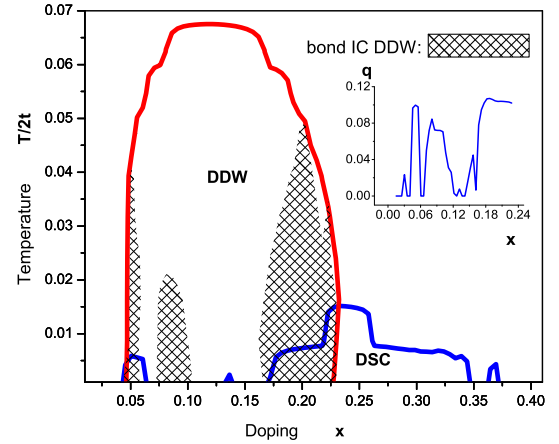


FIG. 6: Same as Fig. 5 except $g_{\text{DDW}} = 0.03\text{eV}$. There is a distinct IC response (inset) at $x = 1/8$ and $x = 1/16$. See Fig. 12 for comparison between $\mu(x)$ and $q(x)$.

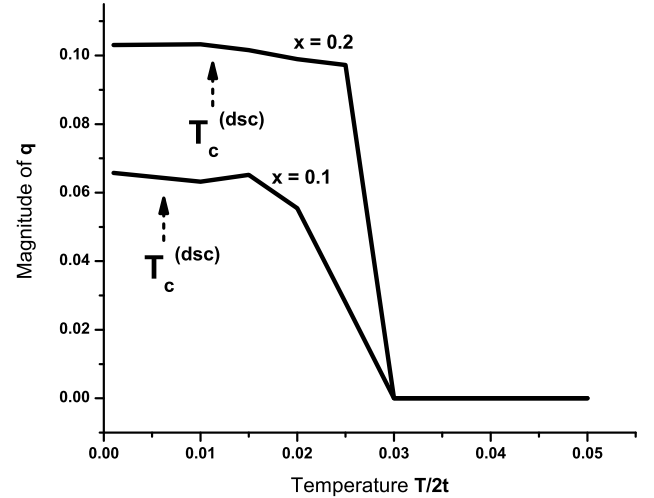


FIG. 7: Dependence of incommensurability on temperature for regions in the phase diagram in Fig. 5 where DDW and DSC compete. Note that nonzero q is found above as well as below the DSC critical temperature.

iar C-IC mechanism discussed by Schulz²⁷, while case (b) appears to be a consequence of negative effective stiffness at special fractions, the exact nature of which at present is not clear. In both cases q is independent of the onset of DSC, Fig. 7, but because incommensurability relieves the DDW-DSC competition, the onset of DSC correlates to the presence of IC DDW.

Let us first discuss (a). It is well known²⁷ that in the weak-coupling Hubbard model at $t' = 0$, the AF insta-

bility at half-filling is driven IC for any non-zero doping (see Sec. 2). The source of the C-IC transition can be traced to the approximate nesting of the bare Fermi surface (FS) at IC wavevectors away from half-filling. Close to half-filling, this picture would produce a linear deviation from commensurability, $q \sim |\mu - \mu_c| \sim x - x_c$, Fig. 8. The incommensurability (deviation from (π, π)) is horizontal or vertical, not diagonal, as we would expect because the bare susceptibility is more divergent due to a greater overlap between nested portions of the Fermi surface²⁷.

A similar scenario happens in the case of DDW order. However, two notable differences from the AF case are present. First, DDW is less sensitive to t'/t , since it is driven mainly by antinodal regions of high density of states (d.o.s.). Therefore, while there is no AF instability without nesting (at half-filling AF Fermi surface instability is only possible if $g_{AF} \gtrsim \mathcal{O}(t')$), DDW is still possible in this regime. This suggests that whenever the antinodal regions of the bare FS evolve away from the anti-nodal regions (which happen to also be regions with a high density of states as a result of the presence of van Hove singularities), a C-IC transition is likely to occur.

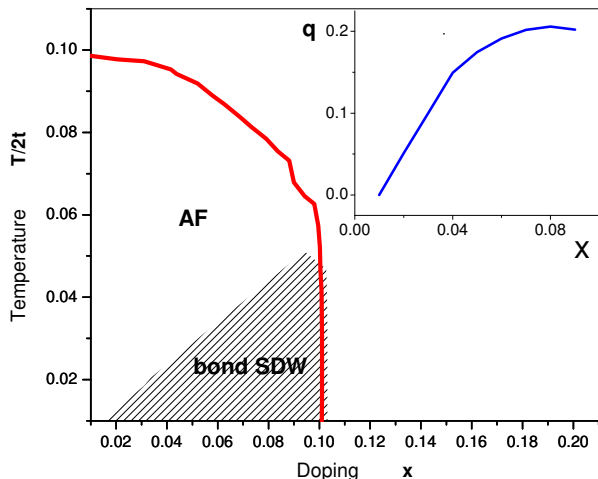


FIG. 8: AF at perfect nesting, $t' = 0$. The results of Schulz²⁷ were recovered. Here, we used $g_{AF} = 2U = 0.05\text{eV}$ with $t = 0.5\text{eV}$. Bond-oriented IC order was found to be energetically favorable, as a direct computation²⁷ in the weak repulsion regime would yield. *Inset*: As expected, the IC wavevector at $T = 0$ is linear in x .

The second difference from the AF case is that DDW has nodes. This implies that the chemical potential in the ordered state need not be higher than the maximal DDW gap. As a result, DDW order can stay commensurate for wider ranges of doping. This is indeed what we find. For example, for all $t'/t \simeq 0$, we obtain $x_{c-ic}^{AF} < x_{c-ic}^{DDW}$ near zero temperature. In general, we find that the doping values x_{c-ic} for which the above type of C-IC DDW is possi-

ble are unrealistically high in the context of the cuprates, if one considers more realistic bare FS, $|t'/t| \gtrsim 0.25$. Furthermore, in the IC DDW case, there need not be a simple relation $q \sim |\mu - \mu_c| \sim x - x_c$ between the doping and deviation from commensurability.

Let us now discuss the C-IC transitions that are present in our phase diagrams proximate to ‘magic’ filling fractions $x \sim 1/2^n$. Although our understanding as to why they arise is incomplete, we would like to point out several interesting features about our results. First, to our knowledge, there is nothing special about the bare FS close to these filling fractions, likewise for the FS of the commensurate ordered state. The C-IC transition is not driven by nesting, since upon variation of t' we see similar signatures proximate to the ‘magic’ dopings. Second, the magnitude of the IC wavevector is generally small (corresponding to periodicity of more than 30 lattice spacings) and shows no clear dependance on n , Figs. 9 -12. Third, we checked that similar behavior is present deep into the AF ordered state³⁶, Fig. 13. Unlike the DDW case, however, the IC lattice spacing in the AF case depends on n : q follows an increasing staircase pattern at ‘magic’ dopings. Note that our results for AF order seem to contradict Schulz’s results²⁷ which predict a linear dependence of $q(x)$.

The naive contradiction is easily resolved by realizing that Schulz’s computation²⁷ of $q(x)$ relies on the Stoner criterion, which is strictly valid at T_c . Indeed, while deep into the ordered state the IC wavevector is stepwise increasing at ‘magic’ fractions, at higher temperatures we regain the linearity of $q(x - x_c)$, Fig. 14. Moreover, the fact that both the bare and the gapped FS in the C case are generally not nested at the ‘magic’ fractions suggests that the transition is not driven by a divergent susceptibility, but is first order. Indeed, at low temperatures, the chemical potential near the special dopings is non-monotonic for both the AF and the DDW+DSC diagrams. Similar behavior of $\mu(x)$ was found by Nayak and Pivovarov in the context of C DDW competing with DSC²⁶.

A simple view of the energetics is given by the following Landau-Ginsburg free energy of two nodeless competing orders (the generalization to order parameters with nodes is straightforward):

$$\mathcal{F} = \int d^2x \left(\rho_\psi |\nabla \psi|^2 + \rho_\chi (\nabla \chi)^2 + K (\nabla^2 \chi)^2 - m_\psi |\psi|^2 - m_\chi \chi^2 + \lambda |\psi|^2 \chi^2 \right) \quad (25)$$

In this free energy, χ plays the role of the DDW order parameter and ψ the role of superconductivity. When ρ_χ becomes negative, χ orders at non-zero wavevector $q = \sqrt{-\rho_\chi/K}$. This occurs at the dopings indicated in Figures 5 and 6. When ψ orders, this further favors incommensurability if $\lambda > 0$ since the competition between the two orders is partially alleviated. This alleviation is a possible explanation of why the onset of DSC at low T is correlated to the presence of IC-DDW.

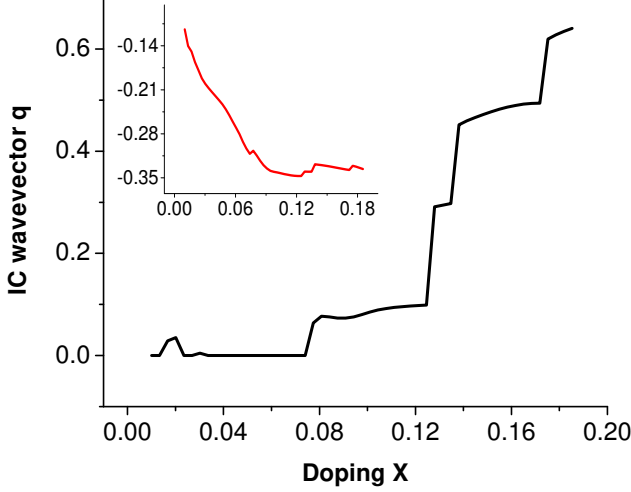


FIG. 9: Comparison between $q(x)$ and $\mu(x)$ (inset) at $T = 0.01$ for $g_{\text{DDW}} = 0.04\text{eV}$, $g_{\text{DSC}} = 0.02\text{eV}$. Note that $|t'| = 0.06\text{eV}$ which is smaller than the value taken in Fig. 4.

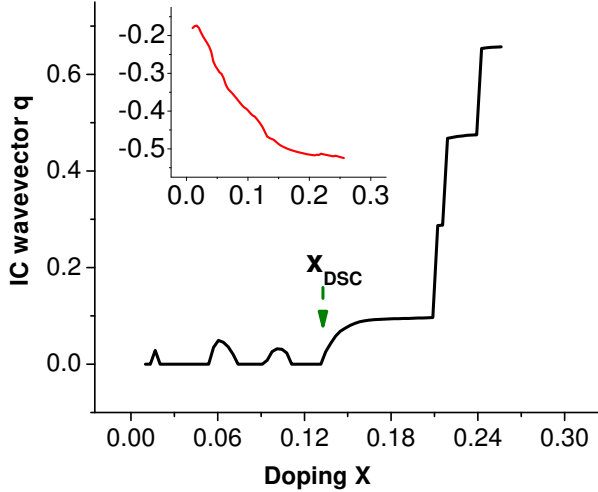


FIG. 10: Same as Fig. 9 except this time $t' = -0.12\text{eV}$ as in Fig. 4.

The same phenomenon can be viewed from the opposite perspective: when DDW order becomes incommensurate, there are regions in which it is suppressed (as in the domain walls of Fig. 2). Superconductivity can occur more easily there. Hence, incommensurability alleviates the competition between DSC and DDW order at the mean-field level, thereby enhancing superconductivity. Of course, IC order appears to suppress superconductivity in the cuprates, but this could be due to effects beyond a simple mean-field theory.

When the superconducting order parameter becomes

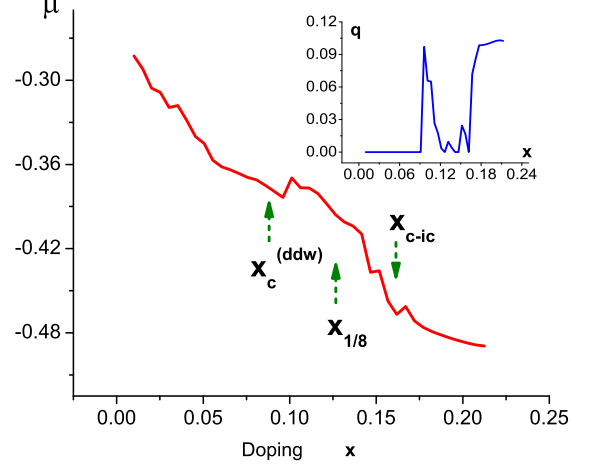


FIG. 11: Comparison of $\mu(x)$ and $q(x)$ (inset) at $T = 0.001\text{eV}$ corresponding to the parameters in Fig. 5. Although here the IC response is not at ‘magic’ fractions, note that in Fig. 5 there is DSC both at $x = 1/8$ and $x = 1/16$.

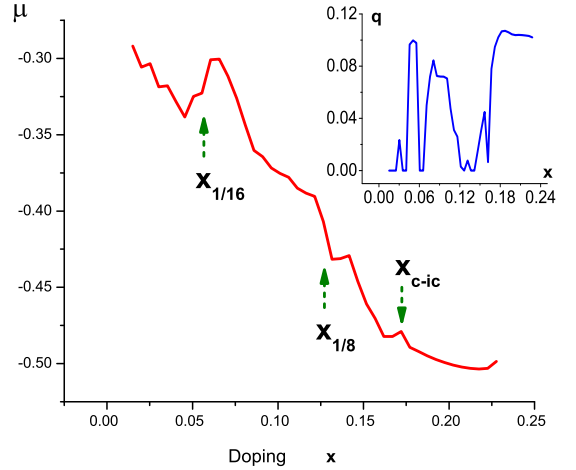


FIG. 12: Same as Fig. 11 (and at the same temperature) except this time there is a clear C-IC transition at ‘magic’ fractions (inset). At the same time $\mu(x)$ is non-monotonic at these dopings. The coupling constants $g_{\text{DDW}} = 0.03\text{eV}$ and $g_{\text{DSC}} = 0.01\text{eV}$ are the same as in Fig. 6.

strong enough, it may become energetically favorable for phase separation to occur. We can guess when this occurs from the usual Maxwell construction whenever the mean field chemical potential $\mu(x)$ does not vary monotonically. This appears to occur at a few isolated ‘magic’ doping values. However, in a real system, proximity to a second order critical point³², Coulomb repulsion³³, or disorder

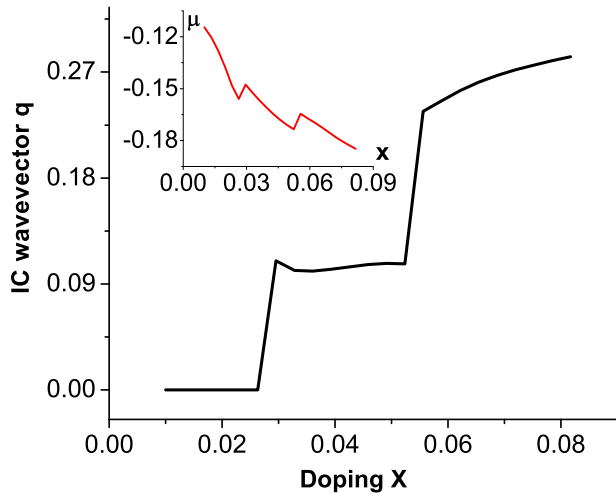


FIG. 13: Example of the low temperature ($T = 0.001$ eV) staircase IC spectrum of AF around ‘magic’ filling fractions. The parameters we have taken here are $g_{AF} = -t' = 0.04$ eV, $t = 0.5$ eV. Inset: $\mu(x)$ is non-monotonic at both jumps of $q(x)$, but is smoothly decreasing whenever q is pinned.

could drive the system in a state of mesoscopic phase separation. Moreover, the lattice pins any IC density wave order, so once the system is IC in order to minimize the free energy, the deviation from commensurability q would be pinned at a finite value. Finally, it is important to remember that disorder could have important effects. It would not only disorder the array of domain walls, but could lead to droplets of one phase in regions of another.

We stress that while the general trend towards IC order may be clear, many of the quantitative aspects are not clear, in particular the precise copings at which DDW order becomes incommensurate. It is not clear to us why such C-IC transitions happen near ‘magic’ filling fractions. The fact that similar behavior occurs in the case of AF order suggests that the tendency of phase separation at ‘magic’ filling fractions is a general trend for a variety of density wave order. Because the AF only case was explored upon taking the $g_{DDW,DSC} \rightarrow 0$ limit in the full free energy, it is not clear yet whether the tendency of phase separation at ‘magic’ filling fractions is purely a feature of density waves competing with other order parameters, or of the lattice. It might be worth reconsidering the AF case in the presence of other order parameters (such as DDW, DSC). What makes our results surprising is that unlike in the frustrated phase separation picture for stripe formation, there is no Coulomb repulsion present. Hence, there is no obvious connection between phase separation and incommensurability. (Please note that while IC DDW order can induce charge density wave order at twice the wavevector, we have not included this effect, which we expect to be small, in our calculation.) Therefore, while Coulomb repulsion may

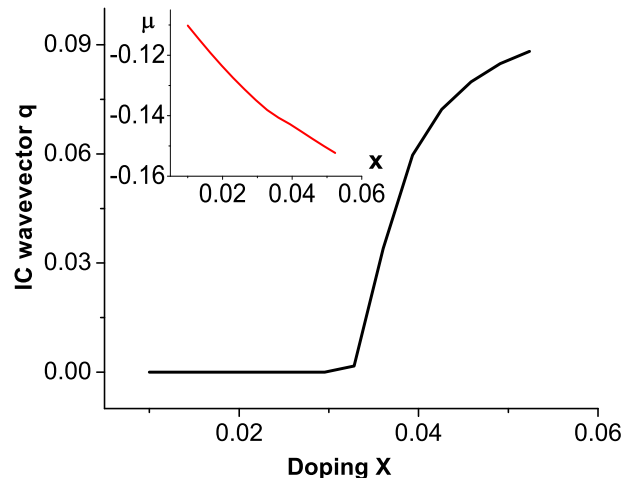


FIG. 14: At higher temperatures $q(x)$ regains its linearity around x_c as predicted by Schulz²⁷. Here $T = 0.035$ eV and all other parameters are as in Fig. 13. Inset: $\mu(x)$ is monotonic throughout, suggesting that at higher temperatures, the C-IC transition is driven purely by IC nesting of the FS away from half-filling.

play a role in determining the CDW spacing at $x = 1/8$ in $LaCuO_2$, in our calculation, the phase separation at ‘magic’ fractions can only arise as interplay between the lattice, competing order physics and energetics. What exactly is the combination of the three deserves some future research³⁷.

V. EXPERIMENTAL SIGNATURES

According to the discussion following (25) it seems likely that within the DSC state a competing DDW order parameter is IC as it develops. Hence, we briefly describe the experimental signatures that would distinguish between C and IC DDW order. Originally, C DDW was also named ‘hidden order’ in the context of the pseudogap, because most of the experimental signatures associated with it are indirect. The magnetic field, created by the alternating currents around neighboring plaquettes, is too small to be detected by neutron scattering ($B \simeq 1 - 30$ G for $\Delta_{DDW} \sim 30$ meV). At the same time, because of the symmetry of the C DDW magnetic field, there is no signature in NMR. The charge of the C DDW state is uniform so STM would not show signatures, unless they are associated with interference of nodal quasiparticles due to scattering off impurities. It has been argued recently³⁴ that such interference disperses weakly enough to account for the pseudogap d.o.s. incommensurate modulations observed by STM. For a further discussion of the signatures of C DDW, the reader is referred to the literature^{7,10,13,17,18,19,20,21}.

An IC DDW is more easily detectable directly. The local electronic density of states would be modulated due to the IC order parameter, and hence could be observable by STM. Secondly, the IC modulations of the staggered currents would produce NMR line splitting of both the Cu and O atoms when the applied magnetic fields are *perpendicular* to the a-b planes. This is in sharp contrast with IC SDW, where there is an NMR line-splitting due to spatially modulated local magnetization, which is directed *along* the a-b plane.

Let us estimate the modulated magnetic field strength arising from IC DDW (the reader is referred to³⁵ where similar considerations are applied to the case of orbital antiferromagnetism proposed to exist in URu_2Si_2). Suppose we have an array of domain walls, Fig. 2, along the y-axis. Deep between the domains the field is zero as in the case of C DDW. Along a domain at $x = 0$, where the field is maximal, again most of the fields cancel except those created by the vertical alternating currents of strength I_0 at $x = -a$ and those of strength $I_0/2$ at $x = a$. Equivalently this would be the field of a single vertical array of alternating currents of strength $I_0/2$ at $x = -a$:

$$B_{\max} = \frac{\mu_0}{4\pi x_0} \sum_i (-1)^i \frac{I_0}{2} (\cos(\theta_{i+1}) - \cos(\theta_i)) \quad (26)$$

where $\cos \theta_i = [(i-1)a + y_0] / [\sqrt{((i-1)a + y_0)^2 + x_0^2}]$ and $(x_0, y_0) = (a, a/2), (a, 0)$ for O, Cu atoms respectively. Clearly at $y_0 = 0$, Cu atoms the field is zero by symmetry. For O atoms the sum can be performed yielding $4\pi B_{\max}/\mu_0 = 0.14I_0$. In the dilute domain limit, this field is independent of the distance between the domains.

For a sinusoidal current modulation, B_{\max} would depend on the modulation length $l_q = 1/q$. If $I(y, x) = I(y)\sin(qx)$ then a good estimate of B_{\max} is given by (26) with I_0 replaced by $\delta I_0 = 2qaI_0 = 2I_0/n$ where n is the periodicity of the modulation (in units of the lattice spacing). Therefore, for large n we obtain $4\pi B_{\max}/\mu_0 = 0.24I_0/n$.

VI. CONCLUSION

Incommensurate order is an important possibility when competing orders are considered. At a first-order

transition the system is phase separated and hence necessarily inhomogeneous. If the competition between the orders is weak, coexistence is possible, but modulations of the competing orders are likely to be induced. The effects of the lattice, disorder, long-range Coulomb repulsion³³ and proximity to criticality³² is to generally stabilize incommensurability on mesoscopic length scales. This is unlike the case of, say, the liquid to vapor phase transition where the competition results in phase separation on macroscopic length scales.

In the case of DDW and DSC, the competition is certainly weak within the framework of the extended Hubbard models we have considered. Because the processes stabilizing both orders are of similar nature and are at the same time smaller than all of onsite repulsion, exchange and hopping, it does not cost much energy to convert DDW order into DSC and vice versa. A simple resolution of the competition is for DDW order to become incommensurate. We find that this occurs for some doping levels, but the incommensuration tends to be relatively small. Such IC DDW could, in principle, be observable at low temperatures by NMR since it creates an inhomogeneous magnetic field at O atoms *perpendicular* to the ab-plane. Most of NMR experiments test for much stronger magnetic fields *parallel* to the ab-plane on the Cu atoms, and at higher temperatures such IC DDW phase would be smeared by thermal fluctuations, which may explain why such IC order, if it exists, it hasn't been seen by experiment.

Acknowledgments

We would like to thank S. Brown, S. Chakravarty, R. Jamei, S. Kivelson, and E. Pivovarov for helpful discussions. Special thanks to E. Pivovarov for letting I. D. generalize some of his computer code. This work has been supported by the NSF under Grant No. DMR-0411800.

¹ U. Schollwöck, S. Chakravarty, J. O. Fjaerestad, J. B. Marston, and M. Troyer, Phys. Rev. Lett. **90**, 186401 (2003);

² E. Dagotto, Rev. Mod. Phys. **66**, 763 (1994); C. S. Hellberg and E. Manousakis, Phys. Rev. Lett. **83**, 132 (1999); S. Sorella, G.B. Martins, F. Becca, C. Gazza, L. Capriotti, A. Parola, E. Dagotto, Phys. Rev. Lett. **88**, 117002 (2002). S. R. White and D. J. Scalapino, Phys. Rev. B **61**, 6320 (2000); D. F. B. ten Haaf, P. W. Brouwer, P. J. H. Dente-

neer, and J. M. J. W. O. Putikka, M. U. Luchini, and R. R. P. Singh, Phys. Rev. Lett. **81**, 2966 (1998); L. P. Pryadko, S. A. Kivelson, O. Zachar, Phys. Rev. Lett. **92**, 067002 (2004); E. Dagotto and T. M. Rice, Science **271**, 618-623 (1996); G. Roux, S. R. White, S. Capponi, A. Laeuchli, D. Poilblanc, Phys. Rev. B **72**, 014523 (2005).

³ Experiments in the cuprates have been interpreted in terms of competing orders discussed in refs. 4,7; and also in C. M. Varma, Phys. Rev. B **55**, 14554 (1997); S. C. Zhang, Sci-

- ence 275, 1089 (1997).
- ⁴ E. W. Carlson, V. J. Emery, S. A. Kivelson, and D. Orgad, in *The Physics of Conventional and Unconventional Superconductors*, ed. K. H. Bennemann and J. B. Ketterson (Springer-Verlag 2003), cond-mat/0206217; A. H. Castro Neto and C. Morais Smith, in *Strong Interactions in Low Dimensions*, ed. D. Baeriswyl and L. Degiorgi (Kluwer Acad. Pub. 2004), cond-mat/0304094; V. J. Emery, S. A. Kivelson, and J. M. Tranquada, Proc. Natl. Acad. Sci. USA **96**, 8814 (1999); M. Vojta and S. Sachdev, Phys. Rev. Lett. **83**, 3916-3919 (1999); J. Zaanen, Nature 404, 714 (2000); and references therein.
 - ⁵ J. M. Tranquada, Physica B 241-243, 745 (1998); in *Neutron Scattering in Layered Copper-Oxide Superconductors*, ed. A. Furrer (Kluwer, Dordrecht, The Netherlands), p. 225.
 - ⁶ J. E. Hoffman, K. McElroy, D.-H. Lee, K. M. Lang, H. Eisaki, S. Uchida, and J. C. Davis, Science **297**, 1148 (2002); K. McElroy, R. W. Simmonds, J. E. Hoffman, D.-H. Lee, J. Orenstein, H. Eisaki, S. Uchida, J. C. Davis, Nature **422**, 592 (2003); C. Howald, H. Eisaki, N. Kaneko, M. Greven, and A. Kapitulnik, Phys. Rev. B **67**, 014533 (2003).
 - ⁷ S. Chakravarty, R. B. Laughlin, D. K. Morr, and C. Nayak, Phys. Rev. B **63**, 094503 (2001).
 - ⁸ C. Nayak, Phys. Rev. B **62**, 4880 (2000).
 - ⁹ T. Timusk and B. Statt, Rep. Progr. Phys. **62**, 61-122 (1999).
 - ¹⁰ S. Tewari *et al.*, Phys. Rev. B **64**, 224516 (2001).
 - ¹¹ J.L. Tallon and J.W. Loram, Physica C **349**, 53 (2001); J.W. Loram *et al.*, J. Phys. Chem. Solids **59**, 2091 (1998); J.L. Tallon *et al.*, Phys. Stat. Sol. B **215**, 531 (1999).
 - ¹² Y. J. Uemura *et al.*, Phys. Rev. Lett. **62**, 2317 (1989); C. Panagopoulos *et al.*, Phys. Rev. B **60**, 14617 (1999); C. Panagopoulos *et al.*, Physica C, **341-348**, 843 (2000).
 - ¹³ S. Chakravarty, C. Nayak, S. Tewari, Phys. Rev. B **68**, 100504/1-4 (2003).
 - ¹⁴ C.C. Homes *et al.*, Phys. Rev. Lett. **71**, 1645 (1993).
 - ¹⁵ C. Stock *et al.*, Phys. Rev. B **66**, 024505 (2002).
 - ¹⁶ H. A. Mook *et al.*, Phys. Rev. B **66**, 144513 (2002).
 - ¹⁷ S. Chakravarty, H. Y. Kee, and C. Nayak, Intl. J. Mod. Phys. **15**, 2901 (2001).
 - ¹⁸ S. Chakravarty, C. Nayak, S. Tewari, X. Yang, Phys. Rev. Lett. **89**, 277003/1-4 (2002).
 - ¹⁹ Balakirev *et al.*, Nature **424**, 912 (2003).
 - ²⁰ S. Tewari *et al.*, Phys. Rev. B **70**, 014514 (2004).
 - ²¹ L.B. Rigal *et al.*, Phys. Rev. Lett. **93**, 137002 (2004).
 - ²² C. Wu, J. Zaanen, S.-C. Zhang, Phys. Rev. Lett. **95**, 247007 (2005).
 - ²³ U. Schollwoeck *et al.* Phys. Rev. Lett. **90**, 186401; J. O. Fjarestad, J. B. Marston, U. Schollwoeck Ann. Phys. (N.Y.) **321**, 894 (2006).; S. Capponi, C. Wu, S.-C. Zhang Phys. Rev. B **70**, 220505(R) (2004).
 - ²⁴ E. Cappelluti and R. Zeyher, Phys. Rev. B **59**, 6475-6486 (1999).
 - ²⁵ H.-Y. Kee and Y. B. Kim, Phys. Rev. B **66**, 012505 (2002).
 - ²⁶ C. Nayak, E. Pivovarov, Phys. Rev. B **66**, 064508 (2002).
 - ²⁷ H. J. Schulz, J. de Physique **50**, 2833 (1989).
 - ²⁸ S. Chakravarty, Phys. Rev. B **66**, 224505 (2002).
 - ²⁹ A. Kotani, J. Phys. Soc. Jpn. **42**, 408 (1977).
 - ³⁰ L. Pryadko, *et. al.*, Phys. Rev. B **60**, 7541 (1999).
 - ³¹ A. Damascelli, Z. Hussain, Z.-X. Shen, Rev. Mod. Phys. **75**, 473 (2003).
 - ³² S. Kivelson, *et. al.*, Rev. Mod. Phys. **75**, 1201 (2003).
 - ³³ R. Jamei, S. Kivelson, B. Spivak, cond-mat/0408066.
 - ³⁴ C. Bena *et. al.*, Phys. Rev. B **69**, 134517 (2004); C. Bena *et. al.* cond-mat/0311299; A. Ghosal, A. Kopp, S. Chakravarty, cond-mat/0412241.
 - ³⁵ V. Tripathi, P. Chandra, P. Coleman, J. Phys.: Condens. Matter **17**, 5285 (2005).
 - ³⁶ The AF only limit was taken by simply letting $g_{DDW}, g_{DSC} \rightarrow 0$ in the total free energy (20).
 - ³⁷ There is a neat way of thinking about IC DDW at finite μ as the analog of the Fulde-Ferrel-Larkin-Ovchinnikov (FFLO) state of DSC in a magnetic field parallel to the plane²⁵. In the absence of next-nearest neighbor hopping, the two mean fields are related via a particle-hole transformation in the same way *commensurate* DDW is related to DSC at half-filling. However, while in the latter case one can rotate C DDW to DSC⁷, in the case of finite μ , the particle-hole transformation cannot interchange FFLO and IC DDW. While the mean-field Hamiltonians of IC DDW and the FFLO are related by a particle-hole transformation, the spectra are not – in the IC DDW state there is a splitting to a generally uncountably many bands (if Q/q is irrational as we discussed in Sec. IV) since the order parameter connects \mathbf{k} and $\mathbf{k} + \mathbf{Q}$ while in the case of DSC there is no such splitting. We are indebted to the authors of²⁵ for pointing out their work to us.