

Doping Dependence of Bilayer Resonant Spin Excitations in (Y, Ca)Ba₂Cu₃O_{6+x}

S. Pailhès^{1,2}, C. Ulrich³, B. Fauqué¹, V. Hinkov³, Y. Sidis¹, A. Ivanov⁴, C.T. Lin³, B. Keimer³ and P. Bourges^{1*}

¹ *Laboratoire Léon Brillouin, CEA-CNRS, CE-Saclay, 91191 Gif sur Yvette, France.*

² *Laboratory for Neutron Scattering, ETH Zurich and PSI Villigen, CH-5232 Villigen PSI, Switzerland.*

³ *Max-Planck-Institut für Festkörperforschung, 70569 Stuttgart, Germany.*

⁴ *Institut Laue Langevin, 156X, 38042 Grenoble cedex 9, France.*

Resonant magnetic modes with odd and even symmetries were studied by inelastic neutron scattering experiments in the bilayer high- T_c superconductor $Y_{1-x}Ca_xBa_2Cu_3O_{6+y}$ over a wide doping range. The threshold of the spin excitation continuum in the superconducting state, deduced from the energies and spectral weights of both modes, is compared with the superconducting d -wave gap, measured on the same samples by electronic Raman scattering in the B_{1g} symmetry. Above a critical doping level of $\delta \simeq 0.19$, both mode energies and the continuum threshold coincide. We find a simple scaling relationship between the characteristic energies and spectral weights of both modes, which indicates that the resonant modes are bound states in the superconducting energy gap, as predicted by the spin-exciton model of the resonant mode.

In high- T_c copper oxides superconductors, inelastic neutron scattering (INS) experiments have shown that the superconducting (SC) phase exhibits an unusual spin triplet excitation, the so-called magnetic resonance mode [1]. This excitation has been observed in several families of copper oxides with SC critical temperatures $T_c \sim 90$ K: $Tl_2Ba_2CuO_{6+x}$, $Bi_2Sr_2CaCu_2O_{8+x}$, and $YBa_2Cu_3O_{6+x}$ (YBCO_{6+x}). Two kinds of theoretical models attempt to describe this mode. Within an itinerant-electron picture, it is described as a *spin-exciton*, that is, it corresponds to a spin-triplet bound states stabilized by the electron-electron interaction in the plane below the electron-hole (e - h) spin-flip continuum, which is gapped in the SC state [2, 3]. As the mode is an intrinsic feature of the SC state, it disappears above T_c . In other approaches [4, 5, 6], the collective spin excitations pre-exist in the normal state, where they are damped by scattering from charge excitations. In the SC state, the damping is suppressed, and the mode sharpens if its energy is below the threshold of the gapped e - h continuum. The charge carriers interacting with the spin excitations can be either uniformly distributed [4] or segregated into quasi-one-dimensional *stripes* that separate nearly insulating antiferromagnetic domains [5, 6]. Although the quantum numbers characterizing the mode are identical in both of these competing approaches, the underlying physical pictures are quite different. It is hence important to establish criteria that allow quantitative experimental tests of these models.

The bilayer structure of YBCO offers an interesting opportunity in this regard. While most calculations have been carried out for a single CuO_2 plane per unit cell [4, 5], both theoretical approaches predict two distinct magnetic resonant modes in a bilayer system. They are characterized by even (e) or odd (o) symmetries, respectively, with respect to the exchange interaction between the two layers in a bilayer unit. Recent INS measurements have shown that the bilayer system YBCO indeed exhibits two magnetic resonant modes, both of

which are apparent as a strong enhancement of the magnetic intensity at the planar antiferromagnetic wave vector $\mathbf{q}_{AF} = (\pi, \pi)$ in the SC state [7, 8]. Their intensities display an order-parameter-like temperature dependence and vanish at T_c , without any significant shift of their characteristic energies. A crucial difference between both theoretical approaches concerns the energy-integrated spectral weight (SW) of the magnetic modes. In *spin exciton* models, this quantity is a function of the binding energy of the modes [2, 3] (that is, the difference of the mode energy and the e - h continuum threshold), whereas in models based on *pre-existing* spin excitations it is not obviously related to the location of the mode with respect to the e - h continuum.

Here we report an INS study of the odd and even resonant spin excitations at $\mathbf{q}_{AF}$ spanning a wide doping range from the underdoped to the overdoped regimes in YBCO. The threshold for e - h excitations, $2\Delta_{max}$, was measured by electronic Raman scattering (ERS) in the B_{1g} channel [9] on the same samples used in the neutron experiments. This eliminates systematic errors invariably associated with comparisons of measurements on samples from different origins. We found that the resonant spin excitations are always located below $2\Delta_{max}$. Assuming that the spin excitations are bound states in the energy gap of the e - h continuum, its threshold at $\mathbf{q}_{AF}$, ω_c , is estimated using the measured energies, $E_r^{o,e}$, and spectral weights, $W_r^{o,e}$, of the odd and even resonance peaks. The threshold energy ω_c estimated in this way is found to be below the independently determined gap $2\Delta_{max}$, so that the analysis is self-consistent. We also observed a systematic scaling relation between $W_r^{o,e}$ and the reduced binding energy $(\omega_c - E_r^{o,e})/\omega_c$. As such a relation is only expected for collective bound states of the e - h continuum, our results support the spin-exciton description of the resonant mode. Further, our study reveals that $2\Delta_{max}$ and the total SW of the resonant spin excitations at $\mathbf{q}_{AF}$ drop precipitously in the overdoped regime close to the hole doping level $\delta \simeq 0.19$. Previous work identified

of this doping level as the end point of the pseudo-gap phase [10, 11, 12].

In addition to previous INS experiments on a slightly overdoped sample (OD85, $\text{Y}_{0.9}\text{Ca}_{0.1}\text{Ba}_2\text{Cu}_3\text{O}_7$, Ref. [7]) and a slightly underdoped sample (UD89), $\text{YBa}_2\text{Cu}_3\text{O}_{6.85}$, Ref. [8]), INS studies of bilayer excitations were performed on two YBCO samples. The first sample is overdoped (OD75), $\text{Y}_{0.85}\text{Ca}_{0.15}\text{Ba}_2\text{Cu}_3\text{O}_7$ with $T_c = 75$ K [13, 14]. Following our previous work with sample OD85, about 50 single crystals, obtained by a top-seeded solution growth method [15], were co-aligned on aluminum plates and fixed with glue or Al screws. The second sample (UD63), $\text{YBa}_2\text{Cu}_3\text{O}_{6.6}$ with $T_c^{\text{onset}} = 63$ K, is underdoped and consists of 180 detwinned squared-shape single crystals [16]. The mosaic spread of these crystals arrays exceeds 1.4° . INS measurements have been performed on the thermal triple axis spectrometer IN8 at the Institute Laue Langevin (Grenoble). The experimental setup and scattering plane are the same as Ref. [8] except that we utilized a PG(002) monochromator. A fixed final neutron energy of 35 meV has been used yielding a typical energy resolution of 7-8 meV.

The spin susceptibility of a bilayer system reads:

$$\chi(\mathbf{Q}, \omega) = \left[\sin^2(\pi z L) \chi_o(\mathbf{q}, \omega) + \cos^2(\pi z L) \chi_e(\mathbf{q}, \omega) \right] \quad (1)$$

where $\mathbf{Q} = (H, K, L)$ is the full wave vector and $\mathbf{q} = (H, K)$ is the planar wave vector in CuO_2 plane. $z=0.28$ stands for the reduced distance between the planes of the bilayer. The L -component of the wave vector can thus be used to select either the odd or the even channel [8]: the magnetic structure factor is maximum for $L \sim 5.2$ in the odd channel and $L \sim$ for 3.4 or 7 in the even. Following the standard terminology [7, 8, 17, 18], we define the magnetic resonant mode as the enhancement of the imaginary part of the magnetic susceptibility, $\Delta \text{Im} \chi(\mathbf{q}_{\text{AF}}, \omega)$ in the SC state, which is derived from the difference between measurements in the SC state at 10 K and the normal state above T_c . The imaginary part of the dynamical magnetic susceptibility is also calibrated in absolute units ($\mu_B^2 \cdot \text{eV}^{-1} / \text{f.u.}$) following a standard procedure with a reference phonon at 42.5 meV [17, 18].

Fig. 1.a provides evidence of the existence of odd and even resonant magnetic peaks in the INS spectra of the highly overdoped sample OD75. These results differ significantly from previous reports at lower doping levels [7, 8], because the energies of both mode are very similar: $E_r^o = 34 \text{ meV}$ and $E_r^e = 35 \text{ meV}$. Further, both modes also display similar amplitudes. In order to determine the amplitudes I^o/e of both modes, the L -dependence of the magnetic intensity at 34 meV (Fig. 1.b) was fitted with Eq. 1. This yields a ratio $I^e/I^o \simeq 0.4$, compared to $1/3$ for sample OD85 [7] and $1/6$ for $\text{YBCO}_{6.85}$ [8]. However, as for lower doping levels [7, 8], the temperature dependence of the intensities of both modes exhibits a marked change at the SC temperature (Fig. 1.c), in-

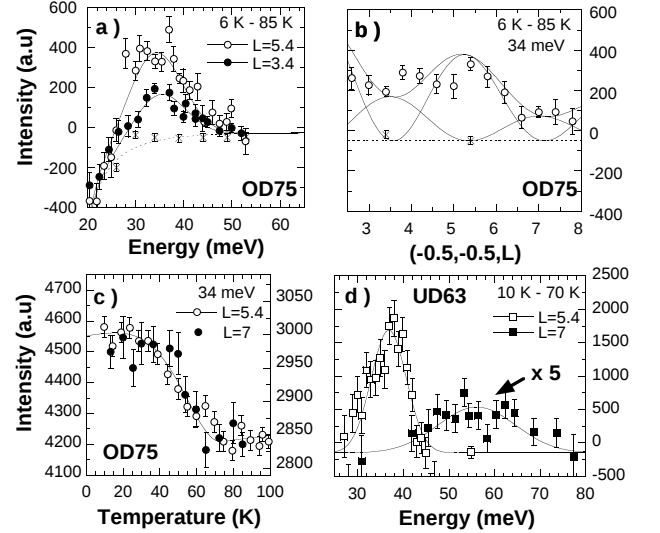


FIG. 1: (color online) a) Differences between INS energy scans measured at the antiferromagnetic wave vector below and above T_c in $\text{Y}_{0.85}\text{Ca}_{0.15}\text{Ba}_2\text{Cu}_3\text{O}_7$ (OD75). Open and closed symbols correspond to the odd and even channels, respectively. The data have been corrected by the anisotropic Cu magnetic form factor. The stars indicate the measured reference level of the magnetic scattering determined by constant-energy scans. b) L -dependence at $E=34$ meV for OD75. The lines describe the intensity of each mode following Eq. 1 multiplied by the Cu magnetic form factor (upper line). c) Temperature dependence of the neutron intensity measured at characteristic energies of the even and odd modes for OD75. d) Same as a) but for sample $\text{YBCO}_{6.6}$ (UD63).

dicating that the phenomena have a similar origin. In the strongly underdoped sample UD63 (Fig. 1.d), the two mode energies and their intensities are very different: $E_r^o = 37 \text{ meV}$, $E_r^e = 55 \text{ meV}$, and $I^e/I^o \simeq 1/20$. As already observed in the OD85 sample [7], the odd mode exhibits a broader energy line shape in OD75, $\Delta E \sim 12 \text{ meV}$, than the resolution-limited energy profile observed in underdoped samples [16]. The energy width of the even mode, $\Delta E \sim 15 \text{ meV}$, is always broader than the resolution, for all doping level.

In order to assess whether or not these resonant modes should be regarded as bound states in the electronic continuum, one has to determine the amplitude of the SC gap. The good surface quality of the single crystals removed from the crystals array OD85 and OD75 enables ERS experiments. The ERS technique probes electronic excitations in selected areas of the Brillouin zone. In the B_{1g} channel, the antinodal areas around $(\pm\pi, 0)$ and $(0, \pm\pi)$ are probed, and a peak appears in the electronic spectrum in the SC state at twice the energy of the maximum d -wave SC gap, $2\Delta_{\text{max}}$ [9]. These measurements were carried out with a triple-grating spectrometer in quasi-back-scattering geometry. The crystals were mounted on the cold finger of an He circulation cryostat.

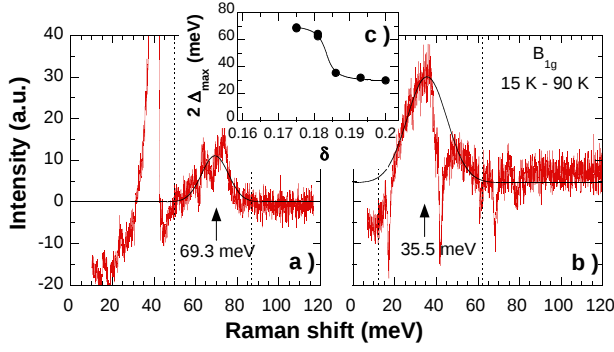


FIG. 2: (color online) Electronic Raman spectra in the B_{1g} channel. The difference between spectra measured at 15 K in the SC state and at 90 K in the normal state is displayed. In addition to sharp features due to phonon renormalization, the difference indicates a broad peak due to the enhancement of the electronic response in the SC state. The electronic peaks were fitted with Gaussian profiles. The inset shows the peak energy of the 5 samples we have studied (see Fig. 3 caption for the determination of the doping levels).

The 514 nm excitation line of a Ar^+/Kr^+ mixed-gas ion laser was used.

Figure 2 shows the B_{1g} peaks in the ERS spectra of single crystals extracted from samples OD85 and OD75. The B_{1g} peak is observed at 69.3 meV in the first sample and shifts to 35.5 meV for the second, whereas T_c is only reduced from 85.5 K to 75 K. The same results were obtained on other crystals selected randomly from the OD85 and OD75 arrays[21]. Further experiments on samples with different T_c also confirm that the characteristic energy of the B_{1g} peak drops steeply by almost a factor two with a minor reduction of T_c . This phenomenon was previously reported in Refs. [19, 20], and it is now confirmed directly on the same samples used for the INS experiments. Systematic errors associated with experiments on samples of different origins could thus be avoided. As shown in the inset of Fig. 2, the drastic decrease of the B_{1g} peak occurs close to a critical hole doping level $\delta_c \simeq 0.19$.

In Fig. 3.a, we report the hole doping dependence (i) of the $2\Delta_{\text{max}}$ determined by ERS from the present study and Refs. [19, 20], and (ii) the odd and even resonant energies obtained from INS data. For all samples, the even resonance appears at higher energy and with less intensity than the odd resonance. While E_r^o evolves as a function of hole doping as $\sim 5 k_B T_c$ (Fig. 3.a), E_r^e does not scale with T_c : it remains almost constant in the underdoped regime and begins to decrease upon entering the overdoped regime. With increasing hole doping, the distance in energy between the magnetic modes decreases from 17 meV in UD63 to 1 meV in OD75. Owing to the differences between the energy lineshapes of the odd and even modes, the most meaningful comparison is based on their energy-integrated spectral weights: $W_r^{o,e} = \int_0^\infty d\omega \Delta \text{Im} \chi_{o,e}(\mathbf{q}, \omega)$. The ratio and the sum of the energy-

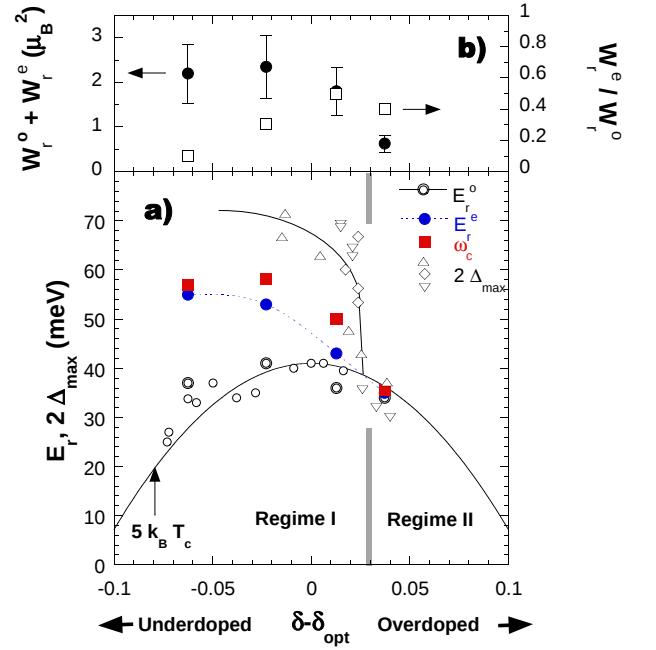


FIG. 3: (color online) Doping dependence of: a) E_r^o , E_r^e , ω_c and $2\Delta_{\text{max}}$ (ERS). Other ERS data were obtained from [20] (Δ), in [19] ($\diamond$), in the present study (∇). b) Ratio and sum of the energy-integrated SW. The hole doping is estimated from the phenomenological relation $T_c(\delta) = T_c^{\text{opt}}(1 - 82.6(\delta - \delta_{\text{opt}})^2)$ [14], δ_{opt} is generally estimated to be 0.16 [14]. T_c^{opt} is 93K for pure YBCO. Ca substitution reduces T_c according to $T_c^{\text{opt}} = 90.6 - 39.2x_{\text{Ca}}$ obtained for our single crystals.

integrated SWs of both modes are shown in Fig. 3.b. Obviously, W_r^e/W_r^o increases with increasing doping.

The dramatic change of the SC gap measured by ERS (Fig. 3.a) separates two distinct regimes on both sides of δ_c : in regime I, encompassing the underdoped samples up to OD85, one obtains the following hierarchy: $5k_B T_c \sim E_r^o < E_r^e < 2\Delta_{\text{max}}$. In regime II (OD75), all energies collapse to $5k_B T_c \sim E_r^o \simeq E_r^e \simeq 2\Delta_{\text{max}}$. The coincidence of the resonant mode energy and the SC energy gap in the overdoped range was suggested by prior tunneling experiments [22]. As the information about the mode energy obtained from tunneling is quite indirect, the interpretation of these data has remained controversial. The total SW of the resonant modes, $W_r^o + W_r^e$, declines precipitously around a similar doping level (Fig. 3.b). It is interesting to note that the doping level $\delta_c \simeq 0.19$ separating these two regimes coincides with the hole concentration where previous work had uncovered rapid doping-induced modifications of the physical properties such as resistivity, specific heat, Knight shift, and muon spin relaxation rate [10, 11, 12]. According to [23], this point in the phase diagram is a quantum critical point associated with the doping-induced disappearance of a putative order parameter characterizing the pseudo-gap phase. Therefore, it is tempting to relate the anomalous hole doping dependencies shown in Fig. 3.a to

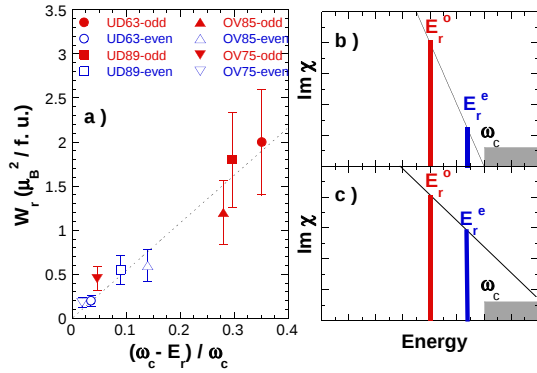


FIG. 4: (color online) a) Resonant modes SW *vs* the reduced binding energy. Sketch of two approaches for the resonant modes: b) bound states of the electronic continuum. c) pre-existing modes whose intensities are enhanced by the disappearance of the fermionic damping below ω_c .

the pseudo-gap phenomenon.

In Fig. 3.a, one also notices that the resonance energies are systematically lower than twice the SC gap. This indicates that the resonant modes are below the continuum threshold at $\mathbf{qAF}$, ω_c , which can be estimated as $1.8\Delta_{\max}$ using the typical Fermi surface topology observed in cuprates [24]. As discussed in Refs. [2, 7], another estimate of ω_c can be made within the spin-exciton model where $W_r^{o,e} \propto (\omega_c - E_r^{o,e})/\omega_c$. ω_c is simply deduced by the ratio of the SWs of the odd and even modes [7, 8]. For the four samples, ω_c extracted in this way from INS (Fig. 3.a) agrees with the value deduced from ERS data.

We now discuss these observations in the light of the various models attempting to describe the resonant modes [2, 3, 4, 5, 6]. As sketched in Fig. 4, one can envisage two situations: either the modes are bound states in the energy gap of the electronic continuum (Fig. 4.b), as assumed in the *spin-exciton* model [2, 3], or they already exist above T_c [4, 5, 6] and their SWs are only enhanced in the SC state (Fig. 4.c). In the former case, the SWs of the modes are proportional to the binding energies, while in the latter case there is no specific relation between the SW and the distance between the mode energy and ω_c . The SWs of the modes, $W_r^{o,e}$, are presented in Fig. 4.a as a function of the reduced binding energy, i.e. $(\omega_c - E_r^{o,e})/\omega_c$. Clearly, these two quantities are proportional to each other with a constant scaling factor over a wide doping level. This is the expected behavior for collective bound states in the SC energy gap where the scaling factor is mostly controlled by doping independent microscopic parameters. In the pre-existing mode picture, on the other hand, the SW ratio W_r^e/W_r^o would be also determined by the spin dynamics in the normal state. To be sure, well-defined magnetic modes are observed in the underdoped samples above T_c [17], but we recently found that there are a number of qual-

itative differences between the excitation spectra in the SC and normal states at energies comparable to the SC gap [25]. In overdoped samples, normal-state excitations appear to be heavily overdamped and have thus far not been clearly identified. It is therefore reasonable to consider the excitations in the SC state separately, as we have done.

In summary, odd and even symmetry resonant magnetic excitations have been observed in bilayer YBCO over a wide doping range. A detailed analysis of the modes energies and spectral weights show that the resonant mode in the high- T_c cuprates arises from bound states in the superconducting energy gap. Our results have no natural explanation in models where the resonant excitations are associated with excitations pre-existing in the normal state.

-
- [1] Y. Sidis *et al.*, Phys. Stat. Sol.(b) **241**, 1204 (2004) (cond-mat/0401328) and references therein.
 - [2] A.J. Millis and H. Monien, Phys. Rev. B **54**, 16172 (1996).
 - [3] For a review, see M. Eschrig, cond-mat/0510286.
 - [4] D.K. Morr, D. Pines, Phys. Rev. Lett. **81**, 1086 (1998); S. Sachdev *et al.*, Science **286**, 2479 (1999); P-A. Lindgard, Phys. Rev. Lett. **95**, 217001 (2005).
 - [5] C.D. Batista *et al.*, Phys. Rev. B **64**, 172508 (2001); cond-mat/0511303; M. Vojta *et al.*, Phys. Rev. Lett. **93**, 127002 (2004). G. S. Uhrig *et al.*, Phys. Rev. Lett. **93**, 267003 (2004); G. Seibold and J. Lorenzana, Phys. Rev. Lett. **94**, 107006 (2005).
 - [6] F. Kruger and S. Scheidl, Phys. Rev. B, **70**, 06442 (2004); J. S. Uhrig *et al.*, J. Phys. Soc. Jpn., **74**, supp. 86 (2005),
 - [7] S. Pailhès *et al.*, Phys. Rev. Lett. **91**, 237002 (2003).
 - [8] S. Pailhès *et al.*, Phys. Rev. Lett. **93**, 167001 (2004).
 - [9] Y. Gallais *et al.*, Phys. Rev. Lett. **88**, 177404 (2002); M. Cardona, Physica C, **318**, 30 (1999); T. P. Devereaux and D. Einzel, Phys. Rev. B, **51**, 16336 (1995).
 - [10] J.L. Tallon *et al.*, Phys. Stat. Sol. (b). **215**, 531 (1999).
 - [11] J.L. Tallon and J. W. Loram, Physica C **349**, 53 (2001).
 - [12] S.H. Naqib *et al.*, Phys. Rev. B **71**, 054502 (2005).
 - [13] E. M. Mc Carron III *et al.*, J. Solid State Chemist. **78**, 192 (1989).
 - [14] J. L. Tallon *et al.*, Phys. Rev. B **51**, R12911 (1995).
 - [15] C. T. Lin *et al.*, J. Cryst. Growth **237**, 778 (2002).
 - [16] V. Hinkov *et al.*, Nature **430**, 650 (2004).
 - [17] H.F. Fong *et al.*, Phys. Rev. B **61**, 14773 (2000).
 - [18] S. Pailhès *et al.*, Phys. Rev. B, **71**, 220507(R) (2005).
 - [19] X. K. Chen *et al.*, Phys. Rev. B **48**, 10530 (1993).
 - [20] A. Bock, An. Phys. B **8**, 441 (1999).
 - [21] S. Pailhès *et al.*, further Raman details, to be published.
 - [22] J. Zasadzinski *et al.*, Phys. Rev. Lett. **87**, 067005 (2001).
 - [23] S. Sachdev, Rev. of Mod. Phys. **75**, 913 (2003); C.M. Varma, Phys. Rev. B **55**, 14554 (1997).
 - [24] A.A. Kordyuk *et al.*, Phys. Rev. B **67**, 064504 (2003).
 - [25] V. Hinkov *et al.*, preprint cond-mat/....