

# M ultipole O rdering and F luctuations in f-E lectron S ystem s

Katsunori Kubo and Takashi Hotta

Advanced Science Research Center, Japan Atomic Energy Agency, Tokai, Ibaraki 319-1195

(Received March 23, 2022)

We investigate effects of multipole moments in f-electron systems both from phenomenological and microscopic viewpoints. First, we discuss significant effects of octupole moment on the magnetic susceptibility in a paramagnetic phase. It is found that even within mean-field approximation, the magnetic susceptibility deviates from the Curie-Weiss law due to interactions between dipole and octupole moments. Next, we proceed to a microscopic theory for multipole ordering on the basis of a  $j$ - $j$  coupling scheme. After brief explanation of a method to derive multipole interactions from the f-electron model, we discuss several multipole ordered phases depending on lattice structure. Finally, we show our new development of the microscopic approach to the evaluation of multipole response functions. We apply fluctuation exchange approximation to the f-electron model, and evaluate multipole response functions.

**KEYWORDS:** octupole moment,  $j$ - $j$  coupling scheme, Curie-Weiss law, fluctuation exchange approximation

## 1. Introduction

Novel magnetism and exotic superconductivity in rare-earth<sup>1</sup> and actinide<sup>2</sup> compounds have attracted much attention in the research field of condensed matter physics. In order to elucidate the mechanism of these phenomena, it is quite important to describe f-electron states in a systematic way by considering correctly the symmetry of f-electron orbitals. On the other hand, we encounter difficulties to express f-electron states by means of a simple combination of spin and orbital degrees of freedom, as has been done for d-electron states, since the spin-orbit interaction is strong for f orbitals in general. For such a case, it is rather convenient to exploit multipole degrees of freedom, including charge (rank-0), dipole (rank-1), quadrupole (rank-2), and octupole (rank-3) components. Fortunately, among such multipole moments, dipole and quadrupole correspond to ordinary spin and orbital degrees of freedom, respectively. Thus, phenomena concerning dipole and/or quadrupole moments are basically understood by analogy with d-electron physics. In this sense, octupole is considered to be the first exotic multipole moment in the solid state physics.

Although it has been very rare to observe phenomena related to octupole moment in d-electron compounds, we have sometimes found octupole-related phenomena in f-electron compounds. For instance, in order to understand anomalous properties of  $\text{CeB}_6$ , significant roles of octupole moment have been discussed actively. In particular, apparent contradiction between neutron scattering and NMR measurements on the so-called phase II of  $\text{CeB}_6$  has been clearly resolved by considering effects of magnetic-field induced octupole moment on the hyperfine coupling.<sup>3</sup> In recent years, furthermore, possibility of ordering of octupoles themselves has been intensively discussed for  $\text{Ce}_x\text{La}_{1-x}\text{B}_6$ <sup>4(19)</sup> and for  $\text{NpO}_2$ .<sup>10(17)</sup> In both materials, the crystalline electric field (CEF) ground states are  $\gamma_8$  quartets,<sup>18(22)</sup> and in such CEF ground states, there are dipole, quadrupole, and octupole degrees of freedom.<sup>23</sup> In fact, several experimental facts

have been reconciled by assuming  $\gamma_8$  antiferro-octupole ordering in these materials.

In order to contribute to the further development of multipole physics, there are two different ways for the direction of research. One is to clarify the effect of octupole moment in a paramagnetic phase, not in the ordered state, in a phenomenological level. It is one of natural extensions of the research for multipoles, since the phenomenological theory for octupole ordering has been developed so far. Here it should be noted that octupole moments are magnetic, that is, parity of octupoles is odd under time reversal. Thus, in principle, octupoles would influence magnetic properties even in the paramagnetic phase. However, such effects have not been studied seriously. We should make efforts to include such effects to analyze magnetic properties of materials with active octupole degrees of freedom.

Another direction of the research is to develop a microscopic theory for multipole-related phenomena. The construction of such a microscopic theory was considered to be difficult, since it has been believed that it is standard to use the LS coupling scheme to express the f-electron state. However, we have recently developed a microscopic theory for f-electron systems by exploiting a  $j$ - $j$  coupling scheme.<sup>24(26)</sup> The ground and low-energy excited states can be well described by a microscopic model on the basis of the  $j$ - $j$  coupling scheme, in contrast to the naive belief for the limitation of the  $j$ - $j$  coupling scheme. For instance, we have successfully explained the microscopic origin of octupole ordering of  $\text{NpO}_2$  even in a simple d-electron-like approximation.<sup>25,26</sup>

Since we have shown that the microscopic model on the basis of the  $j$ - $j$  coupling scheme is useful to understand multipole ordering for f-electron systems, it is natural to investigate further the effect of multipole fluctuations in a microscopic level. We believe that it is challenging and important development of the microscopic theory for f-electron materials. In fact, it has been actually proposed that exotic superconductivity in  $\text{PrO}_2\text{Sb}_{12}$ <sup>27</sup>

may be induced by quadrupole fluctuations,<sup>28,30</sup> since a quadrupole ordered phase appears under a magnetic field.<sup>31,32</sup> In order to discuss such a possibility from a microscopic view point, it is necessary to include multipole fluctuations in a microscopic theory for superconductivity. In particular, we should classify complex fluctuations in f-electron systems into multiple components.

In this paper, we exhibit our new development for multipole physics including review of our previous work. In §2, first we briefly review our simple phenomenological theory to understand the effect of octupole moment in a paramagnetic phase.<sup>33</sup> In particular, we discuss effects of octupoles on the magnetic susceptibility, to clarify how octupoles influence macroscopic properties in the paramagnetic phase. In §3, we explain the recent development of our microscopic theory for multipole phenomena. After a short explanation of the model on the basis of the  $j$ - $j$  coupling scheme, we briefly review the microscopic theory for multipole ordering.<sup>25,26</sup> In particular, we find the  $5u$  longitudinal antiferro-octupole ordering for an fcc lattice, which has been proposed for  $\text{NpO}_2$ . Then, we explain new development of our theory to treat multipole fluctuations. We present our framework for the microscopic approach to evaluate multipole response functions with some calculated results. Finally, in §4, we summarize this paper. Throughout this paper, we use such units as  $\hbar = k_B = 1$ .

## 2. Phenomenological Approach

In order to clarify complex effects of multipole moment, it is useful to consider first the problem in a phenomenological level. In fact, there are lots of literatures treating multipole ordering along this direction and the phase diagram including multipole ordered state has been successfully explained by applying a mean-field approximation to the Heisenberg-like model for multipole moments. In this section, we briefly review our recent result based on such a phenomenological model, to clarify significant effect of octupole moment on magnetic properties in the paramagnetic phase within the mean-field approximation.<sup>33</sup>

Let us here consider a cubic system for simplicity. There is no essential difficulty to extend the theory to other cases. In a cubic system, the octupole moment  $T$  with the same symmetry  $4u$  as the dipole moment  $J$  is an independent degree of freedom in a certain CEF ground state, e.g.,  $8g$  ground state. In such a case, octupole and dipole moments interact each other. In general, we should note that  $T$  is not orthogonal to  $J$ . Thus, we define  $T^0$ , a linear combination of  $T$  and  $J$ , which is orthogonal to  $J$ , i.e.,  $\text{tr}(J T^0) = 0$ , where  $\text{tr}$  indicates a cartesian component and  $\text{tr}(\cdot)$  denotes the sum of the expectation values over the CEF ground states. We normalize  $T^0$  so as to satisfy  $\text{tr}(J J) = \text{tr}(T^0 T^0)$ .

Then, a mean-field Hamiltonian under a magnetic field  $H$  along the  $z$ -direction up to  $O(H)$  is given by

$$H_{MF} = H M_z (g_J \mu_B)^2 [d J_z \hbar J_z + e T_z \hbar T_z + f d_0 (J_z \hbar T_z^0 + T_z^0 \hbar J_z)], \quad (2.1)$$

where  $M_z$  denotes magnetic moment,  $g_J$  is the Landé's

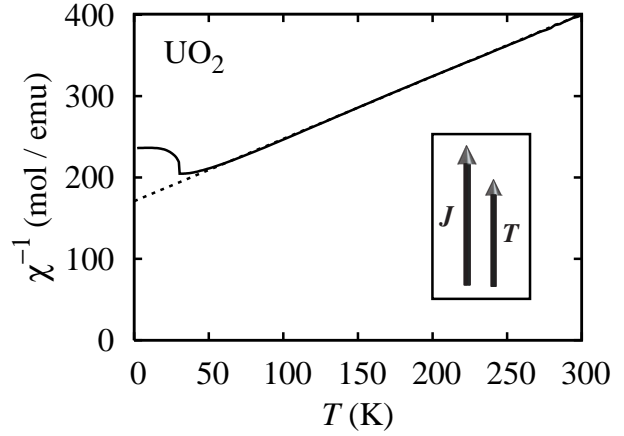


Fig. 1. Temperature dependence of the inverse of the magnetic susceptibility of  $\text{UO}_2$  under  $H = 10$  kOe and  $H \parallel [100]$ <sup>36</sup> (solid curve). The dotted curve represents the Curie-Weiss law with  $\mu_B = 3.23 \mu_B$  [ $C = \frac{2}{3} = (3k_B)$ ] and  $\theta = 223$  K. The inset shows a schematic view of the dipole moment  $J$  and octupole moment  $T$  in a  $5u$  CEF ground state.

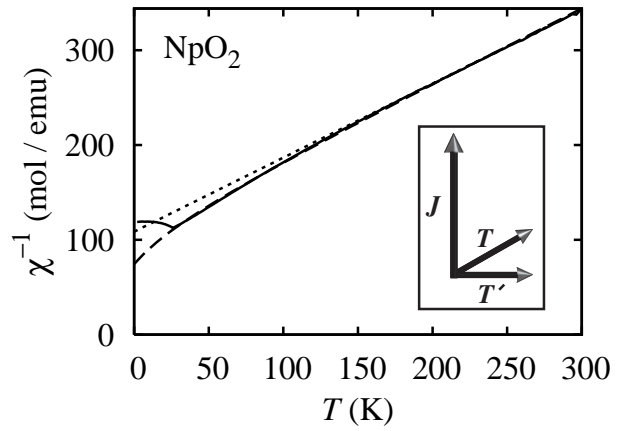


Fig. 2. Temperature dependence of the inverse of the magnetic susceptibility of  $\text{NpO}_2$  under  $H = 10$  kOe and  $H \parallel [100]$ <sup>39</sup> (solid curve). The dashed curve represents the fit obtained with eq. (2.5) with  $\mu_B = 3.20 \mu_B$ ,  $\theta = 146.1$  K,  $\theta_1 = 161.9$  K, and  $\theta_2 = 22.5$  K. The dotted curve represents the Curie-Weiss law with  $\mu_B = 3.20 \mu_B$  and  $\theta = 139$  K. The inset shows a schematic view of the dipole moment  $J$ , octupole moment  $T$ , and  $T^0$  which is orthogonal to  $J$  in a  $8g$  CEF ground state.

$g$ -factor, and  $\mu_B$  is the Bohr magneton. Phenomenological dipole-dipole, octupole-octupole, and dipole-octupole interactions are expressed by  $d$ ,  $e$ , and  $d_0$ . We have multiplied the factor  $(g_J \mu_B)^2$  to the interaction terms for convenience. In general, there are other multipole interactions,<sup>34</sup> but the mean field from them cancel out within  $O(H)$  due to the cubic symmetry. Thus, eq. (2.1) does not change, even if we consider other multipole interactions.

Now we diagonalize the mean-field Hamiltonian by introducing the linear combinations of  $J_z$  and  $T_z^0$ :

$$M_z^{(1)} = g_J \mu_B \cos(\cos J_z + \sin T_z^0); \quad (2.2)$$

$$M_z^{(2)} = g_J \mu_B \sin(\sin J_z - \cos T_z^0); \quad (2.3)$$

We have normalized  $M_z^{(1)}$  and  $M_z^{(2)}$  so that the sum of

then is the magnetic moment  $M_z$ , i.e.,  $M_z^{(1)} + M_z^{(2)} = M_z = g_J \mu_B J_z$ . By choosing the parameter  $\alpha$ , we can diagonalize the mean-field Hamiltonian as

$$\begin{aligned} H_{MF} = & H M_z^{(1)} - \frac{1}{2} M_z^{(1)} H M_z^{(1)} i \\ & H M_z^{(2)} - \frac{1}{2} M_z^{(2)} H M_z^{(2)} i; \end{aligned} \quad (2.4)$$

Then, the moment  $M_z^{(1)}$  ( $M_z^{(2)}$ ) follows the Curie-Weiss law with the Curie constant  $C_1 = C \cos^2 \alpha$  ( $C_2 = C \sin^2 \alpha$ ) and the Weiss temperature  $\theta_1 = C_1 / \chi$  ( $\theta_2 = C_2 / \chi$ ), where  $C = C_1 + C_2$  is the Curie constant for a free ion. The following relations for the Weiss temperatures without the parameter  $\alpha$  may be useful:  $\theta_1 + \theta_2 = C / \chi_0$  and  $\theta_1 \theta_2 = C^2 / \chi_0^2$ . Then, the magnetic susceptibility is given by

$$\begin{aligned} \chi &= \frac{C_1}{T - \theta_1} + \frac{C_2}{T - \theta_2} \\ &= C \frac{T + \theta_1 \theta_2}{(T - \theta_1)(T - \theta_2)}; \end{aligned} \quad (2.5)$$

where  $\chi = (C_1 + C_2) / (T - \theta) = C / \chi_0$  is the Weiss temperature, i.e., the magnetic susceptibility follows the Curie-Weiss law  $\chi = C / (T - \theta)$  asymptotically at high temperatures.

As a typical application of the present theory, we compare experimental results of  $\text{UO}_2$ <sup>35,36</sup> and  $\text{NpO}_2$ .<sup>37,39</sup> In  $\text{UO}_2$ , the CEF ground state is a  $t_{2g}$  triplet.<sup>40,41</sup> In this CEF ground state, the  $t_{2g}$  octupole moment is proportional to the dipole moment (see the inset of Fig. 1), and thus, we expect Curie-Weiss behavior. In Fig. 1, we show the temperature dependence of the magnetic susceptibility of  $\text{UO}_2$ , which follows the Curie-Weiss law very well above the antiferromagnetic transition temperature 30 K at least up to 300 K.

In  $\text{NpO}_2$ , the CEF ground state is a  $e_g$  quartet.<sup>21,22</sup> In this CEF ground state, the  $t_{2g}$  octupole moment is linearly independent of the dipole moment (see the inset of Fig. 2), and the present theory is applicable. Indeed, as shown in Fig. 2, the magnetic susceptibility deviates from the Curie-Weiss law below 150 K. This temperature is much higher than the transition temperature 25 K. Moreover, this transition is probably a transition to an ordered state of  $t_{2g}$  octupole moments,<sup>12,17</sup> which do not influence the magnetic susceptibility at least within the mean-field theory. Thus, this deviation of the magnetic susceptibility from the Curie-Weiss law is unlikely to stem from critical phenomena. Rather, the present theory can naturally explain this deviation, as shown in Fig. 2.

### 3. Microscopic Approach

In the previous section, we have briefly reviewed the phenomenological approach to multipole physics, by focusing on the effect of octupole moment on magnetic susceptibility in the paramagnetic phase. In order to obtain a deeper insight into the phenomena concerning multipole degrees of freedom, it is highly requested to proceed to a microscopic theory beyond the phenomenological level. For this purpose, we have recently developed the theory on the basis of a  $j$ - $j$  coupling scheme. After

the explanation of the starting model, we show our microscopic theory for multipole ordering as well as recent development for the treatment of multipole fluctuations.

#### 3.1 Model in a $j$ - $j$ coupling scheme

In order to include the effect of Coulomb interactions, spin-orbit coupling, and CEF potential in  $f$ -electron systems, the LS coupling scheme has been frequently used. However, it is not possible to apply standard quantum-field theoretical technique in the LS coupling scheme, since Wick's theorem does not hold. In order to overcome this difficulty, it has been proposed to construct a microscopic model for  $f$ -electron systems by exploiting the  $j$ - $j$  coupling scheme,<sup>24</sup> where we include first the spin-orbit coupling so as to define the state labeled by the total angular momentum  $j$ . For  $f$  orbitals with angular momentum  $j = 3$ , we immediately obtain an octet with  $j = 7/2$  ( $= 3 + 1/2$ ) and a sextet with  $j = 5/2$  ( $= 3 - 1/2$ ), which are well separated by the spin-orbit interaction. Since the spin-orbit coupling is, at least, in the order of 0.1 eV for  $f$  electrons, it would be enough to take into account the  $j = 5/2$  sextet, when we investigate low-temperature properties of  $f$ -electron compounds in the  $j$ - $j$  coupling scheme.

Then, the Hamiltonian is written as

$$\begin{aligned} H = & \sum_{r,a} t^a a_{r+a}^\dagger a_r + \sum_{r,j} B_j a_{r,j}^\dagger a_r \\ & + (1/2) \sum_{r,j_1,j_2} I_{j_1,j_2} a_{r,j_1}^\dagger a_{r,j_2}^\dagger a_{r,j_2} a_{r,j_1}; \end{aligned} \quad (3.1)$$

where  $a_r$  is the annihilation operator of the  $f$  electron with the  $z$ -component of the total angular momentum  $j = 5/2$  at site  $r$ ,  $a$  denotes a vector connecting nearest-neighbor sites,  $t^a$  is the hopping integral between electron for  $\uparrow$ -state at site  $r + a$  and that for  $\downarrow$ -state at  $r$ ,  $B_j$  is the CEF potential, and the Coulomb integral  $I$  in the  $j$ - $j$  coupling scheme is expressed by using three Racah parameters,  $E_0$ ,  $E_1$ , and  $E_2$ . In this study, we use a simple form for the hopping integrals, i.e., we consider the hopping integrals through the (ff) bonding.

#### 3.2 Multipole ordering

Concerning multipole ordering, we have already reported a microscopic approach by considering correct  $f$ -electron symmetry.<sup>25,26</sup> Thus, in this subsection, we briefly review the method and obtained multipole ordered states.

Let us consider again a cubic system for simplicity. In this case, it is convenient to express  $f$ -electron state in terms of the eigenstates,  $\gamma$  and  $\delta$ , in a cubic CEF potential. Annihilation operators for the  $\delta$  states are given by

$$f_{r,\gamma} = \frac{1}{\sqrt{5}} a_{r,5/2} + \frac{1}{\sqrt{14}} a_{r,3/2}; \quad (3.2a)$$

$$f_{r,\delta} = \frac{1}{\sqrt{5}} a_{r,5/2} - \frac{1}{\sqrt{14}} a_{r,3/2}; \quad (3.2b)$$

and

$$f_{r,\gamma} = a_{r,1/2}; \quad (3.3a)$$

$$f_{r,\delta} = a_{r,1/2}; \quad (3.3b)$$

where we introduce pseudo-spin index ( $\uparrow$  and  $\downarrow$ ) to distinguish the states in each Kramers doublet, while orbital index distinguishes degenerate Kramers doublets. Annihilation operators for the  $\gamma$  states are given by

$$f_{r\uparrow} = \frac{1}{\sqrt{2}} \frac{1}{\sqrt{2}} f_{r5=2} \quad \frac{1}{\sqrt{2}} \frac{1}{\sqrt{2}} f_{r3=2}; \quad (3.4a)$$

$$f_{r\downarrow} = \frac{1}{\sqrt{2}} \frac{1}{\sqrt{2}} f_{r5=2} \quad \frac{1}{\sqrt{2}} \frac{1}{\sqrt{2}} f_{r3=2}; \quad (3.4b)$$

Now we consider the reduction of the Hamiltonian by suppressing  $\gamma$  orbital, in particular, for actinide dioxides. The reasons are as follows: First, we note that the  $\gamma$  wave-function extends along the  $[111]$  direction and other equivalent directions. Since in actinide dioxides, oxygen anions locate in these directions, the  $\gamma$  state should be energetically penalized. Thus, it is expected to be higher than the  $\delta$  level. Second, when we accommodate two, three, and four electrons in the  $\delta$  orbitals, the ground states are  $^5\delta$ ,  $^6\delta^{(2)}$ , and  $^1\delta$ , respectively. In fact, these states have been found as the CEF ground states in  $\text{UO}_2$ ,<sup>40,41</sup>  $\text{NpO}_2$ ,<sup>21,22</sup> and  $\text{PuO}_2$ ,<sup>42,43</sup> respectively. Finally, the CEF excitation energy in  $\text{PuO}_2$  is as large as 123 meV. It is expected to be the same order of magnitude as the splitting between the  $\delta$  and  $\gamma$  levels, and thus we can ignore the  $\gamma$  states at low temperatures.

After transforming the Hamiltonian eq. (3.1) to that in the  $\gamma$ - $\delta$  basis, we simply discard the terms concerning  $\gamma$  orbital. Then, we obtain the  $\delta$ -orbital Hubbard model as

$$H_\delta = \sum_{r,a;\uparrow,\downarrow} \tau_{r,a;\uparrow,\downarrow}^\dagger f_{r+a}^\dagger f_{r,\uparrow,\downarrow} + U \sum_r n_{r\uparrow} n_{r\downarrow} + U^0 \sum_r n_r n_r + J \sum_{r;\uparrow,\downarrow} f_{r,\uparrow}^\dagger f_{r,\downarrow}^\dagger f_{r,\downarrow} f_{r,\uparrow} + J^0 \sum_{r;\uparrow,\downarrow} f_{r,\uparrow}^\dagger f_{r,\downarrow}^\dagger f_{r,\downarrow} f_{r,\uparrow}; \quad (3.5)$$

where  $\tau_{r,a;\uparrow,\downarrow}$  is the hopping integral of an electron with  $(\uparrow, \downarrow)$  at site  $r+a$  to the  $(\uparrow, \downarrow)$  state at  $r$ ,  $n_r = f_{r,\uparrow}^\dagger f_{r,\uparrow} + f_{r,\downarrow}^\dagger f_{r,\downarrow}$ , and  $n_r = n_{r\uparrow} + n_{r\downarrow}$ . The coupling constants  $U$ ,  $U^0$ ,  $J$ , and  $J^0$  denote the intra-orbital, inter-orbital, exchange, and pair-hopping interactions, respectively. These are expressed in terms of Racah parameters, and we obtain the relation  $U = U^0 + J + J^0$ .

In order to estimate interactions among multipoles from the above  $\delta$ -orbital model, we apply the second-order perturbation theory with respect to the hopping integrals of  $\delta$  electrons, in a manner to estimate the superexchange interactions in d-electron systems. Here we note that the hopping integrals are dependent on the pseudo-spin, orbital, and the direction of the hopping due to the f-electron symmetry. Thus, the hopping integrals depend on the lattice structures, and we obtain different multipole interactions for different lattices.

The obtained multipole interaction models have been further analyzed by using the mean-field theory. For a simple cubic lattice, we find a  $_{3g}$  antiferro-quadrupole ordering at a finite temperature, and as we lower the temperature further, we find another transition to a ferro-

magnetic state. For a bcc lattice, we find a  $_{2u}$  antiferro-octupole transition, and a ferromagnetic transition follows it. For an fcc lattice, we analyze the multipole interaction model carefully, since the fcc lattice has geometrical frustration. Thus, we first evaluate multipole correlation functions numerically, and determine relevant interactions to the ground state. Then, we apply mean-field theory to a simplified model including only these relevant interactions, and find a  $_{5u}$  longitudinal antiferro-octupole ordering. This  $_{5u}$  ordering has been proposed for the ordered state of  $\text{NpO}_2$ , in which Np ions form a simple cubic lattice and the CEF ground state is a  $_{8g}$  quartet.

### 3.3 Multipole fluctuations

In the previous subsection, we have reviewed our microscopic theory for multipole ordering. It is considered to be natural to attempt to extend our theory to treat multipole fluctuations. In order to clarify multipole fluctuations from a microscopic viewpoint, again we resort to a method which has been widely used in the d-electron research field. Namely, we apply the fluctuation exchange (FLEX) approximation to the model based on the  $j$ - $j$  coupling scheme.

Although there is no essential difficulty to consider a three-dimensional lattice, here we consider a two-dimensional square lattice for simplicity. By keeping both  $\gamma$  and  $\delta$  orbitals, we rewrite the model Hamiltonian (3.1) as

$$H = \sum_{r,a;\uparrow,\downarrow} \tau_{r,a;\uparrow,\downarrow}^\dagger f_{r+a}^\dagger f_{r,\uparrow,\downarrow} + U \sum_r n_{r\uparrow} n_{r\downarrow} + U^0 \sum_r n_r n_r + J \sum_{r;\uparrow,\downarrow} f_{r,\uparrow}^\dagger f_{r,\downarrow}^\dagger f_{r,\downarrow} f_{r,\uparrow} + J^0 \sum_{r;\uparrow,\downarrow} f_{r,\uparrow}^\dagger f_{r,\downarrow}^\dagger f_{r,\downarrow} f_{r,\uparrow}; \quad (3.6)$$

where  $U = U^0 + E_0$ . Note that for simplicity, we consider the situation in which one of Racah parameters  $E_0$  is finite and the other Racah parameters are zero, since the interactions between them are complicated in general. We believe that characteristics of multipole fluctuations will be grasped even in this simplified model, as long as we treat the f-electron symmetry correctly. In eq. (3.6), we have introduced CEF parameters  $E_0$  and  $^0$ , where  $E_0$  denotes the splitting energy between  $\delta$  orbitals, while  $^0$  indicates the splitting between  $\delta$  and  $\gamma$  orbitals. Note also that  $^0$  is introduced to include partly the effect of a tetragonal CEF potential.

On a square lattice, the hopping integrals of f electrons through (ff) bonding do not depend on the pseudo-spin, and they are given by

$$t^{(a;0)} = \begin{pmatrix} 0 & 1/\sqrt{3} & 1/\sqrt{3} & 0 \\ 1/\sqrt{3} & 0 & 0 & 0 \\ 1/\sqrt{3} & 0 & 0 & 0 \\ 0 & 0 & 0 & 0 \end{pmatrix} t; \quad (3.7)$$

and

$$t^{(0;a)} = \begin{pmatrix} 0 & 1/\sqrt{3} & 1/\sqrt{3} & 0 \\ 1/\sqrt{3} & 0 & 0 & 0 \\ 1/\sqrt{3} & 0 & 0 & 0 \\ 0 & 0 & 0 & 0 \end{pmatrix} t; \quad (3.8)$$

where  $t = 9(\text{ff}) = 28$  and  $a$  is the lattice constant. In this subsection, the energy unit is  $t$  and  $a$  is taken as unity.

In the present model, since the pseudo-spin is a conserved quantity, the Green's function does not depend on  $\sigma$ . Then, the Green's function is represented by  $3 \times 3$  matrix. The Dyson-Gorkov equation in a matrix form is given by

$$G(k) = G^{(0)}(k) + G^{(0)}(k) \Sigma(k) G(k); \quad (3.9)$$

where  $G(k)$  is the Green's function and  $G^{(0)}(k)$  is the non-interacting Green's function. Here we introduced the abbreviation  $k = (k; i_n)$ , where  $k$  is momentum and  $i_n = (2n+1)/T$  is the Matsubara frequency for fermions with an integer  $n$  and a temperature  $T$ . The self-energy  $\Sigma(k)$  is given by

$$\Sigma_{12}(k) = \frac{T}{N} \sum_{q, i_2} G_{12}^{(0)}(k-q) V_{11; 22}(q); \quad (3.10)$$

where  $N$  is the number of lattice sites,  $q = (q; i_m)$ , and  $i_m = 2m/T$  is the Matsubara frequency for bosons. The interaction exchange interaction  $V(q)$  is given by

$$V(q) = \frac{3}{2} V^s(q) + \frac{1}{2} V^c(q); \quad (3.11)$$

where

$$V^s(q) = U^s(q) U^s + \frac{1}{2} U^s(0) (q) U^s + U^s; \quad (3.12)$$

$$V^c(q) = U^c(q) U^c + \frac{1}{2} U^c(0) (q) U^c + U^c; \quad (3.13)$$

The matrices  $U^s$  and  $U^c$  are given by  $U^s_{ij} = U^c_{ij} = U$ ,  $U^s_{00} = U^c_{00} = U^0$ , and  $U^c_{00} = 2U^0$ , where  $U^0 = 6$ , and the other matrix elements are zero. The susceptibilities  $\chi^s(q)$  and  $\chi^c(q)$  are given by

$$\chi^s(q) = \chi^s(0) [1 - U^s(0) \chi^s(q)]^{-1}; \quad (3.14)$$

$$\chi^c(q) = \chi^c(0) [1 + U^c(0) \chi^c(q)]^{-1}; \quad (3.15)$$

where

$$\chi^s_{12; 34}(q) = \frac{T}{N} \sum_k G_{13}(k+q) G_{42}(k); \quad (3.16)$$

We solve the Dyson-Gorkov equation (3.9) numerically.

When we obtain the self-consistent solution, we can also evaluate the multipole response functions. The multipole response functions are given by

$$\langle q; i_n \rangle = \sum_r \sum_0^Z d e^{iq \cdot r + i i_n} \text{Tr} O_r(\beta) O_0(0) i; \quad (3.17)$$

where 0 denotes the origin and  $\beta = 1/T$ . The Heisenberg representation for the operator  $O_r$  is defined as

$$O_r(\beta) = e^{(\beta \hat{N})} O_r e^{-(\beta \hat{N})}; \quad (3.18)$$

where  $\mu$  is the chemical potential and  $\hat{N} = \sum_r n_r$ ,  $n_r$  is the number operator of electrons. The multipole operator at site  $r$  is given by

$$O_r = \sum_{12} f_{r1}^y O_{11; 22} f_{r2}^y; \quad (3.19)$$

The  $6 \times 6$  matrix  $O$  is obtained by using the operator equivalent method for each multipole operator. We normalize  $O$  so that the sum of squares of eigenvalues is unity, for convenience. It is useful to introduce the  $3 \times 3$  matrices  $O^s$  and  $O^c$  which describe spin and charge parts of the matrix  $O$ , respectively:

$$O_{12}^s = \frac{1}{2} \sum_{12} O_{11; 22} \sigma_{12}; \quad (3.20)$$

$$O_{12}^c = \frac{1}{2} \sum_{12} O_{11; 22} \tau_{12}; \quad (3.21)$$

where  $\sigma$  and  $\tau$  are the Pauli matrices. In the FLEX approximation without the vertex corrections, the multipole response functions are given by

$$\chi(q) = \sum_{1234} \chi_{12; 34}^s(q) O_{21}^s O_{34}^s + \chi_{12; 34}^c(q) O_{21}^c O_{34}^c; \quad (3.22)$$

In the following, we show results for a  $32 \times 32$  lattice, at  $U = U^0 = 4t$ ,  $T = 0.02t$ , and  $\mu = 0$ . The number of electrons per site is one. In the calculation, we use 1024 Matsubara frequencies. In Figs. 3 and 4, we show the multipole response functions for  $\beta = 0$  and  $\beta = 2t$ , respectively. Even for  $\mu = 0$ , the number  $n_r$  of electrons in the  $\gamma$  orbital is almost zero for these model parameters, since the  $\gamma$  orbital in the present model on a square lattice is localized and the system cannot gain kinetic energy by increasing the number of electrons in the  $\gamma$  orbital. Thus, for these parameter sets, the present model is virtually equivalent to the  $s_g$  model, which has been already studied by Takimoto et al.<sup>44</sup> The antiferromagnetic fluctuations pointed out by Takimoto et al. can be classified into multipole fluctuations in  $f$ -electron systems as shown in Figs. 3 and 4.

For  $\beta = 0$ , there is no significant structures in the multipole response functions, as shown in Figs. 3(b) and (d). By changing the CEF parameter  $\Delta$ , the Fermi surface changes [see Figs. 3(a) and 4(a)], and the fluctuations around the M point  $q = (\pi; \pi)$  become significant. Then, the multipole response functions for the  $4u$  dipole,  $4u$  octupole, and  $5u$  octupole moments enhance around the M point. On the other hand, the other multipole response functions do not enhance significantly. The  $4u$  dipole and octupole components around at M point are naturally considered to compose antiferromagnetic fluctuations, but the enhancement of  $5u$  octupole fluctuation is quite peculiar. It seems to be interesting to seek for anomalous component of Cooper pairing induced by  $5u$  octupole fluctuation. This is one of future problems.

#### 4. Summary

In this paper, we have discussed three topics on multipoles in  $f$ -electron systems. First, we have explained effects of octupole moments on the magnetic susceptibility in the paramagnetic phase of a cubic system. When the  $4u$  octupole moment is independent of the dipole moment as in the  $s_g$  CEF ground state, there are interactions between the  $4u$  octupole and dipole moments in

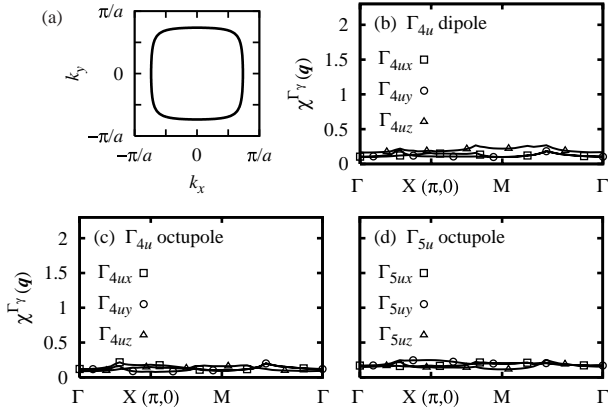


Fig. 3. Fermi surface and multipole response functions for  $U = U^0 = 0$ . (a) Fermi surface for  $U = U^0 = 0$ . (b)  $4u$  dipole response functions. (c)  $4u$  octupole response functions. (d)  $5u$  octupole response functions.

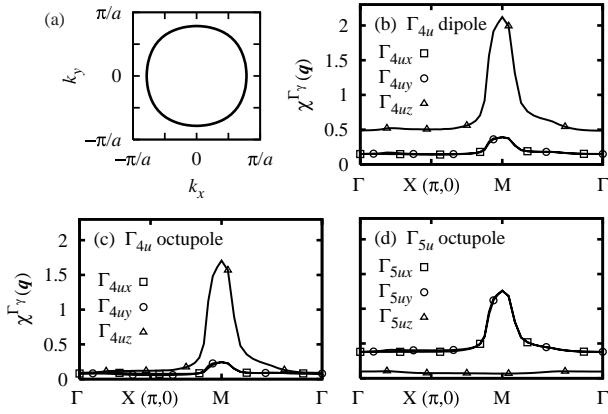


Fig. 4. Fermi surface and multipole response functions for  $U = 2t$ . (a) Fermi surface for  $U = U^0 = 0$ . (b)  $4u$  dipole response functions. (c)  $4u$  octupole response functions. (d)  $5u$  octupole response functions.

general. Then, the magnetic susceptibility deviates from the Curie-Weiss law even within the mean-field theory. By considering such effects of octupoles, we can naturally understand the difference between the temperature dependence of the magnetic susceptibilities of  $UO_2$  and  $NpO_2$ .

Second, we have derived multipole interactions from the microscopic model based on the  $j$ - $j$  coupling scheme. Then, we have found several multipole ordered states, depending on the type of lattice structure. In particular, for an fcc lattice, we find the  $5u$  longitudinal triple- $q$  antiferro-octupole ordering, which has been proposed for  $NpO_2$  phenomenologically.

Finally, we have evaluated multipole response functions by applying the FLEX approximations to the  $j = 5/2$  model including both the  $8$  and  $7$  orbitals. In f-electron systems, the complex fluctuations, which are composed of spin, charge, and orbital degrees of freedom, can be classified into multipole fluctuations. We will study such multipole fluctuations by changing the CEF parameters, dimensionality, and Coulomb interactions, in order to clarify superconductivity relating to the

multipole fluctuations in the near future.

#### Acknowledgements

We are grateful to T. Takimoto for useful comments and discussions on the FLEX approximation. We also thank D. Aoki and Y. Homma for providing us very recent experimental results of the magnetic susceptibilities in  $NpO_2$  and  $UO_2$ , respectively, before publication. We are also grateful to R. H. Heuser, S. Kambe, N. Metoki, A. Nakamura, H. Onishi, Y. Tokunaga, R. E. Walstedt, and H. Yasuoka for fruitful discussions. One of the authors (K.K.) is supported by the REMEIR research Resources of Japan Atomic Energy Research Institute. The other author (T.H.) is supported by a Grants-in-Aid for Scientific Research in Priority Areas "Skutterudites" under the contract No. 16037217 from the Ministry of Education, Culture, Sports, Science, and Technology of Japan. T.H. is also supported by a Grant-in-Aid for Scientific Research (C) (2) under the contract No. 50211496 from Japan Society for the Promotion of Science.

- 1) Proceedings of the International Conference on Strongly Correlated Electrons with Orbital Degrees of Freedom, J. Phys. Soc. Jpn. 71 (Suppl.) (2001).
- 2) P. Santini, R. Lemanski and P. Erdos: Adv. Phys. 48 (1999) 537.
- 3) O. Sakai, R. Shiina, H. Shiba and P. Thalmeier: J. Phys. Soc. Jpn. 66 (1997) 3005.
- 4) Y. Kuramoto and H. Kusunose: J. Phys. Soc. Jpn. 69 (2000) 671.
- 5) H. Kusunose and Y. Kuramoto: J. Phys. Soc. Jpn. 70 (2001) 1751.
- 6) K. Kubo and Y. Kuramoto: J. Phys. Soc. Jpn. 72 (2003) 1859.
- 7) K. Kubo and Y. Kuramoto: J. Phys. Soc. Jpn. 73 (2004) 216.
- 8) D. Mannix, Y. Tanaka, D. Carbone, N. Bernhoeft and S. Kuniti: Phys. Rev. Lett. 95 (2005) 117206.
- 9) H. Kusunose and Y. Kuramoto: cond-mat/0509284.
- 10) P. Santini and G. Amoretti: Phys. Rev. Lett. 85 (2000) 2188.
- 11) P. Santini and G. Amoretti: J. Phys. Soc. Jpn. 71 (Suppl.) (2002) 11.
- 12) J. A. Paixao, C. Delfs, M. J. Long, R. Cacioppo, P. Santini, N. Bernhoeft, J. Rebizant and G. H. Lander: Phys. Rev. Lett. 89 (2002) 187202.
- 13) R. Cacioppo, J. A. Paixao, C. Delfs, M. J. Long, P. Santini, N. Bernhoeft, J. Rebizant and G. H. Lander: J. Phys.: Condens. Matter 15 (2003) S2287.
- 14) S. W. Lovesey, E. Balcar, C. Delfs, G. van der Laan, D. S. Sivia and U. Staub: J. Phys.: Condens. Matter 15 (2003) 4511.
- 15) A. Kiss and P. Fazekas: Phys. Rev. B 68 (2003) 174425.
- 16) Y. Tokunaga, Y. Homma, S. Kambe, D. Aoki, H. Sakai, E. Yamamoto, A. Nakamura, Y. Shiokawa, R. E. Walstedt and H. Yasuoka: Phys. Rev. Lett. 94 (2005) 137209.
- 17) O. Sakai, R. Shiina and H. Shiba: J. Phys. Soc. Jpn. 74 (2005) 457.
- 18) E. Zimigib, B. Hillebrands, S. Blumentroder, G. Guntherodt, M. Loewenhaupt, J. M. Carpenter, K. W. Inzer and Z. Fisk: Phys. Rev. B 30 (1984) 4052.
- 19) N. Sato, S. Kuniti, I. Oguro, T. Komatsubara and T. Kasuya: J. Phys. Soc. Jpn. 53 (1984) 3967.
- 20) B. Luthi, S. Blumentroder, B. Hillebrands, E. Zimigib, G. Guntherodt and K. W. Inzer: Z. Phys. B 58 (1984) 31.
- 21) J. M. Fournier, A. B. Laise, G. Amoretti, R. Cacioppo, J. Larroque, M. T. Hutchings, R. Osborn and A. D. Taylor: Phys. Rev. B 43 (1991) 1142.
- 22) G. Amoretti, A. B. Laise, R. Cacioppo, D. Di Cola, J. M. Fournier, M. T. Hutchings, G. H. Lander, R. Osborn, A. Severing and A. D. Taylor: J. Phys.: Condens. Matter 4 (1992) 3459.

- 23) R. Shiina, H. Shiba and P. Thalmeier: J. Phys. Soc. Jpn. 66 (1997) 1741.
- 24) T. Hotta and K. Ueda: Phys. Rev. B 67 (2003) 104518.
- 25) K. Kubo and T. Hotta: Phys. Rev. B 71 (2005) 140404(R).
- 26) K. Kubo and T. Hotta: Phys. Rev. B 72 (2005) 144401.
- 27) E. D. Bauer, N. A. Frederick, P.-C. Ho, V. S. Zapf and M. B. Maple: Phys. Rev. B 65 (2002) 100506(R).
- 28) K. Miyake, H. Kohno and H. Harima: J. Phys.: Condens. Matter 15 (2003) L275.
- 29) T. Goto, Y. Nemoto, K. Sakai, T. Yamaguchi, M. Akatsu, T. Yanagisawa, H. Hazama, K. Onuki, H. Sugawara and H. Sato: Phys. Rev. B 69 (2004) 180511(R).
- 30) K. Kuwahara, K. Iwasa, M. Kohgi, K. Kaneko, N. Metoki, S. Raymond, M. A. Measson, J. Flouquet, H. Sugawara, Y. Aoki and H. Sato: Phys. Rev. Lett. 95 (2005) 107003.
- 31) Y. Aoki, T. Namiki, S. Ohsaki, S. R. Saha, H. Sugawara and H. Sato: J. Phys. Soc. Jpn. 71 (2002) 2098.
- 32) M. Kohgi, K. Iwasa, M. Nakajima, N. Metoki, S. Arai, N. Bernhoeft, J.-M. Mignot, A. Gukasov, H. Sato, Y. Aoki and H. Sugawara: J. Phys. Soc. Jpn. 72 (2003) 1002.
- 33) K. Kubo and T. Hotta: submitted to J. Phys. Soc. Jpn. (cond-mat/0509788).
- 34) O. Sakai, R. Shiina and H. Shiba: J. Phys. Soc. Jpn. 72 (2003) 1534.
- 35) A. A. Abrikosov and I. E. Gorkunov: Phys. Rev. 108 (1957) 948.
- 36) Y. Homma: private communication.
- 37) J. W. Ross and D. J. Lam: J. Appl. Phys. 38 (1967) 1451.
- 38) P. Erdos, G. Solt, Z. Zolnierak, A. Blaise and J. M. Fournier: Physica 102B (1980) 164.
- 39) D. Aoki: private communication.
- 40) S. Kem, C.-K. Loong and G. H. Lander: Phys. Rev. B 32 (1985) 3051.
- 41) G. Amoretti, A. Blaise, R. Cacioppo, J. M. Fournier, M. T. Hutchings, R. Osborn and A. D. Taylor: Phys. Rev. B 40 (1989) 1856.
- 42) S. Kem, C.-K. Loong, G. L. Goodman, B. Cort and G. H. Lander: J. Phys.: Condens. Matter 2 (1990) 1933.
- 43) S. Kem, R. A. Robinson, H. Nakotte, G. H. Lander, B. Cort, P. Watson and F. A. Vigliani: Phys. Rev. B 59 (1999) 104.
- 44) T. Takimoto, T. Hotta and K. Ueda: Phys. Rev. B 69 (2004) 104504.