

Two-dimensional tetramer-cuprate $\text{Na}_5\text{RbCu}_4(\text{AsO}_4)_4\text{Cl}_2$: phase transitions and AFM order as seen by ^{87}Rb NMR

R. Stem^a, I. Heinmaa^a, A. Kriisa^a, E. Joon^a, S. Viia^a, J. Clayhold^b,
M. Karttunen^c, X. Mo^c, W. Queen^c, and S.-J. Wu^c

^a NICPB, Akadeemia tee 23, EE12618 Tallinn, Estonia

^b Physics Department, Miami University, Oxford, OH 45056, USA

^c Department of Chemistry, Clemson University, Clemson, SC 29634, USA

Abstract

We report the ^{87}Rb nuclear magnetic resonance (NMR) results in a recently synthesized $\text{Na}_5\text{RbCu}_4(\text{AsO}_4)_4\text{Cl}_2$. This complex novel two-dimensional (2D) cuprate is an unique magnetic material, which contains layers of coupled Cu_4O_4 tetramers. In zero applied magnetic field, it orders antiferromagnetically via a second-order low-entropy phase transition at $T_N = 15(1)$ K. We characterise the ordered state by ^{87}Rb NMR, and suggest for it a non-collinear rather than collinear arrangement of spins. We discuss the properties of Rb nuclear site and point out the new structural phase transition(s) around 74 K and 110 K.

Key words: tetramer, cuprate, NMR, antiferromagnetic order
PACS: 71.10.Hf; 71.27.+a; 75.30.Mb

The occurrence of high-temperature superconductivity in doped spin-1=2 square planar antiferromagnets has stimulated the search for new families of low-dimensional magnetic materials. We have studied the compound $\text{Na}_5\text{RbCu}_4(\text{AsO}_4)_4\text{Cl}_2$, whose spin exchange interactions are confined to 2D layers. The compound has a layered structure comprised of square Cu_4O_4 tetramers [1]. The Cu ions are divalent and the system behaves as a low-dimensional $S = 1/2$ antiferromagnet. Spin exchange in $\text{Na}_5\text{RbCu}_4(\text{AsO}_4)_4\text{Cl}_2$ appears to be quasi-2D and nonfrustrated [2].

In this report we present ^{87}Rb NMR results of the compound. The experiments are performed in $B_0 = 8.45$ T and 14.1 T magnetic field in a temperature (T) range $4 \text{ K} < T < 300 \text{ K}$. A single crystal of $\text{Na}_5\text{RbCu}_4(\text{AsO}_4)_4\text{Cl}_2$ (1 × 1 × 0.2 mm) was used.

The NMR spectra of ^{87}Rb ($I = \frac{3}{2}$) central transition ($\frac{1}{2}, \frac{1}{2}$) in Fig. 1 (left) for the orientation of a crystal $B_0 \parallel b$ show a direct observation of the tran-

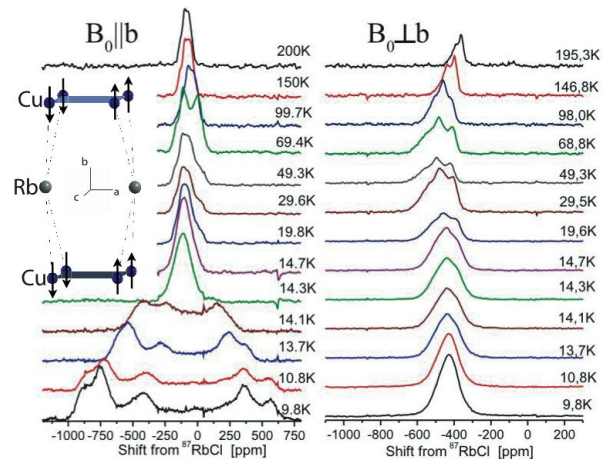


Fig. 1. The T-dependence of ^{87}Rb central transition NMR spectra in $B_0 = 14.1$ T external field $B_0 \parallel b$ (left) and (b) $B_0 \perp b$ (right). Inset shows the position of Rb ions relative to Cu tetramers.

Corresponding author stem@kb.ee, tel: +372 513 22 88.

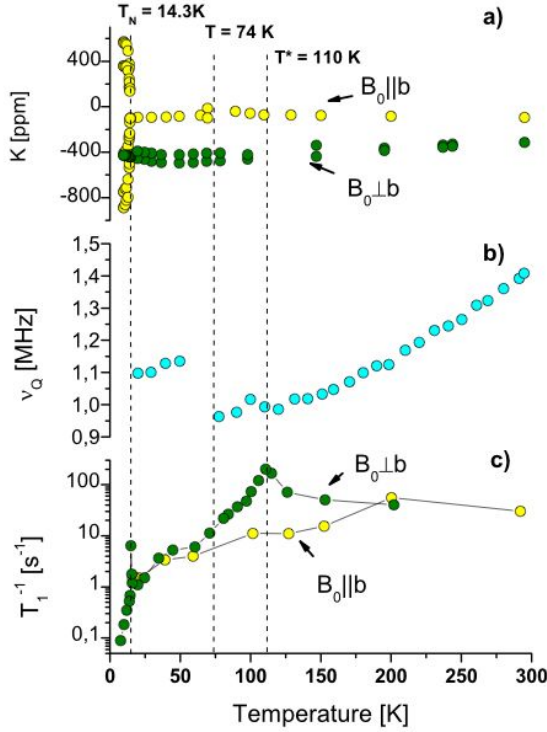


Fig. 2. The T -dependence of (a) the magnetic hyperfine shift K for $B_0 \parallel b$ -axis ($B_0 = 14.1$ T), (b) the quadrupolar coupling parameter $\nu_Q = e^2qQ/2h$, and (c) spin-lattice relaxation rate T_1^{-1} ($B_0 = 8.45$ T). Dotted lines note the T_N and the high T transitions at 74 K and 110 K.

sition into the AFM ordered phase below 14.3 K. The splitting of the resonance line corresponds to the local hyperfine field of 8 mT due to the static magnetic moments at the tetramers coppers. The spectra in Fig. 1 (right) for $B_0 \parallel b$ orientation do not show any measurable splitting in this T -range. From such orientation dependence one can conclude that in the AFM ordered phase the magnetic moments are aligned along the b -axis of the crystal, i.e. perpendicular to the tetramer plane. Rb sites in the lattice neighbor to four nearest coppers belonging to two sides of the two adjacent (along b) tetramers. These four coppers need to create a hyperfine field at Rb site in b -direction (or in opposite direction). A possible arrangement for that would be if the two magnetic moments of the tetramer sides along c axis have " " or " " alignment (insert of Fig. 1). That peculiar magnetic structure may result from strongly different superexchange couplings J_a and J_c between the coppers of a given tetramer [2].

A closer look to the spectra in AFM phase indicates that the real magnetic structure of the compound is not simple at all. The complicated double-horn line shape with continuum of finite intensity between the peaks is

a signature of an incommensurate structure. Generally, the NMR spectrum represents the distribution of magnetic hyperfine field at nuclei parallel to the external field. In a non-collinear incommensurate spin structure the hyperfine field should have a modulation, resulting in the continuum. The peaks in the spectra would then correspond to the extrema of that modulation.

The separation between peaks in the spectrum in the ordered phase grows steeply. We fitted peak shift to a power law $(T_N - T)^{-\alpha}$ and obtained a critical exponent $\alpha = 0.25 \pm 0.05$ and the transition temperature $T_N = 14.8$ K (14.3 K) for $B_0 = 8.45$ T (14.1 T).

The T -dependence of the magnetic hyperfine shift K , the quadrupolar coupling value $\nu_Q = e^2qQ/2h$, and the spin-lattice relaxation rate T_1^{-1} are given in Fig. 2. Panel (a) shows a weak T -dependence of K above $T = T_N$ in both orientations. The splitting of the line in $B_0 \parallel b$ direction reflects a small anisotropy of K in ac -plane. Below $T = 74$ K the resonance lines in both directions show remarkable distortions which we attribute to the change of a local symmetry at Rb site. A clear indication of a symmetry change is the discontinuity of the T -dependence of the quadrupolar coupling constant around that T (Panel (b)). Since ν_Q describes local electric field gradient, it is highly sensitive to structural changes. The T -dependence of spin-lattice relaxation rate T_1^{-1} of ^{87}Rb central transition shows also a Neel temperature at $T_N = 14.8$ K and a broad peak around $T = 110$ K for $B_0 \parallel b$ (Panel (c)). Similar T -dependence of T_1^{-1} was measured in 14.1 T field. The relaxation is caused by local fluctuating magnetic fields that have to be aligned perpendicular to the applied field to see the transitions. The same location of the maximum at 110 K in both fields suggests strongly that not the fluctuation spectrum but the crystal structure is changing at this T . We do not know the resulting low- T crystal structure in details yet, but the new structure may have crucial implications for the distinct magnetic order below T_N .

In conclusion, using ^{87}Rb NMR we have shown the antiferromagnetic ordering and two high- T phase transitions in $\text{Na}_5\text{RbCu}_4(\text{AsO}_4)\text{Cl}_2$. The studies to clarify the nature of those phase transitions using NMR of ^{23}Na , ^{35}Cl , and $^{63/65}\text{Cu}$ are currently in progress.

This work was supported by the Estonian Science Foundation and by the National Science Foundation (NSF) Grants DMR-0077321 and 0322905.

References

- [1] S.-J. Hwu et al, J. Am. Chem. Soc. 124 (2002) 12404.
- [2] J.A. Clayhold et al, Phys. Rev. B. 66 (2002) 052403.