Interface Instability in Shear-Banding Flow

S. Lerouge

Laboratoire M atieres et System es Complexes, Universite Paris 7 2 place Jussieu, 75251 Paris Cedex 05

M . Argentina Institut Non Lineaire, Universite de Nice Sophia Antipolis, UMR 6618 CNRS 1361 route des Lucioles 06560 Valbonne – France

J.P. Decruppe

Laboratoire de Physique des Milieux Denses, Universite de Metz 1 bvd Arago, 57078 Metz Cedex 03 (Dated: March 23, 2024)

We report on the spatio-tem poral dynam ics of the interface in shear-banding ow of a worm like m icellar system (cetyltrim ethylam monium brom ide and sodium nitrate in water) during a start-up experim ent. U sing the scattering properties of the induced structures, we dem onstrate the existence of an instability of the interface between bands along the vorticity direction. D i erent regim es of spatio-tem poral dynam ics of the interface are indenti ed along the stress plateau. We build a model based on the ow sym etry which qualitatively describes the observed patterns.

PACS num bers: 47.50.-d, 47.20.-k,83.60.-a, 05.45.-a, 83.85.-Ei

M any complex uids of various microstructures strongly exhibit non linear properties under simple shear ows. W hen the characteristic times of the ow ('1=_) and of the system are similar, the system is liable to undergo instabilities and ow-induced phase transitions. Such coupling between ow and structure has been observed for example, in worm like micellar solutions [1], lyotropic lam ellar phases [2], telechelic polymer networks [3], soft glassy materials [4] or foam s [5].

For a system showing a shear-thinning behaviour, the mechanical signature, in the measured ow curve (=f(_)), of this type of phenomena is the stress plateau separating low and high viscosity branches. This stress plateau is at the origin of a shear-banding transition from a ow at rst hom ogeneous towards a stationary state where two layers supporting di erent shear rates coexist. A change of the applied shear rate only a ects the relative proportion of each layer, the width of the induced band increasing linearly with the macroscopic shear rate [6].

A m ong the com plex uids with stress plateau, the system s of reversible giant m icelles have been the object of the m ost intensive surveys (see [1] for a review). Very recently, the use of dynam ic light scattering to m easure velocity pro les brought con m ation of the very sim – ple shear-banding scenario previously m entioned for the widely studied CPC I/N aSal solution [7]. However, the authors m ention the existence of tem poral uctuations in the highly sheared band. M ore com plex pictures have also em erged with the developm ent of tim e-and spatiallyresolved techniques such as rapid nuclear m agnetic resonance (NMR) velocimetry [8] and ultrasonic velocimetry [9], with for example, the observation of periodic or quasirandom oscillations of the interface position driven by wall slip. M oreover, the ow birefringence, technique sensitive to m olecular alignment, revealed complex kinetics of banding formation and strongly di ering banding organizations from one sample to another [10].

Som e of these behaviors are reproduced, at least qualitatively, by several theoretical works, which predict uctuating or chaotic ows, taking into account a coupling between ow and microstruture via the concentration or the micellar length [11]. They also motivated a recent theoretical work, in which the author, using the nonlocal Johnson-Segalm an model, studies the stability of planar shear banded ow with respect to small perturbations with wavevectors in the interfacial plane [12]. An interfacial instability is predicted in the plateau domain for almost all shear rates, the interface pro le being then modulated by a wave with wavevectors con ned along the ow direction. In the present letter, we report on the form ation kinetics of the banding structure and follow particularly the spatio-tem poral dynam ics of the interface between bands for a sam ple of cetyltrim ethylam m onium brom ide (CTAB) and sodium nitrate (NaNO3) [13]. D irect visualizations of the gap of the C ouette cell in the plane vorticity/velocity gradient and variations of the shear stress are recorded simultaneouly during a startup experiment. Using the scattering properties of the induced structures, we show that the interface between the two bands becom es unstable with wavevector in the vorticity direction. D i erent patterns of spatio-tem poral dynam ics of the interface are observed, depending on the applied shear rate. Using argum ents based on the sym metry of the ow, we show that the interface position is

Corresponding author ; Electronic address: slerouge@ccr.jussieu.fr

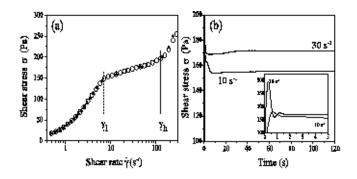


FIG.1: (a) Steady state ow curves obtained under controlled strain rate (, 250s per data point) and controlled shear stress (N, 48s per data point). The dotted lines point out the bounded characteristic values of _ and associated with the stress plateau. (b) Variation of the shear stress versus time after the onset of ow for applied shear rates _ = $10s^1$ and _ = $30 s^1$. The inset shows the response on a shorter time scale.

described by a generic am plitude equation of K uram oto-Sivashinsky type, which reproduces qualitatively the observed patterns [14, 15].

The worm like micellar system chosen in this work is m ade of CTAB at 11% wt. and NaNO $_3$ (0.405 M) in distilled water at T = 30 C.At this concentration, far from the transition concentration towards an orientated nematic phase at rest, the micelles form a highly entangled network. The linear viscoelastic behavior of the solution is Maxwellian with a plateau modulus G_0 = 238 7Pa and a term inal relaxation time $_{\rm R} = 0.15$ 0:02s. The rheological measurements are performed on a stress-controlled rheom eter (Physica MCR 500) working in strain-controlled mode. A home-build transparent Couette cell with a height of 40 mm is used for the experiments. The inner rotating cylinder has a radius $R_1 = 13:33 \text{ mm}$ providing a gap thickness e = 1:13 mm. The C ouette cell is designed in a way which allows the direct observation of the gap in the plane vorticity/velocity gradient. W e form a thin laser sheet in that plane with a cylindrical lens and record the scattered intensity at 90 with a CCD camera.

The steady-state rheological behavior of our sample in strain- and stress-controlled modes of the rheometer is drawn in the sem i-logarithm ic plot in Fig 1.a. The ow curve is composed of two increasing branches separated by a stress plateau extending from $_{-1} = 7$ 0.5s¹ to $_{-h} = 140$ 10s¹, characteristic of the emergence of heterogeneous ow of shear-banding type. This plateau presents a signi cant positive slope partly due to the non hom ogeneity of the C ouette geometry. In fact, the curvature e ects, analysed as in [7] do not allow for a complete explaination of the slope. C oncentration e ects between shear bands could also make the plateau steeper [16].

W e shall now focus on the kinetics of form ation of the heterogeneous ow. At t= 0, a shear rate is applied to the sam ple initially at rest and the evolution of the shear stress and direct observations of the gap of the C ouette cell in the plane vorticity/velocity gradient are recorded simultaneously as function of time until steady-state is achieved. Fig. 1 b illustrates the variations with time of the shear stress for two shear rates associated with the plateau region (____l). The stress (t) follows the generic behavior observed on various sem i-dilute m icellar systems [10, 17] undergoing shear-banding transition induced by the ow : an overshoot at short times, then a slow sigm oidal relaxation (_ = $10s^{1}$) or dam ped oscillations (_ = $30s^{1}$)) and nally a sm all undershoot that continues the transient response tow ards the stationnary state.

Let us correlate such an evolution with the direct visualizations of the gap (Fig. 2). The sample at rest does not present any particular scattering properties as observed on the rst photo (t = 0) where the gap appears dark. Just after the inception of ow, the solution becomes turbid over the entire gap and strongly scatters the incident light in all directions. This strong increase of the turbidity is associated with the elastic overshoot in the shear stress response (see photo 1). The entangled m icellar network is strongly stretched leading to concentration uctuations. Then, the liquid becomes transparent again near the xed wall of the Couette cell (photo 2), this phenom enom correponding to the rapid relaxation of the stress overshoot. Let us note how ever, that the turbidity does not relax all over the gap since a scattering band persists against the rotating inner cylinder, the interface between bands being di used (photo 4). The crucial point here, is that the induced structures are nucleated during the stress overshoot and in all the gap of the cell so as to the induced band is already form ed just after the stress overshoot. The enhancem ent of the concentration uctuations acts as the precursor of the transition. Both bands have di ering optical properties: the induced band is very turbid, indicating that it contains structures of m esoscopic size which scatters the light in all directions. Such a di erence allow sus to per ectly distinguish the interface between bands. Let us note that the turbidity is associated with birefringence banding. From t = 10s the interface becom es clearly sharp (photo 5). This lasts for about t = 20s (photo 6) and then we observe a completely unexpected behavior: the sharp interface between the two bands begins to destabilize itself along the vorticity axis. The instability grows up to t = 29s (photo 9), namely when the stress undershoot occurs in the transient response. Beyond, the interface seem s to adopt a stationnary periodic pro le with a wellde ned characteristic wavelength. An extension of the

eld of observation show s that this ripple of the interface spreads over all the height of the inner cylinder. At the edges of the cylinder, the ripple presents a m inim um of am plitude.

This destabilization process of the interface occurs in all the plateau region of the ow curve. In a general way, the wavelength and the amplitude of the instability clearly increase with the applied shear rate, except when _ approaches _h where they dim inish again. Let

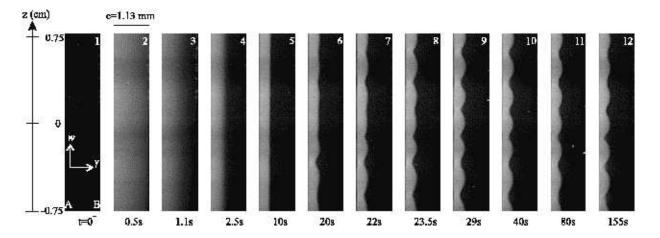


FIG.2: Views of the gap in the plane velocity gradient/vorticity taken out from the recording of the scattered intensity at di erent instants during the form ation of the induced band. The sam ple is subjected to a shear rate of 30s¹. The letters A and B indicate respectively the inner and outer cylinders of the Couette device. Due to the com prom ise between the spatial resolution and the size of the eld of observation, this latter is limited to 1.5cm in height and centered at halfway of the cell.

us note that above $__h$, the gap is completely led by the induced band. Using a simple procedure of im age analysis, we detect the interface pro le on each frame. W e represent in gray levels, the amplitude of the interface as function of time and space coordinate along the vorticity axis as illustrated in Fig.3.a and b., where we sum marized the complete behavior of the interface on spatio-tem poral diagram s for $_ = 10s^{1}$ and $_ = 30s^{1}$ respectively. In rst approximation, we adjust the interface pro le by a sinuso dal function in order to estim ate the wavelength and the amplitude of the instability. The observed patterns are very di erent for both the applied shear rates. At 10s¹, the deform ation of the interface occurs around t = 20 s and the waves form ed seem to propagate along the z-coordinate, alternatively towards the top and the bottom of the cylinder, interacting in a complex scenario. We nd for the amplitude and the mean wavelength, respectively 0.007 0.003mm and 0.4 0.1mm. The evolution at $= 30 \text{ s}^1$ appears simplier since there is no propagation in this case. The interface keeps a spatially stable pro le in course of tim e with an amplitude of 0.05 0.01mm and a wavelength of 2.4 0.02mm namely, more than two times the gap width. W e checked by increasing the duration of the experim ent up to 40 m inutes that there is no coarsening between the "dom ains" (black and white) at very long times. A closer inspection of the diagram reveals the existence of tim e-periodic oscillations. W e can distinguish two di erent frequencies: the st one, in the dark zones, is due to the mechanical imperfection intrinsic to the rheometer; the second one, which is visible in the clear zones, is lower and results from the superposition of the default of coaxiality of the cell with a "beat" of the minimum of am plitude of waves. In other words, the am plitude of the interface instability oscillates with time. This could be due, am ong others, to tridim ensional ow or to destabilization of the interface in the velocity direction [12].

M oreover, from the asymptotic behavior we are able to deduce the proportion of the induced "phase" h: the integration of the interface pro le gives $h = 0.29 \quad 0.02$. The same calculus for each photo from t = 10s gives the same relative proportion. A coording to the sim plest shear-banding scenario described by Cates's theory [6] and recently observed by Salm on et al [7], the width of the induced band increases linearly with the applied shear rate. In our case, the proportion of the induced band com puted from the lever rule seems to be underestim ated : for $_$ = 10s¹ and $_$ = 30s¹, we nd respectively $_{h} = 0.02 \quad 0.01$ and $_{h} = 0.18 \quad 0.02$, values to be compared to 0:04 0:01 and 0:30 0:02. Processing of ultrasonic data on this sam ple is in progress in order to properly correlate the optical response and the local structure of the ow.

We would like to propose a simple model that cap-

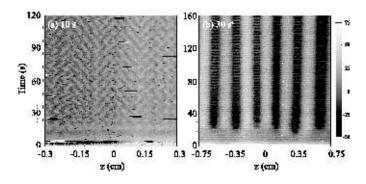


FIG.3: Spatio-tem poralevolution of the interface am plitude for $_= 10s^{1}$ (a) and $_= 30s^{1}$ (b) on a time scale which provides both kinetics of destabilization of the interface and the asymptotic behavior. The z-coordinate gives the spatial position along the vorticity axis. A linear gray scale (in m) is used, the black and white regions being associated respectively with m inim a and m axim a of the interface am plitude.

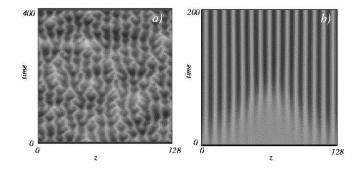


FIG. 4: Spatio-tem poral evolution of the interface position p obtained by num erical simulation of the model 1 with (a) = 0.07 (b) = 0.2.

tures the asymptotic dynamics of the uid ow. As stated previously, when the uid is forced with a shear rate that is inside the plateau region, the system spontaneously coarse-graines into two zones separating two di erent shear rates. Here, as in lubrication approxim ation for new tonian uids, gradients with respect of the transversal coordinate y are higher than those with z the coordinate tangential to the cylinder axis. This length scales di erence yields that the dynamics with respect to z coordinate are slow, and will consequently drive the interface position for asymptotic times. Let us note p the position of the interface separating these two zones. Tem poralevolution of the front must re ect the sym metry of the experiment z ! z, so only term s including spatial derivatives like $(l_{zz}p, (l_{zzzz}p))^2$ are allowed at lowest order. The system is not invariant with respect to translation in the y direction, and the equation must present the broken symmetry : p ! p + constant. The asymptotic dynamics of the interface are given by:

$$\theta_t p = (1 \ p) \ \theta_{zz} p \ \theta_{zzzz} p + (\theta_z p)^2 : (1)$$

Equation 1 is written in non dimensional variables, and introduces the controlparameter in which all the physical attributes of the experiment have been set. The rst term of the rhs of the equation 1 just states that if the interface has a stationary location. Since the uid is set into negative viscosity inside the plateau, the second term is a di usion term with a negative sign. The next term, $\ell_{zzzz}p$ is a linear saturating term. The last term is the

rst non linear term that respects the symmetry at that order. This equation is known as the dam ped K uram oto-Sivashinsky equation [18]. W hen > 1=4 the solution p = 1 is a linearly stable solution. For < 1=4, the perturbed interface becom es oscillatory in space, with a well de ned wave-length. Finally, for < 0:078, the dynam ics are chaotic [18], see for example Fig. 4 (a). When = 0, equation 1 reduces to the usual Kuram oto-Sivashinky equation, and exhibits complex spatio-tem poral behavior that is used to describe phase turbulence [19]. The existence of stationary periodic pattern observed in the experim ent is related to the very low aspect ratio of the Couette cell. Let us nally note that, in the model, when the interface becom es unstable, its position is system atically shifted due to the non-linear term $(\mathfrak{e}_{x}\mathfrak{p})^{2}$. This term has the same e ect as the curvature of the Couette geom etry. This means that the instability of the interface could also explain the "additional" slope of the plateau. In sum m ary, our rheo-optical study of the interfacial dynam ics in shear-banding ow reveals the existence of a destabilization process of the interface between bands with wavevector in the vorticity direction. This observation suggests that the ow eld is three dimensional with the presence of recirculations. We show that there are di erent spatio-tem poraldynam ics of the interface along the stress plateau, with chaotic events at low shear rates, and spatially stable oscillatory behavior at higher strain rates. The physical origin of the destabilization process is still to be determ ined ; how ever, it could partly explain some uctuating behaviors highlighted recently in shear banded ows [7, 8, 9] and it emphasizes the necessity for a complete spatio-tem poral description of the ow and the microstructural organization in the di erent planes. Further, we buid a model equation 1 based upon symetry arguments which described qualitatively the observed complex patterns. This model equation can also be derived using perturbation theory. To this end, it is necessary to adopt a model for the rheology of the uid [12, 20]. It is a computation that we did using the model [20] and we will report it elsewhere [21] with the com plete exploration of the stress plateau.

The authors are grateful to G . G regoire, O . G re er, O . Cardoso, JF . Berret, and JL . Counord for the development of the transparent C ouette cell.

- [1] J.F.Berret.Cond.Matt., 0406681, 2005 and reftherein.
- [2] J.B. Salm on, S.M anneville, and A.Colin. Phys. Rev. E, 68:051503, 2003; J.B. Salm on, S.M anneville, and A.Colin. Phys. Rev. E, 68:051504, 2003.
- [3] J.F.Berret and Y.Serero. Phys. Rev. Lett., 87:4, 2001.
- [4] Coussot et al. Phys. Rev. Lett., 88:218301, 2002.
- [5] Debregeas. Phys. Rev. Lett., 87:4, 2001.
- [6] M E. Cates, T C B. M cLeish, and G. Marrucci. Eur. Phys. Lett., 21:451, 1993.
- [7] J.B. Salmon, A. Colin, and S. Manneville. Phys. Rev. Lett., 90:228303, 2003.
- [8] W. M. Holmes, M.R. Lopez-Gonzales, and P.T. Callaghan. Eur. Phys. Lett., 64274, 2003; M.R. Lopez-Gonzales, W. M. Holmes, P.T. Callaghan, and P.J. Photinos. Phys. Rev. Lett., 93268302, 2004.
- [9] L.Becu, S.M anneville, and A.Colin. Phys. Rev. Lett., 93:018301, 2005.
- [10] S. Lerouge, J. P. Decruppe, and J. F. Berret. Langmuir,

16:6464, 2000 ; S. Lerouge, J. P. D ecruppe, and P. D. O lm sted. Langm uir, 20:11365, 2004.

- [11] S.M. Fielding and P.D. Olm sted. Phys. Rev. E, 68:036313, 2003; S.M. Fielding and P.D. Olm sted. Phys. Rev. Lett., 92:084502, 2004.
- [12] S.Fielding. Phys. Rev. Lett., 95:134501, 2005.
- [13] E. Cappelaere and R. Cressely. Colloid. Polym. Sci., 275:4, 1997.
- [14] M C. Cross and P.C. Hohenberg. Rev. M od. Phys., 65:851, 1993.
- [15] M. Argentina and M.G. Clerc and R. Rojas and E. Tirapegui. Phys. Rev. E, 71.04210, 2005.
- [16] O.Radulescu and P.D.Olm sted. J.Non-Newtonian.

Fluid. M ech., 91:143, 2000.

- [17] J. F. Berret, D. C. Roux, and G. Porte. J. Phys. II France, 4:1261, 1994; C. Grand, J. A rrault, and M. E. Cates. J. Phys. II France, 7:1071, 1997.
- [18] H. Chate and P. M anneville. Transition to turbulence via spatio-temporal interm ittency. Phys. Rev. Lett., 58 (2):112, 1987.
- [19] Y.Kuram oto. Chem ical O scillations, W aves and Turbulence. Springer, 1984.
- [20] JK G. Dhont. Phys. Rev. E, 60:4534, 1999.
- [21] S. Lerouge, M. Argentina, J. P. Decruppe. in preparation.