

X-ray magnetic circular dichroism study of Re $5d$ magnetism in $\text{Sr}_2\text{CrReO}_6$

P. Majewski,* S. Geprägs, O. Sanganas, M. Opel, and R. Gross
*Walther-Meißner-Institut, Bayerische Akademie der Wissenschaften,
 Walther-Meißner Str. 8, 85748 Garching, Germany*

F. Wilhelm and A. Rogalev
*European Synchrotron Radiation Facility (ESRF),
 6 Rue Jules Horowitz, BP 220, 38043 Grenoble Cedex 9, France*

L. Alff†
Darmstadt University of Technology, Petersenstr. 23, 64287 Darmstadt, Germany
 (Dated: 23rd March 2022)

We have measured Re $5d$ spin and orbital magnetic moments in the ferrimagnetic double perovskite $\text{Sr}_2\text{CrReO}_6$ by X-ray magnetic circular dichroism at the $L_{2,3}$ edges. In fair agreement with recent band-structure calculations [1], at the Re site a large $5d$ spin magnetic moment of $-0.68 \mu_B$ and a considerable orbital moment of $+0.25 \mu_B$ have been detected. We found that the Curie temperature of the double perovskites $A_2BB'O_6$ scales with the spin magnetic moment of the 'non-magnetic' B' ion.

PACS numbers: 75.25.+z, 75.30.-m, 75.50.-y

Among the ferrimagnetic double perovskites, which are currently considered as possible spintronics materials, the compound $\text{Sr}_2\text{CrReO}_6$ with its Curie temperature T_C of about 635 K has the highest transition temperature observed so far in this class of materials [2, 3, 4]. The physical mechanism leading to the high Curie temperature is still unclear. Compared to the related double perovskites Sr_2CrWO_6 [5, 6] and $\text{Sr}_2\text{FeReO}_6$ [7, 8] with $T_C \approx 460$ K and $T_C \approx 400$ K respectively, $\text{Sr}_2\text{CrReO}_6$ has a considerably increased T_C . From a recent neutron diffraction study of the mixed compounds $\text{Sr}_2\text{Fe}_{1-x}\text{Cr}_x\text{ReO}_6$, it was speculated that the cation size matching improves with increasing x . This in turn increases the pd hybridization, contributing to an enhancement of T_C [9]. These observations can at least qualitatively be understood within a generalized double exchange or kinetic energy driven exchange model proposed by Sarma *et al.* [10], where the itinerant electrons mediate an indirect antiferromagnetic coupling between the Cr or Fe and the W or Re moments.

It is still an open question whether the magnetic moments at the 'non-magnetic' W/Re sites are *induced* by the hybridization with the magnetic $3d$ ion or *intrinsic* $5d$ moments. It has been suggested recently that the critical temperature in this type of ferrimagnetic double perovskites scales with the magnetic moment of the 'non-magnetic' site [11, 12]. An important experimental test for this idea is the investigation of the spin and orbital magnetic moments at the Re site in $\text{Sr}_2\text{CrReO}_6$ with its unexpectedly high transition temperature. Band-structure calculations based on the full-potential linear muffin-tin orbital method predict a value for the Re spin magnetic moment of $-0.85 \mu_B$ or $-0.69 \mu_B$ using the gen-

eralized gradient approximation (GGA) or local spin density approximation (LSDA), respectively, both with included spin-orbit (SO) coupling [1]. First experimental results from neutron scattering indicate a much smaller value of about $-0.21 \mu_B$ at 5 K [9]. However, it is of great importance to measure directly magnetic moments with a state-of-the-art method as X-ray magnetic circular dichroism (XMCD). The great advantage of XMCD is its element selectivity and the possibility to extract spin and orbital magnetic moments using the magneto-optical sum-rules [13, 14]. A considerable orbital magnetic moment on Re is also predicted by theory ($0.18 \mu_B$), indicating the relevance of spin-orbit-coupling which leads, in turn, to a break-down of the complete half-metallicity in $\text{Sr}_2\text{CrReO}_6$ [1]. In contrast, in Sr_2CrWO_6 [6, 11] and $\text{Sr}_2\text{FeMoO}_6$ [15] the half-metallic character is preserved.

In this letter, we present a XMCD study of the Re moments in $\text{Sr}_2\text{CrReO}_6$ polycrystalline bulk samples supplemented by SQUID (superconducting quantum interference device) magnetization measurements. Our measurements give further evidence that the Curie temperature T_C in the ferrimagnetic double perovskites of the form $A_2BB'O_6$ with A an alkaline earth, B a magnetic metal, and B' an originally non-magnetic $3d$ or $5d$ metal is strongly dependent on the magnetic moment at the B' site.

The samples were made from a stoichiometric mixture of SrO_2 , Re, and CrO_2 powders encapsulated in an evacuated silica tube. The powder was sintered with temperature increased stepwise up to 850°C before pressed to a pellet. This pellet was again sintered in an evacuated silica tube at 1150°C for four days using Ni as getter material. The final samples contain only a tiny amount of elemental Re as seen by x-ray diffraction using a four circle geometry. From Rietveld-analysis we estimate the amount of elemental Re less than 3%. The

*Electronic address: Petra.Majewski@wmi.badw.de

†Electronic address: alff@oxide.tu-darmstadt.de

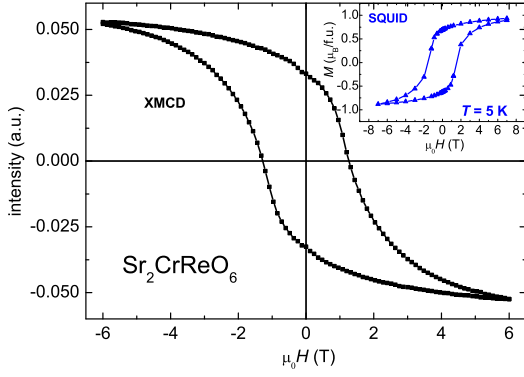


Figure 1: (Color online) XMCD signal of $\text{Sr}_2\text{CrReO}_6$ versus applied magnetic field measured at the Re L_2 edge at $T \approx 10$ K. The inset shows the magnetization vs. magnetic field for this sample measured by SQUID at $T = 5$ K.

amount of Cr/Re antisites is about 9%. From SQUID measurements we obtained $T_C = 635$ K for $\text{Sr}_2\text{CrReO}_6$ and a saturation magnetization $M_{\text{sat}} \approx 0.89 \mu_B/\text{f.u.}$

The XMCD measurements on the Re $L_{2,3}$ edges were performed at the European Synchrotron Radiation Facility (ESRF) at beam line ID12 [16]. The spectra were recorded using the total fluorescence yield detection mode. The XMCD spectra were obtained as direct difference between consecutive XANES scans (X-ray Absorption Near Edge Spectrum) recorded with opposite helicities of the incoming X-ray beam. To ensure that the XMCD spectra are free from experimental artefacts the data was collected for both directions of the applied magnetic field of 6 T (parallel and antiparallel to the X-ray beam). The measurements were performed at about 10 K. Since the samples measured in backscattering geometry were very thick, the spectra were corrected for self-absorption effects. The edge jump ratio L_3/L_2 was normalized to 2.20/1 [17]. This takes into account the difference in the radial matrix elements of the $2p_{1/2}$ to $5d(L_2)$ and $2p_{3/2}$ to $5d(L_3)$ transitions.

In Fig. 1 we show the Re $5d$ magnetization curve in $\text{Sr}_2\text{CrReO}_6$ at $T \approx 10$ K measured by XMCD at the Re L_2 absorption edge. A remarkably large coercive field of about 1.27 T is observed. The XMCD signal is in good agreement with the macroscopic magnetization measured by SQUID at 5 K (see inset of Fig. 1) and other SQUID measurements [4]. The saturation magnetization of $0.89 \mu_B$ per formula unit is quite close to the value of $1 \mu_B$ expected from a simple ionic picture, where the magnetic moments of Cr^{3+} and Re^{5+} are coupled antiferromagnetically.

We now discuss the XANES spectra of $\text{Sr}_2\text{CrReO}_6$ shown in Fig. 2. The white lines at the Re $L_{2,3}$ edges have a fine structure which reflects the Re $5d$ density of unoccupied states influenced by the crystal field. The white lines at both edges show a faint shoulder on the high energy side. This can be interpreted as the signature of the crystal field splitting of the $5d$ band into t_{2g} and e_g states (~ 3 eV). More pronounced double peak struc-

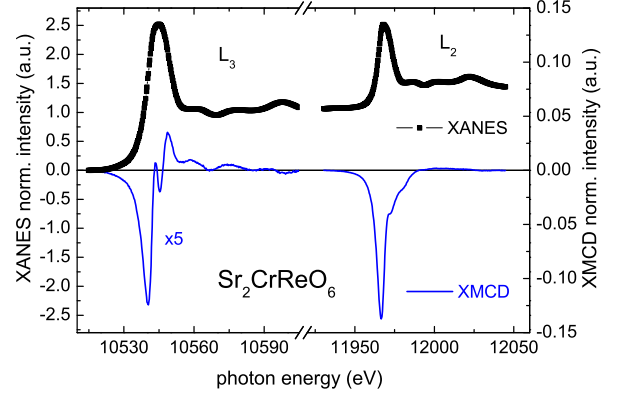


Figure 2: (Color online) Re $L_{2/3}$ XANES (symbols) and XMCD (full line) spectra for $\text{Sr}_2\text{CrReO}_6$ recorded at $T \approx 10$ K and $B = 6$ T. The normalized XANES spectra are corrected for self-absorption effects. The XMCD L_3 spectrum is multiplied by a factor of 5 for better visibility.

tures of similar splitting have been already observed at the Mo $L_{2,3}$ and W $L_{2,3}$ edges for the double perovskites $\text{Sr}_2\text{FeMoO}_6$ [18] and A_2CrWO_6 ($A = \text{Ca}, \text{Sr}$) [11].

As shown in Fig. 2, for both absorption edges we find a rather intense XMCD signal. This is a clear evidence for the existence of a magnetic moment at the Re $5d$ shell. We have extracted spin and orbital moments, m_S and m_L , of Re and summarized in Table I. Note that in order to obtain the spin and orbital magnetic moments separately the data must be normalized to the number of $5d$ holes n_h . According to band-structure calculations we use $n_h = 5.3$ [19]. This has to be kept in mind when comparing data, as n_h is proportional to the obtained moments. Only the ratio m_L/m_S is independent of the estimate of n_h . Both, m_L/m_S and m_L , are clearly larger than expected from the calculations including spin-orbit coupling. This underlines the importance of relativistic effects for the heavy Re.

In Fig. 3 we summarize currently published data for the spin moment of $B' = \text{W}, \text{Mo}, \text{Re}$ to investigate the relation of Curie temperature T_C and spin magnetic moment m_S at the B' site of the ferrimagnetic double perovskites of the type $\text{A}_2\text{BB}'\text{O}_6$. The data suggests that indeed T_C scales with m_S at the B' site. Of course, we cannot draw final conclusions from this comparison as other factors as structure, hybridization, and site occupation can strongly

Table I: Summary of magnetic moments at the 'non-magnetic' ion Re in $\text{Sr}_2\text{CrReO}_6$ ($T_C = 635$ K) measured by XMCD using $n_h = 5.3$. For comparison calculated values with different approximations to the exchange integral are also shown.

	m_S (μ_B/Re)	m_L (μ_B/Re)	$ m_L/m_S $
experiment	-0.68	0.25	0.37
LSDA+SO [1]	-0.69	0.17	0.25
GGA+SO [1]	-0.85	0.18	0.21

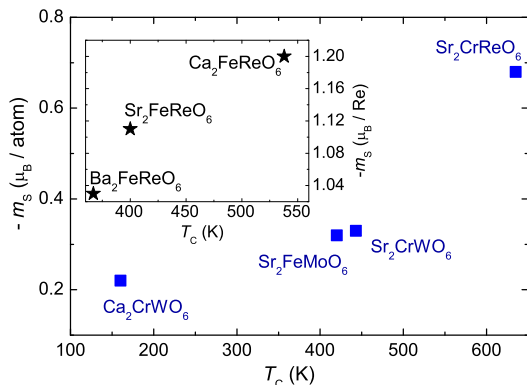


Figure 3: (Color online) B' spin magnetic moments for different double perovskites $A_2BB'O_6$ measured by XMCD on Mo [18], our data on W [11] and Re data presented in this paper. The number of $5d$ holes has been obtained from recent band-structure calculations [1, 11, 19]. In the inset further data deduced from XMCD [12] using a surprisingly high number of $5d$ holes $n_h > 8$ are shown.

influence T_C [4, 20]. However, there is a clear trend that a large T_C is accompanied by a large magnetic moment m_s at the B' site. This finding is in qualitative agreement with the simple model of ferrimagnetism mediated by itinerant minority spin carriers. In the inset of Fig. 3 we show recent XMCD data on other Re-based double

perovskites which show the similar trend [12]. The relatively high values of the spin magnetic moment for these samples are mainly due to the rather high number of d -holes used in their data analysis. Nevertheless our data and those of [12] follow satisfactorily the scaling law of Curie temperature and spin magnetic moment at the B' site. We emphasize that T_C seems not to depend on the total spin moment given by the sum of the local moment on the magnetic B site (Cr, Fe) and the induced magnetic moment on the non-magnetic B' site (Mo, W, Re). If this would be the case, different T_C values would be expected for the Cr and Fe based double perovskites in contrast to the experimental data.

In summary, we have unambiguously demonstrated a large spin magnetic moment at the Re $5d$ site in the ferrimagnetic double perovskite Sr_2CrReO_6 together with a considerable orbital magnetic moment. This result together with data from literature suggest that the critical temperature for such double perovskites scales with the magnetic moment at the 'non-magnetic' site of the compound. The data is in fair agreement with the model prediction and is important for understanding the mechanism of the high Curie temperatures in the ferrimagnetic double perovskites.

This work was supported by the DFG (GR 1132/13), by the BMBF (project 13N8279) and by the ESRF (HE-1882).

-
- [1] G. Vaitheeswaran, V. Kanchana, and A. Delin, Appl. Phys. Lett. **86**, 032513 (2005).
 - [2] H. Kato, T. Okuda, Y. Okimoto, Y. Tomioka, Y. Takenoya, A. Ohkubo, M. Kawasaki, and Y. Tokura, Appl. Phys. Lett. **81**, 328 (2002).
 - [3] H. Asano, N. Kozuka, A. Tsuzuki, and M. Matsui, Appl. Phys. Lett. **85**, 263 (2004).
 - [4] H. Kato, T. Okuda, Y. Okimoto, Y. Tomioka, K. Oikawa, T. Kamiyama, and Y. Tokura, Phys. Rev. B **69**, 184412 (2004).
 - [5] J. B. Philipp, D. Reisinger, M. Schonecke, A. Marx, A. Erb, L. Alff, R. Gross, and J. Klein, Appl. Phys. Lett. **79**, 3654 (2002).
 - [6] J. B. Philipp, P. Majewski, L. Alff, A. Erb, R. Gross, T. Graf, M. S. Brandt, J. Simon, T. Walther, W. Mader, D. Topwal, and D. D. Sarma, Phys. Rev. B **68**, 144431 (2003).
 - [7] K.-I. Kobayashi, T. Kimura, Y. Tomioka, H. Sawada, K. Terakura, and Y. Tokura, Phys. Rev. B **59**, 11159 (1999).
 - [8] N. Auth, G. Jakob, W. Westerburg, C. Ritter, I. Bonn, C. Felser, and W. Tremel, J. Magn. Magn. Mater. **272-276**, 607(E) (2004).
 - [9] J. M. De Teresa, D. Serrate, C. Ritter, J. Blasco, M. R. Ibarra, L. Morellon, and W. Tokarz, Phys. Rev. B **71**, 092408 (2005).
 - [10] D. D. Sarma, P. Mahadevan, T. Saha-Dasgupta, Sugata Ray, and A. Kumar, Phys. Rev. Lett. **85**, 2549 (2000); see also Curr. Opinion in Solid State Mat. Sci. **5**, 261 (2001).
 - [11] P. Majewski, S. Geprägs, A. Boger, M. Opel, A. Erb, R. Gross, G. Vaitheeswaran, V. Kanchana, A. Delin, F. Wilhelm, A. Rogalev, and L. Alff, cond-mat/0506048.
 - [12] M. Sikora, D. Zajac, Cz. Kapusta, M. Borowiec, C. J. Oates, V. Prochazka, D. Rybicki, J. M. De Teresa, C. Marquina, and M. R. Ibarra, cond-mat/0503358.
 - [13] B.T. Thole, P. Carra, F. Sette, and G. van der Laan, Phys. Rev. Lett. **68**, 1943 (1992).
 - [14] P. Carra, B.T. Thole, M. Altarelli, and X. Wang, Phys. Rev. Lett. **70**, 694 (1993).
 - [15] K.-I. Kobayashi, T. Kimura, H. Sawada, K. Terakura, and Y. Tokura, Nature **395**, 677 (1998).
 - [16] A. Rogalev, J. Goulon, Ch. Goulon-Ginet, and C. Malgrange, in *Magnetism and Synchrotron Radiation*, E. Beaurepaire *et al.* (Eds.), LNP vol. **565** (Springer, 2001).
 - [17] B. L. Henke, E. M. Gullikson, and J. C. Davis, At. Data Nucl. Data Tables **54**, 181-342 (1993). Online available: <http://www-cxro.lbl.gov>. Using the Chantler tables (online available: <http://physics.nist.gov/ffast>) the results change by not more than $\pm 4\%$.
 - [18] M. Besse, V. Cros, A. Barthélémy, H. Jaffrès, J. Vogel, F. Petroff, A. Mirone, A. Tagliaferri, P. Bencok, P. Decorse, P. Berthet, Z. Szotek, W.M. Temmerman, S.S. Dhesi, N.B. Brookes, A. Rogalev, and A. Fert, Europhys. Lett. **60**, 608 (2002).
 - [19] A. Delin, G. Vaitheeswaran, V. Kanchana, private communication.
 - [20] J. M. De Teresa, D. Serrate, J. Blasco, M. R. Ibarra, and L. Morellon, Phys. Rev. B **69**, 144401 (2004).