

BRIEF COMMUNICATION ARISING

GLASS BEHAVIOUR

Poisson's ratio and liquid's fragility?

Arising from: V. N. Novikov & A. P. Sokolov, *Nature*, **431**, 961 – 963 (2004)

Lack of a reliable theory of glass physics has led to pursuit of correlations between various glass or viscous liquid parameters, and the slope m of $\log(\text{viscosity})$ against T_g/T plot extrapolated at the glass transition temperature T_g , termed 'fragility', has been used as one of the parameters. Novikov and Sokolov¹ concluded that m of a liquid varies linearly with the ratio of the instantaneous bulk and shear moduli, K_∞/G_∞ , of its glass according to the relation, $m = 29(K_\infty/G_\infty - 0.41)$. Because of the obvious importance of the elastic properties of a glass, here we investigate the basis for this relation¹ and find that its premise is flawed for two reasons, (a) unjustifiable preference for an empirical variation of m with elastic properties and (b) selected use of glasses. When more glasses are considered in the same manner, m does not seem to be linearly related with K_∞/G_∞ .

The square of the ratio of the propagation velocity of longitudinal and transverse ultrasonic (or hypersonic) waves through an isotropic medium, $(v_l/v_t)^2$, yields $K_\infty/G_\infty = [(v_l/v_t)^2 - (4/3)]$. Firstly, we present the data of Fig. 2, Ref. 1, as a plot of m against K_∞/G_∞ and against v_l/v_t in Fig. 1, panel (A), with the incorrectly plotted data point indicated. (Note that the glasses are binary component, molecular, hydrogen bonded, and network structure type.) Straight lines show least square linear fits to the data. It is evident that the linear relation fits the data equally well whether m is plotted against $K_\infty/G_\infty = [(v_l/v_t)^2 - (4/3)]$, or is plotted against v_l/v_t . There seems to

be no reason why a linear relation between m and K_{∞}/G_{∞} had been preferred in Ref. 1 over a linear relation between m and ν_l/ν_t .

Secondly, for a more detailed investigation of the available data on glasses listed in Table I, we present the plot of m against $K_{\infty}/G_{\infty} = [(\nu_l/\nu_t)^2 - (4/3)]$ and against ν_l/ν_t in Fig. 1, panel (B), with the 13 data points taken from Ref. 1. It is evident that there is no linear relation between m and the elastic properties of glasses. The glasses are grouped into three types, inorganic, organic and metallic. The data also show that m does not linearly increase with K_{∞}/G_{∞} , even within one group of glasses.

Evidently, both a preference for a linear variation of m with K_{∞}/G_{∞} (or ν_l^2/ν_t^2) over a linear variation of m with ν_l/ν_t , and the limited data used in the correlation have led to an unreliable conclusion in Ref. 1. Therefore, the physical significance of the subsequent discussion of the glass and liquid properties based upon this relation¹ is questionable.

Our findings are significant because Poisson's ratio of a glass is important for use in technology and in structural design. It is a measure of the change in lateral dimensions on elastically loading an object and it is defined as, $\mu_{Poisson} = \frac{1}{2} - \frac{3}{(6K_{\infty}/G_{\infty}) + 2}$. The conclusion that "fragility of a liquid is fully determined just by the Poisson ratio of its glass"¹ gives hope to a glass technologist that controlled modification of the composition, that determines a glass melt's m , can be used to control its Poisson ratio. Unfortunately the conclusion is untrue.

Spyros N. Yannopoulos*, G. P. Johari†

* Foundation for Research and Technology Hellas – Institute of Chemical Engineering and High Temperature Chemical Processes (FORTH / ICE-HT), P.O. Box 1414, GR–26504 Patras, Greece, and † Department of Materials Science and Engineering, McMaster University, Hamilton, Ont. L8S 4L7, Canada

Table I: List of 50 glasses whose data are used here. The first number in brackets is the reference for the m value, and the second one is the reference of the elastic properties. In cases, especially for metallic glasses, where several m values were reported we used an average value.

<u>Inorganic glasses</u>	<u>Ref. No</u>
GeS ₂	[2, 3]
NBS710 (70.5SiO ₂ 8.7Na ₂ O 7.7K ₂ O 11.6CaO (in wt %))	[4, 5]
ZBLA (58ZrF ₄ 33BaF ₂ 5LaF ₃ 4AlF ₃)	[6, 5]
ZBLAN20 (53ZrF ₄ 20BaF ₂ 4LaF ₃ 3AlF ₃ 20NaF)	[6, 5]
HBLAN20 (53HfF ₄ 20BaF ₂ 4LaF ₃ 3AlF ₃ 20NaF)	[6, 5]
2BiCl ₃ -KCl	[5, 7]
As ₂ S ₃	[8, 9]
As ₂ Se ₃	[10, 9]
As _x S _{100-x} (x=5, 10, 20, 30)	[11, 12]
15LiCl-85H ₂ O	[13, 14]
Ca(NO ₃) ₂ -8H ₂ O	[15, 15]
BSC (borosilicate) 70SiO ₂ 11B ₂ O ₃ 9Na ₂ O 7K ₂ O 3BaO (wt %)	[16, 17]
CaAl ₂ Si ₂ O ₈ (anorthite)	[4, 18]
CaMgSiO ₆ (diopside)	[4, 18]
20K ₂ O-80B ₂ O ₃	[19, 20]
45B ₂ O ₃ -55SiO ₂	[19, 21]
33Li ₂ O-67SiO ₂	[19, 22]
33Na ₂ O-67SiO ₂	[22, 22]
xNa ₂ O-(100-x) 95GeO ₂ , (x=5, 10, 30)	[22, 22]
<u>Metallic glasses</u>	
Pd _{77.5} Si _{16.5} Cu ₆	[23, 24]
Pt ₆₀ Ni ₁₅ P ₂₅	[23, 24]
Zr _{41.2} Ti _{13.8} Cu _{12.5} Ni ₁₀ Be _{27.5}	[25, 26]
P ₃₉ Ni ₁₀ Cu ₃₀ P ₂₁	[25, 26]
Ce ₇₀ Al ₁₀ Cu ₁₀ Ni ₁₀	[27, 27]
Pd ₄₀ Ni ₄₀ P ₂₀	[25, 28]
Zr _{46.75} Ti _{8.25} Cu _{7.5} Ni ₁₀ Be _{27.5}	[25, 29]
Pd ₆₄ Ni ₁₆ P ₂₀	[25, 30]
Pd ₁₆ Ni ₆₄ P ₂₀	[25, 30]
Zr ₅₀ Cu ₅₀	[31, 32]
Pr ₆₀ Cu ₂₀ Ni ₁₀ Al ₁₀	[33, 33]
<u>Alkali-Borate glasses</u>	
xLi ₂ O-(100-x)B ₂ O ₃ (x=10, 20, 30)	[34, 20]
xNa ₂ O-(100-x)B ₂ O ₃ (x=10, 15, 20, 25, 30, 35, 40)	[34, 20]
<u>Bismuth-Borate Glasses</u>	
xBi ₂ O ₃ -(100-x)B ₂ O ₃ (x=20, 25, 30, 35, 45)	[22, 35]

References

1. Novikov, V. N. & Sokolov, A. P. *Nature* **431**, 961-963 (2004).
2. Malek, J. & Shanelova, J. *J. Non-Cryst. Solids* **243**, 116-122 (1999).
3. Nemanich, R. J., Gorman, M. & Solin, S. A. *Solid State Comm.* **21**, 277-280 (1977).
4. Huang, D. & McKenna, G. B. *J. Chem. Phys.* **114**, 5621-5630 (2001).
5. Schroeder, J. *et al. Electron. Lett.* **23**, 1128-1130 (1987)
6. Hasz, W.C., Whang J. H. & Moynihan, C. T. *J. Non-Cryst. Solids* **161**, 127-132 (1993).
7. Torrel, L. M. *J. Non-Cryst. Solids* **56**, 93-98 (1983).
8. Malek, J. *Thermochim. Acta* **311**, 183-198 (1998).
9. Nemanich, R. J. *Phys. Rev. B* **16**, 1655-1674 (1977).
10. Malek, J. & Shanelova, J. *J. Non-Cryst. Solids* **351**, 3458–3467 (2005).
11. Bernatz, K.M., Echeverria, I., Simon, S. L. & Plazek, D. J. *J. Non-Cryst. Solids* **307–310**, 790–801 (2002).
12. Ito, Y., Kashida, S. & Murase, K. *Solid State Commun.* **65**, 449-452 (1988).
13. Moynihan, C. T., Balitactac, N., Boone, L. & Litovitz, T. A. *J. Chem. Phys.* **55**, 3013-3019 (1971).
14. Pohl, R. O., Liu, X. & Thompson, E. *Rev. Mod. Phys.* **74**, 991-1013 (2002).
15. Hassan, K., Borjesson, L. & Torell, L. M. *J. Non-Cryst. Solids* **172-174**, 154-160 (1994).
16. Macedo, P. B. & Napolitano, A. *J. Chem. Phys.* **49**, 887-1895 (1968).
17. Heiman, D., Hamilton, D. S. & Hellwarth, R. W. *Phys. Rev. B* **19**, 6583-6592 (1979).
18. Schilling, F. R., Hausser, M., Sinogeikin, S. V. & Bass, J. D. *Contrib. Mineral. Petrol.* **141**, 297-306 (2001).
19. Avramov, I. *J. Non-Cryst. Solids* **238**, (1998) 6-10.
20. Lorösch, J., Couzi, L. M., Pelous, J., Vacher, R. & Levasseur, A. *J. Non-Cryst. Solids* **69**, 1-25 (1984).
21. El-Moneim, Abd. *Physica B* **325**, 319–332 (2003).
22. Mazurin, O. V., Streltsina, M. V. & Shvaiko-Shvaikovskaya, T. P. *Handbook of glass data*, (Elsevier, Amsterdam, 1983).
23. Komatsu, T. *J. Non-Cryst. Solids* **185**, 199-202 (1995).
24. Chen, H. S., Krause, J. T. & Coleman, E. *J. Non-Cryst. Solids* **18**, 157-171 (1975).
25. Perera, D. N. *J. Phys.: Condens Matter* **11**, 3807-3812 (1999).

26. Wang, W. H., *et al.* *Appl. Phys. Lett.* **79**, 3947-3949 (2001).
27. Zhang, Bo, Wang, R. J., Zhao, D. Q., Pan, M. X. & Wang, W. H. *Phys. Rev. B* **70**, 224208 (1-7) (2004).
28. Lambson, E. F., *et al.* *Phys. Rev. B* **33**, 2380–2385 (1986).
29. Wang, W. H., Dong, C. & Shek, C. H. *Mater. Sci. Eng. R* **44**, 45–89 (2004).
30. Chen, H. S., Krause, J. T., & Coleman, E. J. *J. Non-Cryst. Solids* **18**, 157-171 (1975).
31. Wang, W. H., Lewandowski, J. J. & Greer, A. L. *J. Mater. Res.* **20**, 2037-2313 (2005).
32. Tanner, L. E. & Ray, R. *Scripta Metallurgica* **11**, 783-789 (1977).
33. Zhao, Z. F., *et al.* *Appl. Phys. Lett.* **82**, 4699-4701 (1983).
34. Chryssikos, G. D. *J. Non-Cryst. Solids* **172-174**, 378-383 (1994).
35. El-Adawy, A. & Moustafa, Y. *J. Phys. D: Appl. Phys.* **32**, 2791–2796 (1999).

Figure Caption

Figure 1. Relation between m and elastic properties of glasses. Plots of m showing a preference for data fitting in panel (A), and lack of linear relation with m in panel (B). The data in panel (A) are from Ref. 1, showing the erroneously plotted red dot for glycerol and blue dot for m-toluidine. In panel (B), the black symbols are from Ref. 1, and coloured symbols are data for glasses listed in Table I. Solid circles refer to various inorganic glasses; open triangles to alkali borates; open diamonds to bismuth borates; closed diamonds, to alkali-germanates; half-filled circles to arsenic selenides; and open circles to metallic glasses.

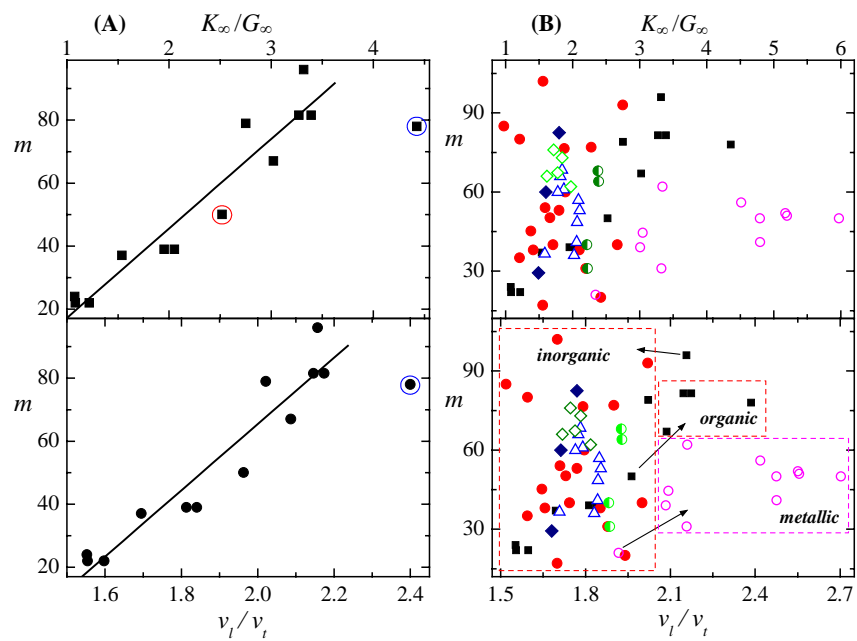


Figure 1