Em ergent N odal Excitations due to the Coexistence of Superconductivity and A ntiferrom agnetism: Cases with and without Inversion Symmetry

Satoshi Fu im oto

D epartm ent of P hysics, K yoto U niversity, K yoto 606-8502, Japan (Received M arch 23, 2024)

We argue the emergence of nodal excitations due to the coupling with static antiferrom agnetic order in fully-gapped superconducting states in both cases with and without inversion symmetry. This line node structure is not accompanied with the sign change of the superconducting gap, in contrast to usual unconventional Cooper pairs with higher angular momenta. In the case without inversion symmetry, the stability of the nodal excitations crucially depends on the direction of the antiferrom agnetic staggered magnetic moment. A possible realization of this phenomenon in $CePt_3Si$ is discussed.

KEYW ORDS: superconductivity, antiferrom agnetism, line node, inversion symmetry

The interplay between magnetism and superconductivity has been one of central issues in the strongly correlated electron systems. It has been argued that in some heavy ferm ion systems such as $C \in CoIn_5$, $C \in RhIn_5$, and UPd_2Al_3 , $C \in RhIn_5$, and UPd_2Al_3 , antiferrom agnetic (AF) critical spin uctuations may mediate unconventional Cooper pairs of which the superconducting (SC) gap has line nodes. Moreover, the coexistence of the AF order and the SC state is realized in CeRhIn5, UPd_2Al_3 , $CePt_3Si_4^{(6)}$ $CeRhSi_3_4^{(7)}$ and $CeIrSi_3_4^{(8)}$ Amongthem , CePt3Si, a superconductor without inversion sym m etry, does not display magnetically critical behaviors, indicating that the spin uctuation is alm ost suppressed, and the static AF order is well stabilized. 6) However, this system exhibits som e curious properties described as follows. The NMR experiments for this system indicate the existence of the coherence peak of $1=(T_1T)$, in plying the realization of the fully-gapped state.9) In contrast, the experim entalm easurem ents of therm altransport in m agnetic $elds_{r}^{10}$ and the penetration depth, t^{11} strongly support the line-node structure of the low-energy excitations. To explain these observations, the present author¹²⁾ and Hayashi et al.¹³⁾ pointed out independently that the coherence factor of $1=(T_1T)$ is enhanced in the absence of inversion symmetry, which leads the prominent coherence peak of $1=(T_1T)$. A lso, the present author proposed that the line node may stem from the coupling with the AF order; i.e. it is an accidental line node which is not associated with the symmetry of the Cooper pair, 12) while Hayashiet al. attribute the existence of the line node to the adm ixture of the spin singlet and triplet pairs.13)

In this paper, we further pursue the possible realization of nodal excitations in SC states due to the coupling with the static antiferrom agnetic order. We would like to stress that this nodal structure is quite dierent from the line-nodes caused by dynamical spin—uctuations as realized in CeCoIn $_{\!5}$ and UPd $_{\!2}{\rm A}\,{\rm l}_{\!3}$ in the point that the form er is not accompanied with the sign change of the SC gap at the line-nodes.

To explain the basic properties of this phenom enon, we, rst, consider the case of the s-wave pairing with inversion symmetry coexisting with AF order. Although systems corresponding to this situation have not been realized in any real compounds so far, the consideration of this case is useful for a simple theoretical description of the mechanism for the emergent line-node due to the AF order. We start from the following mean eld Hamiltonian,

Here, c_k (c_k^y) is the annihilation (creation) operator of an electron with momentum k, and spin . (s) is the swave SC gap independent of the momentum k, and m $_{\mathbb{Q}}$ is the staggered magnetic moment. We do not specify the origin of the AF order in the following argument. It may stem from localized electrons which are not explicitly included in (1). The single-particle excitation energy of (1) is readily obtained as,

$$E_{k} = \frac{\mathbf{n}_{k}^{2} + \mathbf{n}_{k+Q}^{2}}{2} + \mathbf{n}_{k}^{(s)2} + \mathbf{n}_{Q}\mathbf{f}$$

$$= \frac{(\mathbf{n}_{k}^{2} + \mathbf{n}_{k+Q}^{2})^{2}}{2} + \mathbf{n}_{Q}\mathbf{f}\mathbf{f}\mathbf{n}_{Q}\mathbf{f}\mathbf{f}\mathbf{f}\mathbf{h}_{Q}\mathbf{f}\mathbf{f}\mathbf{h}_{Q}\mathbf{f}\mathbf{f}\mathbf{h}_{Q}\mathbf{f}\mathbf{h}_{Q}\mathbf{f}\mathbf{h}_{Q}\mathbf{f}\mathbf{h}_{Q}\mathbf{f}\mathbf{h}_{Q}\mathbf{f}\mathbf{h}_{Q}\mathbf{f}\mathbf{h}_{Q}\mathbf{f}\mathbf{h}_{Q}\mathbf{f}\mathbf{h}_{Q}\mathbf{f}\mathbf{h}_{Q}\mathbf{f}\mathbf{h}_{Q}\mathbf{f}\mathbf{h}_{Q}\mathbf{f}\mathbf{h}_{Q}\mathbf{f}\mathbf{h}_{Q}\mathbf{f}\mathbf{h}_{Q}\mathbf{f}\mathbf{h}_{Q}\mathbf{f}\mathbf{h}_{Q}\mathbf{f}\mathbf{h}_{Q}\mathbf{h}_{Q}\mathbf{f}\mathbf{h}_{Q}\mathbf{h}_{Q}\mathbf{h}_{Q}\mathbf{f}\mathbf{h}_{Q$$

Apparently, in the case of jm $_{\mathbb{Q}}$ j $^{(s)}$, which corresponds to the situation realized in CePt $_3$ Si, excitations with the energy E $_{k+}$ are not important for low-energy properties. Thus we ignore their contributions in the following. The SC gap $^{(s)}$ should be determined by solving the gap equation self-consistently. A ssuming the BCS type attractive interaction between electron pairs, $V_{k;k}^{0}$ $C_{k,n}^{V}$ $C_{k,n}^{V}$ C

$$1 = V \begin{cases} X & \tanh \frac{E_k}{2T} \\ 2E_k \end{cases} = 1 = \frac{\frac{n^2 - n^2}{k} + 2jn_Q j}{E_{k+}^2 + E_k^2}$$
(3)

In the vicinity of the Fermi surface which yields the most dominant contributions to the gap equation, the

factor in the parenthesis of Eq.(3) is non-negative, and thus the right-hand side of the gap equation is always positive for V > 0. This means that for any given values of $^{(s)}$ and jn_0 j there exists a positive value of V > 0 which satis es the gap equation (3). Therefore, in the following, we treat (s) and in o j as independent param eters, without solving the gap equation explicitly. To simplify the calculation below, we assume that $\mathbf{w}_k = k^2 = (2m)$ \mathbf{E}_F with m the electron mass and $E_{\,\mathrm{F}}\,$ the Ferm ienergy, and that the ordering wave vector of the antiferrom agnetism is Q = (0;0;).Forsu ciently large magnitude of in o j the AF order strongly a ects the electronic structure in the vicinity of the magnetic B rillouin Zone at $k_z =$ =2, and eventually, destroys the single-particle excitation gap due to the SC order.W e dem on strate this phenom enon num erically for a particular set of param eters. The results are shown in Fig.1. The height of the hills indicates the magnitude of the excitation gap, which vanishes around the magnetic Brillouin Zone for jm Q j (s), indicating the line-node structure. We also calculate the local density of states D (") = $\frac{1}{k} \operatorname{Im} G_k^R$ ("), where G_k^R (") is the retarded norm alg reen function of the H am iltonian (1). W e show D (") plotted as a function of the energy " in Fig 2. (s), the density of For su ciently small energies " states is linear in ", exhibiting the line-node-like behavior. The existence of the nodal excitations in the s-wave pairing state is understood as follows. In the vicinity of the magnetic Brillouin Zone, we apply an approximation "k+0 ${}_{k}^{"}$. Then, the single-electron excitation energy (2) is recast into E_k = Thus, when $^{(s)} = j_0 \circ j$ the single-electron excitation

Thus, when $^{(s)} = jn_Q j$ the single-electron excitation energy is gapless. More precisely, since the approximation $^{"}_{k+Q}$ $^{"}_k$ becomes worse for kaway from the magnetic Brilloin Zone, it is required to tune the values of $jn_Q j$ much larger than $^{(s)}$ for the realization of the nodal excitations. From this consideration, it is clear that the SC gap itself does not change the sign at this line node. Moreover, this node-like structure is not a true line node, but a minimum of the excitation gap. Nevertheless, the overall behavior of the density of states is quite similar to that of usual SC states with line nodes, and also any therm odynamic quantities at low temperatures behaves as if the true line node exists.

The above mechanism for the emergence of the line nodes is also applicable to systems without inversion symmetry. In this case, parity violation allows the adm ixture of the spin-singlet and triplet states. 14,15) The ratio of the minor component of the SC gap induced by the spin-orbit (SO) interaction to the major component is of order $E_{SO} = E_F$ where E_{SO} is the magnitude of the spin-orbit splitting of the energy band. In any superconductors without inversion sym metry discovered 0:1: 8 Thus, in the folso far, this ratio is less than lowing, we neglect the minor component of the SC gap. As explained above, for CePt3Si, experim ental observations seems to support the realization of the s + p-w ave state.9,12,16) Since the on-site Coulomb repulsion should be considerably large in heavy ferm ion system s, it is appropriate to assume that the major component of the

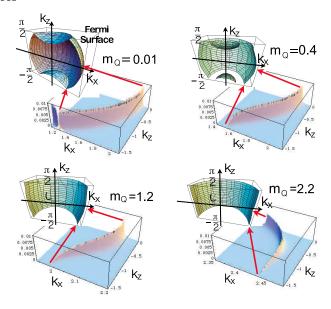


Fig. 1. (Color online) The single-particle excitation gap plotted as a function of k_x and k_z for jn $_{\mathbb{Q}}$ j= $0.01;0.4;1.2;2.2.\,\mathrm{H}\,\mathrm{ere},$ we put the electron m ass m = 1.0, the Ferm i energy E $_F$ = 1.0, and the SC gap $^{(s)}$ = $0.01.\,\mathrm{F}\,\mathrm{igures}$ of a portion of the Ferm i surface folded by the coupling with the AF order are also shown.

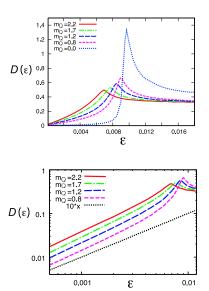


Fig. 2. (Color online) The local density of states for the model (1) plotted against the excitation energy ". The upper panel is in the linear scale. The lower panel is a log-log plot.

SC gap has the p-wave symmetry, and ignore the minor s-wave component. We approximate the inversion-symmetry-broken spin-orbit interaction by the Rashbatype interaction. Then the model Hamiltonian is given by,

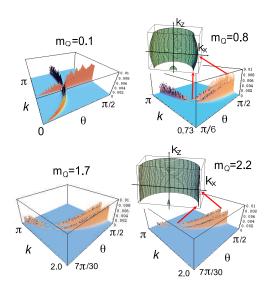


Fig. 3. (Color online) The single-particle excitation gap plotted as a function of k and for jm $_{\rm Q}$ j = 0:01;0:8;1:7;2:2 in the case of the p-wave pairing state w ithout inversion sym m etry and m $_{\rm Q}$ k x. Here, we put m = 1:0, E $_{\rm F}$ = 1:0, = 0:07, and $^{\rm (t)}$ = 0:01. Figures of a portion of the Ferm i surfaces are also shown.

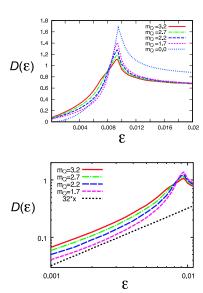


Fig. 4. (Color online) The local density of states for the model (4) plotted against the excitation energy ". The upper panel is in the linear scale. The lower panel is a log-log plot.

Here, the second term of the right-hand side of (4) is the Rashba spin-orbit interaction, $^{(p)}$ is the amplitude of the SC gap. Note that in the above model the d-vector of the triplet pairing is determined by the Rashba spin-orbit interaction. Also, we assume that the magnetic ordering wave vector is $Q=(0;0;)$, and that the AF staggered moment is directed along the x-axis,ie.m $_{Q}=(\text{jn }_{Q}\text{ j};0;0)$, in accordance with the results of the neutron scattering measurements for CePt_3Si, which suggest the existence of the in-plane magnetic moment. As will be shown below, the relative angle between the direction of the staggered moment and that of the inversion-

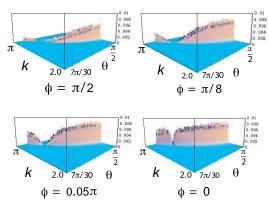


Fig. 5. (Color online) The excitation gap plotted as a function of k and for = =2; =8;0:05;0 for the model (4). The line node structure disappears around 0.




Fig. 6. (Color online) A schematic gure of the line node structure on the Ferm i surface. The depth of the blue color in the vicinity of the magnetic B rillouin Zone k_z =2 indicates the depth of the node of the excitation gap.

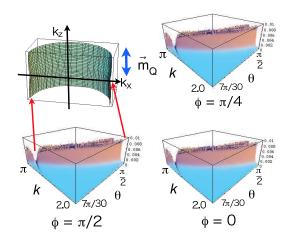


Fig. 7. (Color online) The excitation gap for the model (4) for jm $_{\mathbb{Q}}$ j = 2:7 in the case of m $_{\mathbb{Q}}$ k z-axis that the AF staggered mom ent is parallel to the z-axis.

symmetry-breaking potential gradient (n in Eq.(4)) is crucially in portant for the emergence of the nodal excitations in the spin triplet dominated case. To simplify the following analysis, we assume $\mathbf{w}_k = k^2 = (2m)$ \mathbf{E}_F , again. Although the actual band structure of CePt_3Si is much more complicated, the essential feature of the emergent line node due to the AF order is not a ected by this simplication. Since the single-electron energy of (4) can not be obtained analytically, we diagonalize the Hamiltonian

(4) num erically for a particular set of param eters. The calculated results of the excitation energy gap is plotted in Fig.3, in which we use the spherical coordinate in the momentum space $k = (k \cos \sin i k \sin i k \cos i)$. It is seen that the Ferm i surfaces are splitted into two pieces by the SO interaction. In the vicinity of the magnetic B rillouin Zone at $k_z =$ =2, the excitation gap is collapsed on both the splitted Ferm i surfaces. The local density of states for this model is plotted as a function of the excitation energy in Fig.4.W hen the magnitude of jm o j is much larger than the SC gap, the density of (t), indicating the linestates obeys D (") / " for " node-like structure of the low-energy excitations. How-(t), the energy depenever, for higher energies " dence of the density of states di ers from the line-node behavior, and exhibit a prominent peak structure around (t), as in the case of fully-gapped states. This peak structure m ay be im portant for the realization of the coherence peak of $1=(T_1T)$ observed for $C \in Pt_3Si_*^{9)}$ Since the SC gap does not change the sign at this nodal line, the coherence factor gives substantial contributions to $1=(T_1T)$, resulting in the enhancement of the coherence peak, in agreem ent with the experim ental observations.9) We would like to note that for su ciently large in o i the point nodes of the p-w ave gap at $k_x = 0$, $k_y = 0$ disappear, because of the deformation of the Ferm i surface as depicted in Fig.3. This fact is also favorable for the enhancem ent of the coherence peak.

A nother interesting feature of this nodal structure is that it possesses the C_{2v} symmetry in the momentum space, because of the existence of m o aligned to the x-axis and the inversion-sym metry-breaking SO interaction. This property is clearly seen in Fig.5, in which the variation of the nodal structure as a function of the azim uthal angle is described. We depict the line-node structure with the C_{2v} sym m etry on the Ferm i surface schem atically in Fig.6. The experimental detection of this two-fold symmetry in CePt3Si is an important test for the present theory. Moreover, in contrast to the case of the spin singlet state with inversion symmetry considered before, the emergence of the nodal excitations in the triplet dom inated state without inversion symmetry crucially depends on the direction of the staggered m agnetic m om ent m $_{\mathbb{Q}}$. To see this, we display the excitation gap calculated by assuming $m_Q = (0;0; jm_Q j)$ with j_0 j = 2.7 in Fig.7. The line-node structure does not appear in this case. This observation indicates that in the triplet pairing dom inated case, the em ergence of the nodal excitations, or, conversely, the suppression of the SC gap due to the coupling with the AF order occurs only when the magnetic moment orthogonal to the spin of the triplet Cooper pair exists, which disturbs the form ation of the triplet pair.

Finally, we make a brief comment on the universal conductivity of the nodal excitations perturbed by random impurity potentials. It is known that low-energy exci-

tations from line nodes gives a universal value of the therm al conductivity due to impurity scattering in the zero temperature limit. A ctually, the universal thermal conductivity is observed for CePt₃Si. For the emergent line nodes considered here, the universal conductivity also appears provided that in $_{\rm Q}$ jismuch larger than the SC gap, as veried by the straightforward calculation for the models (1) and (4).

In sum m ary, we have presented a mechanism for the emergence of line-node structures in fully-gapped SC states due to the coupling with static AF order. The possible realization of this phenom enon in CePt₃Sihas been proposed to reconcile the existence of the coherence peak of $1=(T_1T)$ with the experimental observations of nodal excitations.

A cknow ledgm ent

The author is grateful to K. Yam ada, Y. Matsuda, H. Mukuda, M. Yogi, and H. Ikeda for invaluable discussions. This work was partly supported by a Grant-in-Aid from the Ministry of Education, Science, Sports and Culture, Japan.

- R.M. ovshovich, M. Jaime, J.D. Thompson, C. Petrovic, Z. Fisk,
 P.G. Pagluiso and J.L. Sarrao: Phys. Rev. Lett. 86 (2001) 5152.
- 2) H.Hegger, C.Petrovic, E.G.Moshopoulou, M.F.Hundley, J. L.Sarrao, Z.Fisk, and J.D.Thompson: Phys.Rev.Lett.84 (2000) 4986.
- 3) N.K. Sato, N.A. so, K.M. iyake, R.Siina, P.Thalm eier, G.Varelogiannis, C.G. eibel, F.Steglich, P.Fulde and T.Kom atsubara: Nature 410 (2001) 340.
- 4) M .K yogaku, Y .K itaoka, K .asayam a, C .G eibel, C .Schank and F .Steglich: J. Phys. Soc. Jpn. 62 (1993) 4016.
- 5) For a recent review, see, Y. Onuki, R. Settai, K. Sugiyama, T. Takeuchi, T.C. Kobayashi, Y. Haga and E. Yam am oto: J. Phys. Soc. Jpn.73 (2004) 769.
- 6) E. Bauer, G. Hilscher, H. Michor, Ch. Paul, E. W. Scheidt, A. Gribanov, Yu. Seropegin, H. Noel, M. Sigrist, and P. Rogl: oPhys. Rev. Lett. 92 (2004) 027003.
- 7) N. Kimura, K. Ito, K. Saitoh, Y. Umeda, H. Aoki, and T. Terashima: Phys. Rev. Lett. 95 (2005) 247004.
- 8) I.Sugitani, Y.O kuda, H.Shishido, T.Yamada, A.Thamizhavel, E.Yamamoto, T.D.Matsuda, Y.Haga, T.Takeuchi, R.Settai, and Y.Onuki: J.Phys.Soc.Jpn.75 (2006) 043703.
- 9) M. Yogi, Y. Kitaoka, S. Hashim oto, T. Yasuda, R. Settai, T. D. Matsuda, Y. Haga, Y. Onuki, P. Rogl, and E. Bauer: Phys. Rev. Lett. 93 (2004) 027003.
- 10) K. Izawa, Y. Kasahara, Y. Matsuda, K. Behnia, T. Yasuda, R. Settai, and Y. Onuki: Phys. Rev. Lett. 94 (2005) 197002.
- 11) I. Bonalde, W . Bram er-E scam illa, and E. Bauer: Phys. Rev. Lett. 94 (2005) 207002.
- 12) S.Fujim oto: Phys. Rev. B72 (2005) 024515.
- 13) N.Hayashi, K.Wakabayashi, P.A.Frigeri, and M.Sigrist: Phys. Rev. B73 (2006) 092508; ibid 73 (2006) 024504.
- 14) V.M. Edelstein: Sov. Phys. JETP 68 (1989) 1244.
- 15) L.P.G or'kov and E.Rashba: Phys.Rev.Lett.87 (2001) 037004.
- 16) P.A. Frigeri, D.F. Agterberg, A.Koga, and M. Sigrist, Phys. Rev. Lett. 92 (2004) 097001.
- 17) N. Metoki, K. Kaneko, T. D. Matsuda, A. Galatanu, T. Takeuchi, S. Hashimoto, T. Ueda, R. Settai, Y. Onuki, and N. Bemgoeff, J. Phys.: Condens. Matter 16, L207 (2004).
- 18) PA.Lee: Phys. Rev. Lett.71 (1993) 1887.