

Origin and roles of a strong electron-phonon interaction in cuprate oxide superconductors

Fusayoshi J. Ohkawa

Department of Physics, Faculty of Science, Hokkaido University, Sapporo 060-0810, Japan
(Dated: March 23, 2024)

A strong electron-phonon interaction arises from the modulation of the superexchange interaction by phonons. It is responsible for the softening of the half breathing modes, as is studied in Phys. Rev. B 70, 184514 (2004). When antiferromagnetic spin fluctuations are developed around Q , Cu-O bond stretching modes can also be soft around twice Q due to the electron-phonon interaction. However, it can play no or only a minor role in the binding of d -wave Cooper pairs.

PACS numbers: 71.38.-k, 74.20.-z, 75.30.Et

It is an important issue to elucidate high critical temperature (high- T_c) superconductivity in cuprate oxides discovered in 1986 [1]. It occurs in the vicinity of the Mott metal-insulator transition or crossover. In 1987, a theory is proposed that Gutzwiller's quasiparticles are bound into d -wave Cooper pairs due to the superexchange interaction between nearest neighbors [2, 3]. According to observed specific heat coefficients $\gamma = 14 \text{ mJ/K}^2 \text{mol}$ [4], the bandwidth of quasiparticles is $W = 0.3\text{--}0.4 \text{ eV}$. Since the superexchange interaction constant is as strong as $J = (0.10\text{--}0.15) \text{ eV}$ [5], observed high T_c can be easily reproduced. High- T_c superconductivity occurs in an intermediate-coupling regime $J/W = 0.3\text{--}0.5$ for superconductivity, which is realized in the strong-coupling regime for electron correlations.

It is also an important issue to elucidate the origin and roles of a strong electron-phonon interaction, whose presence is implied by pieces of evidence: the softening of the so called half breathing modes around $(\pi/a; 0)$ and $(0; \pi/a)$ in the two-dimensional (2D) Brillouin zone (BZ) [6, 7, 8, 9, 10], with a the lattice constant of CuO_2 planes, the softening of Cu-O bond stretching modes around $(\pi/2a; 0)$ and $(0; \pi/2a)$ [11, 12], kinks in the quasiparticle dispersion [13, 14], and so on. On the other hand, observed small isotope shifts [15] of T_c imply that the strong electron-phonon interaction plays only a minor role in the occurrence of superconductivity.

Since charge fluctuations are suppressed by strong electron correlations, the conventional electron-phonon interaction arising from charge-channel interactions must be weak in cuprate oxides. An electron-phonon interaction arising from spin-channel interactions can be strong when electron correlations are strong. For example, it plays a significant role in the spin-Peierls effect. Then, a novel one is proposed in a previous paper [16]: one arising from the modulation of the superexchange interaction by phonons. It can explain the softening of breathing modes around $(\pi/a; 0)$ and $(0; \pi/a)$; it is predicted that the softening must be small around $(\pi/a; \pi/a)$. An attractive interaction arising from the virtual exchange of a single phonon of the modes is very weak between nearest neighbors; it is strong between next-nearest neighbors.

Then, it can play no significant role in the formation of d -wave Cooper pairs [16]. The observed small isotope shifts of T_c can never contradict the presence of this novel and strong electron-phonon interaction. One of the purposes of this Letter is to explain the softening around $(\pi/2a; 0)$ and $(0; \pi/2a)$ in 2D-BZ.

The superexchange interaction arises from the virtual exchange of pair excitations of 3d electrons across the upper Hubbard band (UHB) and the lower Hubbard band (LHB) [17]. When their non-zero bandwidths are ignored, the exchange interaction constant between nearest-neighbor Cu ions is given by

$$J = \frac{4V^4}{(d_p + U)^2} \frac{1}{d_p + U} + \frac{1}{U}; \quad (1)$$

with V the hybridization matrix between nearest-neighbor 2p and 3d orbits, d and p the depths of 3d and 2p levels, and U the on-site repulsion between 3d electrons. One may argue that parent cuprate oxides with no hole doping must be charge-transfer insulators rather than Mott insulators because doped holes reside mainly at O ions, so that $p > d$. However, this argument disagrees with $d \approx p \approx 1 \text{ eV}$ predicted by band calculations [18, 19, 20]. The preferential doping does not necessarily mean $p > d$, but it simply means that the local charge susceptibility of 3d electrons is much smaller than that of 2p electrons. When we follow the band calculations and we use $V = 1.6 \text{ eV}$, $d \approx p = 1 \text{ eV}$, and $U = 5 \text{ eV}$ [17], Eq. (1) gives $J = 0.27 \text{ eV}$. This is about twice as large as the experimental $J = (0.10\text{--}0.15) \text{ eV}$ [5]. This discrepancy is resolved when nonzero bandwidths of UHB and LHB are considered [17].

Displacements of the i th Cu ion and the $[ij]$ th O ion, which lies between the i th and j th Cu ions, are given by

$$u_i = \sum_q \frac{h\tilde{v}_{i,q}}{2NM_d!} e^{iq \cdot R_i} a_q b_q^y + b_q; \quad (2)$$

$$u_{[ij]} = \sum_q \frac{h\tilde{v}_{[ij],q}}{2NM_p!} e^{iq \cdot R_{[ij]}} a_q b_q^y + b_q; \quad (3)$$

with R_i and $R_{[ij]} = (1/2)(R_i + R_j)$ positions of the i th Cu and $[ij]$ th O ions, M_d and M_p masses of Cu and O

ions, b_q and b_q^\dagger annihilation and creation operators of a phonon with a polarization α and a wave vector q or q_x, q_y, q_z a phonon energy, $\epsilon_q = (\epsilon_{qx}; \epsilon_{qy}; \epsilon_{qz})$ a polarization vector, and N the number of unit cells. Here, we consider only longitudinal phonons; we assume $\epsilon_q = (\epsilon_x; \epsilon_y; \epsilon_z) = \epsilon$ for q within the first BZ. The q dependence of $v_{d,q}$ and $v_{p,q}$ is crucial. For example, $v_{d,q} = 0$ and $v_{p,q} = 0$ (1) for modes that bring no change in adjacent Cu-Cu distances.

Denoting creation and annihilation operators of 3d electrons at the i th site by d_i^\dagger and d_i and those of 3d electrons with wave number k by d_k^\dagger and d_k , we define spin operators by $S_i = \frac{1}{2} d_i^\dagger \sigma d_i$ and $S(q) = (\frac{1}{N}) \sum_k \frac{1}{2} d_{(k+\frac{1}{2}q)}^\dagger \sigma d_{(k-\frac{1}{2}q)}$, with $\sigma = (\sigma_x; \sigma_y; \sigma_z)$ the Pauli matrices. Two types of electron-phonon interactions arise from the modulations of J by the vibrations of O and Cu ions:

$$H_p = iC_p \sum_q \frac{h v_{p,q}}{2N M_p \epsilon_q} b_q^\dagger + b_q \sum_i S_i(q) \frac{1}{2} q \cdot P(q); \quad (4)$$

$$H_d = iC_d \sum_q \frac{h v_{d,q}}{2N M_d \epsilon_q} b_q^\dagger + b_q \sum_i S_i(q) P(q); \quad (5)$$

with C_p and C_d given in the previous paper [16],

$$S_x(q) = 2 [\epsilon_{qx} \sin(q_x a/2) + \epsilon_{qy} \sin(q_y a/2)]; \quad (6)$$

$$S_y(q) = 2 [\epsilon_{qx} \sin(q_x a/2) - \epsilon_{qy} \sin(q_y a/2)]; \quad (7)$$

$$S_z(k) = \cos(k_x a) + \cos(k_y a); \quad (8)$$

$$S_d(k) = \cos(k_x a) - \cos(k_y a); \quad (9)$$

being form factors, and

$$P(q) = \frac{1}{2} \sum_{q^0} (q^0) S(q^0 + \frac{1}{2}q) S(q^0 - \frac{1}{2}q); \quad (10)$$

being a dual-spin operator. Here, the x and y axes are within CuO_2 planes, and the z axis is perpendicular to CuO_2 planes. The d-p model is approximately mapped to the t-J model [21]. Then, we consider the t-J-infinite U model including H_p and H_d on a square lattice:

$$H = \sum_{ij} t_{ij} d_i^\dagger d_j + \frac{1}{2} J \sum_{hiji} (S_i \cdot S_j) + U_1 \sum_i d_{i\uparrow}^\dagger d_{i\uparrow} d_{i\downarrow}^\dagger d_{i\downarrow} + H_p + H_d; \quad (11)$$

with $hiji$ over nearest neighbors, and U_1 an infinitely large on-site repulsion to exclude double occupancy. Quasi-2D features are considered in terms of an anisotropy factor of spin fluctuations introduced below.

Every physical quantity is divided into single-site and multi-site ones. Calculating the single-site one is reduced to determining and solving selfconsistently the Anderson model, which is an effective Hamiltonian for the Kondo problem. This is the single-site approximation (SSA) that includes all the single-site terms [22, 23, 24]; the SSA can also be formulated as the dynamical mean-field theory [25] or the dynamical-coherent-potential approximation [26]. Multi-site or intersite effects can be perturbatively considered starting from a unperturbed state constructed in the non-perturbative SSA theory. Such a perturbative theory is nothing but a Kondo-lattice theory.

The irreducible polarization function in spin channels is the sum of single-site $\sim_s(i; 1)$, which is the same as that of the Anderson model, and multi-site $\sim_s(i; 1; q)$: $\sim_s(i; 1; q) = \sim_s(i; 1) + \sim_s(i; 1; q)$. Spin susceptibilities of the Anderson model and the t-J model are given by

$$\sim_s(i; 1) = \frac{2 \sim_s(i; 1)}{1 - U_1 \sim_s(i; 1)}; \quad (12)$$

$$\sim_s(i; 1; q) = \frac{2 \sim_s(i; 1; q)}{1 - \frac{1}{4} J(q) + U_1 \sim_s(i; 1; q)}; \quad (13)$$

with $J(q) = 2J_x(q)$. A physical picture for Kondo lattices is that local spin fluctuations at different sites interact with each other by an intersite exchange interaction. Following this picture, we define an intersite exchange interaction $I_s(i; 1; q)$ by

$$\sim_s(i; 1; q) = \frac{\sim_s(i; 1)}{1 - \frac{1}{4} I_s(i; 1; q) \sim_s(i; 1)}; \quad (14)$$

Then, it follows that $I_s(i; 1; q) = J(q) + 2U_1^2 \sim_s(i; 1; q)$. The main term of $2U_1^2 \sim_s(i; 1; q)$ is an exchange interaction arising from the exchange of pair excitations of Gutzwiller's quasiparticles [27]. It has a novel property that its strength is proportional to the width of Gutzwiller's band. It is antiferromagnetic (AF) when the chemical potential lies around the center of Gutzwiller's band or the nesting of the Fermi surface is sharp enough; it is ferromagnetic when the chemical potential lies around the top or bottom of Gutzwiller's band.

In cuprate oxides, the exchange interaction $I_s(0; q)$ is AF and is maximal around nesting wave numbers of the Fermi surface. We assume that it is maximal at $Q = (\frac{3}{4}\pi; \frac{3}{4}\pi; \pi)$ and $(\frac{3}{4}\pi; \frac{3}{4}\pi; \pi)$ in 2D-BZ, and that the susceptibility is approximately given by

$$\sim_s(i; 1; Q + q) = \frac{\sim_s(0; Q)^2}{2 + (q_x a)^2 + (q_y a)^2 + \frac{1}{4} J_{AF}}; \quad (15)$$

around each of Q , where $q_k = (q_x; q_y)$, J_{AF} is an energy scale of AF spin fluctuations, and c is the lattice constant along the z axis. The anisotropy factor is introduced to consider quasi-2D AF spin fluctuations; the correlation length within the x - y plane is a and that along the

z axis is $c = a$. A cut-off $q = \pi/3a$ is introduced so that $\chi_s(i!_1; Q + q) = 0$ for $j_k j > q_c$ or $j_y j > q_c$. The anisotropy of the lattice constants plays no role when a and q_c are defined in these ways.

The Green function for phonons is given by $D(i!_1; q) = 2!_q = (i!_1)^2 / (q^2 + 2!_q) + 2!_q / (i!_1)$, with $!_q$ the renormalization or softening of phonons. Three types of fluctuations can be developed: AF spin ones due to $I_s(i!_1; q)$, and d-wave superconducting (SC) and charge bond order (CBO) ones due to a mutual interaction between quasiparticles, which is given by

$$\chi_s(i!_1; q) \sim \chi_s(i!_1) = \frac{\frac{1}{4} I_s(i!_1; q) \sim_s^2(i!_1)}{1 - \frac{1}{4} I_s(i!_1; q) \sim_s(i!_1)}; \quad (16)$$

multiplied by U_1^2 and two single-site reducible vertex functions. The softening around $2Q$ occurs mainly due to AF spin ones around Q ; $2Q$'s are equivalent to $(-\pi/2a; 0)$ and $(0; -\pi/2a)$. When only the AF spin ones are considered, it follows that [16]

$$!_q(i!_1) = \frac{\hbar^2}{2M_p} \frac{3}{q^2} \sum_{\mathbf{p}} Y(\mathbf{q}) Y(\mathbf{p}) X(\mathbf{p} + \frac{1}{2}\mathbf{q}; i!_1; \mathbf{q}); \quad (17)$$

with

$$Y(\mathbf{q}) = \chi_s(\mathbf{q}) C_p V_{p; \mathbf{q}} + \frac{1}{2} \mathbf{q} + C_d V_{d; \mathbf{q}} \frac{M_p}{M_d}; \quad (18)$$

$$X(\mathbf{p} + \frac{1}{2}\mathbf{q}; i!_1; \mathbf{q}) = \frac{k_B T}{N} \sum_{\mathbf{p}} \langle \mathbf{p} \rangle \langle \mathbf{p} + \frac{1}{2}\mathbf{q} \rangle \chi_s(i!_1; \mathbf{p} + \frac{1}{2}\mathbf{q}; i!_1; \mathbf{q}); \quad (19)$$

In Eq. (19), two χ_s 's appear because of the dual-spin operator (10). Since we are interested in Cu-O bond stretching modes around $2Q$, we ignore vibrations of Cu ions; we assume that $C_d V_{d; \mathbf{q}} \frac{M_p}{M_d} = 0$ and

$$C_p V_{p; \mathbf{q}} = c_p eV = A; \quad (20)$$

where c_p is a dimensionless constant and it is likely $c_p = 0$ (1) [16]. Since the contribution from small p is large in Eq. (19), we consider only the contribution from the $= s$ channel. The softening is given by

$$!_q(i!_1) = A_q \chi_s(i!_1; q); \quad (21)$$

with

$$A_q = \frac{\hbar^2}{2M_p} \frac{3}{q^2} A_F \chi_s(0; Q) \chi_s^2(0; Q) C_p V_{p; \mathbf{q}}^2, \quad (22)$$

$$(i!_1; q) = \chi_s^2(q) \chi_s^2(\frac{1}{2}q) \frac{X_{ss}(i!_1; q)}{A_F [\chi_s(Q)]^2}; \quad (23)$$

In Eq. (22), t is the effective transfer integral between nearest neighbors for quasiparticles, and we assume $e \sim j'$, $W = 8 \sim 40$ –50 meV and $!_q = 50$ meV. It is likely that $A_F = \chi_j = 0$ (1) and $\chi_s(0; Q) \chi_s^2(j) = 0$ (1). We note that $\chi_s(i!_1; q)$ is defined as a dimensionless quantity.

We examine the q , Q , and $!$ dependence of $!(+i0; q)$; $T = 0$ K is assumed in the $!$ sum of Eq. (19), and the softening around one of $2Q$'s or $2Q_0$, with $Q_0 = (-\pi/3a; -\pi/3a)$ in 2D-BZ, is considered; $2Q_0$ is equivalent to $(-\pi/2a; 0)$. Figure 1 shows $\text{Re}[\chi_s(+i0; q)]$ as a function of q^2 or q_x for several sets of Q and $! = A_F$. According to Fig. 1, $\text{Re}[\chi_s(+i0; q)]$ has a minimum around $2Q_0$ as a function of q ; it is likely that its minimum value is as large as (10–20) meV for $q^2 = 1$ and $! = 1$.

It is definite that $q^2 = 1$ in the critical region, and it is certain that $q < 10^3$ for cuprate oxides. Then, we propose that this second-harmonic effect of AF spin fluctuations is mainly responsible for the observed softening [11, 12] as large as (10–20) meV around $2Q$.

Since the softening is small when q^2 is large or AF spin fluctuations are not developed, it must be small in the so called over-doped cuprate oxides. When AF spin fluctuations are developed similarly or differently between $(-\pi/3a; -\pi/3a)$ and $(-\pi/3a; \pi/3a)$ because of the anisotropy of the Fermi surface within 2D-BZ, the softening must also occur similarly or differently between $(-\pi/2a; 0)$ and $(0; -\pi/2a)$. These two predictions are consistent with observations [11, 12].

The soft modes with $2Q$ correspond to the so called stripes and checker-boards observed at low temperatures [28, 29, 30, 31, 32]. Since a charge density wave (CDW) can appear following the complete softening, it should be examined if the stripes and checker-boards can be explained in terms of the CDW. In general, the $2Q$ component of the density of states, $\rho_{2Q}(!)$, as a function of $!$ is composed of symmetric and asymmetric ones with respect to the chemical potential or $! = 0$. The asymmetric one is large when CDW with $2Q$ is stabilized as a fundamental $2Q$ effect. According to an experiment [28], the symmetric one is larger than the asymmetric one. This contradicts the scenario of CDW, even if the softening of the $2Q$ modes is large and the $2Q$ fluctuations are well developed; the amplitude of CDW must be small, even if it is stabilized. On the other hand, the symmetric one is large when the $2Q$ modulation is due to a second-harmonic effect of a spin-density wave (SDW) with Q [33]. The observed almost symmetric $\rho_{2Q}(!)$ can be explained by the second-harmonic effect of SDW. When stripes and checker-boards are really static orders, stripes must be due to single- Q SDW and checker-boards must be due to double- Q SDW; magnetizations of the two waves must be orthogonal to each other in double- Q SDW [34, 35].

On the other hand, it is proposed [36] that a stripe or a checker-board at rather high temperatures must be an exotic ordered state, that is, a fluctuating state in a quan-

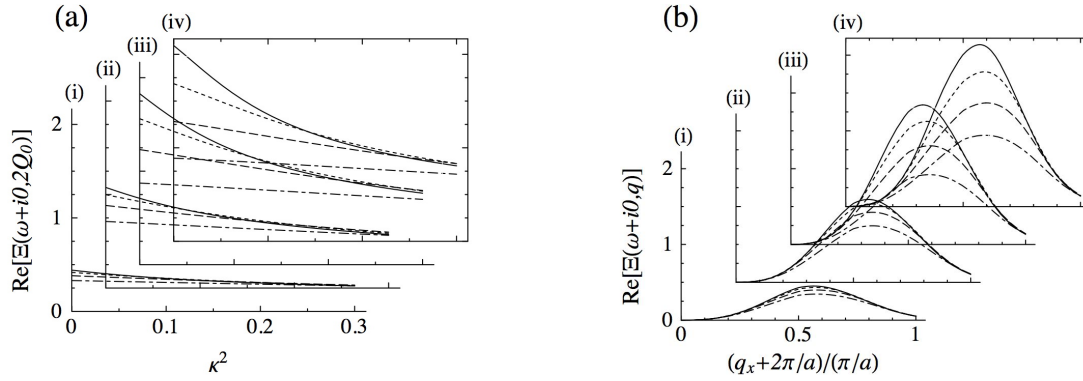


FIG. 1: (a) $\text{Re}[\chi(\omega + i0; 2Q_0)]$ as a function of κ^2 , with $Q_0 = (\frac{3}{2}a; \frac{3}{2}a)$, and (b) $\text{Re}[\chi(\omega + i0; q)]$ as a function of q_x ($\frac{2}{a} = a$, $q_x = a$) for $q_y = \frac{2}{a}$. For the anisotropy factor, (i) $\Delta_{AF} = 1$, (ii) $\Delta_{AF} = 10^{-2}$, (iii) $\Delta_{AF} = 10^{-1}$, and (iv) $\Delta_{AF} = 10^{-3}$. In each figure, solid, dotted, dashed, and dashed chain lines are for $\Delta_{AF} = 0.2, 0.4, 0.8$, and 1.6 , respectively.

tum disordered phase. It should be examined whether it is actually such an exotic state. Another possibility is that it is a rather normal low-energy fluctuating state, whose energy scale is as small as that of the soft phonons. The other one is that it is an disorder-induced SDW [27]; it must be a rather simple but inhomogeneous SDW.

According to Eq. (16), two mechanisms of attractive interactions, the spin-fluctuation one and the exchange-interaction one, are essentially the same as each other in Kondo lattices. However, the main part of the attractive interaction in cuprate oxides is the superexchange interaction rather than an interaction mediated by low-energy AF spin fluctuations. Since it is as strong as $J = (0.10 - 0.15)$ eV [5], observed high T_c can be easily reproduced. Although the strong electron-phonon interaction plays only a minor role in the formation of d-wave Cooper pairs, a small isotope shift of T_c can arise from the depression of superconductivity by the $2Q$ fluctuations.

In conclusion, the strong electron-phonon interaction arising from the modulation of the superexchange interaction by phonons is strong in cuprate oxides superconductors. It is responsible for the softening of the half breathing modes around $(\frac{1}{2}a; 0)$ and $(0; \frac{1}{2}a)$. In the critical region of SDW, where antiferromagnetic spin fluctuations are developed around nesting wave numbers Q of the Fermi surface, Cu-O bond stretching modes can also be soft around $2Q$. The softening is accompanied by the development of $2Q$ or $2Q - 2Q$ fluctuations, that is, stripe or checker-board fluctuations. However, the observation that in ordered stripe and checker-board states the $2Q$ component of the density of states is almost symmetric with respect to the chemical potential can never be explained by CDW with $2Q$ following the complete softening of the $2Q$ modes; they can be explained by the second-harmonic effect of SDW with Q .

Electronic address: fohkawa@phys.sci.hokudai.ac.jp

- [1] J. G. Bednortz and K. A. Müller, Z. Phys. B 64, 189 (1986).
- [2] F. J. Ohkawa, Jpn. J. Appl. Phys. 26, L652 (1987).
- [3] F. J. Ohkawa, J. Phys. Soc. Jpn. 56, 2267 (1987).
- [4] J. W. Loram, et al, Phys. Rev. Lett. 71, 1740 (1993).
- [5] K. B. Lyons, et al, Phys. Rev. Lett. 60, 732 (1988).
- [6] R. J. M. Cooney, et al, Phys. Rev. Lett. 82, 628 (1999).
- [7] L. Pintschovius and M. Braden, Phys. Rev. B 60, R15039 (1999).
- [8] R. J. M. Cooney, et al, Phys. Rev. Lett. 87, 077001 (2001).
- [9] L. Pintschovius, et al, Phys. Rev. B 64, 094510 (2001).
- [10] M. Braden, et al, Physica C 378-381, 89 (2002).
- [11] L. Pintschovius, et al, Phys. Rev. B 69, 214506 (2004).
- [12] D. Reznik, et al, Nature, 440, 1170 (2006).
- [13] P. D. Johnson, et al, Phys. Rev. Lett. 87, 177007 (2001).
- [14] T. Sato, et al, Phys. Rev. Lett. 91, 157003 (2003).
- [15] J. P. Franck, (Physical Properties of High Temperature Superconductors IV, ed. D. M. Ginsberg, World Scientific, Singapore, 1994) p189.
- [16] F. J. Ohkawa, Phys. Rev. B 70, 184514 (2004).
- [17] F. J. Ohkawa, Phys. Rev. B 59, 8930 (1999).
- [18] T. Takegahara, H. Harima, and Y. Yanase, Jpn. J. Appl. Phys. Part 1, 26, L352 (1987).
- [19] N. Hamada, et al, Phys. Rev. B 40, 4442 (1989).
- [20] O. K. Andersen, et al, Phys. Rev. B 49, 4145 (1994).
- [21] F. C. Zhang and T. M. Rice, Phys. Rev. B 37, R3759 (1988).
- [22] F. J. Ohkawa, Phys. Rev. B 44, 6812 (1991).
- [23] F. J. Ohkawa, J. Phys. Soc. Jpn. 60, 3218 (1991).
- [24] F. J. Ohkawa, J. Phys. Soc. Jpn. 61, 1615 (1992).
- [25] A. Georges and G. Kotliar, Phys. Rev. B 45, 6479 (1992).
- [26] Y. Kakehashi and P. Fulde, Phys. Rev. B 69, 45101 (2004).
- [27] F. J. Ohkawa, J. Phys. Soc. Jpn. 74, 3340 (2005).
- [28] C. Howard, et al, Phys. Rev. B 67, 014533 (2003).
- [29] M. Vershinin, et al, Science 303, 1995 (2004).
- [30] T. Hanaguri, et al, Nature 430, 1001 (2004).
- [31] N. Momono, et al, J. Phys. Soc. Jpn. 74, 2400 (2005).
- [32] K. McElroy, et al, Phys. Rev. Lett. 94, 197005 (2005).

- [33] F. J. Ohkawa, Phys. Rev. B 73, 092506 (2006).
- [34] F. J. Ohkawa, J. Phys. Soc. Jpn. 67, 535 (1998).
- [35] F. J. Ohkawa, Phys. Rev. B 66, 014408 (2002).
- [36] S. A. Kiverson, et al, Rev. Mod. Phys. 75, 1202 (2003).