

Observing the fluctuating stripes in high T_c superconductors

V. Cvetkovic,¹ Z. Nussinov,² S. Mukhin,³ and J. Zaanen¹

¹Instituut Lorentz voor de theoretische natuurkunde,
Universiteit Leiden, P.O. Box 9506, 2300 RA Leiden, The Netherlands

²Dept. of Physics, Washington University, St. Louis, MO 63160

³Theoretical Physics Department, Moscow Instituut for Steel & alloys, 119991 Moscow, Russia
(Dated: March 23, 2022)

Resting on the gauge theory of topological quantum melting in 2+1 dimensions, we predict that a superconductor characterized by crystalline correlations on a length scale large compared to the lattice carries a new collective mode: the massive shear photon. This mode is visible in the electrodynamic response and the ramification of our theory is that electron energy loss spectroscopy can be employed to prove or disprove the existence of dynamical stripes in cuprate superconductors.

The explanation of conventional superconductivity by the BCS theory belongs to the highlights of twentieth century physics. However, it appears that BCS is too primitive to address the high T_c superconductivity found in copper oxides. It is well established [1, 2, 3] that the superconducting liquid found in the cuprates is in competition with the so-called stripe phase [4], which can be viewed as a special kind of electron crystal. By studying the behavior of the spin [1, 5, 6] and phonon [7] system with inelastic neutron scattering an intriguing case emerged that these stripes survive in the form of transient correlations in the liquid up to rather large length (~ 10 nm) and time (~ 10 meV) scales. This affair is still quite controversial because the data can also be explained in other ways [8, 9, 10] and there is a need for a unique, experimentally accessible signature for the 'quantum stripes' [11]. In this Letter we present such a feature which we identified by studying the quantum field theory describing the topological quantum melting of crystals [12, 13, 14, 15]. We claim that there should be an extra propagating mode in the 'nearly ordered' superconductor, reflecting directly the presence of the transient stripe correlations.

One can already anticipate the presence of the extra mode by a simple quantum hydrodynamical consideration. Shear rigidity, the ability of the medium to respond reactively on a force acting in opposite directions on opposite sides of the medium, is uniquely associated with translational symmetry breaking, i.e., crystalline order. In a classical fluid one finds a viscous response on shear, but in the dissipationless superfluids there is no response to shear at all: these carry only compressional rigidity, turning into magnetic (Meissner) and electrical screening in the superconductor [16]. However, the 'nearly ordered' superconductor should still have the capacity to mediate shear forces at short distances and in analogy with the London penetration depth associated with magnetic forces, we call the characteristic length over which shear sources can make their presence felt in the medium the 'shear penetration depth' ξ_s . The natural velocity scale of reactive shear corresponds to the transversal phonon velocity of the crystal c_T , and

assuming a coherent quantum dynamics, one anticipates the presence of 'photon-like' excitation in the system carrying the shear stress, characterized by an energy gap at zero momentum, $\omega = c_T = \xi_s$: the 'massive shear photon'. We claim that such a mode has to exist in high T_c superconductors when the dynamical stripe interpretation is correct, which implies that ξ_s is a lattice constant. Moreover, a controlled mathematical description is available in this limit [12, 13, 14, 15], based on modern developments in quantum field theory [17, 18], making it possible to arrive at a detailed, quantitative prediction for an observable quantity: the massive shear photon should give rise to a pole in the electron-energy loss function at small momenta and energies (Fig. 1), revealing its identity through the characteristic dependence of its pole strength on momentum (Fig. 1, inset).

The applicability of the field theory requires some other conditions to be satisfied which are in fact implied by the assumption of a large crystalline correlation length. This means that the system has to be close to a continuous quantum phase transition between the crystal and the superconductor, and this implies in turn: (a) The liquid and the solid have to be microscopically similar and since the superconductor is a bosonic entity the crystal is also formed from bosons. It is about preformed pairs which can either form stripes or the superconductor [19]. (b) The transition from the crystal to the superconductor is first order, and to make possible a large shear length it appears necessary to assume that the superconductor is at the same time a quantum liquid crystal of either the smectic or nematic kind [20]. It turns out that with regard to the shear stress photon it does not make much of a difference [14] and we will present here results for the simpler nematic superconductor.

The theory can be viewed as the quantum generalization of the famous Nelson-Halperin-Young theory [22] of classical melting in two dimensions, based on the notion that the liquid crystal can be viewed as a crystal where topological defects (dislocations) have proliferated. The quantum version rests on a Kramers-Wannier duality arising in elasticity theory, first explored by Kleinert in the 1980's in the context of the classical problem in

three dimensions [17], and only recently implemented on the quantum level [12]. This earlier work contained some technical flaws (ignoring the relativistic character of the dislocation condensate, a faulty gauge \mathcal{L}) obscuring the view on the electrodynamic response. We present here a summary of the main steps of the correct derivation, and we refer for further details to Ref.'s [14, 15, 21].

In the 'borderline' limit $\epsilon \rightarrow 1$, the constituent bosons of the gaseous limit are no longer relevant and instead the work is done by the collective degrees of freedom: the phonons and the topological defects. The latter correspond to dislocations and disclinations, restoring the translational and rotational symmetry, respectively. In this language, liquid crystals are states where dislocations have proliferated, restoring translations, while disclinations are still massive excitations such that rotational symmetry remains broken [15, 18]. The phonons of a (Wigner) crystal of charged bosons in 2+1 Euclidean space-time dimensions are described by the following Lagrangian density, following [12] from the gradient expansion in terms of the displacement fields u^i ,

$$L_0 = \frac{1}{2} \epsilon u^a C_{ab} \partial_\mu u^b + iA^a \partial_\mu u^a + \frac{1}{4} F_{\mu\nu} F^{\mu\nu}; \quad (1)$$

where C_{ab} is a shorthand for the tensor of elastic moduli, now including the kinetic energy $(=2) \epsilon (u^a)^2$ (Greek indices label space-imaginary time directions $x; y; \dots$, Latin indices space directions $x; y$; notice that $C_{ab} = \rho \delta_{ab}$ where ρ is the mass density). For simplicity we limit ourselves to isotropic elasticity characterized by just a shear and compression modulus, and respectively, which are related by the Poisson ratio $\nu = \frac{1 + \epsilon}{2} \frac{c_L}{c_T}$. This defines the velocities $v_x = \frac{c_T}{\epsilon}$, $c_L = \frac{c_T}{2(1-\nu)}$, $c = c_T (1 + \nu) = \frac{c_T}{2}$, corresponding to the transversal and longitudinal phonon velocities of the crystal, while c is the compressional (real sound) velocity. The last term is the usual Maxwell term describing the electromagnetic fields while the electromagnetic vector potentials A^a couple to the elastic strains via the effective combination $A^a = (n_e e) [A_a - A_a]$ (e is the microscopic electrical charge, n_e is the density of charged particles). The scales associated with the electromagnetism are the plasma frequency $\omega_p = \sqrt{4 n_e e^2}$ and the Debye electrical screening length $\lambda_D = \frac{1}{\omega_p}$ and Debye momentum $q_D = \frac{1}{\lambda_D}$.

The crucial insight, due to Kleinert, is to turn this into a 'stress gauge theory' [17]. The first step is to use strain-stress duality, such that Eq. (1) becomes,

$$L_{dual} = \frac{1}{2} \frac{\hbar}{\epsilon} \frac{(\partial_\mu a)^2}{4} + \frac{(\partial_x^x \partial_y^y)^2 + (\partial_x^y + \partial_y^x)^2}{4} + \frac{(\partial_\mu a)^2}{4} + iA^a C_{ab} \partial_\mu a^b + \frac{1}{2} A^a C_{ab} \partial_\mu a^b + \frac{1}{4} F_{\mu\nu} F^{\mu\nu}; \quad (2)$$

in terms of the stress fields a^a , with the a^a 's having the status of canonical momenta. Notice that the antisymmetric components of the spatial stress vanish, $\partial_x^x \partial_y^y = 0$ (Ehrenfest constraint). The key is that this

is augmented by the law expressing the conservation of stress $\partial_\mu a^a = 0$ and this can be imposed in 2+1D by expressing the stresses in terms of the stress gauge fields,

$$\partial_\mu a^a = \epsilon B^a{}_\mu; \quad (3)$$

The magic of these stress-gauge fields is, that like in vortex duality [26], the sources of these stress gauge fields correspond to the non-integrable displacement field configurations [17],

$$L_{disl} = iB^a J^a; \quad J^a = \epsilon \partial_\mu u^a; \quad (4)$$

corresponding to the dislocation currents which can be factorized as $J^a = b^a J^a$: world-lines of dislocations with Burgers vector $b = (b_x; b_y)$. This implies in turn that $B^a J^a = (b^a B^a) J$. Hence, we arrive at a description of elasticity which is a close sibling of electromagnetism: the stress gauge fields ('stress photons') express the capacity of the elastic medium to propagate elastic forces, and the dislocations take the role of charged sources.

In the 2+1 space-time dimensions of relevance to cuprates, the miracle is that the quantum-nematic crystal can be equally well viewed as a 'dual superconductor' [12, 13], in close analogy with the superfluid-superconductor duality in 2+1 dimensional phase dynamics [23, 24, 26]. In the path-integral language, the 'dual nematic shear superconductor' corresponds to a tangle of dislocation worldlines in space-time. As we explained elsewhere [15], these describe either smectic or nematic quantum liquid crystals depending on the orientational ordering of the Burgers vectors: in the smectic, dislocations condense with their Burgers vectors oriented in one particular direction while in the nematic they condense with equal probability for their Burgers vectors to be oriented along all allowed directions [18]. As we are dealing with isotropic elasticity, we focus on the quantum hexatic, derived from the hexagonal crystal where the Burgers vectors are equally distributed along the six directions associated with the rotational D_6 symmetry.

The dislocation condensate is gauged by the stress gauge fields, and Eq. (4) implies a covariant derivative structure of the form $j(\partial_\mu - i\epsilon B^a) j^a$ where ϵ is the order parameter of the dislocation condensate; as we overlooked in the earlier work [12], it is vital to keep here the time derivatives given the relativistic nature of the dislocation condensate [26]. Elsewhere, we will present in detail the averaging procedure leading to the correct Higgs term in the stress-sector [14, 21]. We need a bare Higgs term for the quantum hexatic $L_{Higgs, bare} = \frac{1}{4} j_0^2 B^a B^a$, where j_0 is the expectation value of the disorder field. Both the glide [25] and Ehrenfest constraints have to be imposed on the bare Higgs term. The glide constraint is implemented via a Lagrange multiplier term $L_{glide} = i(J_x^y - J_y^x)$. This operation removes the compressional stress $\partial_x^x + \partial_y^y$ from the Higgs term, having also the effect of turning [12, 14, 21] the second sound velocity

of the condensate into the glide velocity' $c_g = c_T = \frac{p}{2}$. Subsequently, the Ehrenfest constrained is implemented by eliminating the antisymmetric stresses $\frac{y}{x}$ $\frac{x}{y}$ from the Higgs term. It is particularly convenient to represent the resulting Higgs term in a gauge invariant way [13],

$$L_H = \frac{1}{2} \frac{h^2}{4} \frac{2(\frac{x}{y} + \frac{y}{x})^2}{(\theta)^2 + c_g^2 (\theta_x)^2} + \frac{(\frac{x}{y} + \frac{y}{x})^2 (1 + c_g^2 (\theta_x)^2 = (\theta)^2)}{(\theta)^2 + c_T^2 (\theta_x)^2} i; \quad (5)$$

where we defined the 'shear Higgs mass' as $\mu = j_0 \frac{p}{2}$. This result is revealing: by counting derivatives it is immediately obvious that both the longitudinal ($\frac{x}{x}$ $\frac{y}{y}$) and transversal ($\frac{y}{x} + \frac{x}{y}$) shear stresses acquire a Higgs mass, while compressional stress is left unaffected.

Ignoring the EM fields, the elastic response of the neutral quantum hexatic can be straightforwardly calculated from Eqs. (2, 5) yielding similar results for the mode spectrum as we discussed for the smectic [15]. Let us now focus on the electromagnetic response, the only way to probe the system from the outside given that we deal with electrons. According to standard linear response theory, the electrodynamic response is governed by the dielectric tensor, which is completely parametrized in terms of transversal and longitudinal dielectric functions. For isotropic media, these can be expressed in terms of diagonal elements of the photon self-energy as [27] (with q the momentum and ω_n the Matsubara frequencies),

$$\epsilon_L(q; \omega_n) = 1 - \frac{(q; \omega_n)}{q^2}; \quad \epsilon_T(q; \omega_n) = 1 - \frac{\tau(q; \omega_n)}{\omega_n^2}; \quad (6)$$

in the Coulomb gauge for the EM fields, $\partial_a A_a = 0$. We observe that the total dual action Eq. (2, 5) can schematically be rewritten as,

$$L_{\text{dual}} = \frac{1}{2} B^a(G) \frac{1}{ab} B^b + i B^a g_a; \quad A + \frac{1}{4} F F \quad \frac{1}{2} A (\text{bare}) A; \quad (7)$$

where all the physics of the stress sector is lumped together in the fully dressed stress gauge field propagator $(G)_{ab}$. Given that the coupling between stress and EM gauge fields is linear, the photon self-energies are easily derived by straightforwardly integrating out the stress photons from Eq. (7),

$$(q; \omega_n) = \text{bare} \quad q_a; \quad (G(q; \omega_n))_{ab} g_b; \quad (8)$$

The coupling constants g_a and the bare are tabulated in Ref. [14]. It is a straightforward exercise to obtain explicit expressions for the dielectric functions Eqs. (6).

As we already noticed in the earlier work [12], from the transverse electromagnetic response it follows that the quantum hexatic is also an electromagnetic Meissner state: this should be surprising because this superconductivity does not involve off-diagonal long range order of the constituent bosons and the presence of the dual dislocation state turns out to be a sufficient condition.

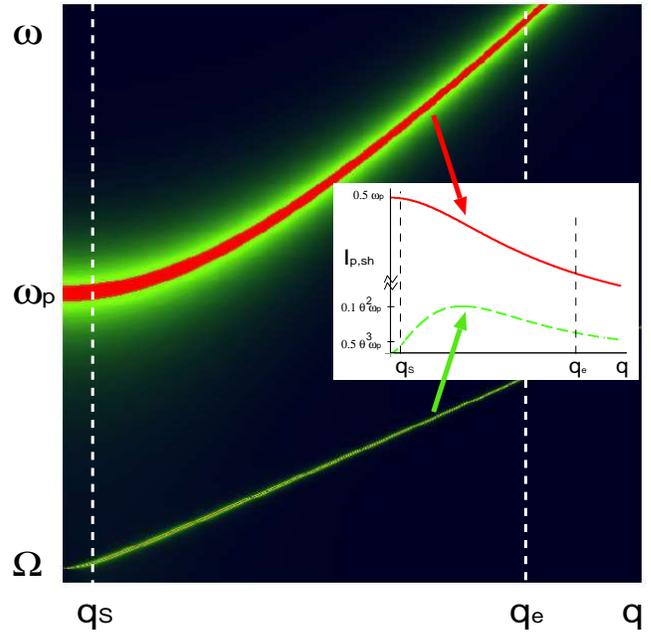


FIG. 1: The electromagnetic absorptions in the nearly ordered' superconductor as seen by electron-energy loss spectroscopy ($\text{Im}[\epsilon_L(q; \omega)]$) as function of frequency ω and momentum q . In this example, we take a typical Poisson ratio $\nu = 0.28$, characterizing the background' Wigner crystal, while the 'shear Higgs mass' $\mu = 0.05 \mu_p$ and shear penetration depth $\xi_s = 1/q_s = c_T =$ are taken to be representative for the situation cuprate superconductors ($\mu_p \sim 1$ eV, $\xi_s \sim 50$ nm, $\xi_s \sim 10$ nm). Besides the strong plasmon pole dominating the long wavelength dielectric response, we also find a weak absorption which corresponds to the massive shear photon giving away the presence of the 'dual shear superconductor', to be regarded as the unique fingerprint of a superconductor characterized by transient translational order extending over distances large compared to the lattice constant. In the inset, the weights of the plasmon (solid red, I_p) and the shear photon (dashed green, I_{sh}) in the electron energy loss spectrum as function of momentum are given. The latter can be used to isolate the shear photon in the experimental data. At long wavelengths ($q < q_s$) I_{sh} grows quadratically with momentum, with a prefactor set by the ratio of the shear mass and the plasmon frequency $\mu = \mu_p$, while it reaches a maximum at intermediate wavelengths ($q_s < q < q_e$).

In the remainder of this paper, we will focus on the longitudinal electromagnetic response for which

$$\epsilon_L = 1 + \frac{\mu_p^2 (c_g^2 q^2 + \mu^2)}{(c_g^2 q^2 - \omega^2) (c_L^2 q^2 - \omega^2) + \mu^2 (c^2 q^2 - \omega^2)}; \quad (9)$$

This is our main result: the longitudinal response is at least in principle accessible by experiment at the finite momenta which are required to see the incoherence of the transient order: all that is needed is a measurement of the electron energy loss spectrum corresponding to $\text{Im}[\epsilon_L(q; \omega)]$ in the relevant kinematic regime. The

existence of two modes is evident from the poles. In the limit $\kappa_s \rightarrow 1$, this expression has a universal status for small momenta; at larger momenta one has to account also for damping by perturbative mode couplings, single particle excitations, etcetera. In Fig. 1, we show an example of the loss spectrum which could be representative for cuprates assuming that the characteristic disorder scales revealed by the measurements of the spin fluctuations are rooted in the charge fluctuations discussed here: as compared to the plasma frequency ≈ 1 eV, the shear Higgs mass should be small, ($\approx 10^{-2}$ eV), while the characteristic length scale parameterized by κ_s should be ≈ 10 nm), consistent with a typical electronic velocity $v_F \approx 1$ eV/Å. The bottom line is that besides the intense plasmon one finds a weak feature at low energy in the loss spectrum, corresponding to the massive shear photon.

The weight of the shear photon has a non-trivial dependence on both the ratio $\kappa = \kappa_p$ as well as on the momentum q . This is easily computed from Eq. (9) and the results are summarized in inset of Fig. 1. In the 'liquid' long wavelength regime $q < q_c$, the weight of the shear photon $I_{sh}(q) = \frac{(1-\kappa^2)}{4(1-\kappa^2)} q^2 + O(q^4)$. I_{sh} has a maximum at intermediate momenta $q_{max} = \frac{2(1-\kappa^2)}{(3+3\kappa^2)} \approx 0.4q$ where the shear photon acquires a weight relative to the plasmon ($I_{sh}(q_{max}) = I_p$) $\approx \frac{(3-3(1-\kappa^2))}{(16+3\kappa^2)} \approx 0.16$ which we expect to be of order 0.1% in cuprates given that $\kappa \approx 0.05$: the electromagnetic weight of the shear photon is expected to be very small. This momentum and dependence of the electromagnetic strength of the shear photon can however be taken as its fingerprint, since it is rooted in the mechanism through which the shear photon becomes electromagnetically active. Both shear stress and dislocations forming the building blocks for the massive shear photon do not carry volume and are therefore electrically neutral. However, in the Wigner crystal and in the liquid, at distances small compared to κ_s , the plasmon carries like longitudinal phonon shear components at finite momenta. These shear components have to be 'removed' from the plasmon, turning it into the purely compressional mode of the liquid at distances large compared to κ_s . This causes a linear mode coupling between the plasmon and the shear photon, with the latter 'stealing' some electromagnetic weight from the former. This explains the strong dependence on κ , the characteristic maximum, and the vanishing of the weight at $q \rightarrow 0$ as even in the Wigner crystal, the plasmon turns into a purely compressional mode in the long wavelength limit.

What has to be done to detect the shear photon? It is clear that one needs a very high resolution measurement of the loss function, given its low energy (≈ 10 meV) and very small spectral weight. Optical methods are not suited because these measure at momenta which can be regarded as infinitesimal even on the scale of q_c . Obviously, the easy way is to measure directly the loss

function in this kinematic regime. This requires a millielectronvolt energy, and nanometer spatial resolution. Although such instruments are not available right now, it just seems to involve a relatively minor engineering effort to get into this regime: reflection (low energy) EELS has the resolution but for unknown reasons there are problems measuring the electronic response [31]; transmission (high energy) EELS is limited to a resolution of order of 100 meV but there seems much room for improvement using modern electron optics. The strongest contender appears to be resonant inelastic soft X-Ray scattering, where at present a major instrumental development program is unfolding aimed at reaching meV resolution.

ACKNOWLEDGMENTS

This work was supported by the Netherlands foundation for fundamental research of Matter (FOM).

Electronic address: vladimir@lorentz.leidenuniv.nl

- [1] J.M. Tranquada, Nature 375, 561 (1995).
- [2] T. Hanaguri et al., Nature 430, 1001 (2004).
- [3] P. Abbamonte et al., Nature Phys. 1, 155 (2005).
- [4] J. Zaanen, O. Gunnarsson, Phys. Rev. B 40, 7391 (1989).
- [5] J.M. Tranquada et al., Nature 429, 534 (2004).
- [6] S.A. Kivelson et al., Rev. Mod. Phys. 75, 1201 (2003).
- [7] D. Reznik et al., Nature 440, 1170 (2006).
- [8] V. Hinkov et al., Nature 430, 650 (2004).
- [9] I. Eremin, et al. Phys. Rev. Lett. 94, 147001 (2005).
- [10] J. Brinckmann, P.A. Lee, Phys. Rev. Lett. 82, 2915 (1999).
- [11] J. Zaanen, Nature 440, 1118 (2006).
- [12] J. Zaanen, Z. Nussinov, S.I. Mukhin, Ann. Phys. (NY) 310, 181 (2004).
- [13] H. Kleinert, J. Zaanen, Phys. Lett. A 324, 361 (2004).
- [14] V. Cvetkovic, Ph.D. thesis, University of Leiden (2006).
- [15] V. Cvetkovic, J. Zaanen, Phys. Rev. Lett., in press (available at <http://arxiv.org/cond-mat/0604639>).
- [16] X.G. Wen, A. Zee, Phys. Rev. B 41, 240 (1990)
- [17] H. Kleinert, Gauge fields in Condensed Matter, Vol. II: Stresses and Defects, Differential Geometry, Crystal Defects (World Scientific, Singapore, 1989).
- [18] F.A. Bais, C.J.M. Mathy, (available at <http://arxiv.org/cond-mat/0602101>).
- [19] S.R. White, D.J. Scalapino, Phys. Rev. Lett. 80, 1272 (1998).
- [20] S.A. Kivelson, E. Fradkin, V.J. Emery, Nature 393, 550 (1998).
- [21] V. Cvetkovic, et al., in preparation.
- [22] D.R. Nelson, B.I. Halperin, Phys. Rev. B 19, 2457 (1979); A.P. Young, Phys. Rev. B 19, 1855 (1979)
- [23] M.P.A. Fisher, P.B. Weichman, G. Grinstein, D.S. Fisher, Phys. Rev. B 40, 546 (1989).
- [24] J. Hove, A. Sudb, Phys. Rev. Lett. 84, 3426 (2000).
- [25] V. Cvetkovic, et al., Phil. Mag. B 86, 2995 (2006).
- [26] V. Cvetkovic, J. Zaanen, submitted to Phys. Rev. B (available at <http://arxiv.org/cond-mat/0511586>).

- [27] G.D. Mahan, *Many-particle Physics*, (Plenum Press, New York, 1981)
- [28] J. Friedel, *Dislocations*, (Pergamon press, New York, 1954).
- [29] J. Zaanen, et al., *Phil. Mag. B* 81, 1485 (2001).
- [30] Our 'roton like' shear photon could be related to the A_{1g} electronic peak as discussed by Y.J. Uemura [32]. However, there should be only Raman activity in the two shear photon channel which renders it to be a rather indirect measurement. Amazingly, Uemura's observation that the superconducting transition temperature $k_B T_c$ scales with a dynamical frequency scale finds a natural explanation in our 'orderly superconductor': T_c is actually set by the transition temperature of the dual shear superconductor and since this is a truly relativistic (Higgs) condensate, T_c is set by the Higgs mass and therefore $k_B T_c \sim \omega$!
- [31] K.H.G. Schulte, Ph.D. thesis, Groningen Univ. (2002).
- [32] Y.J. Uemura, *Physica B* 374, 1 (2006).