

Renormalization of the thermal conductivity of disordered d-wave superconductors by impurity-induced local moments

Brian M. Andersen^a and P. J. Hirschfeld^{a,b}

^aDepartment of Physics, University of Florida, Gainesville, Florida 32611-8440, USA

^bLaboratoire de Physique des Solides, Université Paris-Sud, 91405 Orsay, France

Abstract

The low-temperature thermal conductivity $\kappa_0 = T$ of d-wave superconductors is generally thought to attain a "universal" value independent of disorder at sufficiently low temperatures, providing an important measure of the magnitude of the gap slope near its nodes. We discuss situations in which this inference can break down because of competing order, and quasiparticle localization. Specifically, we study an inhomogeneous BCS mean-field model with electronic correlations included via a Hartree approximation for the Hubbard interaction, and show that the suppression of $\kappa_0 = T$ by localization effects can be strongly enhanced by magnetic moment formation around potential scatterers.

Key words: thermal conductivity, d-wave superconductivity, disorder, antiferromagnetic correlations, theory.

1. Introduction

Thermal conductivity measurements at low temperatures T in the superconducting state have played an important role in strengthening the case for a d-wave BCS-like description of quasiparticles in optimally doped cuprate superconductors. They are bulk probes of the superconducting state, unlike ARPES and STM, and can currently be performed at lower T than microwave experiments. One drawback is the need to separate phonon and electron contributions, but in the cuprate superconductors an asymptotic linear term, $\kappa_0 = T \text{ const}$ which can be attributed solely to quasiparticles is almost always present at the lowest temperatures. After theoretical predictions of the universality of low- T quasiparticle transport in nodal superconductors[1], experimental confirmation was obtained in a number of optimally doped materials[2]. According to the theory, which relies on the disorder-averaged self-consistent T -matrix approximation (SCTMA), the low- T thermal conductivity is given by

$$\kappa_0 = \frac{\gamma_0}{T}, \quad \frac{\gamma_0}{3} = \frac{k_B^2}{v} + \frac{v}{v_F}; \quad (1)$$

where v is the gap slope at the node, and v_F the Fermi velocity. This result has been shown to be insensitive to vertex corrections due to anisotropic scattering[3]. Since v_F is generally well-known, Eq.(1) has been used to extract the gap slope for a number of cuprates at lower doping as well[4], leading to the conclusion that v increases with underdoping[4]. This conclusion is in apparent contradiction to recent ARPES experiments[5], so it is worthwhile to examine physical effects outside the framework of the SCTMA which could lead to a suppression of $\kappa_0 = T$ and thereby to the possible erroneous conclusion based on Eq. (1) that v was increasing.

There are several effects known to lead to a suppression of $\kappa_0 = T$. Localization effects were discussed in this context in Ref. [6], and effects of bulk subdominant competing orders have been shown to suppress $\kappa_0 = T$ but do not immediately eliminate it, despite the removal of the d-wave nodes[7]. Here, we inves-

investigate the effects on $\kappa(T)$ by local impurity-induced moments relevant e.g. to the underdoped regime of $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ (LSCO) [9].

2. Magnetic correlations.

The model used to study disordered d-wave superconductors with magnetic correlations is:

$$\hat{H} = \sum_{ij} t_{ij} \hat{c}_i^\dagger \hat{c}_j + \sum_{ij} U_{ij} \hat{n}_i \hat{n}_j + \sum_i V_i \hat{n}_i : (2)$$

Here, $\hat{c}_i^\dagger$ creates an electron of spin $\uparrow$ on the site i on a two-dimensional lattice, ϵ_i is the chemical potential and $\hat{n}_i = \hat{c}_i^\dagger \hat{c}_i$ is the particle number operator. In general, magnetic order induced by U will compete with the superconducting order Δ_{ij} and lead to a bulk magnetic state above some critical U_{c0} . However, even for $U_c < U < U_{c0}$, disorder $V_i \neq 0$ caused by point-like impurities can induce localized $S = 1/2$ states with staggered magnetization. Here, U_c is the critical U necessary for local moment formation, and will in general depend on the impurity strength. In this paper we study impurity configurations with 2% randomly positioned point-like impurities of strength $V_i = 35t$ which is in the unitary limit. We have solved Eq. (2) selfconsistently on 40×40 lattices with hole doping $x = 12\%$, and calculated the electronic $\kappa(T)$ as outlined in Ref. [6].

In Fig. 1, we show the thermal conductivity averaged over 20 different random impurity configurations. For $U = 0$ the results agree well with those obtained previously for the dilute impurity limit [6]:

$\kappa(T) = \kappa_0 + T^2$, and the spatial inhomogeneity of Δ_{ij} only slightly modifies κ_0 as seen by comparing the SC and NSC results. For the bulk system we have $\Delta_{ij} = 0.4t$ on each link resulting in the universal value $\kappa_0 = 1/3 (v_F = v + v_{\text{SC}}) = 0.967$, which is nicely reproduced by the numerics. For $0 < U < U_c$, $\hat{n}_i \hat{n}_{i\pm 1} = \hat{n}_{i\pm 1} \hat{n}_i$ and U enters as a chemical potential shift which is compensated by a modified μ (to get $x = 12\%$) and consequently $\kappa(T)$ is identical to the $U = 0$ result. In the regime $U_c < U < U_{c0}$, local moments are formed and the corresponding thermal conductivity is also shown in Fig. 1. As seen, when U increases, $\kappa(T) = T$ (and $\kappa_0 = T$) is continuously suppressed, and $\kappa_0 = T$ will eventually vanish in the bulk insulating state around $U = U_{c0}$. The origin of the suppressed thermal conductivity can be traced to a

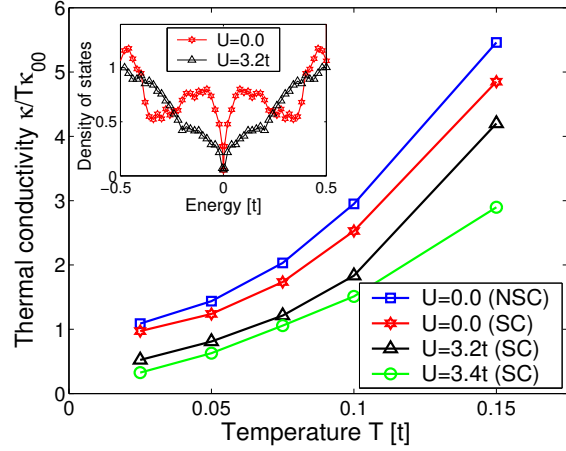


Fig. 1. $\kappa(T) = T \kappa_0$ versus T for 2% point-like impurities with $U = 0$ (non-selfconsistent (NSC) (□), selfconsistent (SC) (★)), $U = 3.2t$ (▲), and $U = 3.4t$ (●). The finite system size restricts us to study the region $T = t \leq 0.02$. Inset: Selfconsistent DOS for the cases $U = 0.0$ (★) and $U = 3.2t$ (▲).

reduction of the low-energy density of states (DOS) by the local magnetic moments as shown in the inset in Fig. 1. Thus, in impurity-driven local moment formation in the underdoped regime may explain the doping dependence of $\kappa_0 = T$ measured in LSCO [10]. In addition, since the low- T thermal conductivity is severely suppressed, measured values of κ_0 and a naive use of the "universal" clean d-wave result in Eq. (1) would lead to an erroneous estimate the superconducting gap.

Acknowledgements This work is supported by ONR grant N00014-04-0060.

References

- [1] P. A. Lee, Phys. Rev. Lett. 71, 1887 (1993); M. J. Graf et. al., Phys. Rev. B 53, 15147 (1996).
- [2] L. Taillefer et. al., Phys. Rev. Lett. 79, 483 (1997).
- [3] A. C. Durst and P. A. Lee, Phys. Rev. B 62, 1270 (2000).
- [4] M. Sutherland et. al., Phys. Rev. Lett. 94, 147004 (2005); X. F. Sun et. al., ibid 96, 017008 (2006).
- [5] J. Mesot et. al., Phys. Rev. Lett. 83, 840 (1999); Z.-X. Shen, private communication.
- [6] W. A. Atkinson and P. J. Hirschfeld, Phys. Rev. Lett. 88, 187003 (2002).
- [7] V. P. Gusynin and V. A. Miransky, Eur. Phys. J. B 37, 363 (2004).
- [8] P. J. Hirschfeld and W. O. Putikka, Phys. Rev. Lett. 77, 3909 (1996).
- [9] B. Lake et. al., Nature 415, 299 (2002).
- [10] J. Takeya et. al., Phys. Rev. Lett. 88, 077001 (2002).