

# Decoherence of Vortices with Continuously Variable Fractions of the Unit Flux Quanta in Two-Gap Superconductors

Jun Goryo, Singo Soma<sup>(a)</sup> and Hiroshi Matsukawa

<sup>1</sup> Department of Physics and Mathematics, Aoyama Gakuin University - 5-10-1, Fuchinobe, Sagamihara, 229-8558, Japan

PACS 74.20.De { Phenomenological theories (two-fluid, Ginzburg-Landau, etc.)

**Abstract.** – We propose a new stage of con-m ent-deco nm ent transition, which can be observed in laboratory. In two-gap superconductors (SCs), two kinds of vortex exist and each of them carries a continuously variable fraction of the unit flux quanta  $\phi_0 = hc/2e$ . The con ned state of these two is a usual vortex and stable in the low tem perature region of the system under a certain magnetic eld above  $H_{c1}$ . We see an analogy to quarks in a charged pion. An entropy gain causes two fractional vortices to be deco nned above a certain tem perature.

Introduction. { Topological defects furnish fascinating problems in physics, and keep attracting a lot of concerns. In general, they lead the quantization of physical quantities. Vortex is one of the most important example of topological defects [1]. It is well known that in superconductors (SCs), the requirement that the order parameter is a single-valued function guarantees the quantization of the magnetic flux of a vortex in the unit of  $\phi_0 = hc/2e$ .

The fractionalization of topologically quantized numbers have also been researched extensively in many different contexts [2]. Vortices with fractional fluxes have been discussed in p-wave superfluid <sup>3</sup>He [3] and d-wave SCs with a grain boundary [4] (See also a notice [5]). The fractionalization comes from unconventional structures of order parameters for these superfluid and SCs without any contradiction to their single-valued nature.

Here we discuss vortex state in two-gap SCs [6] which has two superconducting gaps on two separate Fermi surfaces. The two-gap superconductivity can be seen in a lot of SCs in solid state and has been paid special attention. MgB<sub>2</sub> is a recent typical textbook [7]. The possibility of the two-gap superconducting state is also pointed out in 2H-NbSe<sub>2</sub> [8], PrO<sub>4</sub>Sb<sub>12</sub> [9], Y<sub>2</sub>C<sub>3</sub> [10], Ca-doped YBCO [11], and liquid hydrogen [12]. The fractionalization of the flux quanta has also been discussed in two-gap SCs [13,14]. Tanaka considered a wire ring and showed that a trapped flux in the ring can be an arbitrary fraction of  $\phi_0$  [13]. Babaev considered a planar geometry and dis-

cussed the spontaneous fractional vortices associated with the Berezinskii-Kosterlitz-Thouless (BKT) transition [15] in the weak coupling limit of an internal Josephson interaction with respect to the relative phase of the two gap functions [14].

Besides these pioneering works, searching for the appearance of the fractional vortices under other setups is challenging and important since it gives new viewpoints of the problem and also new possibility for experimental discovery. In this paper, we propose a novel mechanism for the appearance of fractional vortices in the two-gap SCs. We consider the system under an applied magnetic eld and show that a vortex with the unit flux is divided into two vortices with continuously variable fraction of  $\phi_0$  by entropic effect. This phenomena can be seen as decoherence of two fractional vortices. We see that in the con ned state, two vortices behave like quarks in the charged pion [15]. Hence the present theory gives rise to a new stage of con-m ent-deco nm ent transition, which can be examined in laboratory.

Fractional vortices in a two-gap SC. { Let us discuss the property of fractional vortices in a type-II two-gap SC. We consider two gap functions  $\psi_L$  and  $\psi_S$  ( $j_L$ ,  $j_S$ ) opened on two different Fermi surfaces. Their pairing symmetry does not matter. We can consider not only s-wave but also unconventional pairing states [16]. We apply a magnetic eld along z-direction to a sample of thin lm geometry, i.e.,  $d < m$  in  $(\frac{L}{z}; \frac{S}{z})$ , where  $d$  is the sample thickness and  $\frac{L}{z}$  and  $\frac{S}{z}$  are the coherence lengths

<sup>(a)</sup> Present Address; (C) HONDA Motor Co., Ltd.

of the gap functions along z-direction. The gap functions are then expressed as,  $\psi_{L,S}(r) = j_{L,S}(r) \exp[i\phi_{L,S}(r)]$ ; where  $r$  is the two dimensional vector in the xy-plane. The Ginzburg-Landau (GL) free energy for two-gap system is straight extension of conventional one and given in Ref. [17]. We consider the GL free energy in the London limit, namely, we neglect the spacial dependence of  $j_L(r)$  and  $j_S(r)$  and obtain

$$F_{GL} = \int d^2r \left[ \frac{H^2}{8} + \frac{1}{8} \frac{1}{\lambda_L^2(T)} |A - \frac{0}{2} r \cdot \nabla_L|^2 + \frac{1}{8} \frac{1}{\lambda_S^2(T)} |A - \frac{0}{2} r \cdot \nabla_S|^2 + \frac{1}{2} \cos(\phi_L - \phi_S) \right]; \quad (1)$$

The characteristic points of this free energy are the presence of two typical length scales,  $\lambda_{L,S}(T) = \sqrt{4e^2 K_{L,S} j_{L,S}(T) / \hbar^2 c^2}$ , where  $K_{L,S}$  are the coefficients of the gradient terms in GL free energy, and of the Josephson-type interaction with a temperature dependent coupling  $\frac{1}{2} j_L(T) j_S(T)$ . This coupling causes the locking effect for the relative phase  $\phi_L - \phi_S$ . The equation of motion for the gauge field  $A$  is obtained from  $\delta F_{GL} / \delta A = 0$  as,

$$\nabla^2(r \cdot \nabla) H = -A + \frac{\lambda_L(T)}{2} r \cdot \nabla_L + \frac{\lambda_S(T)}{2} r \cdot \nabla_S; \quad (2)$$

where

$$\lambda^2(T) = \frac{1}{\frac{1}{\lambda_L^2(T)} + \frac{1}{\lambda_S^2(T)}} \quad (3)$$

is the London penetration depth, and

$$\lambda_{L,S}(T) = \sqrt{\frac{\hbar^2 c^2}{4e^2 K_{L,S} j_{L,S}(T)}}; \quad (4)$$

$$\lambda_L(T) + \lambda_S(T) = \lambda; \quad (5)$$

The following boundary conditions are imposed,

$$r \cdot \nabla \psi_{L,S}(r) = 0 \quad \text{at } r = R_{L,S}; \quad (6)$$

which would be relevant for the dilute vortex system with  $H \ll H_{c1}$ . The singlevaluedness of two gap functions is guaranteed except for  $R_L$  and  $R_S$  because of the 2 winding. From Eq. (2), we obtain the London equation for the two-gap case

$$\nabla^2(r \cdot \nabla) H = -H + H = 0 \quad \text{at } r = R_L, R_S; \quad (7)$$

This equation tells us important implications. When  $R_L = R_S = R$ , the equation reduces to the usual London equation  $\nabla^2(r \cdot \nabla) H = -H$  at  $r = R$ , and we have a vortex with the unit flux passing through  $R$ . When  $R_L \neq R_S$ , however, we have two vortices with  $\lambda_L(T)$  through  $R_L$  and  $\lambda_S(T)$  through  $R_S$ . It should be emphasized that  $\lambda_L(T)$  and  $\lambda_S(T)$  are fractions of

$\lambda$  and its ratio is determined by the ratio  $\lambda_L(T) = \lambda_S(T)$  (See, Eqs. (3), (4), and (5)). When  $\lambda_L(T) = \lambda_S(T)$  is limited to unity (such a limitation could come from the crystal symmetry, if we consider unconventional states in two dimensional irreducible representations in a system with single Fermi surface [16]), we have only the half unit flux vortex are possible to exist when  $\lambda_L(T) \neq \lambda_S(T)$ . It should be also emphasized that these fractional vortices vary continuously with  $j_L(T) \neq j_S(T)$ , which determines the ratio  $\lambda_L(T) = \lambda_S(T)$ .

There is a possibility to observe these fractional vortices when their separation is large enough. It would be small in the low temperature region due to the Josephson type interaction in the GL free energy (1), but is possible to be large in the high temperature regime in order to gain entropy. To check this scenario, we calculate the energy cost and the entropy gain for a certain configuration of two vortices with  $\lambda_L(T)$  and  $\lambda_S(T)$ .

Configuration energy. { We can eliminate the gauge field from Eq. (1) by using the equation of motion (2), and obtain the energy cost,

$$H_v = \int d^2r \left[ \frac{H^2}{8} + \frac{\lambda^2(T)}{8} (r \cdot \nabla)^2 + \frac{K(T)}{2} \text{fr}(\phi_L - \phi_S) g^2 \cos(\phi_L - \phi_S) \right]; \quad (8)$$

where  $K(T) = \frac{1}{2} j_L(T) j_S(T) g = 16^{-3} (T)^2$ . The vortex solution in the thin film geometry for the single gap SC has been investigated [18]. The extension to the two-gap case is straightforward. We introduce the effective London penetration depth in the thin film  $\lambda_e(T) = \lambda^2(T) d$  [18]. When  $\lambda_e(T)$  is comparable to the system size, we obtain

$$H_v = \sum_{i=L,S} \left[ \frac{1}{2} K(T) \ln \frac{R_L R_S}{\lambda_e(T)} + E_{rel} \right]; \quad (9)$$

where

$$\lambda_{L,S}(T) = \frac{\lambda^2(T)}{\lambda_{L,S}(T)} = 16^{-2} \lambda_e(T) \ln(\lambda_e(T) / \lambda_{L,S}(T))$$

are the creation energy for L- and S-vortices,  $\lambda_{L,S}(T) \hbar v_F^{L,S} = j_{L,S}(T)$  the coherence lengths of L- and S-gap functions, each of which should be in the same order of each vortex core, and  $v_F^{L,S}$  the Fermi velocities. The logarithmic term in the r.h.s is the magnetic interaction between two vortices, which is repulsive and shows the logarithmic behavior. The last term has a sine-Gordon form

$$E_{rel} = \int d^2r \left[ \frac{K(T)}{2} \text{fr}(\phi_L - \phi_S) g^2 \cos(\phi_L - \phi_S) \right]; \quad (10)$$

When  $\lambda = 0$ ,  $\lambda_e(T) = 0$  and  $E_{rel} / \ln(R_L R_S)$  [14]. Such a case can be applied to the superconductivity in liquid

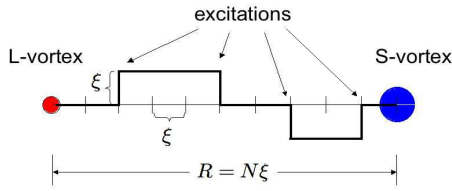


Fig. 1: A draw with four excitations of the string. The tick line denotes the string connecting two fractional vortices with a distance  $R$ .

hydrogen [12]. We go beyond the weak coupling limit of , which would be significant for the two-gap superconductivities in solid state, e.g., MgB<sub>2</sub> [7].

In Eq. (10), the spatial dependence of the relative phase loses the elastic energy. The Josephson-type term favors to be  $L_{st} = 2n$  for  $> 0$  and  $L_{st} = (2n+1)$  for  $< 0$ . But we have the boundary condition (6). There should be a line-like singularity between separated vortices associated with a  $2\pi$  jump of the relative phase. This "string" is the two-dimensional extension of the kink in the sine-Gordon model in one dimension [19]. Therefore, for large ,

$$E_{rel} = \epsilon_{st}(T) L_{st} + \text{const}; \quad (11)$$

where  $\epsilon_{st}(T) = \frac{1}{2} K(T) j(T) + O(1)$  is the string creation energy per a unit length and  $L_{st} = |R_L - R_S|$  is the length of the string. To minimize  $H_v, L_{st} \propto |R_L - R_S|$ . This indicates that there is a linear confinement potential between L- and S-vortices. We have also the two-dimensional Coulomb type repulsion. Then, two fractional vortices is analogous to massive "quarks" with "fractional electric charge"  $q_L$  and  $q_S$ , except for the spatial dimensionality [15]. The L-S confined state corresponds to the "charged pion" (total charge  $+e$  of pion corresponds to the unit flux  $\phi_0 = \frac{2\pi}{q_L + q_S}$  of L-S confined state).

Entropy, confinement, and deconfinement. { Let us examine the thermodynamic stability of the separated state with a distance  $R = |R_L - R_S| = N\xi > 0$ , where  $\xi = \max(\xi_L, \xi_S)$  and we refer it as the cut-off length of this system at the short length scale. We introduce an artificial square lattice with a constant  $\xi$  so that two vortices sit on one of the lattice axes. We discuss the free energy  $F = H_v - TS$ , where  $H_v$  is given in Eqs. (9) and (11). There are two contributions to the entropy  $S = S_{loc} + S_{st}$ , the former one comes from the location of two vortex cores  $S_{loc} \propto 2k_B \ln(\xi^2 / \Lambda^2)$  (  $\Lambda$ : the area of the system ) and the latter the string conformation  $S_{st}$ .

The lowest energy conformation of the string is the straight line connecting two vortices, where  $L_{st} = R$ . The kink-like conformations of the string would be thermally

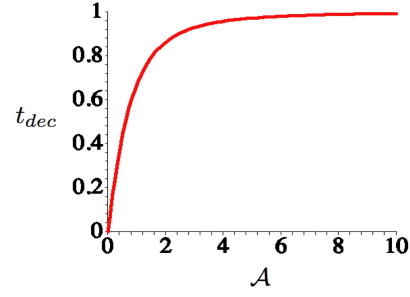


Fig. 2: A dependence of  $t_{dec} = T_{dec}/T_c$ , where  $T_{dec}$  is the deconfinement temperature.

excited and each excitations contributes to  $L_{st}$  (See, Fig. 1). As shown in Fig. 1, there are two kinds of excitations one of which is directed to the "upward" and the other "downward". The numbers of the upward and downward excitations are equal each other so that the string is ended by two fixed points (vortices) and we denote them as  $n$ .

We consider states with  $L_{st} \geq R$ , i.e.,  $n \geq N$ . By using the dilute approximation we obtain  $S_{st} = k_B \ln C_n N^n C_n \propto k_B (R/\xi) [\ln R - 2\ln 2]$ , where  $R = 2n\xi$ . We find the value of  $R$  which minimize  $F$  at fixed  $R$  is  $R_0(R) = 2R \exp[-\epsilon_{st}/k_B T]$ . Let us define a function  $F^*(R) = F(R; R_0(R))$ . We introduce  $a(T)$  as the value of the vortex distance  $R$  at the minimum of  $F^*(R)$  and it shows a diameter of the confined region of two fractional vortices. We obtain

$$a(T) = \frac{2K(T) = \epsilon_{st}(T)}{1 - \frac{2k_B T}{(T)_{st}(T)} \exp\left[-\frac{(T)_{st}(T)}{k_B T}\right]}; \quad (12)$$

Remind that the solution of  $1 - 2x \exp[-x] = 0$  is  $x = \text{LambertW}(-2) \approx 0.85$ . Then,  $a(T) \rightarrow 1$  [20] when

$$k_B T = \frac{(T)_{st}(T)}{\text{LambertW}(-2)} = 0; \quad (13)$$

The temperature that satisfies Eq. (13) would correspond to the deconfinement temperature and we refer it as  $T_{dec}$ . We emphasize that it is surely to be  $T_{dec} < T_c$ , where  $T_c$  is the gap opening temperature. The reason is that  $(T)_{st}(T)$  monotonically decreases to increase  $T$  and vanishes at  $T_c$ . Then, the lhs of Eq. (13) changes its sign once between the zero temperature and  $T_c$ . This statement is crucial since vortices cannot exist above  $T_c$  and the argument becomes inconsistent when  $T_{dec} > T_c$ .

We can also show the presence of  $T_{dec}$  when we consider states with  $L_{st} \gg R$ . Let us remind that the number of the conformation  $N_{con} = n^c$  for the  $n$ -step self-avoiding random walk, where  $c$  is a constant and equal to 3 for the 2D square lattice case. For the string with sufficiently large  $L_{st}$ ,  $N_{con}$  would be well approximated by the random walk result and we obtain  $N_{con} \propto L_{st}^c$ .

Table 1: Parameters which would be relevant for MgB<sub>2</sub> [7]

|                     |      |     |             |
|---------------------|------|-----|-------------|
| $\phi(0) = \phi(0)$ | 0.32 |     | 1.6/eV/cell |
| $d$                 | 10 Å | $x$ | 0.33        |
|                     | 2.2  | $k$ | 2.1         |

Then, the entropy of the string is proportional to  $L_{st}$  [15] and the string free energy  $F_{st} = \int_{st} (T) L_{st}$ , where the coefficient  $\int_{st} (T) = \int_{st} f_{st} (T) / k_B T = \int_{st} \ln g$  denotes the string tension and is positive in the low temperature region, i.e., fractional vortices are confined. Above a certain temperature,  $\int_{st} (T) < 0$ , namely, the string loses its tension and deconfinement occurs.  $T_{dec}$  is obtained from the equation  $\int_{st} (T_{dec}) = 0$ , which is equivalent to Eq. (13) when we take  $\beta = \exp[\text{LambertW}(2)] \approx 2.35$ .

To obtain  $T_{dec}$ , we should know the temperature dependence of two gaps. By using GL equation for two-gap superconductor with sufficiently large  $\lambda$  [17], we check that  $j_{L,S}(T) \neq j_{L,S}(0) = k \frac{1}{1+t}$ , where  $t = T/T_c$  and  $k$  is a constant which can be obtained numerically. Then, Eq. (13) becomes  $A \frac{1}{1+t} = \text{LambertW}(2)$ , where, in the case of  $K_S = K_L = 1$  [17],

$$A = \frac{0}{4^{5/2}} \frac{\phi(0)d}{\phi(0)} = k \frac{2x}{(x+1-x)^2};$$

and  $x = j_S(0) \neq j_L(0)$ . We see from Fig. 2 that  $T_{dec} = T_c$  depends on  $A$  strongly when  $A \rightarrow 0$  (1). By using the parameters in Table 1 which would be relevant for MgB<sub>2</sub>, we obtain  $A \approx 5.7$  and  $T_{dec} \approx 0.97$ .

We discuss BKT transition temperature associated with the usual vortex ( $L = S$ ) obtained from  $k_B T_{BKT} = \frac{1}{2} = 32 \frac{1}{e^2} (T_{BKT})$  (See, Eq. (1)). By using the parameters in Table 1, we see  $T_{BKT} \approx 0.90$ , which is lower than  $T_{dec}$  we have obtained. The present argument for  $T_{dec}$  is relevant for the dilute vortex system but does not include the multi-vortex effect which would be important above  $T_{BKT}$ , since a lot of them ally activated vortices and anti-vortices exist above  $T_{BKT}$  even in the system under the applied magnetic field considered here [21]. Then, the result would be corrected in this case. It should be noted that the coefficient  $A$  includes  $\phi(0)$  explicitly, on the other hand, the equation for  $T_{BKT}$  does not. So,  $T_{dec}$  can be lower than  $T_{BKT}$  in the system with sufficiently small  $\phi(0)$  and the present argument can be precise. It is well known that high- $T_c$  cuprates have rather small coherence length in the order of 10 Å. Therefore a two-gap superconductor Ca-doped YBCO [11] seems to be one of the best candidates to apply the present argument.

We comment on the relation to the renowned decoupling transition [22]. The renormalization group (RG) approach of the 2D sine-Gordon model discussed in Ref. [22] suggests that the cosine term in Eq.(10) becomes irrelevant above a certain temperature  $T^*$ , which indicates that the

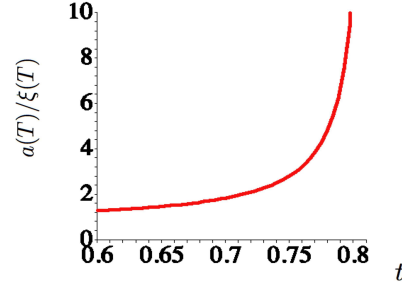


Fig. 3:  $a(T)$  for  $A = 1.6$ . In this case,  $T_{dec} \approx 0.91$ . Note that the unit of the vertical line is  $\int_{st} (T) = \phi(0) = \frac{1}{1+t}$ . Here, we use the relation  $a(0) \approx 0.3 \phi(0)$  obtained from Table 1.

decoupling between  $L$  and  $S$  occurs. The lower bound of  $T^*$  is obtained from  $T^* = 8 K (T_c) d$  in the limit  $\lambda \rightarrow 0$  [22]. This RG analysis takes into account string loops (closed strings) only, i.e., it is assumed that the relative phase  $L - S$  is single valued. The open string (See, Fig. 1) should be taken into account since it would be created by the thermal fluctuations. Actually, we have shown that the open string is stabilized by the entropic effect and the deconfinement occurs at  $T_{dec}$ . For sufficiently small  $A$ ,  $T_{dec}$  can be lower than the lower bound value of  $T^*$ , i.e., the deconfinement can occur even in the temperature region that the cosine term is relevant.

We also find that

$$\frac{a(T)}{a(0)} = 1 - \frac{2t}{A \frac{1}{1+t}} \exp \left( - \frac{1}{A \frac{1}{1+t}} \right); \quad (14)$$

where  $a(0) = 2 K (0) = \int_{st} (0)$ . The plot of  $a(T)$  is given in Fig. 3 for  $A = 1.6$ . We see that even in the confined phase it seems to be possible to observe each of fractional vortices in the region of large  $a(T)$  by using some appropriate vortex imaging techniques.

The authors are grateful to J. Akimitsu, E. Babaev, G. Baskaran, G. Blatter, H. Fukuyama, M. Hayashi, I. Herbut, T. Ishida, R. Ikeda, K. Ohashi, and Y. Tanaka for their critical comments. This work is financially supported by Grant-in-Aid for Scientific Research from Japan Society for the Promotion of Science under Grant Nos. 15540370, 16740226, and 18540381.

## REFERENCES

- [1] See, for example, P. G. de Gennes, Superconductivity in Metals and Alloys (Perseus Books, MA) 1999.
- [2] See, for reviews, A. J. Nieminen and G. W. Semenoff, Phys. Rep., 135 (1986) 99; R. B. Laughlin, Rev. Mod. Phys., 71 (1999) 863; G. E. Volovik, The Universe in a Helium Droplet (Oxford University Press, Oxford) 2003.

- [3] G. E. Volovik and V. P. Mineev, *Pis'ma Zh. Exp. Teor. Fiz.*, 24 (1976) 605 [*JETP Lett.*, 24 (1976) 561]
- [4] M. Sgrist, D. B. Bailey, and R. B. Laughlin, *Phys. Rev. Lett.*, 74 (1995) 3249; D. B. Bailey, M. Sgrist, and R. B. Laughlin, *Phys. Rev. B*, 55 (1997) 15239
- [5] The fractional vortex is defined as a vortex with a flux less than  $\phi_0=2$  in Ref. [4], while less than  $\phi_0$  in this paper.
- [6] H. Suhl, B. T. Matthias, and L. R. Walker, *Phys. Rev. Lett.*, 12 (1959) 552
- [7] T. Muranaka et al, *Frontiers in Superconducting Materials*, edited by A. V. Narlikar (Springer-Verlag, Berlin) 2005
- [8] T. Yokoya et al, *Science*, 294 (2001) 2518
- [9] G. Seyfarth et al, *Phys. Rev. Lett.*, 95 (2005) 107004; M. Yogi et al, *J. Phys. Soc. Jpn.*, 75 (2006) 124702.
- [10] S. Akutagawa et al, (unpublished).
- [11] J. H. Ngai et al, *cond-mat/0703423*.
- [12] N. W. Ashcroft, *J. Phys.*, A 129 (2000) 12.
- [13] Y. Tanaka, *J. Phys. Soc. Jpn.*, 70 (2001) 2844; *Phys. Rev. Lett.*, 88 (2002) 017002.
- [14] E. Babaev, *Phys. Rev. Lett.*, 89 (2002) 067001; *Nucl. Phys. B*, 686 (2004) 397; E. Babaev, A. S. Sudbo and N. W. Ashcroft, *Nature*, 431 (2004) 666.
- [15] J. B. Kogut, *Rev. Mod. Phys.*, 51 (1979) 659.
- [16] M. Sgrist and K. Ueda, *Rev. Mod. Phys.*, 63 (1991) 239
- [17] M. E. Zhitomirsky and V. H. Dao, *Phys. Rev. B*, 69 (2004) 054508
- [18] J. PEARL, *App. Phys. Lett.*, 5 (1964) 65
- [19] T. H. R. Skyrme, *Proc. Roy. Soc.*, A 247 (1958) 26.
- [20] Actually,  $a(T)$  would have a cut off determined by the inverse of the square root of the applied magnetic field.
- [21] S. Doniach and B. A. Huberman, *Phys. Rev. Lett.* 42, 1979 (1169) .
- [22] J. P. Rodriguez, *J. Phys. Cond. Mat.*, 9 (1997) 5117; *Phys. Rev. B*, 62 (2000) 9117; R. Goldin and B. Horowitz, *ibid.*, 72 (2005) 024518; S. Coleman, *ibid.*, 11 (1975) 2088; S. E. Korshunov, *Europhys. Lett.*, 11 (1990) 757.