

Rheological Study of Transient Networks with Junctions of Limited Multiplicity

Tsutomu Indei*

*Fukui Institute for Fundamental Chemistry,
Kyoto University, Kyoto 606-8103, Japan*

Tel: +81-75-711-7907

Fax: +81-75-781-4757

Abstract

Viscoelastic and thermodynamic properties of transient gels comprised of telechelic polymers are theoretically studied. We extend classical theories of transient networks so that correlations among polymer chains through the network junctions are taken into account. This extension enables us to investigate how rheological quantities, such as viscosity and elastic modulus, are affected by the association equilibrium conditions, and how these quantities are related to the aggregation number of junctions. We present a theoretical model of transient networks with junctions comprised of variable number of hydrophobic groups on the chain ends. Elastically effective chains are defined as the chains whose both ends are associated with end groups on other chains. It is shown that the dynamic shear moduli are well described in terms of the Maxwell model characterized by a single relaxation time and the high-frequency plateau modulus as in the classical theories, but the reduced dynamic shear moduli depend on the polymer concentration and temperature through the reduced concentration c given as a combination of the association constant and the volume fraction of end groups. The plateau modulus and the zero-shear viscosity rise nonlinearly with increasing c when c is small, but they are proportional to c for higher c . The relaxation time also increases as c increases due to the presence of pairwise junctions at small c .

Keywords

thermoreversible gels / associating polymers / transient network theory / junction-multiplicity / linear rheology

*Electronic address: indei@fukui.kyoto-u.ac.jp

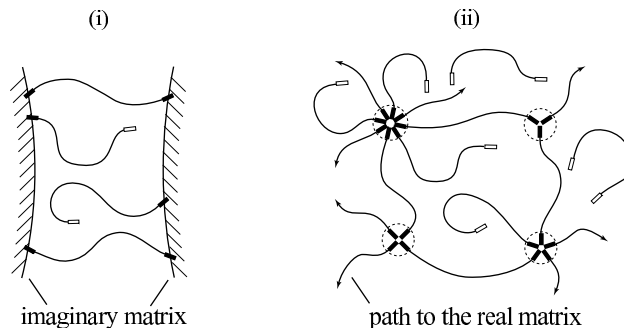


FIG. 1: (i) Drawing of the "network" postulated in the conventional transient network theories. Each chain interacts with fictitious matrix. (ii) Schematic of the network supposed in the present series of papers. Chains interact with each other through dissociation/association among end groups. Arrows indicate paths to the (real) network matrix.

I. INTRODUCTION

In some polymer gels, junctions can break and recombine in thermal fluctuations or under external forces. They are called transient gels or physical gels. Most transient gels exhibit thermoreversible properties, i.e., they reversibly change state between gel and sol as thermodynamic conditions vary. Typically, polymers forming such transient thermoreversible gels carry a small fraction of interacting groups capable of forming bonds due to associative forces such as hydrophobic interaction, ionic association, hydrogen bonding, cross-linking by crystalline segments and so on. Among them, hydrophobically-modified water-soluble amphiphilic polymers have attracted widespread interest in recent years [1]. Amphiphilic properties stem from the hydrophilicity of the main chain and the hydrophobicity of the associative functional groups embedded in the main chain. Attractive force among the functional groups induces the formation of transient network in aqueous media above a certain concentration.

One of the simplest class of associating polymers capable of forming a network is the linear polymers having functional groups only at both ends. They are called telechelic polymers. Rheological properties of these polymers have been well studied from experimental [2, 3, 4, 6, 9, 10, 11, 12, 13, 14, 15, 16, 17, 18] as well as theoretical [19, 20, 21, 22, 23, 24, 25, 26] point of view with an intention of obtaining a fundamental understanding of associating polymer systems. Examples of telechelic polymers are poly(ethylene oxide) (PEO) chains end-capped with short alkyl groups [2, 3, 4, 5, 6, 7, 8, 9, 10, 12, 13, 15, 16, 25], perfluoroalkyl end-capped PEO [11, 14] and telechelic poly(*N*-isopropylacrylamide) (PNIPAM) carrying octadecyl groups at both ends [18]. They exhibit characteristic rheological properties such as temperature-frequency superposition onto a Maxwell fluid [3], breakdown of the Cox-Merz rule [3, 16], strain hardening [11, 16], shear thickening at relatively low shear rate followed by shear thinning [2, 3, 6, 11, 12], etc [16, 17].

In order to investigate molecular origin of these phenomena, Tanaka and Edwards (referred to as TE in the following) developed the theory for transient networks [20, 21] by extending the kinetic theory for reacting polymers [27]. Under the Gaussian chain assumption, TE succeeded to explain, for example, the linear response to the small oscillatory deformation described in terms of the Maxwell model with a single relaxation time. Shear thickening can be also explained by extending the TE theory so that the tension along the middle chain contains a nonlinear term [26]. We can also treat trifunctional associating polymers carrying two different species of functional groups by an straightforward extension of the TE theory [28, 29]. Several theories to treat dynamic properties of transient networks have also been presented up to now. For example, Wang [22] took isolated chains into consideration, and Vaccaro and Marrucci [24] incorporated the effect of incomplete relaxation of detached chains.

In all transient network theories proposed so far [20, 21, 22, 23, 24, 26, 28, 29], it is implicitly assumed that a fictitious network exists a priori (see Fig.1 (i)). This network matrix is not a substantial one in a sense that it itself does not contribute to the elasticity of the system, but it plays a role as a substrate of the chains on which association/dissociation of the end groups takes place. Chains whose both ends are connected with this matrix are supposed to be elastically effective. Correlations among chains are not taken into account in this treatment because each chain interacts only with such matrix, and consequently the concentration dependence of the rheological quantities cannot be properly predicted; the elastic modulus, viscosity etc are simply proportional to the polymer concentration. Furthermore, it is difficult by definition to incorporate the information about the network junction such as the aggregation number and to study the effect of surfactants added to the system.

In this series of papers, we remove this unfavorable assumption and develop a theory of thermoreversible transient networks formed by multiple junctions comprised of any number of functional groups as depicted in Fig.1 (ii). This modification enable us to deal with the sol/gel transition phenomenon and to predict the proper concentration

dependence of the dynamic shear moduli G' and G'' in the postgel regime of the solution. In the following, we refer to the number of functional groups per a junction (so called aggregation number) as the junction multiplicity according to ref. [30].

In this paper, we formulate a theory of transient network formed by thermoreversible multiple junction. Elastically effective chains, or active chains, are defined only in local, i.e., chains whose both ends are associated with other functional groups are supposed to be elastically effective. We derive a formula to calculate G' and G'' as a function of the frequency ω of applied small oscillation, and analyze how G' and G'' characterized by the high-frequency plateau modulus G_∞ , zero-shear viscosity η_0 and relaxation time τ depend on the polymer concentration. It is shown that G_∞ and η_0 increase nonlinearly with concentration at lower concentration and τ also increases with concentration corresponding to experimental observation [3, 9, 25]. In equilibrium, we find the following mass action law: $\psi_k = K_k(\psi_1)^k$ under the assumption that the connection rate of a functional group to a junction with the multiplicity k (called k -junction) is proportional to the number of functional groups in k -junctions. (ψ_k is the volume fraction of the functional groups belonging to k -junctions, and K_k is the reaction constant for the formation of a k -junction from k isolated functional groups.) This relation is equivalent to the multiple-equilibrium condition that Tanaka and Stockmayer derived in the theory of associating polymer solutions [30]. In order to investigate the critical behavior of G' and G'' near the gelation point, we need to define active chains taking account of global structure of the network. Studies on the basis of this definition for active chains will be presented in the following paper. Looped chains, and then flower micelles comprised of loops, are assumed to be absent for simplicity throughout this series. Effects of the competition between the intra- and intermolecular association at a junction as well as the effect of additives such as surfactants [31, 32, 33] will be investigated in the forthcoming papers.

This paper is organized as follows. In section II, we will derive time development equations for the distribution function of chains whose one end is incorporated into a k -junction while the other end is belonging to a k' -junction. Kinetic equations for these chains will be also derived in this section. In section III, we will introduce the dissociation/association rates of functional groups. Equilibrium distribution of the junction multiplicity and its mean value as a function of polymer concentration will be discussed in section IV. In section V, we will study linear rheology of the system. Finally, a relation between the present theory and the TE theory will be discussed in section VI.

II. TIME DEVELOPMENT OF TRANSIENT NETWORKS FORMED BY JUNCTIONS WITH VARIABLE MULTIPLICITY

A. Assumptions

We consider athermal solutions of linear polymers (or primary chains) carrying two functional groups at their both ends. Here, functional group is a groups or a short segment of the primary chain that can form aggregates (or junctions) in a solution through the noncovalent bonding. Primary chains can associate with each other in a solution through the aggregation of functional groups, while they can be detached from others due to thermal agitation or macroscopic deformations applied to the system. In equilibrium, thermodynamic conditions (temperature, polymer concentration etc) determine the association/dissociation rate of functional groups and hence the amount of junctions in the solution. In this sense, these junctions are thermoreversible. Above a certain polymer concentration, primary chains eventually construct a macroscopic network physically cross-linked by these junctions. Thus the network we are going to study is also thermoreversible as well as transient. The association-dissociation reaction of functional groups is assumed to occur step by step.

We allow junctions to be formed by any number of functional groups. According to Tanaka and Stockmayer [30], the number of functional groups forming a junction is referred to as the junction multiplicity. We also call the junction of the multiplicity k ($=1, 2, 3, \dots$) the k -junction, i.e., 1-junction is an unreacted group (or a functional group which remains unassociated), 2-junction is a pairwise junction, etc. For a while, let us identify a head and a tail of each chain for convenience by marking one end of each chain temporarily. Of course, this does not affect mechanical properties of our system. Then we term the primary chain whose head is incorporated into a k -junction whereas tail is a member of the distinct k' -junction as the (k, k') -chain. For instance, $(k, 1)$ -chain ($k \geq 2$) is a (primary) dangling chain whose tail is not connected with any other groups, and $(1, 1)$ -chain is an isolated chain.

We assume that chains are elastically effective when their both ends are connected with any other functional groups. These chains are called active chains. Active chains are assumed to deform affinely to the macroscopic deformation applied to the system. Note that active chains are defined only in local in a sense that chains are elastically effective irrespective of whether functional groups they are connected with belong to the infinite network or not. As shown below, we can study the sol/gel transition phenomenon only in unsatisfactory in this theoretical framework. The definition of active chains will be extended in the following paper so that global information of the network can be included. The Rouse relaxation time τ_R of the primary chain is assumed to be much smaller than the characteristic

time of a macroscopic deformation applied to the system and the lifetime of active chains, so that chains in elastically non-effective (i.e., dangling and isolated) states are virtually in an equilibrium state even under flow. The primary chains are assumed to be Gaussian with uniform molecular weight M (number of repeat units is N) that is smaller than the entanglement molecular weight.

B. Time-Development Equation for Active Chains

Let $F_{k,k'}(\mathbf{r}, t)d\mathbf{r}$ be the number of (k, k') -chains at time t per unit volume having the head-to-tail vector $\mathbf{r} \sim \mathbf{r} + d\mathbf{r}$. Then the total number $\nu_{k,k'}(t)$ of (k, k') -chains (per unit volume) is given by

$$\nu_{k,k'}(t) = \int d\mathbf{r} F_{k,k'}(\mathbf{r}, t). \quad (\text{II.1})$$

Dangling and isolated chains are the Gaussian chain irrespective of time, that is,

$$F_{1,k'}(\mathbf{r}, t) = \nu_{1,k'}(t)f_0(r) \quad (\text{for } k \geq 1), \quad (\text{II.2a})$$

$$F_{k,1}(\mathbf{r}, t) = \nu_{k,1}(t)f_0(r) \quad (\text{for } k' \geq 1), \quad (\text{II.2b})$$

where

$$f_0(\mathbf{r}) \equiv \left(\frac{3}{2\pi Na^2} \right)^{3/2} \exp \left(-\frac{3|\mathbf{r}|^2}{2Na^2} \right) \quad (\text{II.3})$$

is the probability distribution function (PDF) that the chain takes the end-to-end vector \mathbf{r} (a is the length of a repeat unit of the chain). The number of chains whose head is incorporated into a k -junction is given by

$$\chi_k^{(h)}(t) = \sum_{l \geq 1} \nu_{k,l}(t), \quad (\text{II.4})$$

while the number of chains whose tail is belonging to a k -junction is

$$\chi_k^{(t)}(t) = \sum_{l \geq 1} \nu_{l,k}(t). \quad (\text{II.5})$$

Then the number of chains whose one end, irrespective of whether it is a head or tail, is incorporated into a k -junction (called k -chain hereafter) can be expressed as

$$\chi_k(t) = \frac{1}{2} \left(\chi_k^{(h)}(t) + \chi_k^{(t)}(t) \right). \quad (\text{II.6})$$

A factor $1/2$ is necessary to avoid double counting of the k -chain. Our aim in this section is to find time-development equations that $F_{k,k'}(\mathbf{r}, t)$, $\nu_{k,k'}(t)$ and $\chi_k^{(\cdot)}(t)$ (dot represents h or t) obey when a macroscopic deformation represented by the rate of deformation tensor $\hat{\kappa}(t)$ is applied to the system.

Firstly, we derive the equation for active (k, k') -chains ($k, k' \geq 2$). According to the affine deformation assumption, $F_{k,k'}(\mathbf{r}, t)$ satisfies the following evolution equation:

$$\frac{\partial F_{k,k'}(\mathbf{r}, t)}{\partial t} + \nabla \cdot (\dot{\mathbf{r}}(t) F_{k,k'}(\mathbf{r}, t)) = W_{k,k'}^{(h)}(\mathbf{r}, t) + W_{k,k'}^{(t)}(\mathbf{r}, t) \quad (\text{for } k, k' \geq 2), \quad (\text{II.7})$$

where $\dot{\mathbf{r}}(t) = \hat{\kappa}(t)\mathbf{r}$ is the rate of deformation of the head-to-tail vector \mathbf{r} of the active chain. The first (or the second) term in the right-hand side of (II.7) is a reaction term that describes the net increment of $F_{k,k'}(\mathbf{r}, t)$ per unit time due to association-dissociation reactions among the head (or tail) of the (k, k') -chain and the functional groups on the other chains. The kinetic equation for active (k, k') -chains is then given by integrating both sides of (II.7) with respect to \mathbf{r} . We find

$$\frac{d\nu_{k,k'}(t)}{dt} = w_{k,k'}^{(h)}(t) + w_{k,k'}^{(t)}(t), \quad (\text{II.8})$$

where

$$w_{k,k'}^{(\cdot)}(t) \equiv \int d\mathbf{r} W_{k,k'}^{(\cdot)}(\mathbf{r}, t) \quad (\text{for } k, k' \geq 2). \quad (\text{II.9})$$

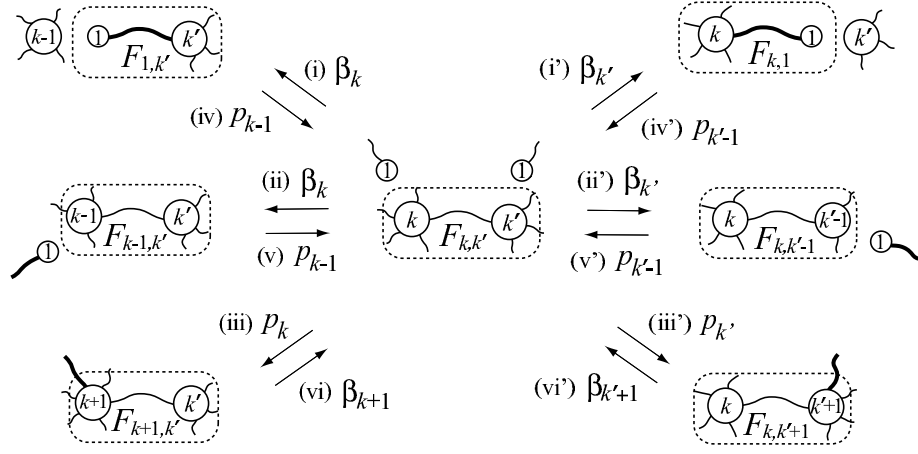


FIG. 2: Reaction between the functional group on the (k, k') -chain and the functional group on the other chains. Circles indicate junctions and lines emanating from circles represent the primary chains. The letter inside the circle denotes the junction multiplicity. Smaller circles with the number 1 inside represent unreacted functional groups. Chains depicted by bold lines participate in the reaction. The number of (k, k') -chains change if one of these (stepwise) reaction occur. Reaction rates are shown near arrows for each reaction.

The reaction terms $W_{k,k'}^{(h)}(\mathbf{r}, t)$ and $w_{k,k'}^{(h)}(t)$ are derived according to the following procedure. The number of active (k, k') -chains decreases if^a

- (i) the head of the (k, k') -chain is dissociated from a k -junction, or
- (ii) a functional group on the other chain is dissociated from the head of the (k, k') -chain, or
- (iii) an unreacted functional group connects with the head of the (k, k') -chain.

On the other hand, the number of active (k, k') -chains increases if

- (iv) the unreacted head of the $(1, k')$ -chain is connected with $k-1$ -junction, or
- (v) the unreacted group of the other chain is connected with a head of the $(k-1, k')$ -chain, or
- (vi) a functional group on the other chain is disconnected from the head of the $(k+1, k')$ -chain.

These reactions (i) \sim (vi) are schematically depicted in Fig.2 where the corresponding reactions regarding the tail of the (k, k') -chain, (i') \sim (vi'), are also shown. Now we introduce the probability (or dissociation rate) $\beta_k(r)$ that a functional group incorporated into the k -junction ($k \geq 2$) detaches itself from the junction per unit time. In general, it is an increasing function with respect to the end-to-end length $r = |\mathbf{r}|$ of the k -chain [20]. Then the increment of (k, k') -chains with the head-to-tail vector \mathbf{r} due to the reactions (i) and (ii) per unit time is written as

$$\int \prod_{s=1}^{k_h} d\mathbf{r}_s^{(h)} \int \prod_{s'=1}^{k_t} d\mathbf{r}_{s'}^{(t)} \left(\beta_k(r) + \sum_{s''=1}^{k_h} \beta_k(r_{s''}^{(h)}) + \sum_{s''=1}^{k_t} \beta_k(r_{s''}^{(t)}) \right) \mathcal{F}_{k,k'}(\mathbf{r}, \{\mathbf{r}^{(h)}\}, \{\mathbf{r}^{(t)}\}; t), \quad (\text{II.10})$$

where the first term $\beta_k(r)$ in the parenthesis stems from the reaction (i) while the second and the third terms are originated from the reaction (ii). $\mathcal{F}_{k,k'}(\mathbf{r}, \{\mathbf{r}^{(h)}\}, \{\mathbf{r}^{(t)}\}; t)$ is the number of (k, k') -chains with the head-to-tail vector \mathbf{r} whose head is incorporated into the k -junction formed by k_h heads of the other chains each having the head-to-vector $\mathbf{r}_1^{(h)}, \dots, \mathbf{r}_{k_h}^{(h)}$ and k_t tails of the other chains each having the head-to-vector $\mathbf{r}_1^{(t)}, \dots, \mathbf{r}_{k_t}^{(t)}$ (see Fig.3). Note that a relation $(k_h + 1) + k_t = k$ holds. We can express $\mathcal{F}_{k,k'}$ as follows:

$$\mathcal{F}_{k,k'}(\mathbf{r}, \{\mathbf{r}_s^{(h)}\}, \{\mathbf{r}_{s'}^{(t)}\}; t) = C_{k_h} F_{k,k'}(\mathbf{r}, t) \prod_{s=1}^{k_h} f_k^{(h)}(\mathbf{r}_s^{(h)}, t) \prod_{s'=1}^{k_t} f_k^{(t)}(\mathbf{r}_{s'}^{(t)}, t), \quad (\text{II.11})$$

^a We are considering reactions regarding the head of the (k, k') -chain. The multiplicity of the junction to which its tail is connected is assumed to be fixed at k' .

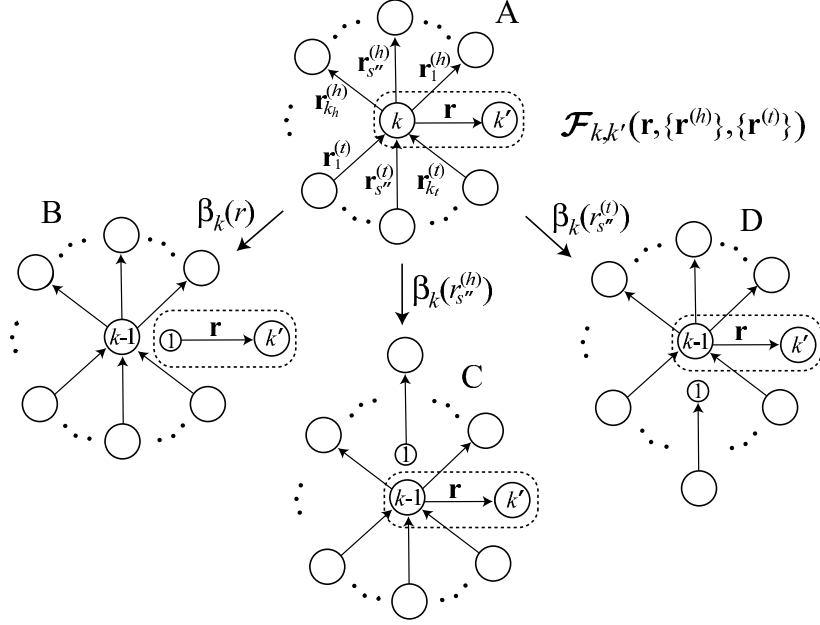


FIG. 3: Explanation of eq. (II.10). Circles stand for junctions. Arrows connecting two junctions represent the head-to-tail vector of the chain (chains are not shown for simplicity). The number of the state A is given by (II.11). The first term in the parenthesis of (II.10) describes the transition from the state A to the state B, while the second (or the third) term in the parenthesis of (II.10) represents the transition from A to C (or to D).

where

$$f_k^{(h)}(\mathbf{r}, t) \equiv \frac{\sum_{l \geq 1} F_{k,l}(\mathbf{r}, t)}{\sum_{l \geq 1} \nu_{k,l}(t)} \quad (\text{II.12})$$

is the PDF that the chain whose head is incorporated into a k -junction has the head-to-tail vector \mathbf{r} , and similarly

$$f_k^{(t)}(\mathbf{r}, t) \equiv \frac{\sum_{l \geq 1} F_{l,k}(\mathbf{r}, t)}{\sum_{l \geq 1} \nu_{l,k}(t)} \quad (\text{II.13})$$

is the PDF that the chain whose tail is belonging to a k -junction takes the head-to-tail vector \mathbf{r} . Note that $f_k^{(\cdot)}(\mathbf{r}, t)$ is normalized to one, i.e.,

$$\int d\mathbf{r} f_k^{(\cdot)}(\mathbf{r}, t) = 1. \quad (\text{II.14})$$

A prefactor C_{k_h} is the probability that the k -junction is formed by k_h heads and k_t tails (in addition to a head of the (k, k') -chain), and hence it is given by

$$C_{k_h} = \frac{1}{2^{k-1}} \frac{(k-1)!}{k_h! k_t!}. \quad (\text{II.15})$$

Upon substitution of (II.11) together with (II.12), (II.13) and (II.15), eq. (II.10) reduces to

$$\beta_k(r) F_{k,k'}(\mathbf{r}, t) + (k-1) \langle \beta_k(r) \rangle(t) F_{k,k'}(\mathbf{r}, t), \quad (\text{II.16})$$

where

$$\langle \beta_k(r) \rangle(t) \equiv \int d\mathbf{r} \beta_k(r) f_k(\mathbf{r}, t) \quad (\text{II.17})$$

is the expectation value of $\beta_k(r)$ averaged with respect to the PDF for k -chains given by

$$f_k(\mathbf{r}, t) \equiv \frac{1}{2} \left(f_k^{(h)}(\mathbf{r}, t) + f_k^{(t)}(\mathbf{r}, t) \right). \quad (\text{II.18})$$

The number of (k, k') -chains decreases through the reaction (iii) only when the k -junction, to which an unreacted group are going to connect, includes the head of a (k, k') -chain (with head-to-vector \mathbf{r}). Here let us introduce the probability (or connection rate) $p_k(t)$ that an unreacted functional group catches a k -junction per unit time.^b Then the decrement of $F_{k,k'}(\mathbf{r}, t)$ due to the reaction (iii) is written as the product of the number $p_k(\chi_1^{(h)}(t) + \chi_1^{(t)}(t))$ of unreacted ends (both head and tail) that catches the k -junction per unit time and the number of (k, k') -chain with head-to-vector \mathbf{r} per a k -junction, that is,

$$p_k(t) \left(\chi_1^{(h)}(t) + \chi_1^{(t)}(t) \right) \frac{F_{k,k'}(\mathbf{r}, t)}{\mu_k(t)} = kp_k(t) \frac{\chi_1(t)}{\chi_k(t)} F_{k,k'}(\mathbf{r}, t), \quad (\text{II.19})$$

where

$$\mu_k(t) \equiv \frac{\chi_k^{(h)}(t) + \chi_k^{(t)}(t)}{k}. \quad (\text{II.20})$$

is the number of k -junctions and a relation (II.6) has been used for the equality. The increment of the (k, k') -chain with the head-to-tail vector \mathbf{r} through the reaction (iv) is given by

$$p_{k-1}(t) F_{1,k'}(\mathbf{r}, t). \quad (\text{II.21})$$

The increment of $F_{k,k'}(\mathbf{r}, t)$ due to the reaction (v) is obtained by replacing k in (II.19) with $k-1$ as follows:

$$(k-1)p_{k-1}(t) \frac{\chi_1(t)}{\chi_{k-1}(t)} F_{k-1,k'}(\mathbf{r}, t), \quad (\text{II.22})$$

whereas the increment due to the reaction (vi) is given by replacing k in the second term of (II.16) with $k+1$, i.e.,

$$k \langle \beta_{k+1}(r) \rangle (t) F_{k+1,k'}(\mathbf{r}, t). \quad (\text{II.23})$$

Summarizing, the reaction term regarding the head of the (k, k') -chains found to be

$$\begin{aligned} W_{k,k'}^{(h)}(\mathbf{r}, t) = & -\beta_k(r) F_{k,k'}(\mathbf{r}, t) + p_{k-1}(t) F_{1,k'}(\mathbf{r}, t) \\ & -B_k(t) F_{k,k'}(\mathbf{r}, t) + B_{k+1}(t) F_{k+1,k'}(\mathbf{r}, t) \\ & -P_k(t) F_{k,k'}(\mathbf{r}, t) + P_{k-1}(t) F_{k-1,k'}(\mathbf{r}, t) \quad (\text{for } k, k' \geq 2) \end{aligned} \quad (\text{II.24})$$

where we have put

$$B_k(t) \equiv (k-1) \langle \beta_k(r) \rangle (t), \quad (\text{II.25a})$$

$$P_k(t) \equiv kp_k(t) \frac{\chi_1(t)}{\chi_k(t)}. \quad (\text{II.25b})$$

Integrating (II.24) with respect to \mathbf{r} , we also obtain^c

$$\begin{aligned} w_{k,k'}^{(h)}(t) = & - \int d\mathbf{r} \beta_k(r) F_{k,k'}(\mathbf{r}, t) + p_{k-1}(t) \nu_{1,k'}(t) \\ & -B_k(t) \nu_{k,k'}(t) + B_{k+1}(t) \nu_{k+1,k'}(t) \\ & -P_k(t) \nu_{k,k'}(t) + P_{k-1}(t) \nu_{k-1,k'}(t) \quad (\text{for } k \geq 2). \end{aligned} \quad (\text{II.26})$$

According to the similar procedure, reaction terms regarding the tail of the (k, k') -chain are derived as follows:

$$\begin{aligned} W_{k,k'}^{(t)}(\mathbf{r}, t) = & -\beta_{k'}(r) F_{k,k'}(\mathbf{r}, t) + p_{k'-1}(t) F_{k,1}(\mathbf{r}, t) \\ & -B_{k'}(t) F_{k,k'}(\mathbf{r}, t) + B_{k'+1}(t) F_{k,k'+1}(\mathbf{r}, t) \\ & -P_{k'}(t) F_{k,k'}(\mathbf{r}, t) + P_{k'-1}(t) F_{k,k'-1}(\mathbf{r}, t) \quad (\text{for } k, k' \geq 2) \end{aligned} \quad (\text{II.27})$$

^b In general, $p_k(t)$ depends on the number $\mu_k(t)$ of the k -junction in the system; the more the k -junction, the higher the probability for an unreacted group to catch the junction (see section III for detail). Thus $p_k(t)$ depends on time through $\mu_k(t)$.

^c Eq. (II.26) holds for $k' \geq 1$, while (II.28) holds for $k \geq 1$.

and

$$\begin{aligned}
w_{k,k'}^{(t)}(t) = & - \int d\mathbf{r} \beta_{k'}(r) F_{k,k'}(\mathbf{r}, t) + p_{k'-1}(t) \nu_{k,1}(t) \\
& - B_{k'}(t) \nu_{k,k'}(t) + B_{k'+1}(t) \nu_{k,k'+1}(t) \\
& - P_{k'}(t) \nu_{k,k'}(t) + P_{k'-1}(t) \nu_{k,k'-1}(t) \quad (\text{for } k' \geq 2).
\end{aligned} \tag{II.28}$$

Next, we derive the kinetic equation for dangling chains, i.e., eq. (II.8) with $k = 1, k' \geq 2$ or $k \geq 2, k' = 1$. The reaction term $w_{1,k'}^{(h)}(t)$ can be derived as follows. The $(1, k')$ -chain is generated by detaching a head of the (l, k') -chain ($l \geq 3$) from the l -junction. The increment of $\nu_{1,k'}$ due to this process per unit time is

$$\sum_{l \geq 3} \int d\mathbf{r} \beta_l(r) F_{l,k'}(\mathbf{r}, t). \tag{II.29}$$

The number of the $(1, k')$ -chain also increases when the 2-junction to which a head of the $(2, k')$ -chain is belonging divides into two unreacted groups. The increment according to this procedure is given by (see Appendix A)

$$\int d\mathbf{r} \beta_2(r) F_{2,k'}(\mathbf{r}, t) + \left(\int d\mathbf{r} \beta_2(r) f_2(\mathbf{r}, t) \right) \nu_{2,k'}(t). \tag{II.30}$$

On the contrary, $(1, k')$ -chains are annihilated if the head of the $(1, k')$ -chain is connected with l -junction ($l \geq 2$). The decrement of $\nu_{1,k'}(t)$ caused by this process is given by $\left(\sum_{l \geq 2} p_l(t) \right) \nu_{1,k'}(t)$. Besides, $(1, k')$ -chains are annihilated when its head captures the unreacted group. The decrement due to this reaction is estimated to be $2p_1(t) \nu_{1,k'}(t)$ (see Fig.17 in Appendix A as a reference) As a result, we obtain the reaction term with respect to the head of $(1, k')$ -chain as^d

$$\begin{aligned}
w_{1,k'}^{(h)}(t) = & \sum_{l \geq 2} \int d\mathbf{r} \beta_l(r) F_{l,k'}(\mathbf{r}, t) - \left(\sum_{l \geq 1} p_l(t) \right) \nu_{1,k'}(t) \\
& + B_2(t) \nu_{2,k'}(t) - p_1(t) \nu_{1,k'}(t).
\end{aligned} \tag{II.31}$$

The reaction term $w_{1,k'}^{(t)}$ regarding the tail of $(1, k')$ -chain ($k' \geq 2$) is given by (II.28) with $k = 1$. According to the similar way, the reaction term for the tail of $(k, 1)$ -chains is found to be

$$\begin{aligned}
w_{k,1}^{(t)}(t) = & \sum_{l \geq 2} \int d\mathbf{r} \beta_l(r) F_{k,l}(\mathbf{r}, t) - \left(\sum_{l \geq 1} p_l(t) \right) \nu_{k,1}(t) \\
& + B_2(t) \nu_{k,2}(t) - p_1(t) \nu_{k,1}(t)
\end{aligned} \tag{II.32}$$

and $w_{k,1}^{(h)}$ ($k \geq 2$) is given by (II.28) with $k' = 1$. Finally, the kinetic equation for isolated chain can be obtained by setting $k = k' = 1$ in (II.8), where $w_{1,1}^{(h)}(t)$ (or $w_{1,1}^{(t)}(t)$) is given by (II.31) with $k' = 1$ (or $k = 1$).

By making use of (II.26), (II.28), (II.31) and (II.32), we can also obtain the equation for $\chi_k^{(\cdot)}(t)$ as follows:

$$\begin{aligned}
\frac{d\chi_k^{(\cdot)}(t)}{dt} = & - \left(\int d\mathbf{r} \beta_k(r) f_k^{(\cdot)}(\mathbf{r}, t) \right) \chi_k^{(\cdot)}(t) + p_{k-1}(t) \chi_1^{(\cdot)}(t) \\
& - B_k(t) \chi_k^{(\cdot)}(t) + B_{k+1}(t) \chi_{k+1}^{(\cdot)}(t) \\
& - P_k(t) \chi_k^{(\cdot)}(t) + P_{k-1}(t) \chi_{k-1}^{(\cdot)}(t) \quad (\text{for } k \geq 2),
\end{aligned} \tag{II.33a}$$

$$\begin{aligned}
\frac{d\chi_1^{(\cdot)}(t)}{dt} = & \sum_{l \geq 2} \left(\int d\mathbf{r} \beta_l(r) f_l^{(\cdot)}(\mathbf{r}, t) \right) \chi_l^{(\cdot)}(t) - \left(\sum_{l \geq 1} p_l(t) \right) \chi_1^{(\cdot)}(t) \\
& + B_2(t) \chi_2^{(\cdot)}(t) - p_1(t) \chi_1^{(\cdot)}(t).
\end{aligned} \tag{II.33b}$$

^d Eq. (II.31) holds for any $k' (\geq 1)$ and (II.32) is satisfied for any $k (\geq 1)$.

One can confirm from (II.33) that the total number of chains conserves, i.e.,

$$\frac{d}{dt} \sum_{k \geq 1} \sum_{k' \geq 1} \nu_{k,k'}(t) = \sum_{k \geq 1} \frac{d\chi_k^{(h)}(t)}{dt} = \sum_{k' \geq 1} \frac{d\chi_{k'}^{(t)}(t)}{dt} = 0. \quad (\text{II.34})$$

Note that (II.34) holds for arbitrary $\beta_k(r)$ and p_k . Hereafter, we denote the number of total chains (per unit volume) as n , i.e.,

$$n \equiv \sum_{k \geq 1} \sum_{k' \geq 1} \nu_{k,k'}(t). \quad (\text{II.35})$$

Up to now, the head and the tail of the chain have been distinguished for convenience. Since we are treating symmetric chains actually, however, subscript of $\nu_{k,k'}$ is exchangeable: $\nu_{k,k'}(t) = \nu_{k',k}(t)$, and hence kinetic equations for (k, k') -chain (II.8) with the reaction term (II.26), (II.28), (II.31) and (II.32) can be summarized into

$$\frac{d\nu_{k,k'}(t)}{dt} = w_{k,k'}(t) + w_{k',k}(t) \quad (\text{II.36})$$

where, for $k' \geq 1$,

$$w_{k,k'}(t) = - \int d\mathbf{r} \beta_k(r) F_{k,k'}(\mathbf{r}, t) + p_{k-1}(t) \nu_{1,k'}(t) - (B_k(t) + P_k(t)) \nu_{k,k'}(t) \\ + B_{k+1}(t) \nu_{k+1,k'}(t) + P_{k-1}(t) \nu_{k-1,k'}(t) \quad (\text{for } k \geq 2), \quad (\text{II.37a})$$

$$w_{1,k'}(t) = \sum_{l \geq 2} \int d\mathbf{r} \beta_l(r) F_{l,k'}(\mathbf{r}, t) + B_2(t) \nu_{2,k'}(t) - \left(p_1(t) + \sum_{l \geq 1} p_l(t) \right) \nu_{1,k'}(t). \quad (\text{II.37b})$$

Further, we find that $\chi_k(t) = \chi_k^{(h)}(t) = \chi_k^{(t)}(t)$ satisfies the following equation:

$$\frac{d\chi_k(t)}{dt} = u_k(t), \quad (\text{II.38})$$

where

$$u_k(t) = -k \langle \beta_k(r) \rangle(t) \chi_k(t) + k \langle \beta_{k+1}(r) \rangle(t) \chi_{k+1}(t) \\ + k p_{k-1}(t) \chi_1(t) - k p_k(t) \chi_1(t) \quad (\text{for } k \geq 2), \quad (\text{II.39a})$$

$$u_1(t) = \sum_{l \geq 2} \langle \beta_l(r) \rangle(t) \chi_l(t) - \left(\sum_{l \geq 1} p_l(t) \right) \chi_1(t) \\ + \langle \beta_2(r) \rangle(t) \chi_2(t) - p_1(t) \chi_1(t). \quad (\text{II.39b})$$

Evolution equation (II.7) with the reaction terms given by (II.24) and (II.27) as well as the kinetic equations for (k, k') -chain (II.36) together with (II.37) and for k -chain (II.38) together with (II.39) are fundamental equations of our transient networks and will be solved in the following sections.

III. REACTION RATES OF FUNCTIONAL GROUPS

In the rest of this article, we treat the dissociation rate of the functional group as constant independent of the end-to-end length of a chain. This treatment is valid since we are going to apply a small oscillatory deformation to the system and the change of the dissociation rate through r is quite small in this case. Then, according to TE, the dissociation rate from the k -junction takes a form: $\beta_k = \omega_0 \exp(-W_k/k_B T)$ [21] where ω_0 is a reciprocal of a microscopic time and W_k is a potential barrier for the dissociation. We further assume that the potential barrier does not depend on the multiplicity of the junction and set $W_k = W$ for all k . Then the dissociation rate also does not depend on the junction multiplicity and is written as

$$\beta_k = \omega_0 \exp(-W/k_B T) \quad (\equiv \beta). \quad (\text{III.1})$$

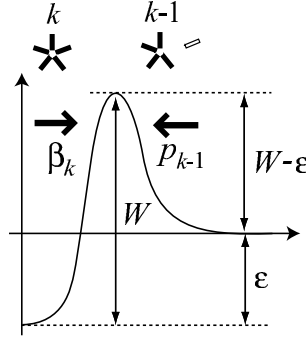


FIG. 4: The potential barrier around a k -junction for the dissociation-association reaction of the functional group.

The connection rate of an unreacted group to a k -junction should increase with increasing the number of functional groups forming the k -junction in the close vicinity of the unreacted group. We assume that the connection rate takes the form

$$p_k(t) = \omega_0 \exp(-(W - \epsilon)/k_B T) k \mu_k(t) v_0 h_k, \quad (\text{III.2})$$

where ϵ is a binding energy between the functional group and the junction^e (see Fig.4), $k \mu_k(t) v_0$ is the number of functional groups forming k -junctions in the effective volume v_0 of the (unreacted) functional group, and h_k is a proportional factor given in the next section. Note that the connection rate depends on time through the number of k -junction in general. Eq. (III.2) can be rewritten as

$$p_k(t) = \beta \lambda(T) \psi q_k(t) h_k \quad (\text{III.3})$$

where

$$q_k(t) \equiv \frac{k \mu_k(t)}{2n} = \frac{\chi_k(t)}{n} \quad (\text{III.4})$$

is the probability that an arbitrary chosen functional group belongs to a k -junction, $\psi \equiv 2n v_0$ is the volume fraction of functional groups, and

$$\lambda(T) \equiv \exp\left(\frac{\epsilon}{k_B T}\right) \quad (\text{III.5})$$

is the association constant of the reactions introduced in ref. [30]. Thus the connection rate to the k -junction is proportional to the volume fraction ψq_k of k -junctions.

IV. EQUILIBRIUM PROPERTIES

In equilibrium state, the number χ_k of k -chain, or equivalently q_k , is formally obtained by setting the left-hand side of (II.33) to 0. (Here and hereafter, all quantities in equilibrium are denoted without the argument t . For example, $\nu_{k,k'}$ is the number of (k, k') -chains in equilibrium.) Thus we find

$$q_k = \frac{p_{k-1}}{\langle \beta_k(r) \rangle} q_1 \quad (\text{for } k \geq 2) \quad (\text{IV.1})$$

where q_1 is obtained from the normalization condition $\sum_{k \geq 1} q_k = 1$:^f

$$q_1 = \frac{1}{1 + \sum_{k \geq 2} p_{k-1} / \langle \beta_k(r) \rangle}. \quad (\text{IV.2})$$

^e It is also assumed that the binding energy does not depend on the junction multiplicity.

^f This equation is equivalent to the number conservation equation $\sum_{k \geq 1} \chi_k = n$ for chains.

On substitution of (III.1) and (III.3), eq. (IV.1) becomes

$$q_k = \lambda\psi h_{k-1} q_{k-1} q_1 \quad (\text{for } k \geq 2). \quad (\text{IV.3})$$

By an iterating procedure, we find the following mass action law:

$$q_k = \gamma_k (\lambda\psi)^{k-1} q_1^k \quad (\text{for } k \geq 2), \quad (\text{IV.4})$$

$$q_1 = 1/\gamma(z), \quad (\text{IV.5})$$

where

$$\gamma_k \equiv \begin{cases} 1 & (k=1) \\ \prod_{l=1}^{k-1} h_l & (k \geq 2) \end{cases}, \quad (\text{IV.6})$$

$$\gamma(z) \equiv \sum_{k \geq 1} \gamma_k z^{k-1} \quad (\text{IV.7})$$

and $z \equiv \lambda\psi q_1$. If λ and ψ are given, q_1 can be derived by solving (IV.5). Then we can obtain q_k ($k \geq 2$) from (IV.4). The association condition (IV.4) together with (IV.5) have been derived in the theory of thermoreversible gelation with junctions of variable multiplicity developed by Tanaka and Stockmayer (referred to as TS) [30].^g In the TS theory, γ_k is interpreted as a factor giving the surface correction for the binding energy, although it is set to unity for all k for simplicity. We will adjust h_k (and hence γ_k) to derive specific models for junctions (see below). TS has shown that most quantities describing transient gels in equilibrium depend on the polymer volume fraction ψ through the combination of $\lambda(T)$ and $\psi (= 2\phi/N)$. This holds not only in equilibrium state but also under small deformation as shown in the next section. Therefore, we use $c \equiv \lambda(T)\psi$ as the reduced polymer concentration in the following. In equilibrium, (II.37) reduces to a simpler form:

$$w_{k,k'} = -\beta k(1 + zh_k)\nu_{k,k'} + \beta k\nu_{k+1,k'} + \beta(k-1)zh_{k-1}\nu_{k-1,k'} + \beta ch_{k-1}q_{k-1}\nu_{1,k'} \quad (\text{for } k \geq 2), \quad (\text{IV.8a})$$

$$w_{1,k'} = \beta \left(\nu_{2,k'} + \sum_{l \geq 2} \nu_{l,k'} \right) - \beta c \left(h_1 q_1 + \sum_{l \geq 1} h_l q_l \right) \nu_{1,k'}. \quad (\text{IV.8b})$$

By solving a equation ($d\nu_{k,k'}/dt = 0$), we can obtain the number of (k, k') -chains in equilibrium as

$$\nu_{k,k'} = n q_k q_{k'}. \quad (\text{IV.9})$$

Note that $\nu_{k,k'}/n = q_k q_{k'}$ is the probability that one end of an arbitrary chosen chain is incorporated into a k -junction while its other end is belonging to a k' -junction. Thus (IV.9) is compatible with the definition of the (k, k') -chain.

Now we consider two special cases as for the multiplicity that the junction can take; 1) a saturating junction model and 2) a fixed multiplicity model. These two models have been considered by Tanaka and Stockmayer [30] in studies of the phase behavior of associating polymer solutions in equilibrium.^h In the saturating junction model, junction multiplicity has an upper limit s_m , that is, the multiplicity is allowed to take a limited range $k = 1, 2, \dots, s_m$. This model might be applied to the junction formed by ionic dipolar interaction or hydrophobic aggregation because the space around such a junction is packed with polymer chains and steric hindrance among them restricts the number of chains connected with the junction. [30]. The mean multiplicity generally depends on the reduced polymer concentration in this model. On the other hand, in the fixed multiplicity model, the multiplicity can take only one fixed number s , i.e., we have only $k = 1$ (unreacted) and $k = s$ (reacted) irrespective of the reduced polymer concentration.

A. Saturating Junction Model

We can impose the upper limit on the junction multiplicity by assuming that h_k is given as a stepwise function:

$$h_k = \begin{cases} 1 & (1 \leq k \leq s_m - 1) \\ 0 & (k \geq s_m) \end{cases}. \quad (\text{IV.10})$$

^g In this series of articles, we denote the probability that an arbitrary chosen functional group belongs to a k -junction as q_k , although the same quantity is represented as p_k in ref.[30], because the symbol p_k is used as the connection rate of functional groups.

^h They have also considered a minimum junction model [30], where junctions are allowed to take the multiplicity $k = 1$ (unreacted) and $k = s_0, s_0 + 1, \dots$.

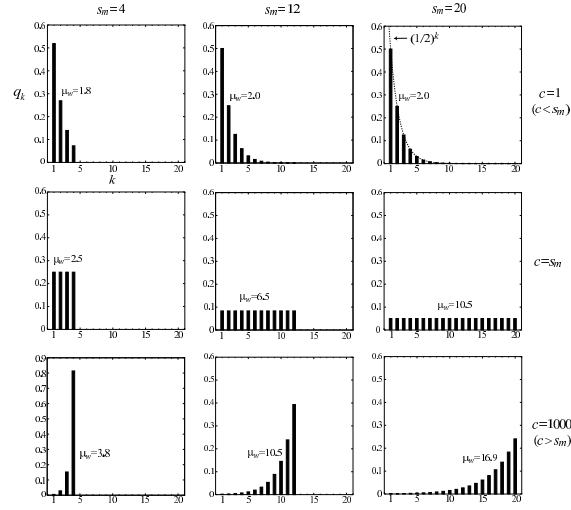


FIG. 5: The probability distribution q_k that a randomly selected functional group to be in a k -junction for the maximum multiplicity $s_m = 4$ (left column), 12 (middle column), 20 (right column), and for the reduced polymer concentration $c = 1$ (top row), $c = s_m$ (middle row), $c = 1000$ (bottom row). The weight-average multiplicity μ_w of the junction is shown in each figure.

For such h_k , (IV.6) reduces to

$$\gamma_k = \begin{cases} 1 & (1 \leq k \leq s_m) \\ 0 & (k \geq s_m + 1) \end{cases}, \quad (\text{IV.11})$$

and hence q_k takes the form

$$q_k = \begin{cases} (cq_1)^{k-1} q_1 & (2 \leq k \leq s_m) \\ 0 & (k \geq s_m + 1) \end{cases}. \quad (\text{IV.12})$$

Thus, junctions with the multiplicity larger than s_m do not exist anymore. We can obtain q_1 by solving (IV.5):

$$\frac{1}{q_1} = \frac{1 - (cq_1)^{s_m}}{1 - cq_1}. \quad (\text{IV.13})$$

Note that the right-hand side of (IV.13) (denoted as $g(q_1)$ for simplicity) is s_m when $q_1 = 1/c$. Therefore, when the condition $s_m = c$ is satisfied, a solution of (IV.13) is $q_1 = 1/c$. As a result, q_k does not depend on k , i.e., $q_k = 1/c$ for all $k (\leq s_m)$ (see middle row figures of Fig.5). When s_m is larger than c , $g(q_1 = 1/c) = s_m$ is also larger than c . Therefore, a solution of (IV.13) satisfies a condition $q_1 < 1/c$ because $g(q_1)$ is an increasing function with respect to q_1 . Consequently, q_k is a decreasing function with respect to k (see top row figures of Fig.5). On the contrary, when s_m is smaller than c , a solution of (IV.13) fulfills a condition $q_1 > 1/c$, and hence q_k is an increasing function of k (see bottom row figures of Fig.5).

Fig.6 (i) shows the extent of reaction $\alpha = 1 - q_1$ as a function of s_m for several reduced concentration c . We see that α approaches to a fixed value for each c as s_m increases. This value can be estimated as follows. In an extreme case where s_m is much larger than c , the right-hand side of (IV.13) is close to $1/(1 - cq_1)$ thanks to the condition $cq_1 < 1$. Thus we find

$$q_1 = \frac{1}{1 + c} \quad (\text{for } s_m \gg c), \quad (\text{IV.14})$$

and therefore

$$\alpha = \frac{c}{1 + c} \quad (\text{for } s_m \gg c). \quad (\text{IV.15})$$

In this extreme, q_k is expressed as

$$q_k = \frac{1}{c} \left(\frac{c}{1 + c} \right)^k = \frac{1}{c} \exp[-k/\kappa] \quad (\text{for } s_m \gg c), \quad (\text{IV.16})$$

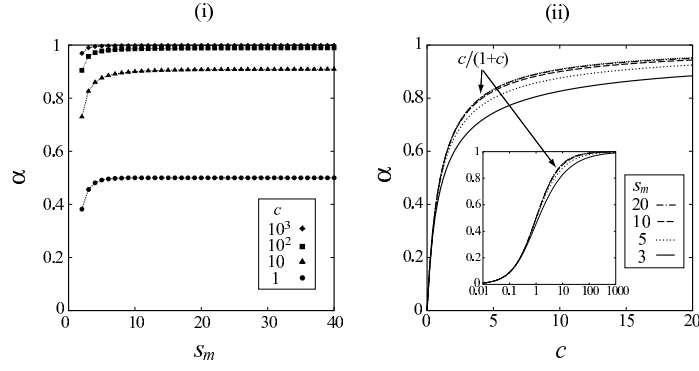


FIG. 6: The extent of reaction α of the saturating junction model as a function of the maximum multiplicity s_m (i), and of the reduced polymer concentration c (ii). The reduced concentration is varying from curve to curve in (i), while the maximum multiplicity is changing in (ii). The inset of (ii) shows the linear-log plot of α as a function of c . Dotted curves (behind the curves for $s_m = 20$) in (ii) represent $\alpha = c/(1+c)$.

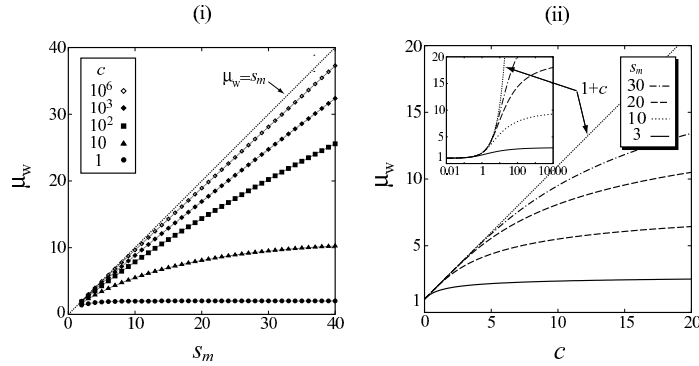


FIG. 7: The weight-average multiplicity μ_w of the junction for the saturating junction model as a function of the maximum multiplicity s_m (i), and of the reduced polymer concentration c (ii). The reduced concentration is varying from curve to curve in (i), while the maximum multiplicity is changing in (ii). The inset of (ii) shows the linear-log plot of μ_w as a function of c .

where

$$\kappa \equiv 1/\log[(1+c)/c] \quad (\text{IV.17})$$

indicates the width of the distribution. As an example, (IV.16) is drawn in Fig.5 for $c = 1$ and $s_m = 20$. As seen from Fig.6 (ii), the extent of reaction behaves as $c/(1+c)$ for c much smaller than s_m , while it approaches to 1 if c exceeds s_m .

The weight-average multiplicity defined by

$$\mu_w = \sum_{k=1}^{s_m} k q_k \quad (\text{IV.18})$$

is shown in Fig.5 for each s_m and c and is depicted in Fig.7 as a function of s_m (i) and of c (ii). Note that μ_w includes unreacted groups as $k = 1$ junctions. When s_m is much larger than c , it is close to (see Fig.7 (i) and (ii))

$$\mu_w = 1 + c \quad (\text{for } s_m \gg c). \quad (\text{IV.19})$$

When the reduced concentration is low and satisfies the condition $c \ll s_m$, we see from top three figures of Fig.5 that μ_w is much smaller than s_m and close to 1 irrespective the value of s_m . This is because there are many unreacted groups (represented by q_1) in the system. On the other hand, when the reduced concentration is high and $c \gg s_m$, μ_w is close to s_m (see bottom three figures of Fig.5) since many functional groups are incorporated into junctions with $k = s_m$. These tendencies can also be confirmed from Fig.7 (i). When s_m is much smaller than c , then μ_w is approximately s_m , while μ_w approaches to $1+c$ when s_m exceeds c for each c . As seen from Fig.7 (ii), μ_w behaves as $1+c$ irrespective of the value of s_m when $c \ll s_m$, and it approaches to s_m as c increases beyond s_m .

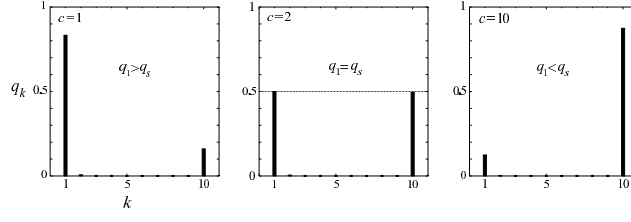


FIG. 8: The probability distribution q_k that a randomly selected functional group to be in a k -junction for the reduced concentration $c = 1$ (left), 2 (middle), and 10 (right). The multiplicity of the junction is fixed at $s = 10$.

B. Fixed Multiplicity Model

Let h_k be

$$h_k = \begin{cases} \delta & (1 \leq k < s-1) \\ \delta^{-(s-2)} & (k = s-1) \\ 0 & (k > s-1) \end{cases}, \quad (\text{IV.20})$$

where δ is a positive value. Then q_k becomes

$$q_k = \begin{cases} (\delta c)^{k-1} q_1^k & (1 \leq k < s) \\ c^{s-1} q_1^s & (k = s) \\ 0 & (k > s) \end{cases}. \quad (\text{IV.21})$$

All junctions take approximately the same multiplicity s if we employ δ much smaller than 1ⁱ because q_k is nearly equal to 0 except for the case of $k = s$ (and $k = 1$), i.e.,

$$q_k \simeq \begin{cases} c^{s-1} q_1^s & (k = s) \\ 0 & (k \neq s) \end{cases} \quad (\text{for } \delta \ll 1). \quad (\text{IV.22})$$

It should be emphasized here that we cannot fix the junction multiplicity rigorously at s by putting $\delta = 0$ because junctions whose multiplicity is less than s must exist for the creation of s -junctions under the assumption of stepwise reactions. We set $\delta = 0.01$ in this series of papers. This δ value is enough to describe characteristic properties of the system where junctions can take only one multiplicity. In the following, we often use the equal sign instead of the nearly equal sign (\simeq) for equations (such as (IV.22)) that approximately hold for small δ . In the fixed multiplicity model, the extent of reaction is given by $\alpha = q_s$ because of the normalization condition $q_1 + q_s = 1$.

The probability q_1 to find an unreacted group can be obtained by solving (IV.5):

$$\frac{1}{q_1} = 1 + (cq_1)^{s-1}. \quad (\text{IV.23})$$

The right-hand side of (IV.23) (denoted as $g(q_1)$) is equal to 2 for $q_1 = 1/c$. Therefore, if $c = 2$, a solution of (IV.23) is given by $q_1 = 1/2 (= q_s)$. If $c > 2$, a solution of (IV.23) satisfies a condition $1/c < q_1 < 1/2$ because $g(q_1 = 1/2) = 1 + (c/2)^{s-1}$ is greater than 2. Then $q_s (> 1/2)$ is larger than q_1 (see Fig.8) indicating that there are more reacted groups than unreacted ones. Note that when s is much larger than 1, $g(q_1)$ is equal to 1 for $q_1 \leq 1/c$ but it almost diverges at $q_1 > 1/c$, and therefore, a solution of (IV.23) approaches to $1/c$. On the other hand, if $c < 2$, the solution of (IV.23) satisfies a condition $1/2 < q_1 < \min(1, 1/c)$, and it approaches to $1/c$ for c satisfying $1 < c < 2$, or to 1 for $c \leq 1$ with increasing s . Summarizing,

$$q_1 = \begin{cases} 1/c & (c > 1) \\ 1 & (c \leq 1) \end{cases} \quad (\text{for } s \gg 1) \quad (\text{IV.24})$$

or, equivalently,

$$\alpha = \begin{cases} 1 - 1/c & (c > 1) \\ 0 & (c \leq 1) \end{cases} \quad (\text{for } s \gg 1). \quad (\text{IV.25})$$

ⁱ On the other hand, the saturating junction model can be realized by setting $\delta = 1$ in (IV.20).

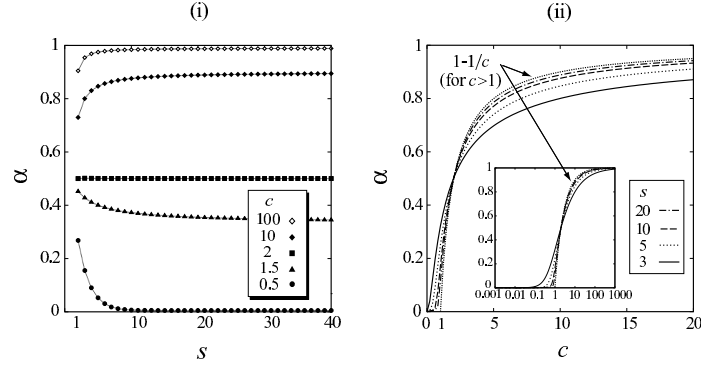


FIG. 9: The extent of reaction of the fixed multiplicity model as a function of the reduced polymer concentration c (i), and of the junction multiplicity s (ii). The inset of (ii) shows the linear-log plot of α as a function of c .

Thus junctions suddenly appear at $c = 1$ in this extreme.

Fig.9 (i) shows the extent of reaction as a function of s . We can confirm the tendency stated above. If $c \leq 1$, the extent of reaction approaches to 0 with increasing s . If $c > 1$, on the other hand, it approaches to $1 - 1/c$ for a given c . But when $c = 2$, it does not depend on s . Fig.9 (ii) shows the extent of reaction as a function of c . It increases abruptly around $c = 1$ when s is large. Such a sharp increase in α stems from the fact that the junctions can take (approximately) only one multiplicity; even if several functional groups spend a certain duration of time in the close vicinity of each other, they cannot aggregate unless s groups participate in this event. Actually, this tendency cannot be observed in the saturating junction model (see Fig.6) since the junction can be formed by any number of functional groups less than a certain value.

V. DYNAMIC-MECHANICAL AND VISCOELASTIC PROPERTIES

Now, we apply a small oscillatory shear deformation to the present system whose rate of deformation tensor is represented by

$$\hat{\kappa}(t) = \begin{pmatrix} 0 & \epsilon\omega \cos \omega t & 0 \\ 0 & 0 & 0 \\ 0 & 0 & 0 \end{pmatrix}, \quad (\text{V.1})$$

where ϵ is a dimensionless infinitesimal amplitude and ω is the frequency of the oscillation. By substituting (V.1) into the left-hand side of (II.7), and by putting (III.1) and (III.3) into the right-hand side (given by (II.24) and (II.27)), we have the evolution equation for $F_{k,k'}(\mathbf{r}, t)$ given as follows:

$$\begin{aligned} \frac{\partial F_{k,k'}(\mathbf{r}, t)}{\partial t} + \frac{\partial F_{k,k'}(\mathbf{r}, t)}{\partial x} \epsilon y \omega \cos \omega t \\ = -Q_{k,k'}(t)F_{k,k'}(\mathbf{r}, t) + B_{k+1}F_{k+1,k'}(\mathbf{r}, t) + B_{k'+1}F_{k,k'+1}(\mathbf{r}, t) \\ + P_{k-1}(t)F_{k-1,k'}(\mathbf{r}, t) + P_{k'-1}(t)F_{k,k'-1}(\mathbf{r}, t) \\ + \beta c(h_{k-1}q_{k-1}(t)\nu_{k',1}(t) + h_{k'-1}p_{k'-1}(t)\nu_{k,1}(t))f_0(\mathbf{r}) \quad (\text{for } k, k' \geq 2), \end{aligned} \quad (\text{V.2})$$

where^j

$$B_k = \beta(k-1), \quad (\text{V.3})$$

$$P_k(t) = \beta z(t)kh_k \quad (\text{V.4})$$

as defined in (II.25), and

$$Q_{k,k'}(t) \equiv \beta k + P_k(t) + \beta k' + P_{k'}(t). \quad (\text{V.5})$$

^j $z(t) \equiv \lambda\psi q_1(t)$.

Here, we expand $F_{k,k'}(\mathbf{r}, t)$ with respect to the powers of ϵ up to the first order:

$$F_{k,k'}(\mathbf{r}, t) = F_{k,k'}^{(0)}(\mathbf{r}) + \epsilon F_{k,k'}^{(1)}(\mathbf{r}, t). \quad (\text{V.6})$$

On the other hand, the first-order terms of $\nu_{k,k'}(t)$ and $q_k(t)$ are negligible [20, 28], i.e., they have equilibrium values and satisfy the association condition (IV.4) even under the small shear deformation. The zeroth-order term of $F_{k,k'}(\mathbf{r})$ represents its equilibrium value in the absence of the oscillation, and hence it is written as

$$F_{k,k'}^{(0)}(\mathbf{r}) = \nu_{k,k'} f_0(\mathbf{r}). \quad (\text{V.7})$$

By comparing the order, we see that the first-order term $F_{k,k'}^{(1)}(\mathbf{r}, t)$ satisfies the following equation:

$$\begin{aligned} \frac{\partial F_{k,k'}^{(1)}(\mathbf{r}, t)}{\partial t} - \nu_{k,k'} \frac{3xy}{Na^2} f_0(\mathbf{r}) \omega \cos \omega t \\ = -Q_{k,k'} F_{k,k'}^{(1)}(\mathbf{r}, t) + B_{k+1} F_{k+1,k'}^{(1)}(\mathbf{r}, t) + B_{k'+1} F_{k,k'+1}^{(1)}(\mathbf{r}, t) \\ + P_{k-1} F_{k-1,k'}^{(1)}(\mathbf{r}, t) + P_{k'-1} F_{k,k'-1}^{(1)}(\mathbf{r}, t) \quad (\text{for } k, k' \geq 2). \end{aligned} \quad (\text{V.8})$$

The solution of (V.8) after the long-time limit takes the form^k

$$F_{k,k'}^{(1)}(\mathbf{r}, t) = \left(g'_{k,k'}(\omega) \sin \omega t + g''_{k,k'}(\omega) \cos \omega t \right) \frac{3xy}{Na^2} f_0(\mathbf{r}). \quad (\text{V.9})$$

Note that subscripts of g' (and g'') are exchangeable, i.e., $g'_{k,k'} = g'_{k',k}$ (or $g''_{k,k'} = g''_{k',k}$), and we can put $g'_{k,1} = g''_{k,1} \equiv 0$ for $k \geq 1$. Substituting (V.9) into (V.8), we obtain the simultaneous equation for $g'_{k,k'}$ and $g''_{k,k'}$ as follows:

$$g'_{k,k'} = (-Q_{k,k'} g''_{k,k'} + B_{k+1} g''_{k+1,k'} + B_{k'+1} g''_{k,k'+1} + P_{k-1} g''_{k-1,k'} + P_{k'-1} g''_{k,k'-1}) / \omega + \nu_{k,k'}, \quad (\text{V.10a})$$

$$g''_{k,k'} = (Q_{k,k'} g'_{k,k'} - B_{k+1} g'_{k+1,k'} - B_{k'+1} g'_{k,k'+1} - P_{k-1} g'_{k-1,k'} - P_{k'-1} g'_{k,k'-1}) / \omega \quad (\text{for } k, k' \geq 2) \quad (\text{V.10b})$$

In the high frequency limit, (V.10) reduces to

$$g'_{k,k'}(\omega \rightarrow \infty) = \nu_{k,k'}, \quad (\text{V.11a})$$

$$g''_{k,k'}(\omega \rightarrow \infty) = 0. \quad (\text{V.11b})$$

The shear stress $\sigma_{k,k'}$ ascribed to the (k, k') -chain is derived from the following formula for the Gaussian chain:

$$\sigma_{k,k'} = \frac{3k_B T}{Na^2} \int d\mathbf{r} \, xy F_{k,k'}(\mathbf{r}, t) = \epsilon [G'_{k,k'}(\omega) \sin \omega t + G''_{k,k'}(\omega) \cos \omega t] \quad (\text{V.12})$$

where the dynamic shear moduli with respect to the (k, k') -chain are defined by

$$G'_{k,k'}(\omega) = k_B T g'_{k,k'}(\omega), \quad (\text{V.13a})$$

$$G''_{k,k'}(\omega) = k_B T g''_{k,k'}(\omega). \quad (\text{V.13b})$$

Since we are assuming that any chains whose both ends are associated with other functional groups are elastically effective, the total moduli are given by

$$G'(\omega) = k_B T \sum_{k \geq 2} \sum_{k' \geq 2} g'_{k,k'}(\omega), \quad (\text{V.14a})$$

$$G''(\omega) = k_B T \sum_{k \geq 2} \sum_{k' \geq 2} g''_{k,k'}(\omega). \quad (\text{V.14b})$$

^k Eq.(V.9) assures that the number of (k, k') -chains of the first order, say $\nu_{k,k'}^{(1)}(t)$, is zero; $\nu_{k,k'}^{(1)}(t) = \int d\mathbf{r} F_{k,k'}^{(1)}(\mathbf{r}, t) = 0$.




FIG. 10: The breakage rate of a pairwise junction is 2β because it decays if one of two functional groups in the junction is disconnected from the other. Since active chains are connected with two pairwise junctions through both ends, the breakage rate of the active chain is 4β .

The high-frequency plateau modulus is then found from (V.11a) to be

$$G_\infty \equiv G'(\omega \rightarrow \infty) = \nu_0^{eff} k_B T \quad (\text{V.15})$$

where

$$\nu_0^{eff} = \sum_{k \geq 2} \sum_{k' \geq 2} \nu_{k,k'} = n\alpha^2 \quad (\text{V.16})$$

is the total number of active chains.

As an example, let us study the simplest case that the association is allowed only in pairs. In other words, only junctions whose multiplicity is two are allowed to exist in the system. There is no difference between two models for junctions (i.e., the saturating junction model and fixed multiplicity model) in this case. Since we are treating telechelic polymers, only linearly extended chains can be formed rather than a three dimensional network. Nevertheless, it is worth studying such simple situation because this is the only case that the moduli can be analytically expressed in simple forms, thereby giving insight into the system with multiple junctions. Note that $g'_{3,2} = g'_{2,3} = g''_{3,2} = g''_{2,3} = 0$ since there are no 3-junctions. Then (V.10) reduces to

$$g'_{2,2} = -Q_{2,2}g''_{2,2}/\omega + \nu_{2,2}, \quad (\text{V.17a})$$

$$g''_{2,2} = Q_{2,2}g'_{2,2}/\omega. \quad (\text{V.17b})$$

As a result, the moduli becomes the Maxwellian with a single relaxation time $1/Q_{2,2}$, i.e.,

$$G'/k_B T = g'_{2,2} = \frac{(Q_{2,2}\omega)^2}{(Q_{2,2}\omega)^2 + 1} \nu_0^{eff}, \quad (\text{V.18a})$$

$$G''/k_B T = g''_{2,2} = \frac{Q_{2,2}\omega}{(Q_{2,2}\omega)^2 + 1} \nu_0^{eff}, \quad (\text{V.18b})$$

where the number of active chains is $\nu_0^{eff} = \nu_{2,2} = n(zh_1q_1)^2$, and the reciprocal of the relaxation time, or the breakage rate of the active chain, is given by $Q_{2,2} = 4\beta + 2P_2 = 4\beta$.¹ The coefficient 4 of the chain breakage rate stems from the annihilation rate 2β of the junction to which one end of the chain is belonging and 2β for the other end (see Fig.10).

A. Saturating Junction Model

Now we study dynamic-mechanical and viscoelastic properties of the system where multiple junctions (i.e., $k > 2$) are allowed to exist. We first consider the saturating junction model, i.e., the junction takes a limited range $k = 1, 2, \dots, s_m$ of the multiplicity. This condition can be attained by employing (IV.10) for P_k , i.e.,

$$P_k = \begin{cases} \beta z k & (1 \leq k \leq s_m - 1) \\ 0 & (k \geq s_m) \end{cases}. \quad (\text{V.19})$$

By putting (V.19) into (V.10) and by solving a set of linear algebraic equations for $g'_{k,k'}$ and $g''_{k,k'}$, we can obtain the dynamic shear moduli with the help of (V.14) where the summation is taken over $2 \leq k, k' \leq s_m$. Note that the number of unknowns in (V.10) is $s_m(s_m - 1)$; when $s_m = 4$, for example, there are 12 unknowns: $g'_{2,2}, g'_{3,2}, g'_{3,3}, g'_{4,2}, g'_{4,3}, g'_{4,4}$ and $g''_{2,2}, g''_{3,2}, g''_{3,3}, g''_{4,2}, g''_{4,3}, g''_{4,4}$.

¹ The probability p_2 that an unreacted group is connected with a 2-junction is zero since 3-junction is not allowed to exist by definition. Therefore, $P_2 \propto p_2 = 0$.

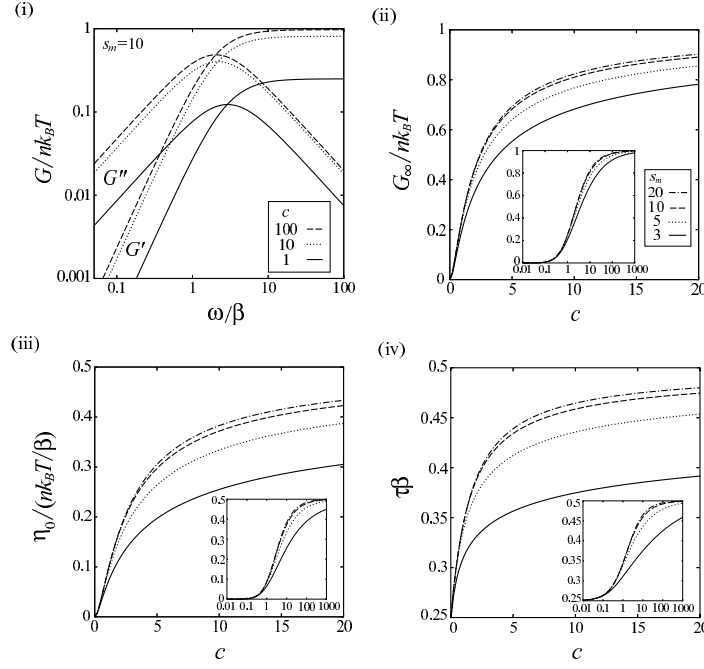


FIG. 11: (i) The dynamic shear moduli (reduced by $nk_B T$) for the saturating junction model as a function of the frequency. The reduced polymer concentration c is varying from curve to curve, while the maximum multiplicity is fixed at $s_m = 10$. (ii) The reduced plateau modulus, (iii) reduced zero-shear viscosity, and (iv) relaxation time plotted against the reduced concentration. The maximum multiplicity is varying from curve to curve. The insets of (ii) ~ (iv) show the linear-log plot of each quantity as a function of c .

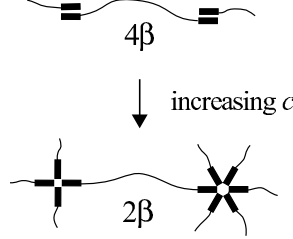


FIG. 12: The breakage rate of the chain linking two $k = 2$ junctions (upper figure) is 4β (see Fig.10). On the other hand, the breakage rate of the chain connecting two junctions with the multiplicity $k \geq 3$ (lower figure) is 2β because the chain debridges if its one of two ends are dissociated from the junction.

Fig.11 (i) shows the dynamic shear moduli reduced by $nk_B T$ as a function of the unitless frequency. The reduced polymer concentration is changed from curve to curve for a maximum multiplicity fixed at $s_m = 10$. It appears that they are Maxwellian with a single relaxation time. To see the detail, the plateau modulus $G_\infty = \lim_{\omega \rightarrow \infty} G'(\omega)$ reduced by $nk_B T$ is drawn in Fig.11 (ii) as a function of c . The reduced plateau modulus increases as c^2 irrespective of the value of s_m when c is small^m and approaches to 1 with increasing c . Fig.11 (iv) shows the relaxation time determined from the peak position of G'' as a function of c . The relaxation time becomes close to $1/(4\beta)$ in the limit of low reduced concentration because most active chains belong to junctions with $k = 2$ in this limit. On the other hand, τ approaches to $1/(2\beta)$ with increasing c because more active chains tend to connect with junctions with $k \geq 3$ when c is large (see Fig.12). Thus τ increases with increasing c . The zero-shear viscosity $\eta_0 = \lim_{\omega \rightarrow 0} G''(\omega)/\omega$ reduced by $nk_B T/\beta$ is shown in Fig.11 (iii) as a function of c . The zero-shear viscosity is roughly estimated to be $\eta_0 \sim G_\infty \tau$ (or $\eta_0/(nk_B T/\beta) \sim G_\infty/(nk_B T)\beta\tau$), and hence the reduced viscosity starts to increase at $c = 0$ and approaches to 0.5 with increasing c .

Fig.13 (i) shows the reduced shear moduli for several maximum multiplicity s_m . The reduced plateau modulus,

^m When c is small, the extent of reaction is proportional to c , i.e., $\alpha \sim c/(1+c) \sim c$. Therefore, we find $G_\infty/nk_B T = \alpha^2 \sim c^2$.

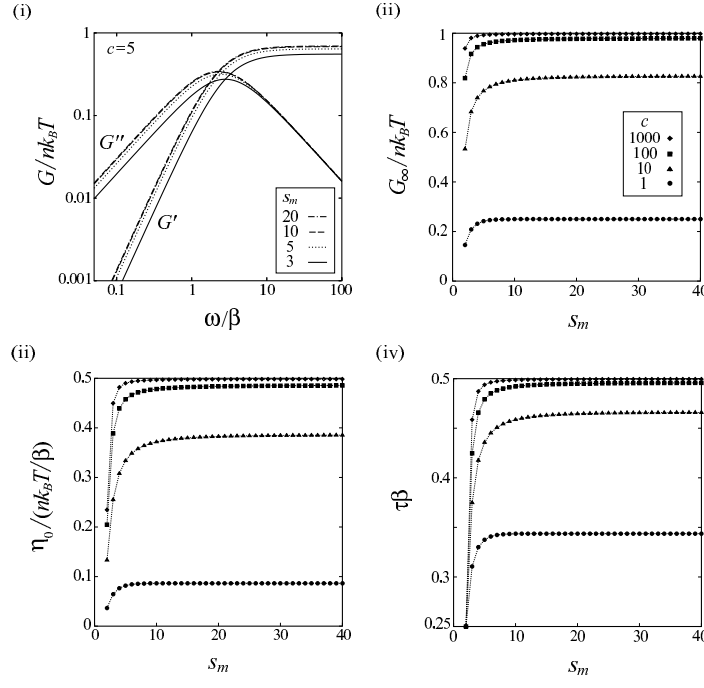


FIG. 13: (i) The dynamic shear moduli (reduced by $nk_B T$) for the saturating junction model as a function of the frequency. The maximum multiplicity s_m is varying from curve to curve for a reduced concentration fixed at $c = 5$. (ii) The reduced plateau modulus, (iii) reduced zero-shear viscosity, and (iv) relaxation time plotted against the maximum multiplicity for several reduced concentrations.

reduced zero-shear viscosity and relaxation time are also plotted in Fig.13 as a function of s_m . Let us comment on the relaxation time here. The relaxation time is determined from the ratio between the number of active chains incorporated into the junction with multiplicity $k \geq 3$ and that with $k = 2$. When $s_m = 2$, for example, all active chains belong to 2-junctions, and therefore we have $\tau = 1/(4\beta)$ irrespective of the value of c . When $s_m \geq 3$, more chains can connect to junctions with $k \geq 3$, so that the fraction q_2 of chains belonging to 2-junctions decreases (this tendency can also be confirmed from Fig.5). Thus τ increases with increasing s_m and approaches to a fixed value for each c . As for the dependence of $G_\infty/nk_B T = \alpha^2$ on s_m , see IV A for reference.

B. Fixed Multiplicity Model

Next, we consider the fixed multiplicity model, i.e., the multiplicity can take only $k = 1$ (unreacted) and $k = s$ (reacted) for all junctions. This condition can be approximately attained by employing (IV.20) for P_k , i.e.,

$$P_k = \beta z k \begin{cases} \delta & (1 \leq k < s-1) \\ \delta^{-(s-2)} & (k = s-1) \\ 0 & (k > s-1) \end{cases}, \quad (\text{V.20})$$

where we are setting $\delta = 0.01$. By putting (V.20) into (V.10) and by solving a simultaneous equation, we can obtain the dynamic shear moduli for the (approximate) fixed multiplicity model.

Fig.14 shows the dependence of the reduced shear moduli on c . The reduced plateau modulus (figure (ii)) increases with increasing s for $c > 2$, but it decreases for $c < 2$ according to the s dependence of α (see Fig.9). The relaxation time (figure (iv)) is almost $1/(2\beta)$ irrespective of the values of $s (\geq 3)$ and c because almost all junctions take the multiplicity larger than or equal to three. However, there is a small number of 2-junctions in the system, especially when c is close to 0, due to the finite δ . Thus, the relaxation time becomes smaller than $1/(2\beta)$ (but larger than $1/(4\beta)$) for c close to 0. The reduce zero-shear viscosity (figure (iii)) is approximately half the reduced plateau modulus because $\beta\tau$ is about 0.5.

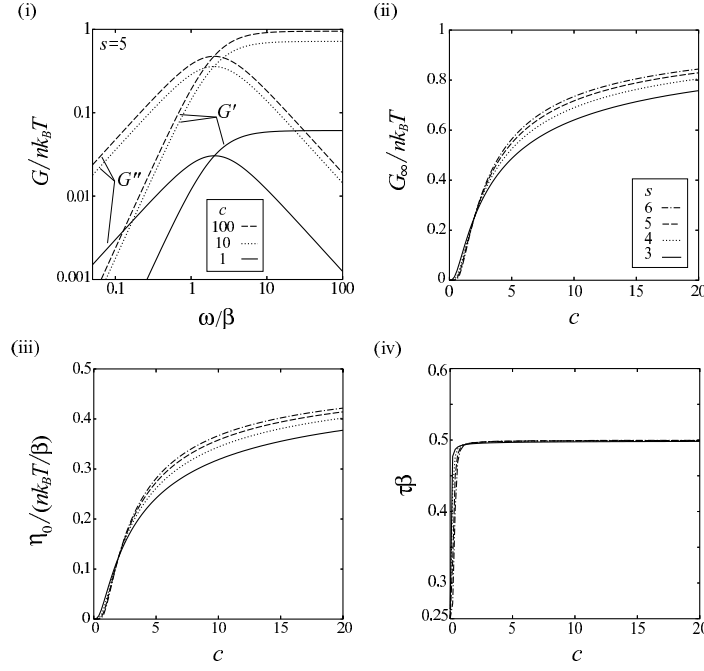


FIG. 14: (i) The dynamic shear moduli (reduced by $nk_B T$) for the fixed multiplicity model as a function of the frequency. The reduced concentration is varying from curve to curve while the multiplicity is fixed at $s = 5$. (ii) the reduced plateau modulus, (iii) reduced zero-shear viscosity, and (iv) relaxation time plotted against the reduced concentration.

VI. SUMMARY AND DISCUSSIONS

In this paper, we developed a theory for transient networks with multiple junctions. One of our objectives is to investigate relations between rheological (and equilibrium) properties of the network and the junction multiplicity in the absence of looped chains. We assumed that the connection rate of a functional group is proportional to the volume fraction of junctions to which it is going to connect, and showed that the law of mass action holds. As a first attempt, we defined active chains locally, i.e., chains whose both ends are connected with any other functional groups are elastically effective. The dynamic shear moduli are well described in terms of the Maxwell model characterized by a single relaxation time and the high-frequency plateau modulus (and the zero-shear viscosity). The reduced moduli depend on thermodynamic quantities such as polymer concentration and temperature through the reduced polymer concentration c . The plateau modulus and the zero-shear viscosity increase nonlinearly at small c and proportional to c when c is large. The relaxation time also increases with increasing c due to the presence of pairwise junctions at small c .

The modulus, viscosity and relaxation time start to rise at $c = 0$. This indicates that the critical concentration for the sol/gel transition is $c^* = 0$ in this model. In other words, the system is always in the postgel regime irrespective of the amount of polymers. This unfavorable result can be ascribed to the lack of global information in the current definition of active chains.

The present theory reduces to the TE theory in the high reduced concentration limit $c \rightarrow \infty$. Let us take a summation over $2 \leq k, k' \leq s_m$ in (II.7). Then we have

$$\begin{aligned} \frac{\partial F(\mathbf{r}, t)}{\partial t} + \nabla \cdot (\dot{\mathbf{r}} F(\mathbf{r}, t)) = & -2\beta(r)F(\mathbf{r}, t) - B_2(t) \sum_{k=2}^{s_m} (F_{k,2}(\mathbf{r}, t) + F_{2,k}(\mathbf{r}, t)) \\ & + \left(\sum_{k=1}^{s_m-1} p_k(t) + p_1(t) \right) \nu^d(t) f_0(\mathbf{r}), \end{aligned} \quad (\text{VI.1})$$

where

$$F(\mathbf{r}, t) \equiv \sum_{k=2}^{s_m} \sum_{k'=2}^{s_m} F_{k,k'}(\mathbf{r}, t) \quad (\text{VI.2})$$

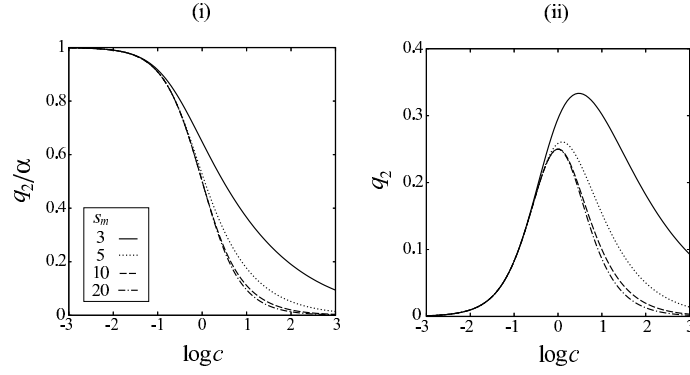


FIG. 15: (i) Effects of the terms in (VI.1) and (VI.4) associated with the creation/annihilation process of 2-junctions, and (ii) the fraction of chains belonging to 2-junctions plotted against the reduced polymer concentration. The maximum multiplicity is varying from curve to curve in both figures.

is the total number of active chains with the head-to-vector \mathbf{r} , and

$$\nu^d(t) \equiv \sum_{k=2}^{s_m} (\nu_{k,1}(t) + \nu_{1,k}(t)) \quad (\text{VI.3})$$

is the total number of dangling chains. (We are assuming that the dissociation rate does not depend on the junction multiplicity as in the text.) The second term of the right-hand side in (VI.1) and p_1 inside the second parentheses are related with the annihilation/creation process of 2-junctions. As shown below, the relative amount of 2-junctions becomes negligible in the high c limit, and hence effects of these terms disappear. Let us consider the case that a small shear deformation is applied to the system as discussed in the text. Upon integration with respect to \mathbf{r} , eq.(VI.1) becomes

$$0 = -2\beta(\nu^{eff} + \sum_{k \geq 2} \nu_{k,2}) + \left(\sum_{k \geq 1} p_k + p_1 \right). \quad (\text{VI.4})$$

The terms $\sum_{k \geq 2} \nu_{k,2}$ and p_1 associated with 2-junctions satisfy the following relation:

$$\frac{\sum_{k \geq 2} \nu_{k,2}}{\nu^{eff}} = \frac{p_1}{\sum_{k \geq 1} p_k} = \frac{q_2}{\alpha}. \quad (\text{VI.5})$$

With increasing the reduced concentration, q_2/α approaches to zero as shown in Fig.15 (i),ⁿ and hence the right-hand side of (VI.4) becomes close to $-2\beta\nu^{eff} + \sum_{k \geq 1} p_k$. It indicates that (VI.1) reduces to

$$\frac{\partial F(\mathbf{r}, t)}{\partial t} + \nabla \cdot (\dot{\mathbf{r}} F(\mathbf{r}, t)) = -2\beta F(\mathbf{r}, t) + p\nu^d f_0(\mathbf{r}) \quad (\text{VI.6})$$

in the high c limit where

$$p \equiv \sum_{k \geq 1} p_k \quad (\text{VI.7})$$

is the probability that an unreacted group connects to *any* junctions per unit time. Eq. (VI.6) is equivalent to the fundamental equation of the TE theory when we regard p as a constant and assume that isolated chains are absent.^o

In Fig.16, theoretically obtained plateau modulus, zero-shear viscosity and relaxation time for the saturating junction model are compared with experimental data for aqueous solutions of telechelic PEO end-capped with C_{16} alkanes [3, 9]. The reduced concentration c used in the theory was converted into the polymer concentration in weight percentage c_w through a relation $c = \xi c_w$, where $\xi \equiv (2000N_A/M)\lambda v_0$ (N_A is Avogadro's number). We see

ⁿ Eq. (VI.5) can be approximately expressed as $1/(1+c)$ when s_m is large.

^o 2β is the transition rate from active chains to dangling chains. This quantity is denoted as β in the TE theory [20, 21].

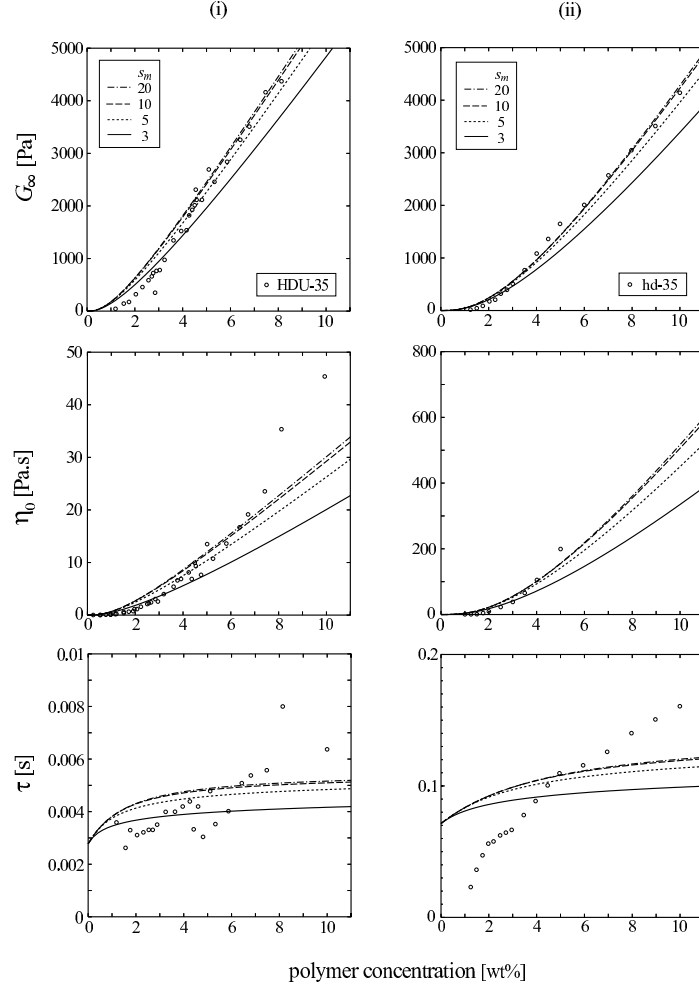


FIG. 16: Comparison between theoretical results for the saturating junction model and experimental data obtained for (i) telechelic PEO with narrow molecular weight distributions ($Mw = 35\text{kg/mol}$) fully end-capped with C_{16} alkanes reported by Pham *et al.* [9] (called HDU-35) and (ii) hydrophobically modified ethylene oxide-urethane copolymers (HEUR) with similar molecular weight end-capped with the same hydrophobes reported by Annable *et al.* [3] (called hd-35 after ref.[25]). Theoretical curves for the zero-shear viscosity and the relaxation time are drawn with $\beta = 90$ (1/sec) for HDU-35 and $\beta = 3.5$ (1/sec) for hd-35.^a A factor ξ (see text) is assumed to be 1 for HDU-35 and 0.35 for hd-35, respectively.

^aA discrepancy in the value of β for the same alkanes might stem from the difference in the coupling agents between the alkanes and the PEO backbone [9, 25].

that both agree fairly well with each other for larger s_m except for the relaxation time of HEUR aqueous solutions. According to Annable *et al.* [3], a concentration dependence of the relaxation time is strongly affected by the amount of *superbridges* formed by connecting several primary bridges in series because they have shorter lifetime due to a number of possible disengagement points inside. Actually, we can infer from Fig.15 (i) that a considerable fraction of active chains are forming superbridges at low concentration; a fraction of active chains $(q_2/\alpha)^2$ whose both ends are connected with 2-junctions becomes close 1 when $c \rightarrow 0$ although both α and q_2 approach to 0 (see Fig.6 (ii) and Fig.15 (ii) respectively). In order to treat such superbridges in more appropriate manner, we need to consider a global structure of the network by introducing a concept of the path connectivity to the infinite network according to refs.[34, 35]. The effect of superbridges on the viscoelasticities will be discussed in detail in the following paper.

APPENDIX A: DERIVATION OF (II.30)

The number of the state X depicted in Fig.17 (corresponding to the state A in Fig.3 with $k_h = 1$ and $k_t = 0$) is

$$\mathcal{F}_{2,k'}(\mathbf{r}, \mathbf{r}^{(h)}; t) = \frac{1}{2} F_{2,k'}(\mathbf{r}, t) f_2^{(h)}(\mathbf{r}^{(h)}, t). \quad (\text{A.1})$$

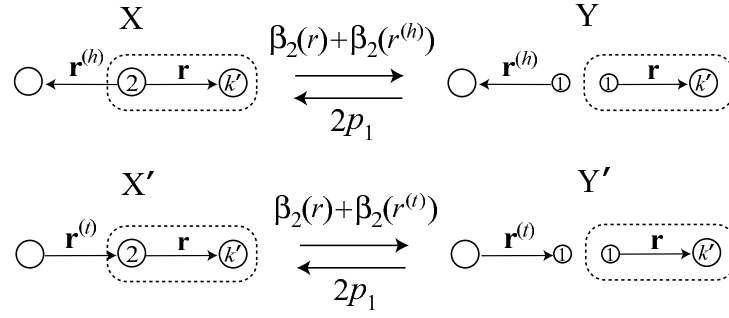


FIG. 17: Transitions between the $k = 1$ chain and the $k = 2$ chain.

The $(1, k')$ -chain is generated from the state X if the head of the $(2, k')$ -chain *or* the head of another chain is detached from the 2-junction (see the transition from the state X to state Y in Fig.17). Then the increment of $(1, k')$ -chains due to this process is estimated to be

$$\begin{aligned} & \int d\mathbf{r} \int d\mathbf{r}^{(h)} \left(\beta_2(r) + \beta_2(r^{(h)}) \right) \mathcal{F}_{2,k'}(\mathbf{r}, \mathbf{r}^{(h)}; t) \\ &= \frac{1}{2} \int d\mathbf{r} \beta_2(r) F_{2,k'}(\mathbf{r}, t) + \frac{1}{2} \left(\int d\mathbf{r} \beta_2(r) f_2^{(h)}(\mathbf{r}, t) \right) \nu_{2,k'}(t). \end{aligned} \quad (\text{A.2})$$

Similarly, the increment of $(1, k')$ -chains as a result of the transition from the state X' (in Fig.17) to Y' is written as

$$\frac{1}{2} \int d\mathbf{r} \beta_2(r) F_{2,k'}(\mathbf{r}, t) + \frac{1}{2} \left(\int d\mathbf{r} \beta_2(r) f_2^{(l)}(\mathbf{r}, t) \right) \nu_{2,k'}(t). \quad (\text{A.3})$$

By adding (A.2) and (A.3), we obtain (II.30).

-
- [1] M.A.Winnik, A.Yekta, Associative polymers in aqueous solution, *Curr. Opin. Colloid Interface Sci.*, 2 (1997) 424-436.
 - [2] R.D.Jenkins, C.A.Silebi, M.S.El-Aasser, Steady-shear and linear viscoelastic material properties of model associative polymer solutions, *ACS Symp. Ser.*, 462 (1991) 222-233.
 - [3] T.Annable, R.Buscall, R.Ettelaie, D.Whittlestone, The rheology of solutions of associating polymers: Comparison of experimental behavior with transient network theory, *J. Rheol.*, 37 (1993) 695-726.
 - [4] R.D.Jenkins, D.R.Bassett, C.A.Silebi, M.S.El-Aasser, Synthesis and characterization of model associating polymers, *J. Appl. Polym. Sci.*, 58 (1995) 209-230.
 - [5] A.Yekta, B.Xu, J.Duhamel, H.Adiwidjaja, M.A.Winnik, Fluorescence studies of associating polymers in water: determination of the chain end aggregation number and a model for the association process, *Macromolecules*, 28 (1995) 956-966.
 - [6] K.C.Tam, R.D.Jenkins, M.A.Winnik, D.R.Bassett, A structural model of hydrophobically modified urethane-ethoxylate (HEUR) associative polymers in shear flows, *Macromolecules*, 31 (1998) 4149-4159.
 - [7] O.Vorobyova, A.Yekta, M.A.Winnik, W.Lau, Fluorescent probe studies of the association in an aqueous solution of a hydrophobically modified poly(ethylene oxide), *Macromolecules*, 31 (1998) 8998-9007.
 - [8] Q.T.Pharm, W.B.Russel, J.C.Thibeault, W.Lau, Micellar solutions of associative triblock copolymers: Entropic attraction and gas-liquid transition, *Macromolecules*, 32 (1999) 2996-3005.
 - [9] Q.T.Pharm, W.B.Russel, J.C.Thibeault, W.Lau, Micellar solutions of associative triblock copolymers: The relationship between structure and rheology, *Macromolecules*, 32 (1999) 5139-5146.
 - [10] W.K.Ng, K.C.Tam, R.D.Jenkins, Lifetime and network relaxation time of a HEUR-C20 associative polymer system, *J. Rheol.* 44 (2000) 137-147.
 - [11] Y.S  r  ro, V.Jacobsen, J.-F.Berret, R.May, Evidence of non-linear chain stretching in the rheology of transient networks, *Macromolecules* 33 (2000) 1841-1847.
 - [12] S.X.Ma, S.L.Cooper, Shear thickening in aqueous solutions of hydrocarbon end-capped poly(ethylene oxide), *Macromolecules*, 34 (2001) 3294-3301.
 - [13] S.X.Ma, S.L.Cooper, Effect of polydispersity on viscoelasticity and shear thickening in aqueous solutions of hydrocarbon end-capped poly(ethylene oxide), *Macromolecules*, 35 (2002) 2024-2029.
 - [14] D.Calvet, A.Collet, M.Viguier, J.-F.Berret, Y.S  r  ro, Perfluoroalkyl end-capped poly(ethylene oxide). Synthesis, characterization, and rheological behavior in aqueous solution, *Macromolecules*, 36 (2003) 449-457.
 - [15] F.Laf  che, D.Durand, T.Nicolai Association of adhesive spheres formed by hydrophobically end-capped PEO. 1. Influence of the presence of single end-capped PEO, *Macromolecules*, 36 (2003) 1331-1340.

- [16] L.Pellens, R.G.Corrals, J.Mewis, General nonlinear rheological behavior of associative polymers, *J. Rheol.*, 48 (2004) 379-393.
- [17] L.Pellens, K.H.Ahn, S.J.Lee, J.Mewis, Evaluation of a transient network model for telechelic associative polymers, *J. Non-Newtonian Fluid Mech.*, 121 (2004) 87-100.
- [18] P.Kujawa, H.Watanabe, F.Tanaka, F.M.Winnik, Amphiphilic telechelic poly(N-isopropylacrylamide) in water: from micelles to gels, *Eur. Phys. J. E*, 17 (2005) 129-137.
- [19] A.N.Semenov, J.-F.Joanny, A.R.Khokhlov, Associating polymers: Equilibrium and linear viscoelasticity, *Macromolecules*, 28 (1995) 1066-1075.
- [20] F.Tanaka, S.F.Edwards, Viscoelastic properties of physically crosslinked networks. Transient network theory, *Macromolecules*, 25 (1992) 1516-1523.
- [21] F.Tanaka, S.F.Edwards, Viscoelastic properties of physically crosslinked networks, Parts 1-3, *J. Non-Newtonian Fluid Mech.*, 43 (1992) 247-271, 273-288, 289-309.
- [22] S.Q.Wang, Transient network theory for shear-thickening fluids and physically cross-linked systems, *Macromolecules*, 25 (1992) 7003-7010.
- [23] G.Marrucci, S.Bhargava, S.L.Cooper, Models of shear-thickening behavior in physically cross-linked networks, *Macromolecules*, 26 (1993) 6483-6488.
- [24] A.Vaccaro, G.Marrucci, A model for the nonlinear rheology of associating polymers, *J. Non-Newtonian Fluid Mech.*, 92 (2000) 261-273.
- [25] X.-X.Meng, W.B.Russel, Rheology of telechelic associative polymers in aqueous solutions *J. Rheol.*, 50 (2006) 189-205.
- [26] T.Indei, Necessary conditions for shear thickening in associating polymer networks, *J. Non-Newtonian Fluid Mech.*, to appear (2006).
- [27] M.S.Green, A.V.Tobolsky, A new approach to the theory of relaxing polymeric media, *J. Chem. Phys.*, 14 (1946) 80-92.
- [28] T.Indei, F.Tanaka, Rheological study of transient polymer networks crosslinked by two-component associative groups, - inversion of the gel skeletal structure, *J. Rheol.*, 48 (2004) 641-661.
- [29] T.Indei, F.Tanaka, Theory of transient polymer networks crosslinked by two-component associative groups, *Nihon Reoroji Gakkaishi (J Soc Rheol, Jpn)*, 32, (2004) 285-293.
- [30] F.Tanaka, W.H.Stockmayer, Thermoreversible gelation with junctions of variable multiplicity, *Macromolecules*, 27 (1994) 3943-3954.
- [31] W.Binana-Limbele, F.Clouet, J.Francois, Hydrophobically end-capped poly(ethylene oxide) urethanes. 3. Effect of sodium dodecyl-sulfate on their association in aqueous-solution, *Colloid Polym. Sci.*, 271 (1993) 748-758.
- [32] T.Annable, R.Buscall, R.Ettelaie, P.Shepherd, D.Whittlestone, Influence of surfactants on the rheology of associating polymers in solution, *Langmuir*, 10 (1994) 1060-1070.
- [33] K.Zhang, B.Xu, M.A.Winnik, P.M.Macdonald, Surfactant interactions with HEUR associating polymers *J. Phys. Chem.*, 100 (1996) 9834-9841.
- [34] F.Tanaka, M.Ishida, Elastically effective chains in transient gels with multiple junctions, *Macromolecules*, 29 (1996) 7571-7580.
- [35] D.S.Pearson, W.W.Graessley, The structure of rubber networks with multifunctional junctions, *Macromolecules*, 11 (1978) 528-533.